

**PHILIPS**

Ferroxcube for power, audio/video and accelerators

**C5**

**1986**

**PHILIPS**

Data handbook



Electronic  
components  
and materials

Components and  
materials

Book C5

1986

Ferroxcube for power, audio/video and accelerators

# **FERROXCUBE FOR POWER, AUDIO/VIDEO AND ACCELERATORS**

*page*

## **SECTION A**

### **General properties of manganese-zinc and nickel-zinc ferrites**

Introduction . . . . .	3
Applications . . . . .	4
Symbols, terms, definitions and basic formulae . . . . .	5
Technical data . . . . .	9
Characteristic curves . . . . .	19

## **SECTION B**

### **Yoke rings for use in deflection coils for picture tubes**

Survey of types . . . . .	53
Device data . . . . .	54

## **SECTION C**

### **E/EC/ETD/U/I cores**

#### **Introduction**

Core type and material grade selection guide . . . . .	75
Survey of types . . . . .	126

#### **Device data**

E-cores . . . . .	128
EC-cores . . . . .	197
ETD-systems . . . . .	241
U/I-cores . . . . .	262

## **SECTION D**

### **Materials and cores for magnetic recording**

Material data . . . . .	301
-------------------------	-----

*continued overleaf*

## **SECTION E**

### **Small cores and chokes**

Iron powder materials . . . . .	316
Toroids . . . . .	317
Rods and tubes . . . . .	319
Ferrite coil formers . . . . .	325
Beads . . . . .	327
Beads on wire . . . . .	330
Multi-hole tubes . . . . .	331
Screw cores . . . . .	333
Wound six-hole beads . . . . .	334

## **SECTION F**

### **Materials for particle accelerators**

Selection guide . . . . .	339
---------------------------	-----

## **SECTION G**

Ferroxcube for microwave applications . . . . .	345
---	-----

Index of catalogue numbers to core types/mounting parts . . . . .	351
---	-----

See Book C4 for Ferroxcube potcores, square cores and cross cores

## DATA HANDBOOK SYSTEM

Our Data Handbook System comprises more than 60 books with specifications on electronic components, subassemblies and materials. It is made up of four series of handbooks:

ELECTRON TUBES	BLUE
SEMICONDUCTORS	RED
INTEGRATED CIRCUITS	PURPLE
COMPONENTS AND MATERIALS	GREEN

The contents of each series are listed on pages iv to viii.

The data handbooks contain all pertinent data available at the time of publication, and each is revised and reissued periodically.

When ratings or specifications differ from those published in the preceding edition they are indicated with arrows in the page margin. Where application information is given it is advisory and does not form part of the product specification.

Condensed data on the preferred products of Philips Electronic Components and Materials Division is given in our Preferred Type Range catalogue (issued annually).

Information on current Data Handbooks and on how to obtain a subscription for future issues is available from any of the Organizations listed on the back cover.

Product specialists are at your service and enquiries will be answered promptly.

## ELECTRON TUBES (BLUE SERIES)

The blue series of data handbooks comprises:

- T1      Tubes for r.f. heating**
- T2a     Transmitting tubes for communications, glass types**
- T2b     Transmitting tubes for communications, ceramic types**
- T3      Klystrons**
- T4      Magnetrons for microwave heating**
- T5      Cathode-ray tubes**  
Instrument tubes, monitor and display tubes, C.R. tubes for special applications
- T6      Geiger-Müller tubes**
- T8      Colour display systems**  
Colour TV picture tubes, colour data graphic display tube assemblies, deflection units
- T9      Photo and electron multipliers**
- T10     Plumbicon camera tubes and accessories**
- T11     Microwave semiconductors and components**
- T12     Vidicon and Newvicon camera tubes**
- T13     Image intensifiers and infrared detectors**
- T15     Dry reed switches**
- T16     Monochrome tubes and deflection units**  
Black and white TV picture tubes, monochrome data graphic display tubes, deflection units

## SEMICONDUCTORS (RED SERIES)

The red series of data handbooks comprises:

**S1 Diodes**

Small-signal silicon diodes, voltage regulator diodes (< 1,5 W), voltage reference diodes, tuner diodes, rectifier diodes

**S2a Power diodes**

**S2b Thyristors and triacs**

**S3 Small-signal transistors**

**S4a Low-frequency power transistors and hybrid modules**

**S4b High-voltage and switching power transistors**

**S5 Field-effect transistors**

**S6 R.F. power transistors and modules**

**S7 Surface mounted semiconductors**

**S8a Light-emitting diodes**

**S8b Devices for optoelectronics**

Optocouplers, photosensitive diodes and transistors, infrared light-emitting diodes and infrared sensitive devices, laser and fibre-optic components

**S9 Power MOS transistors**

**S10 Wideband transistors and wideband hybrid IC modules**

**S11 Microwave transistors**

**S12 Surface acoustic wave devices**

**S13 Semiconductor sensors**

## INTEGRATED CIRCUITS (PURPLE SERIES)

The purple series of data handbooks comprises:

### **EXISTING SERIES**

		Superseded by:
<b>IC1</b>	<b>Bipolar ICs for radio and audio equipment</b>	<b>IC01N</b>
<b>IC2</b>	<b>Bipolar ICs for video equipment</b>	<b>IC02Na and IC02Nb</b>
<b>IC3</b>	<b>ICs for digital systems in radio, audio and video equipment</b>	<b>IC01N, IC02Na and IC02Nb</b>
<b>IC4</b>	<b>Digital integrated circuits CMOS HE4000B family</b>	
<b>IC5</b>	<b>Digital integrated circuits – ECL ECL10 000 (GX family), ECL100 000 (HX family), dedicated designs</b>	<b>IC08N</b>
<b>IC6</b>	<b>Professional analogue integrated circuits</b>	<b>IC03N and Supplement to IC11N</b>
<b>IC7</b>	<b>Signetics bipolar memories</b>	
<b>IC8</b>	<b>Signetics analogue circuits</b>	<b>IC11N</b>
<b>IC9</b>	<b>Signetics TTL logic</b>	<b>IC09N and IC15N</b>
<b>IC10</b>	<b>Signetics Integrated Fuse Logic (IFL)</b>	<b>IC13N</b>
<b>IC11</b>	<b>Microprocessors, microcomputers and peripheral circuitry</b>	<b>IC14N</b>

## NEW SERIES

IC01N	Radio, audio and associated systems Bipolar, MOS	(published 1985)
IC02Na	Video and associated systems Bipolar, MOS Types MAB8031AH to TDA1524A	(published 1985)
IC02Nb	Video and associated systems Bipolar, MOS Types TDA2501 to TEA1002	(published 1985)
IC03N	Integrated circuits for telephony	(published 1985)
IC04N	HE4000B logic family CMOS	
IC05N	HE4000B logic family — incased ICs CMOS	(published 1984)
IC06N*	High-speed CMOS; PC74HC/HCT/HCU Logic family	(published 1986)
IC07N	High-speed CMOS; PC54/74HC/HCT/HCU — uncased ICs Logic family	
IC08N	ECL 10K and 100K logic families	(published 1984)
IC09N	TTL logic series	(published 1986)
IC10N	Memories MOS, TTL, ECL	
IC11N	Linear LSI	(published 1985)
Supplement to IC11N	Linear LSI	(published 1986)
IC12N	Semi-custom gate arrays & cell libraries ISL, ECL, CMOS	
IC13N	Semi-custom Integrated Fuse Logic	(published 1985)
IC14N	Microprocessors, microcontrollers & peripherals Bipolar, MOS	(published 1985)
IC15N	FAST TTL logic series	(published 1984)

### Note

Books available in the new series are shown with their date of publication.

\* Supersedes the IC06N 1985 edition and the Supplement to IC06N issued Autumn 1985.

## COMPONENTS AND MATERIALS (GREEN SERIES)

The green series of data handbooks comprises:

- C1 Programmable controller modules  
PLC modules, PC20 modules
- C2 Television tuners, coaxial aerial input assemblies, surface acoustic wave filters
- C3 Loudspeakers
- C4 Ferroxcube potcores, square cores and cross cores
- C5 Ferroxcube for power, audio/video and accelerators
- C6 Synchronous motors and gearboxes
- C7 Variable capacitors
- C8 Variable mains transformers
- C9 Piezoelectric quartz devices
- C10 Connectors
- C11 Varistors, thermistors and sensors
- C12 Potentiometers, encoders and switches
- C13 Fixed resistors
- C14 Electrolytic and solid capacitors
- C15 Ceramic capacitors
- C16 Permanent magnet materials
- C17 Stepping motors and associated electronics
- C18 Direct current motors
- C19 Piezoelectric ceramics
- C20 Wire-wound components for TVs and monitors
- C21\* Assemblies for industrial use  
HNIL FZ/30 series, NORbits 60-, 61-, 90-series, input devices
- C22 Film capacitors

\* To be issued shortly.

SECTION A  
GENERAL PROPERTIES OF MANGANESE-ZINC  
AND NICKEL-ZINC FERRITES



## INTRODUCTION

The Ferroxcube\* range of manganese-zinc and nickel-zinc magnetically soft ferrites are intended for use as core material in coils and transformers operating over a wide range of frequencies. Ferroxcube is a ceramic material, manufactured from high-grade raw materials of controlled composition; the composition defines the electrical and mechanical properties.

Ferroxcube products are made by a sequence of ceramic techniques: mixing, pre-firing, milling, drying, shaping by pressing or extruding, sintering and machining. The finished products have a stable structure and high electrical resistivity. This electrical resistivity allows them to be used at high frequencies without the eddy current losses becoming prohibitively high. Ferroxcube is made in a wide range of permeabilities.

Ferroxcube cores are available in convenient shapes such as potcores, square cores, E and I-cores, EC-cores, X-cores, U-cores, toroids, aerial rods, yoke rings, screw cores, rods, tubes, beads, cores for magnetic recording and special materials for proton accelerators.

Potcores, square cores, E and I-cores and X-cores enable well-defined air gaps to be used without introducing appreciable stray fields. In this way the permeability of the material may be reduced to an effective value at which core and copper losses are matched. The dependence of the permeability on temperature and time is furthermore reduced to values that guarantee correct operation of the equipment.

This section contains comprehensive data on manganese-zinc and nickel-zinc ferrites and their various grades.

When ordering cores or associated parts, such as coil formers, adjusters and mounting parts, please quote the 12-digit catalogue number for the product in question given in the device data. Whenever this number ends with 'zero', the actual delivered goods may bear a different figure which is for logistic purposes only.

So if you order e.g. type 4322 021 30180 you may receive 4322 021 30182.

\* Our trade name for magnetically soft ferrites.

## APPLICATIONS

The various grades of Ferroxcube, the forms in which they are available and their principal applications are listed in the table below.

grade	core shapes and some preferred applications
• 2A2	yoke rings
• 3B	rods and tubes
3B7	potcores and square cores
• 3B8	potcores, square cores and cross cores
• 3C2	yoke rings
3C6	rods and tubes
• 3C8	E, EC, ETD, U and I cores, square cores
• 3C85	E, ETD, square cores
• 3D3	potcores, square cores, screw cores
3E1	E and I cores, toroids, potcores, square cores
• 3E2	H cores and toroids
• 3E4	potcores and square cores
3E5	square cores, toroids
• 3F3	ETD, square cores
• 3H1	potcores, square cores, cross cores
3H2	tubes, rods, toroids
• 3H3	potcores, square cores
4A4	frames for i.f. transformers, rods and tubes
• 4B1	frames for i.f. transformers, rods and tubes
• 4C6	potcores, square cores, toroids, frames for i.f. transformers, rods and tubes
4D1, 4D2	frames for i.f. transformers, screw cores, rods and tubes
4E1	rods and tubes
3H22, 3F1, 4E2, 4L2, 4M2, 8C11, 8C12	special-purpose ferrites developed for resonant cavities for particle accelerators. A technical discussion is usually necessary to determine the correct material for this type of application.
8A5, 8C1, 8E1, 8E2, 8E21, 8X1	cores and structural material for magnetic recording heads.

## SYMBOLS, TERMS, DEFINITIONS AND BASIC FORMULAE

This list of symbols is based on the recommendations of IEC Publications 50, 125 and 401. Where symbols or formulae are used in connection with one application, material or core only, they are explained in the relevant section or data sheet.

symbol	units	definition
$A_{\min}$	$\text{mm}^2$	nominal value of the minimum cross-sectional area.
$A_e$	$\text{mm}^2$	effective cross-sectional area.
$A_{e \min}$	$\text{mm}^2$	minimum effective cross-sectional area.
$A_L$	nH	inductance factor = $L/N^2$ .  Note: unless otherwise stated in this Handbook, $A_L$ is the inductance factor in nH.
AT	A	ampere-turns.
B	T	flux density.
$B_s$	T	saturation flux density.
$B_r$	T	remanence: flux density remaining after magnetization to saturation and removal of the external field.
$\hat{B}$	T	peak flux density.
$C_1$	$\text{mm}^{-1}$	core constant: $C_1 = \Sigma(\ell/A)$ .
D	—	disaccommodation: the fractional change of permeability of a magnetic material measured at a constant temperature over a period of time after cessation of a disturbance
$D = \frac{\mu_1 - \mu_2}{\mu_1}$		
$D_F$	—	disaccommodation factor: obtained by dividing D by the first measured relative permeability (at $t_1$ ) and the logarithm of the ratio of the measuring times
$D_F = \frac{\mu_1 - \mu_2}{\mu_1^2 \log(t_2/t_1)}$		
Times $t_1$ and $t_2$ are given in the core data.		
$E_1$	V	voltage at fundamental frequency.
$E_3$	V	voltage at third harmonic.
$f_{Cu}$	—	space (copper) factor: proportion of the winding cross section occupied by conductor.
f	Hz	frequency.
H	A/m	magnetic field strength.
$H_c$	A/m	coercivity: the value of the external field strength for which the flux density is zero after the material has been magnetized to saturation.

## MnZn and NiZn ferrites

$\hat{H}$	A/m	peak magnetic field strength.
$I_0$	A	direct current.
$l_e$	mm	effective magnetic path length.
$L$	H	inductance.
N	-	number of turns.
P	kW/m <sup>3</sup>	specific power loss in core material.
Q	-	inductance quality factor.
$R_h$	$\Omega$	effective series resistance of an inductor due to hysteresis losses in the core.
$T_c$	°C	Curie temperature: the temperature at which a ferromagnetic material becomes paramagnetic.
$V_e$	mm <sup>3</sup>	effective volume of a core: the volume of an ideal toroid of the same material and having the same magnetic properties:
		$V_e = \frac{\Sigma(l/A)^3}{\Sigma(l/A^2)^2}.$
$\alpha$	-	turns factor: number of turns for an inductance of 1 mH.
$\alpha_F$	K <sup>-1</sup>	temperature factor of a core without air gap. The original definition in IEC 133

$$\alpha_F = \frac{\mu_\theta - \mu_{ref}}{\mu_{ref}^2 (\theta - \theta_{ref})}$$

$$= \frac{0.4\pi(A_L\theta - A_L\text{ref})}{A^2 L \text{ref} C_1 (\theta - \theta_{ref})}$$

where  $\theta$  is the applied temperature, was superseded in 1976 by the definition in IEC 367-1:

$$\alpha_F = \frac{\mu_\theta - \mu_{ref}}{\mu_\theta \mu_{ref} (\theta - \theta_{ref})}$$

$$= \frac{0.4\pi(A_L\theta - A_L\text{ref})}{A_L\theta A_L \text{ref} C_1 (\theta - \theta_{ref})}$$

The second definition is required for new, close-tolerance products, and for products whose properties are guaranteed over a wide temperature range.

$\alpha_\mu$  K<sup>-1</sup> temperature coefficient of a core with an (ground) air gap. Where  $\mu_e$  is the effective permeability of the core,

$$\alpha_\mu \approx \alpha_F \mu_e$$

Alternatively,

$$\alpha_\mu \approx \alpha_F C_1 A_L / \mu_0$$

These approximations hold for fairly small changes in  $\mu_e$  or  $A_L$  over the temperature range considered.

$\beta_F$	—	d.c. sensitivity constant for a core: $\beta_F = \frac{\mu_e - \mu_{e\Delta}}{\mu_e \mu_{e\Delta}}$ where $\mu_{e\Delta}$ is the relative incremental permeability of the core.
$\frac{\tan \delta}{\mu_i}$	—	eddy-current and residual loss constant at a given frequency, measured at $\widehat{B} \leq 0,1$ mT. The corresponding R/L value is given by $R/L = 2\pi f \mu \frac{\tan \delta}{\mu_i}$
$\Delta$	mm	air-gap length.
$\eta_B$	T <sup>-1</sup>	hysteresis constant: $\eta_B = \frac{\Delta R_h}{\Delta \mu_e 2\pi f L}$ where $\Delta \widehat{B} = \widehat{B}_2 - \widehat{B}_1$ and $\Delta R_h = R \widehat{B}_2 - R \widehat{B}_1$ . (That is, series resistance $R \widehat{B}_1$ is measured at $\widehat{B}_1$ and then $R \widehat{B}_2$ at $\widehat{B}_2$ .)
$\theta$	°C	temperature.
$\mu_a$	—	relative amplitude permeability for a signal of amplitude greater than that for $\mu_\Delta$ so that the value is dependent on flux density B: $\mu_a = \frac{1}{\mu_0} \cdot \frac{B}{H}$
$\mu_e$	—	relative effective permeability: the permeability of a core with an air gap $\mu_e = \frac{C_1}{\Sigma \ell / A} \text{ or } \frac{1}{\mu_e} \cdot \frac{L}{N^2} C_1$
$\mu_i$	—	relative initial permeability: measured on a core without air gap for a small field change $\Delta H \rightarrow 0$ . $\mu_i = \lim_{(H \rightarrow 0)} \mu_a$
$\mu_{rem}$	—	relative incremental permeability about remanence.
$\mu_\Delta$	—	relative incremental permeability of a polarized core: at a given d.c. applied field, the permeability observed when a small alternating field is superimposed. $\mu_\Delta = \frac{\Delta B}{\mu_0 \Delta H}$ Here, $\Delta B \leq 0,2$ mT and $f = 4$ kHz.
$\mu_\theta$	—	relative permeability at a given temperature.
$\rho$	Ωm	specific resistance for direct current.

## MnZn and NiZn ferrites

### FORMULAE

$$L = \frac{\mu_0 \mu_e N^2 \times 10^{-3}}{C_1}$$

H inductance.

$$A_L = 10^6 \mu_e \mu_0 / C_1$$

(nH) initial induction factor.

$$B = E / (4,44 f N A_e) \times 10^{-6}$$

(T) peak flux density.

$$E_3/E_1 = 0,6 \tan \delta_h$$

3rd harmonic distortion.

$$N = \sqrt{(10^9 L / A_L)} = \alpha \sqrt{(10^3 L)}$$

(turns) number of turns.

$$Q = 1 / \tan \delta_{tot}$$

quality factor.

$$\tan \delta_h = \mu B \eta_B$$

hysteresis loss factor

$$1 \text{ mT} = 10 \text{ Gauss}$$

$$1 \text{ Oe} = 79,6 \text{ A/m}$$

## TECHNICAL DATA


Ferroxcube data are given in the tables on the following pages in accordance with the recommendations of IEC 401, and using symbols defined in the previous section.

### GENERAL PROPERTIES

Specific heat at 25 °C	
MnZn ferrites (FXC 3--)	1100 J/(kgK)
NiZn ferrites (FXC 4--)	750 J/(kgK)
Thermal conductivity from 25 °C to 85 °C	3,5 to 4,3 W/(mK)
Coefficient of linear expansion	10 to 12 × 10 <sup>-6</sup> /K
Modulus of elasticity	15 × 10 <sup>4</sup> N/mm <sup>2</sup>
Ultimate tensile strength	18 N/mm <sup>2</sup>
Crushing strength	73 N/mm <sup>2</sup>

### NOTES TO THE DATA TABLES

- The data given apply to medium-sized toroids and should be taken as a guide. Cores that are small or have other shapes will have slightly different properties that cannot readily be predicted on the basis of toroid properties. For this reason, product characteristics are guaranteed for the products themselves and are given on the appropriate data sheets.
- The temperature coefficient  $\alpha_F$  is measured on circuits without a (ground) air gap, with the exception of 3B7 products, for which  $\alpha_F$  is measured on toroidally-wound core halves. For FXC 3-- products, the measuring sequence is that shown in the figure. The measurement circuits for FXC 3H3 and FXC 4-- products are thermally demagnetized by being heated to 25 °C above their Curie temperature, after which they are cooled slowly to room temperature and left for 24 h.

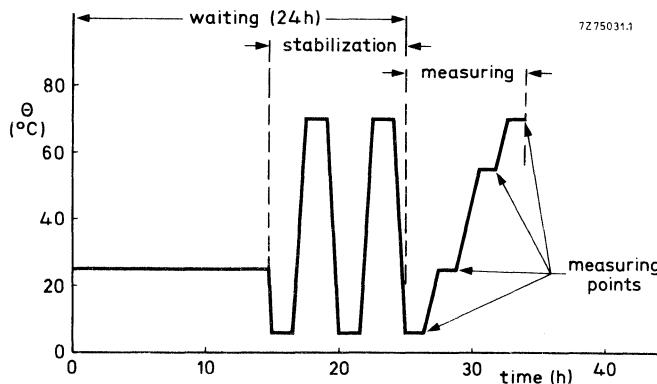

# MnZn and NiZn ferrites

			materials for deflection units	
	unit	•2A2	•3C2	
Initial permeability $\mu_i$ at $B \leq 0,1$ mT, $\theta = 25^\circ\text{C}$		$350 \pm 20\%$	$900 \pm 25\%$	
Induction B, ballistically measured at H = 500 A/m $\theta = 100^\circ\text{C}$ H = 800 A/m $\theta = 20^\circ\text{C}$ H = 800 A/m $\theta = 25^\circ\text{C}$ H = 800 A/m $\theta = 70^\circ\text{C}$ H = 800 A/m $\theta = 100^\circ\text{C}$ H = 1600 A/m $\theta = 25^\circ\text{C}$ H = 1600 A/m $\theta = 100^\circ\text{C}$ H = 3200 A/m $\theta = 25^\circ\text{C}$ H = 3200 A/m $\theta = 100^\circ\text{C}$ H = 4800 A/m $\theta = 25^\circ\text{C}$ H = 4800 A/m $\theta = 100^\circ\text{C}$	mT	$\approx 200$  $\approx 140$	$\approx 350$  $\approx 245$	
Coercivity Hc $\theta = 20^\circ\text{C}$	A/m	60		
Eddy current and residual loss constant $\tan \delta$ at $B \leq 0,1$ mT, $\theta = 25^\circ\text{C}$ $\mu_i$ f = 100 kHz f = 450 kHz f = 500 kHz f = 700 kHz f = 1 MHz f = 1,5 MHz f = 2 MHz f = 3 MHz f = 5 MHz f = 10 MHz f = 20 MHz f = 25 MHz f = 40 MHz		$\approx 50$  $\times 10^{-6}$		
Hysteresis constant $\eta_B$ at $B = 0,3 - 1,2$ mT $f = 100$ kHz	$\times 10^{-3} \text{ T}^{-1}$			
Power loss at f = 16 kHz and B = 50 mT $\theta = 20^\circ\text{C}$ B = 400 mT $\theta = 25^\circ\text{C}$ B = 400 mT $\theta = 50^\circ\text{C}$ B = 400 mT $\theta = 100^\circ\text{C}$	kW/m <sup>3</sup>	$\approx 70$		
Resistivity $\rho$ measured with d.c.	$\Omega\text{m}$	$\geq 10^6$	$\geq 0,1$	
Dielectric constant at f = 1 MHz, $\theta = 25^\circ\text{C}$				
Temperature factor $\alpha_F$ $\theta = +25$ to $+55^\circ\text{C}$ $\theta = +25$ to $+70^\circ\text{C}$	$\times 10^{-6}/\text{K}$	$\approx 35$	0 to +4,5	
Disaccommodation factor D <sub>F</sub> between 10 and 100 min after demagnetization, $B \leq 0,1$ mT, $\theta = 25 \pm 1^\circ\text{C}$	$\times 10^{-6}$		$\leq 10$	
→ Curie temperature	°C	$\geq 135$	$\geq 150$	
Mass density	kg/m <sup>3</sup>	$\approx 4300$	4700-4900	
Core shapes		yoke rings		

• preferred material

materials for small parts						
•3B	3C6	4A4	•4B1	4D1	4D2	4E1
900 ± 20%	1700 ± 25%	500 ± 20%	250 ± 20%	50 ± 20%	60 ± 10%	15 ± 20%
≈ 345	≥ 290	≈ 270 ≈ 210	≈ 325 ≈ 260	≈ 240 ≈ 220		≈ 175 ≈ 165
≈ 230						
≤ 50		≤ 30 ≤ 40 ≤ 70	≤ 70 ≤ 90 ≤ 140	≤ 180 ≤ 210 ≤ 300	≤ 100 ≤ 200 ≤ 600	≤ 300 ≤ 300 ≤ 360
		≤ 1,8				
	≤ 170 ≤ 160 ≤ 140					
≥ 0,2		≥ 10 <sup>5</sup>	≥ 10 <sup>5</sup>	≥ 10 <sup>3</sup>	≥ 10 <sup>3</sup>	≥ 10 <sup>3</sup>
	15-20					
0 to +3		+5 to +15	0 to +8	0 to +15	0 to +15	0 to +15
≥ 150	≥ 190	≥ 135	≥ 250	≥ 400	≥ 350	≥ 500
4700-4900	4750-4850	4700-5100	4400-4800	4000-4400		3500-4000
tubes and rods		frames for i.f. trans-formers, tubes and rods		frames for i.f. transformers, screw cores, tubes and rods		tubes and rods

# MnZn and NiZn ferrites

		unit	
Initial permeability $\mu_i$ at $\hat{B}$ (mT), $f = 4$ kHz $\theta$ (°C) $\leq 0,1$	25		
Optimum frequency range		kHz	
Induction $\hat{B}$ at $f$ (kHz)	$\hat{H}$ (A/m)	$\theta$ (°C)	
0	800	25	
0	800	100	
0	3000	25	mT
25	250	25	
25	250	100	
Power loss at $f$ (kHz)	$\hat{B}$ (mT)	$\theta$ (°C)	
25	200	25	
25	200	100	kW/m <sup>3</sup>
25	200	100	
100	100	25	
100	100	100	
400	50	25	
400	50	100	
Temperature factor $\alpha_F$ at $\theta$ (°C) +5 to +25 +25 to +55 +25 to +70		$\times 10^{-6}/K$	
Curie temperature		°C	
Mass density		kg/m <sup>3</sup>	
D.C. sensitivity constant $\beta_F = \frac{\mu_i - \mu_i \Delta}{\mu_i \mu_i \Delta}$ at $\mu_e \times \frac{N \times l_o}{l_e}$ $= 1,20 \times 10^5$ A/m $= 1,80 \times 10^5$ A/m $= 2,60 \times 10^5$ A/m		$\times 10^{-6}$	
Core shapes			

high level transformer materials (power materials)			
● 3B8	● 3C8	● 3C85	● 3F3
2300 ± 20%	2000 ± 25%	2000 ± 20%	2000 ± 20%
up to 150	up to 100	up to 200	up to 500
≈ 500	≈ 500	≈ 500	≈ 500
≥ 330	≥ 330	≥ 330	≥ 330
≤ 140	≤ 110*	≤ 190	≤ 120
≤ 155	≤ 100*	≤ 140	≤ 90
		≤ 230	≤ 110
		≤ 165	≤ 80
			≤ 150
			≤ 150
5 ± 2			
5 ± 2			
5 ± 2			
≥ 200	≥ 200	≥ 200	≥ 200
4700-4900	4750-4850	4700-4900	4650-4850
≤ 120			
≤ 300			
≤ 1000			
potcores square cores	E, EC, ETD, U and I	E, ETD, square cores	square cores, ETD

\* at 16 kHz.

● Preferred material.

# MnZn and NiZn ferrites

	unit	
Initial permeability $\mu_i$ , $f = 4$ kHz at $\hat{B} \leq 0,1$ mT $\theta = 25$ °C at $\hat{B} \leq 1$ mT $\theta = 5$ to $70$ °C at $\hat{B} 0,7 - 1$ mT $\theta = 25$ to $70$ °C		
Induction $\hat{B}$ ballistically measured $H = 800$ A/m $\theta = 25$ °C $\theta = 70$ °C	mT	
Eddy current and residual loss constant $\frac{\tan \delta}{\mu_i}$ at $\hat{B} \leq 0,1$ mT, $\theta = 25$ °C $f = 4$ kHz $f = 10$ kHz $f = 30$ kHz $f = 100$ kHz $f = 500$ kHz	$\times 10^{-6}$	
Hysteresis constant $\eta_B$ at $\hat{B} = 1,5 - 3,0$ mT $f = 4$ kHz	$\times 10^{-3}$ T <sup>-1</sup>	
Resistivity $\rho$ measured with d.c.	Ωm	
Temperature factor $\alpha_F$ $\theta = +5$ to $+25$ °C $\theta = +25$ to $+55$ °C $\theta = +25$ to $+70$ °C	$\times 10^{-6}/K$	
Disaccommodation factor $D_F$ between 10 and 100 min after demagnetization, $\hat{B} \leq 0,1$ mT $\theta = 25 \pm 1$ °C	$\times 10^{-6}$	
Curie temperature	°C	
Mass density	Kg/m <sup>3</sup>	
Core shapes		

\* ± 20%.  
● preferred material.

	low level transformer materials (broadband materials)					
	3E1	•3E2	•3E4	•3E45	3E5	3H2
	$3800 \pm 20\%$	$\geq 5000$	$4700 \pm 20\%$	$6000 \pm 20\%$ $\geq 4200$	$10000 \pm 20\%$	$2300 \pm 20\%$
	$\approx 350$ $\approx 270$	$\approx 355$ $\approx 260$	$\approx 350$ $\approx 270$	$\approx 350$ $\approx 270$	$\approx 380$ $\approx 280$	$\approx 400$
	$\leq 2,5$ $\leq 20$ $\leq 200$	$\leq 2,5$ $\leq 15$ $\leq 90$	$\leq 2,5$ $\leq 20$ $\leq 200$	$\leq 5$ $\leq 40$	$\leq 3$ $\leq 25$ $\leq 75$	$\leq 1$ $\leq 6$
	$\leq 1,1$	$\leq 1,1$	$\leq 0,85$	$\leq 1,0$	$\leq 0,85$	$\leq 0,85$
	$\geq 0,3$	$\geq 0,1$	$\geq 0,3$	$\geq 0,05$	$\geq 0,01$	$\geq 1$
	$1 \pm 1$ $1 \pm 1$ $1 \pm 1$					
	$\leq 4,3$	$\leq 1,9$	$\leq 4,3$	$\leq 3$	$\leq 2$	$\leq 4,3$
	$\geq 125$	$\geq 130$	$\geq 125$	$\geq 130$	$\geq 120$	$\geq 160$
	4700-4900	4700-4900	4700-4900	4700-4900	4800-5000	4700-4900
	E and I cores, toroids potcores square cores	toroids	potcores, square cores	potcores, square cores	square cores, toroids	toroids tubes and rods

# MnZn and NiZn ferrites


	unit	
Initial permeability $\mu_i$ at $B \leq 0,1$ mT $\theta = 25^\circ\text{C}$		
Induction B ballistically measured at H = 800 A/m $\theta = 25^\circ\text{C}$ $\theta = 70^\circ\text{C}$ H = 2400 A/m $\theta = 25^\circ\text{C}$ $\theta = 70^\circ\text{C}$	mT	
Eddy current and residual loss constant $\tan \delta$ at $B \leq 0,1$ mT, $\theta = 25^\circ\text{C}$ $\eta_i$ f = 4 kHz f = 30 kHz f = 100 kHz f = 500 kHz f = 1 MHz f = 2 MHz f = 10 MHz	$\times 10^{-6}$	
Hysteresis constant $\eta_B$ at $B = 0,3 - 1,2$ mT      f = 100 kHz at $B = 1,5 - 3$ mT      f = 4 kHz at $B = 1,5 - 3$ mT      f = 100 kHz	$\times 10^{-3} \text{ T}^{-1}$	
Resistivity $\rho$ measured with d.c.	$\Omega\text{m}$	
Temperature factor $\alpha_F$ $\theta = +5$ to $+25^\circ\text{C}$ $\theta = +25$ to $+55^\circ\text{C}$ $\theta = +25$ to $+70^\circ\text{C}$	$\times 10^{-6}/\text{K}$	
Disaccommodation factor $D_F$ between 10-100 min after demagnetization, $B \leq 0,1$ mT $\theta = 25 \pm 1^\circ\text{C}$ between 24 and 48 h after thermal demagnetization, $B \leq 0,1$ mT $\theta \leq 35^\circ\text{C}$	$\times 10^{-6}$	
Curie temperature	$^\circ\text{C}$	
Mass density	$\text{kg/m}^3$	
Core shapes		

materials for tuned circuits					
3B7	•3D3	•3D35	•3H1	•3H3	•4C6
2300 ± 20%	750 ± 20%	1000 ± 20%	2300 ± 20%	2000 ± 20%	120 ± 20%
≈ 430 ≈ 345	≈ 350	≈ 350	≈ 360 ≈ 280	≈ 400	≈ 380 ≈ 350
≤ 1,0 ≤ 5,0	≤ 8 ≤ 12 ≤ 24	≤ 3 ≤ 8 ≤ 30	≤ 1,0 ≤ 5,0	1,2 ± 0,4 2 ± 0,5	≤ 40 ≤ 100
- ≤ 1,1	≤ 0,8	≤ 0,5	≤ 0,85	≤ 0,6	≤ 6,2
≥ 1	≥ 1,5	≥ 7	≥ 1		≥ 10 <sup>5</sup>
0 ± 0,6	1 ± 1	1 ± 0,5 1 ± 0,5 1 ± 0,5	1 ± 0,5 1 ± 0,5 1 ± 0,5	0,7 ± 0,3 0,7 ± 0,3 0,7 ± 0,3	1 ± 3 3 ± 3
≤ 4,3	≤ 12	≤ 8	≤ 4,3	≤ 3	≤ 10
≥ 170	≥ 200	≥ 180	≥ 130	≥ 160	≥ 350
4700-4900	4500-4900	4300-4500	4700-4900		4000-5000
potcores, square cores	potcores, square cores, screw cores	potcores, square cores, screw cores	potcores, square cores, cross cores	potcores, square cores	potcores square cores, toroids, frames for i.f. transformers, rods and tubes



## CHARACTERISTIC CURVES


The curves are valid for toroids of not too small dimensions and should be considered as a guide. For guarantees on products, refer to the pages on the relevant products.


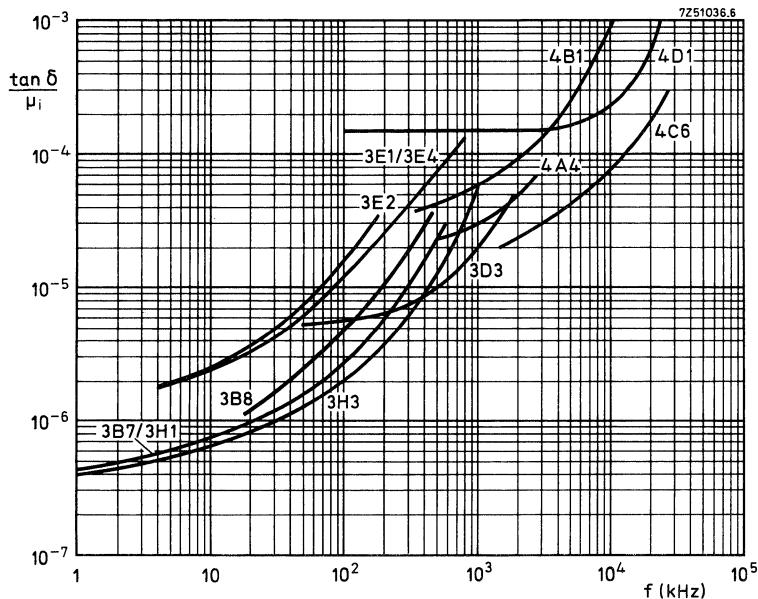


Eddy current losses and residual losses as a function of the frequency at low induction level.



# MnZn and NiZn ferrites



Amplitude permeability as a function of the induction.

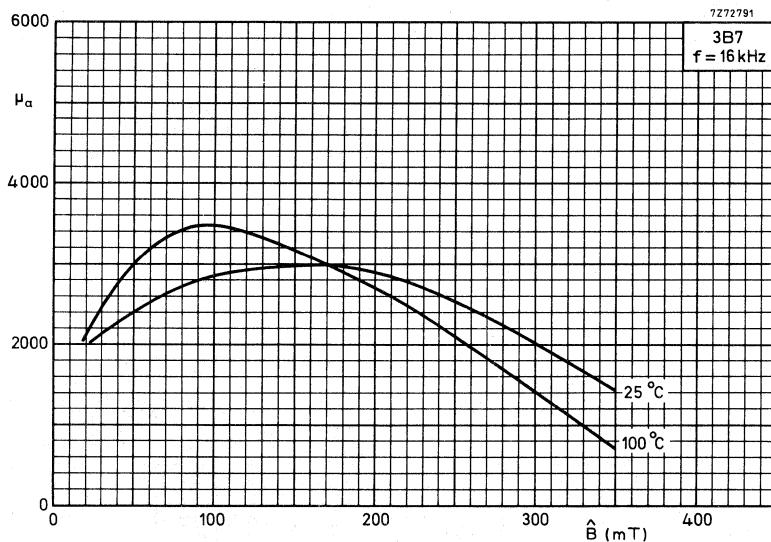

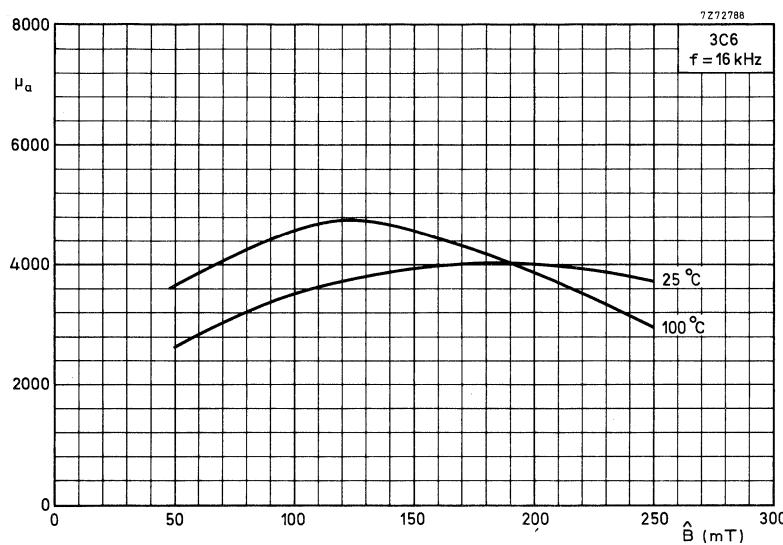
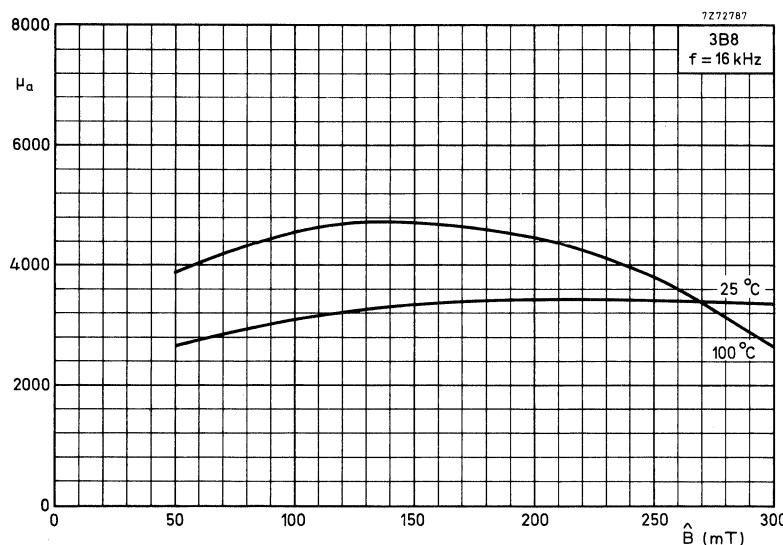




## MnZn and NiZn ferrites

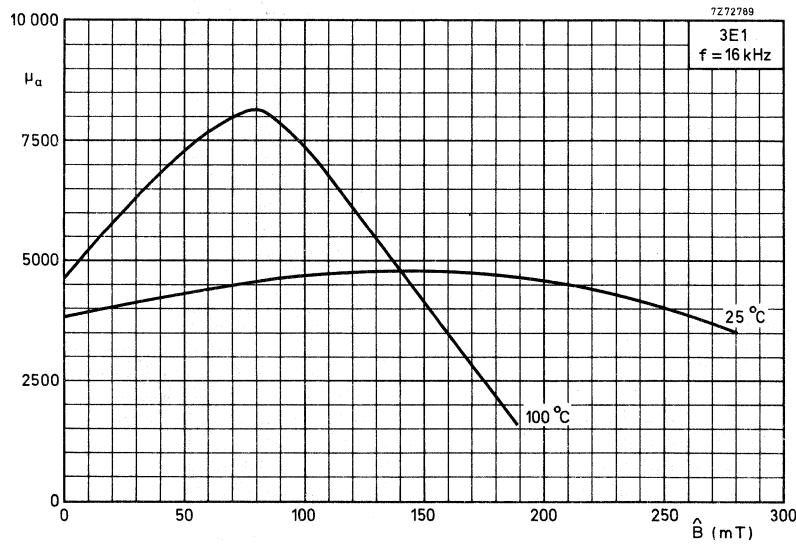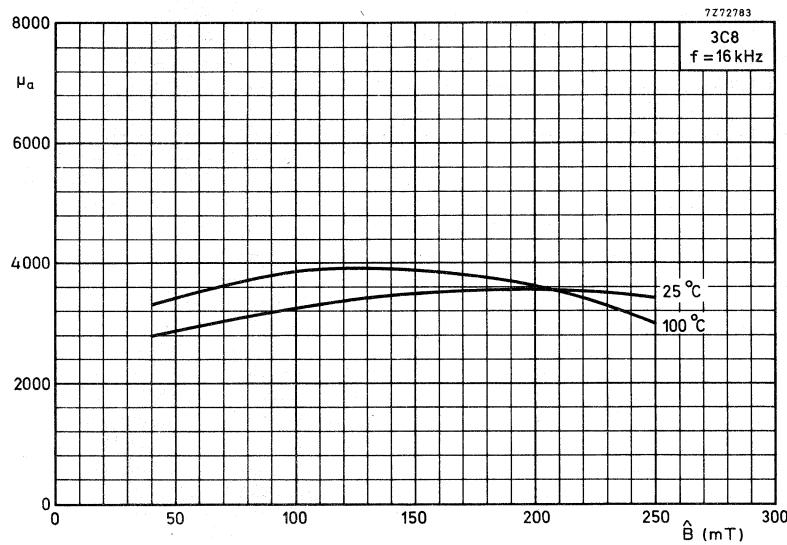

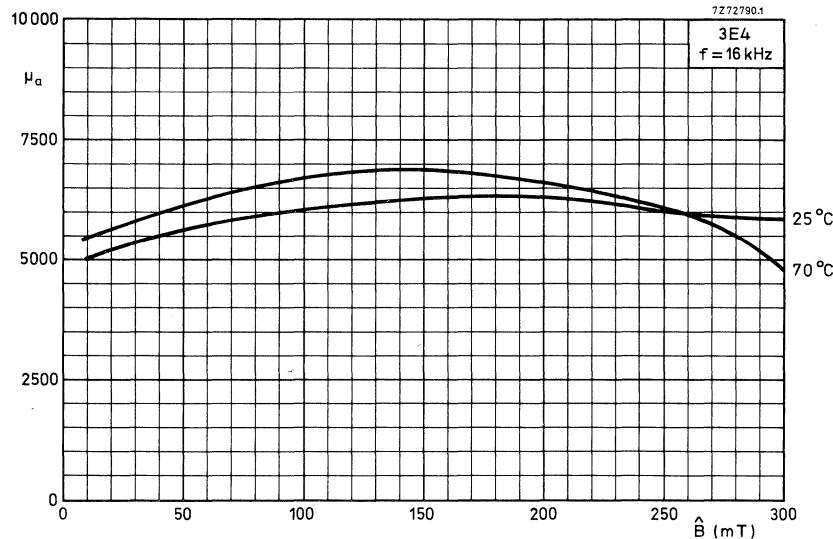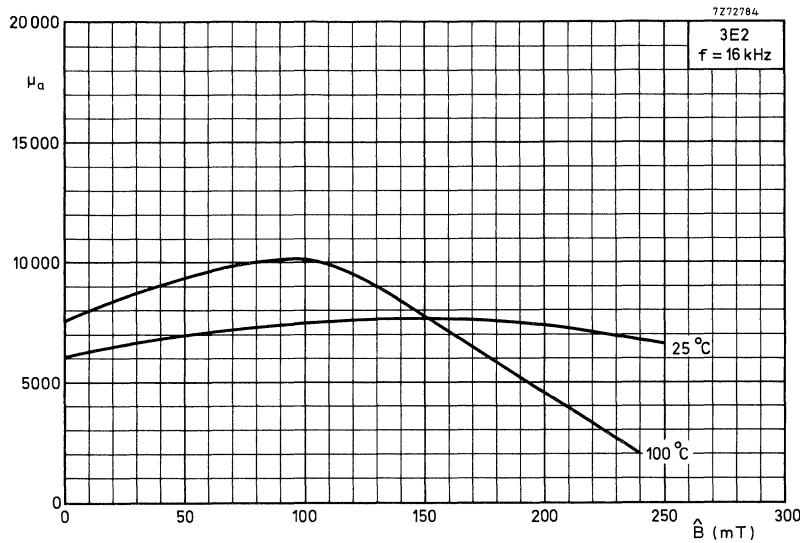

## MnZn and NiZn ferrites

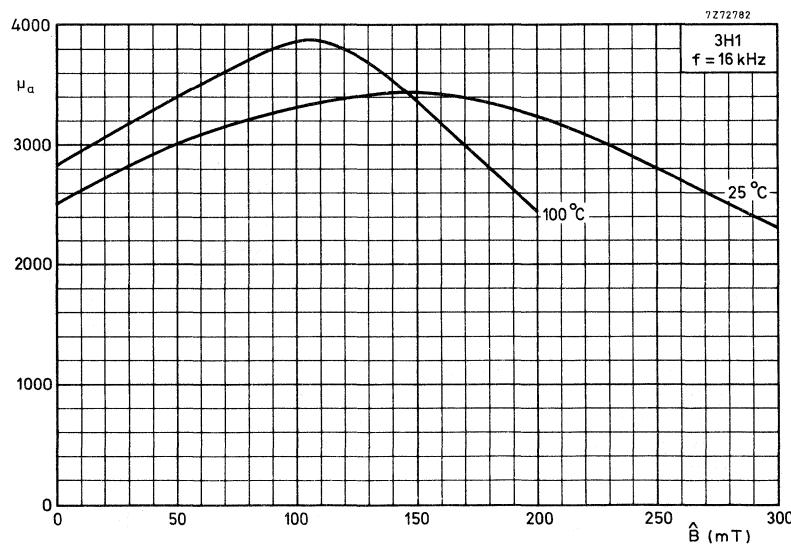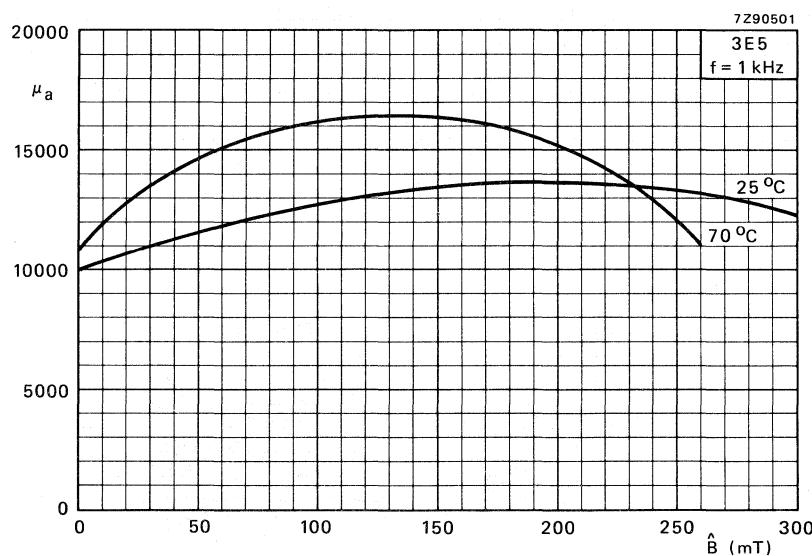


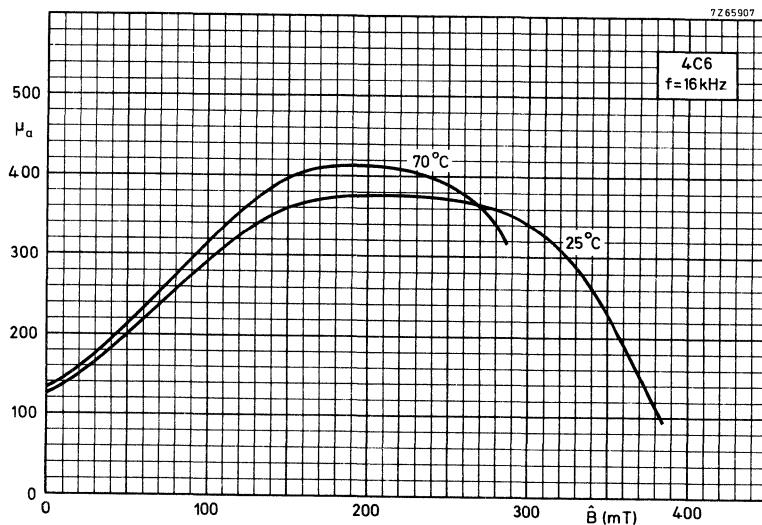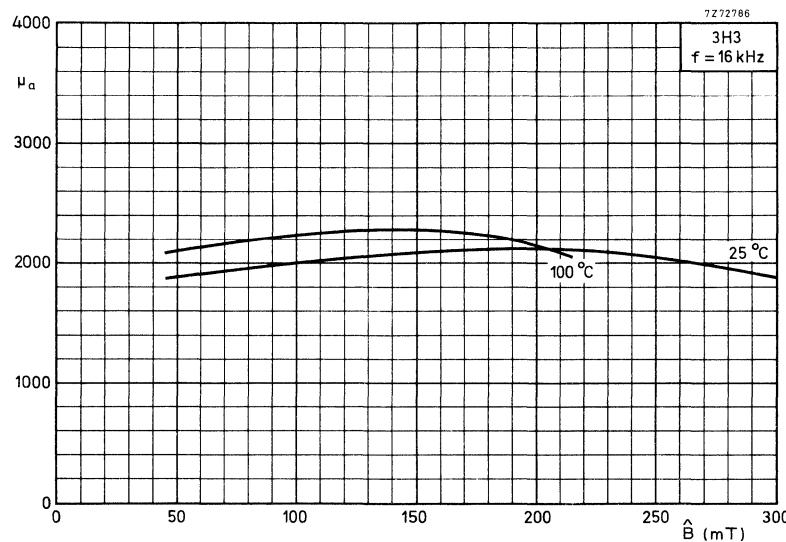


# MnZn and NiZn ferrites

## TYPICAL BH-CURVES (measured ballistically)


ballistic curves

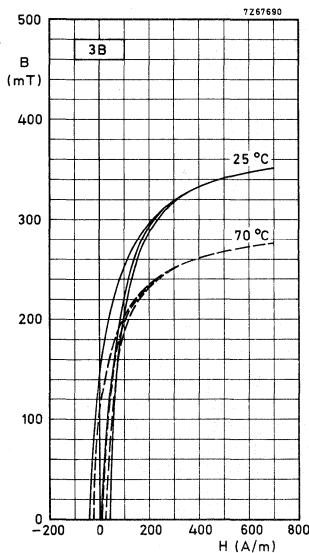


ballistic curves

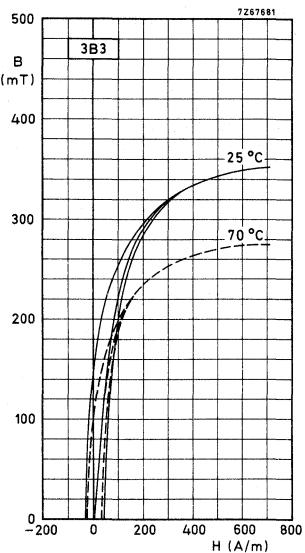


ballistic curves

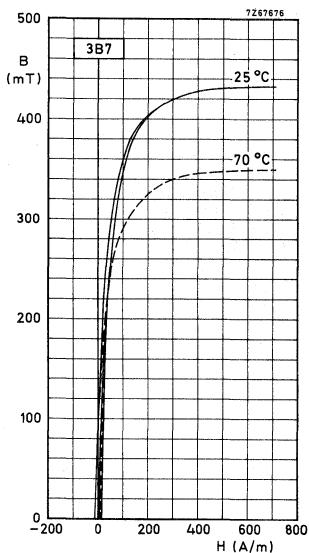


dynamic curves,  $f = 10$  kHz

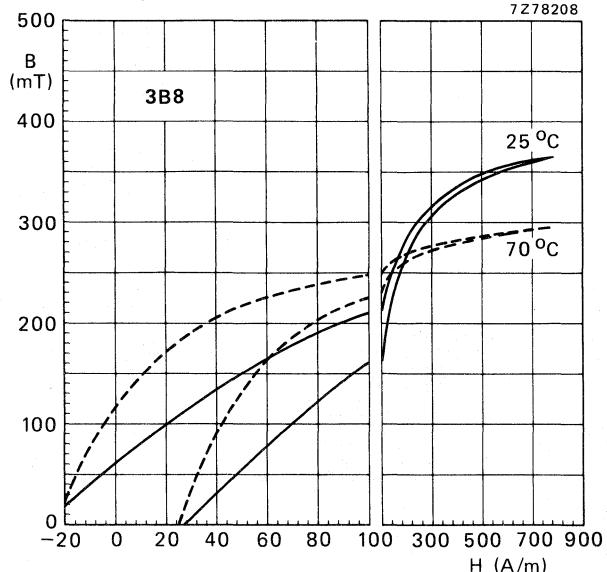


ballistic curves

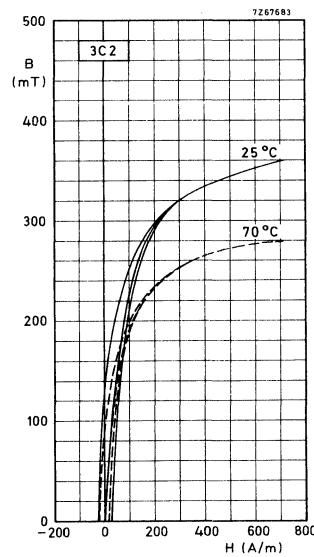


ballistic curves

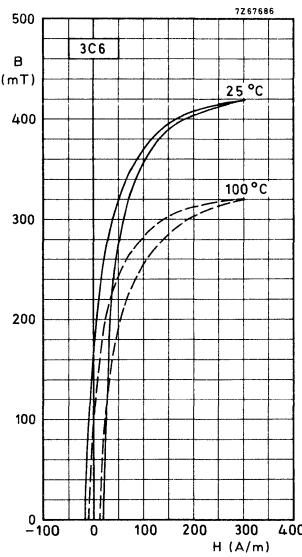

ballistic curves

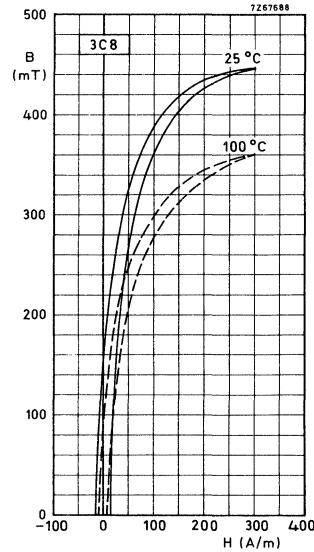


ballistic curves

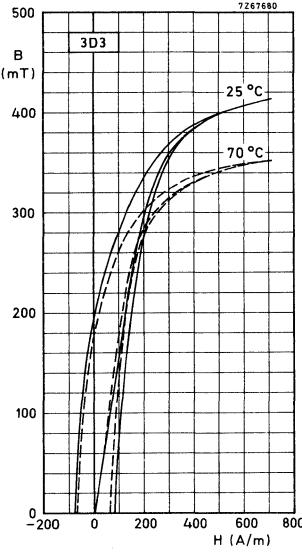


# MnZn and NiZn ferrites


dynamic curves,  $f = 10$  kHz

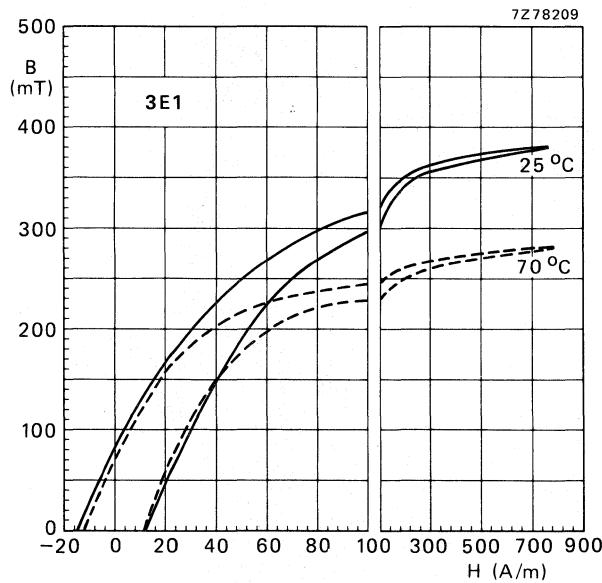


dynamic curves,  $f = 10$  kHz


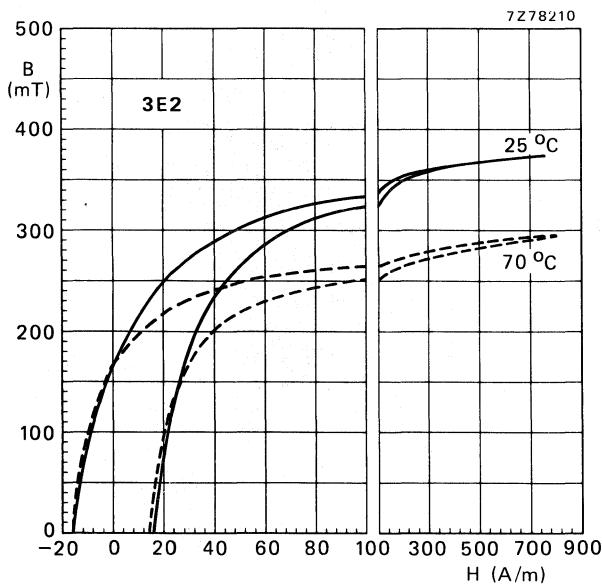


ballistic curves

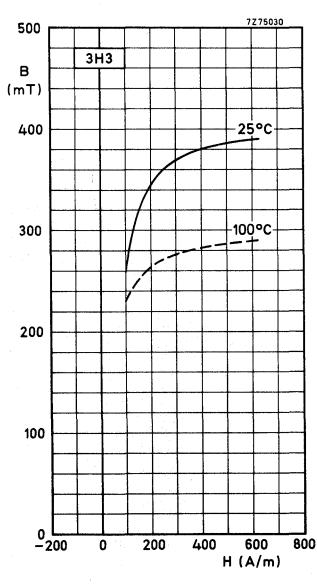


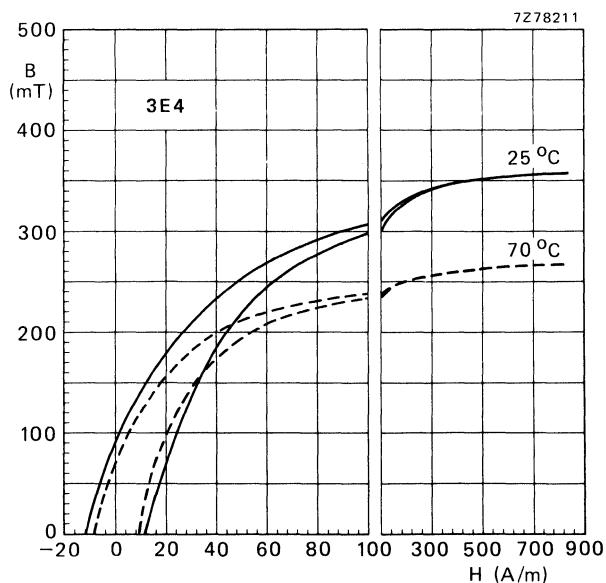dynamic curves,  $f = 10$  kHz

ballistic curves

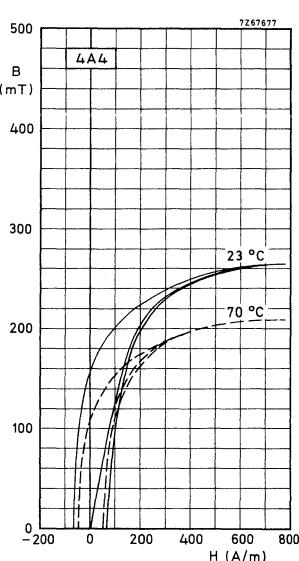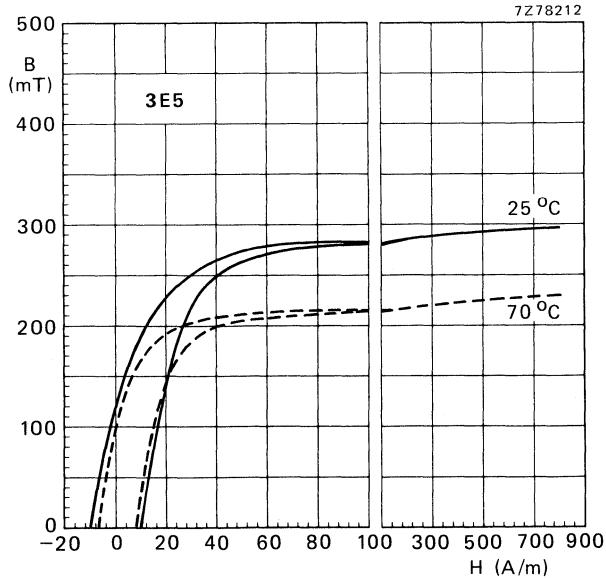
dynamic curves,  $f = 10$  kHz

ballistic curves

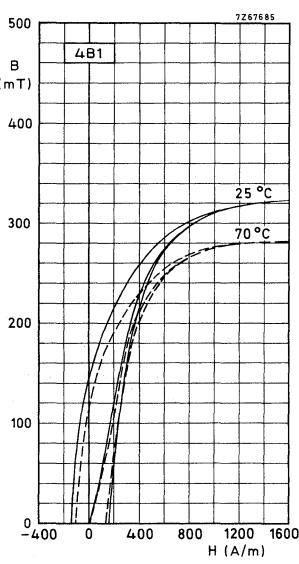


# MnZn and NiZn ferrites


dynamic curves,  $f = 10$  kHz

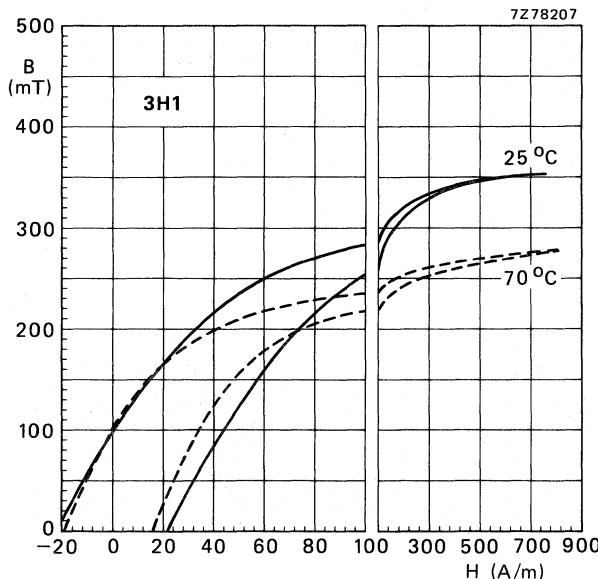


ballistic curves

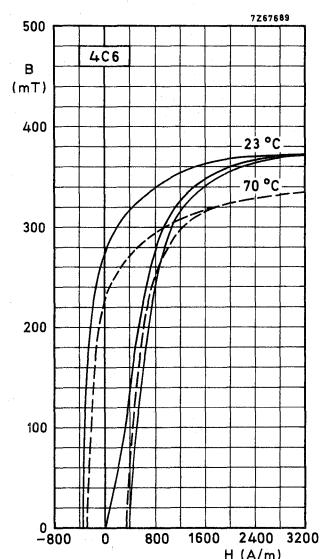



ballistic curves

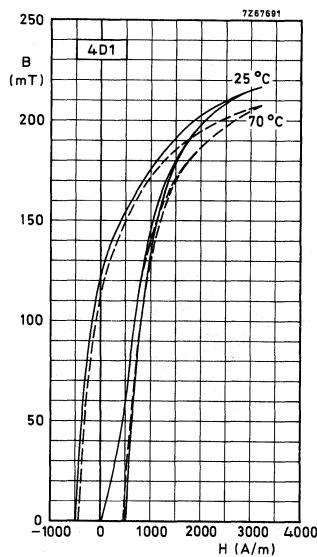



ballistic curves

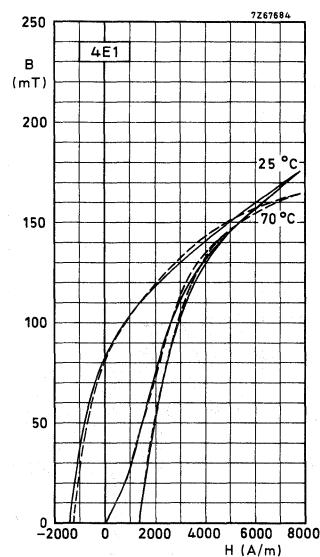



## Relative initial permeability as a function of the temperature

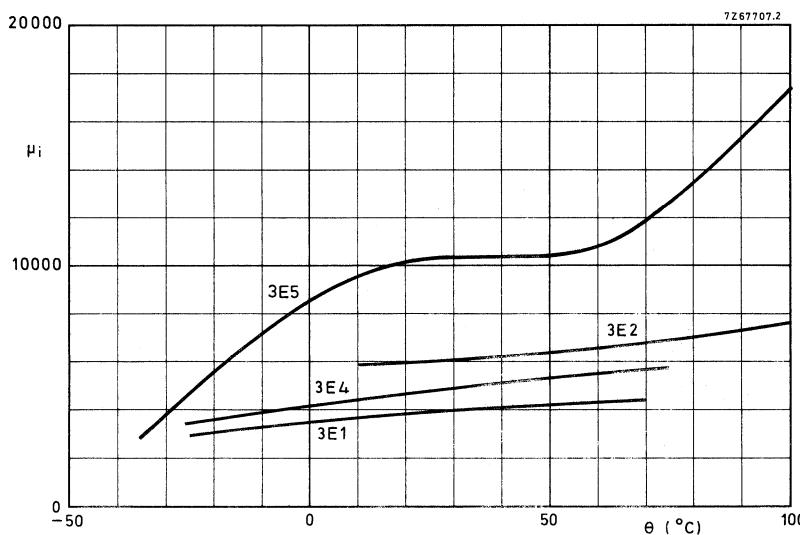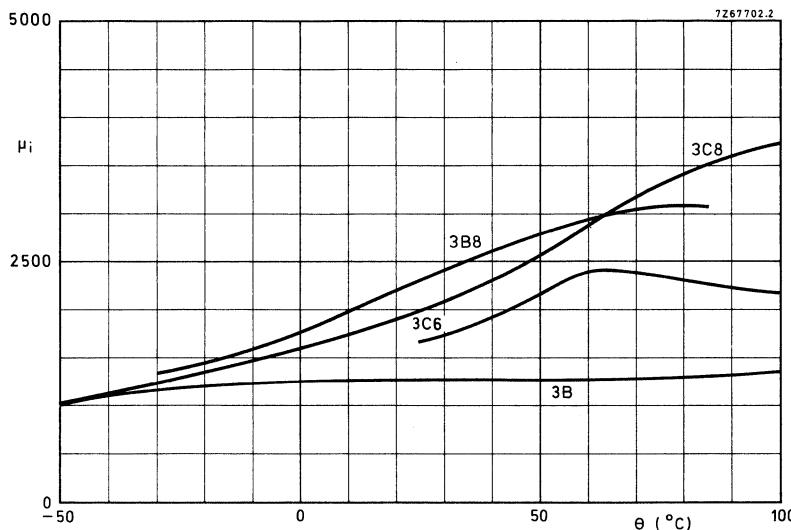



## MnZn and NiZn ferrites

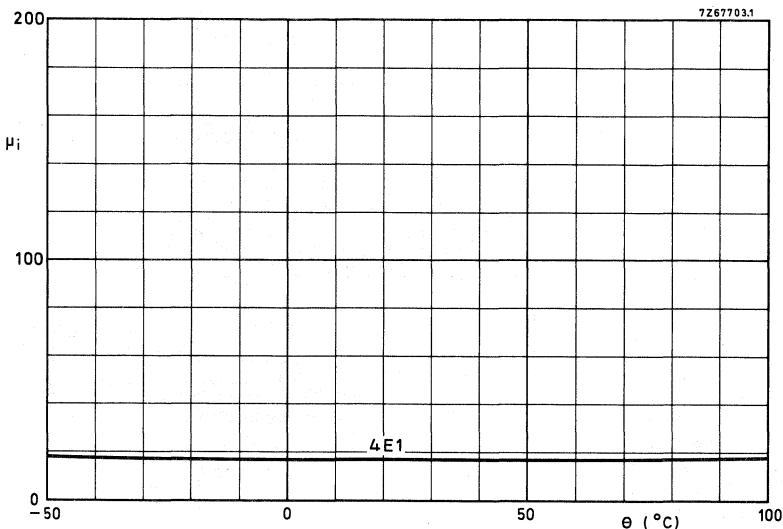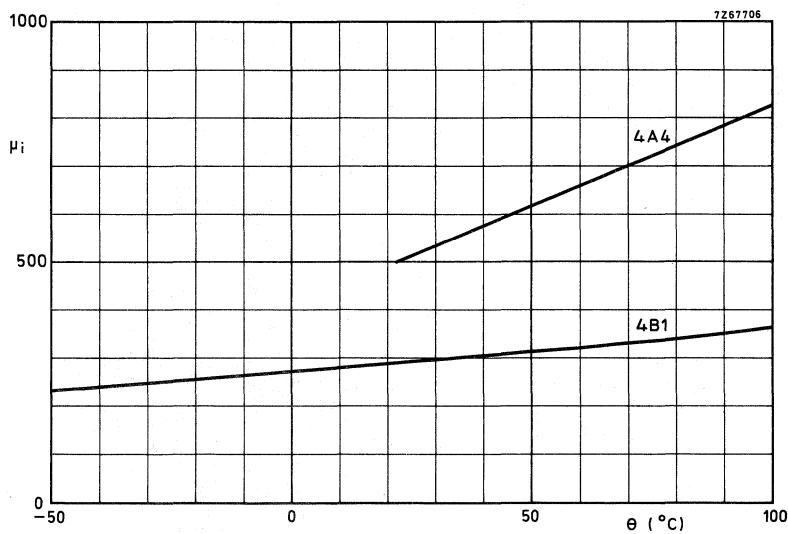


## Permeability factor as a function of the temperature

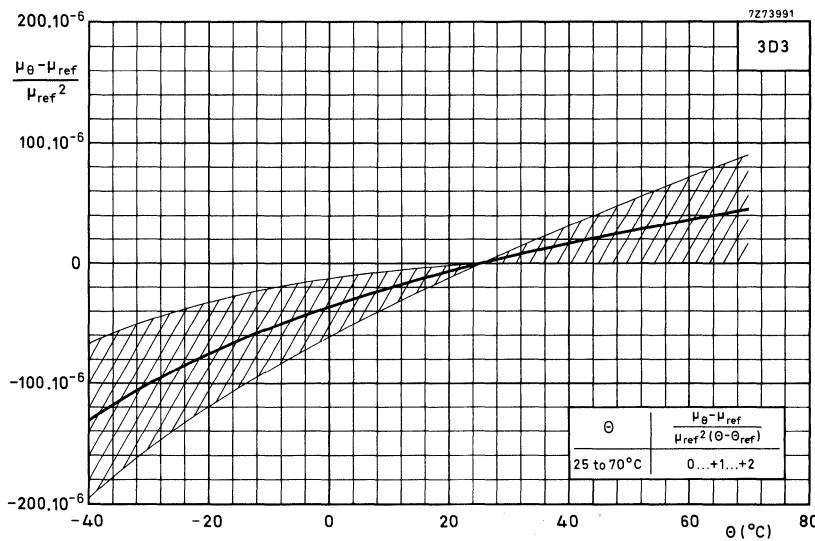
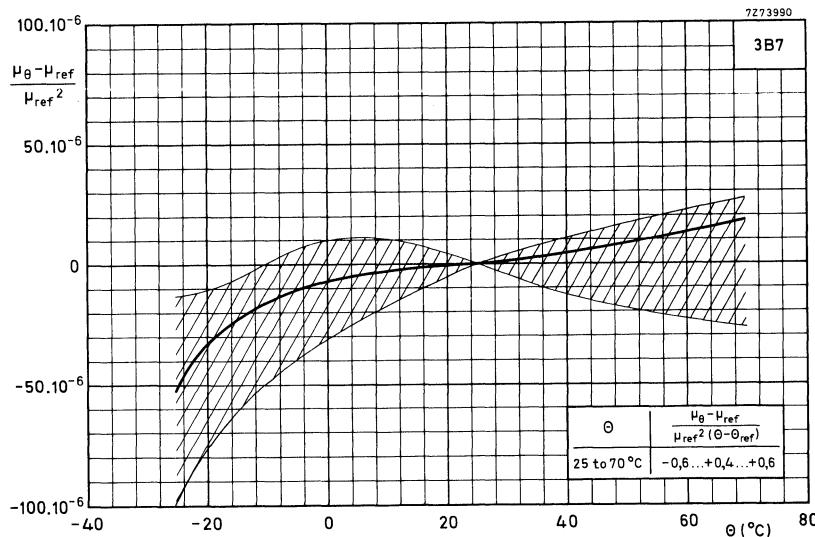




# MnZn and NiZn ferrites

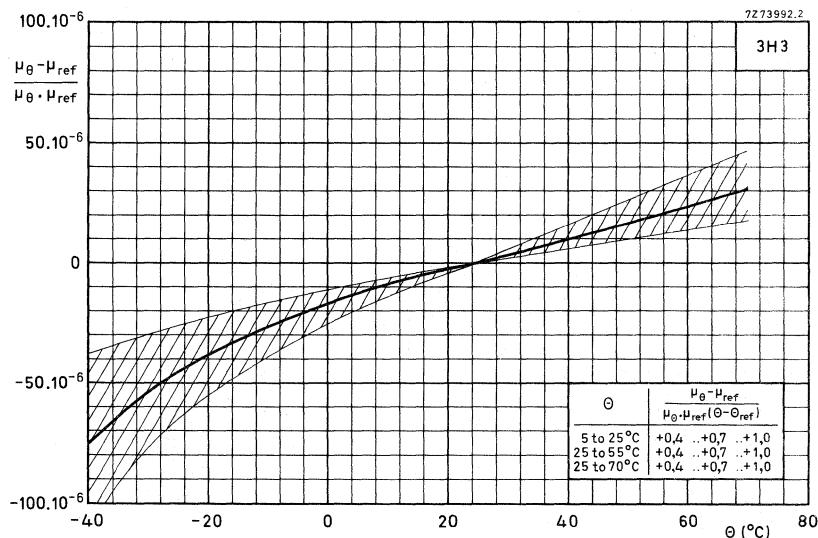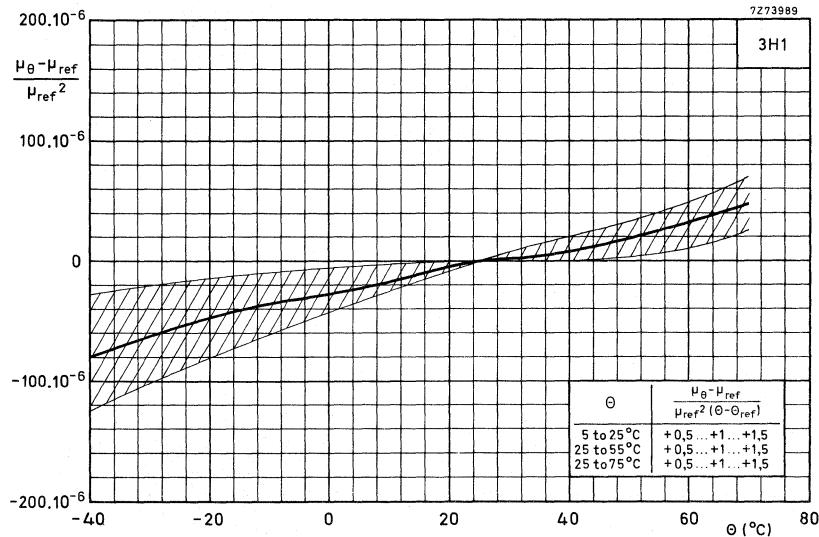


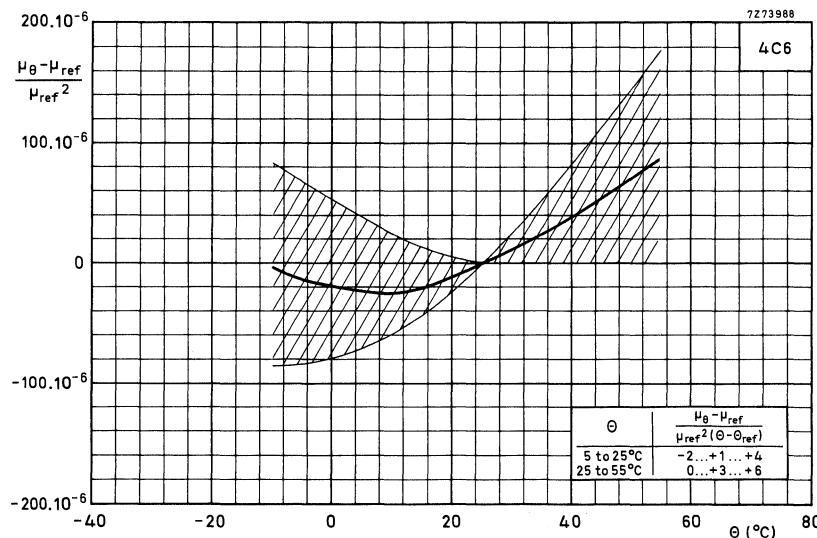


Power loss as a function of the induction

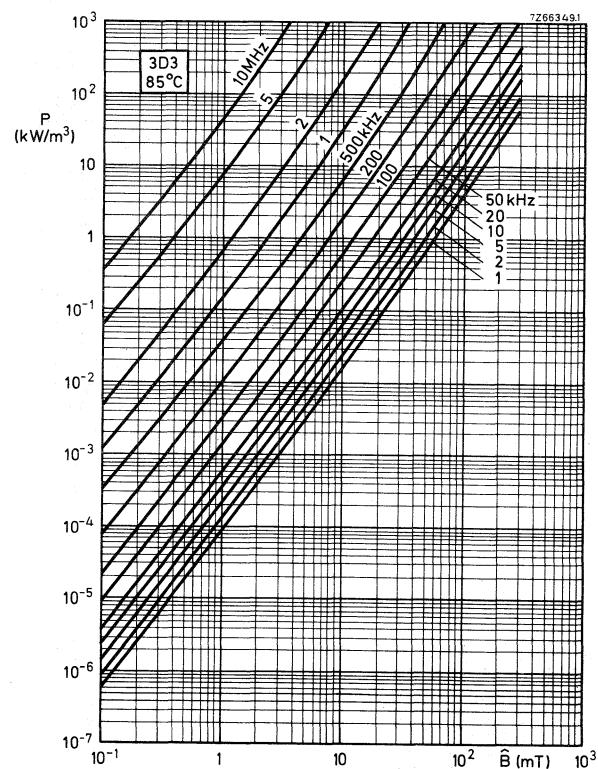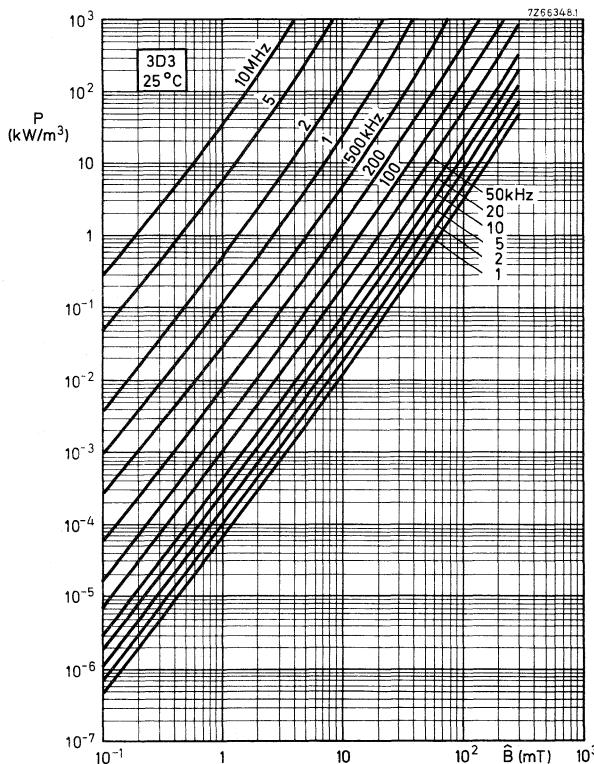

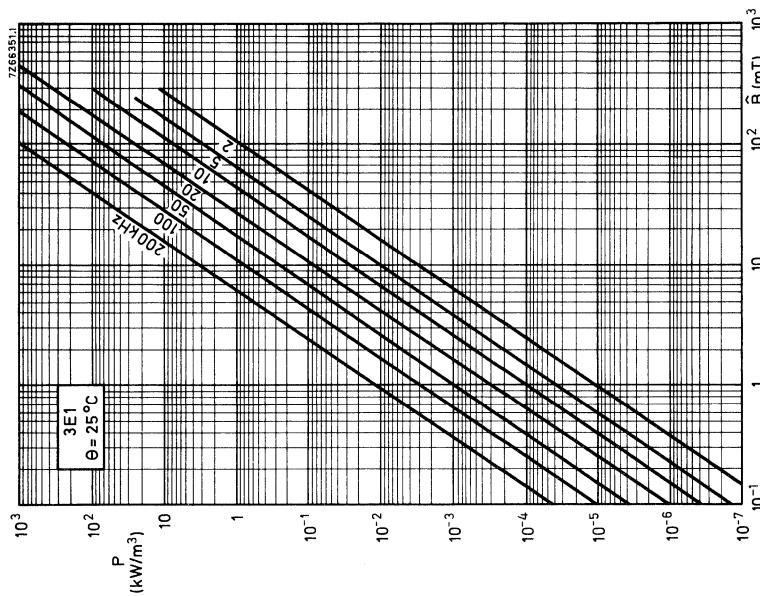
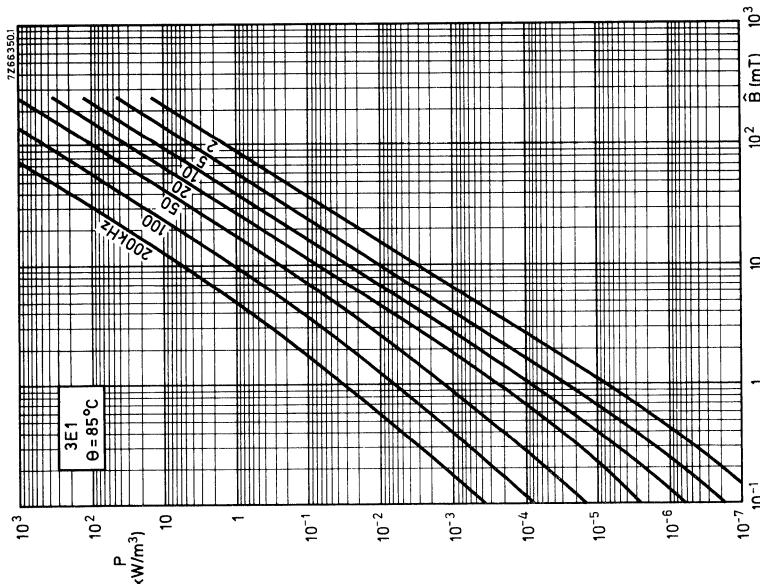


MnZn and  
NiZn ferrites

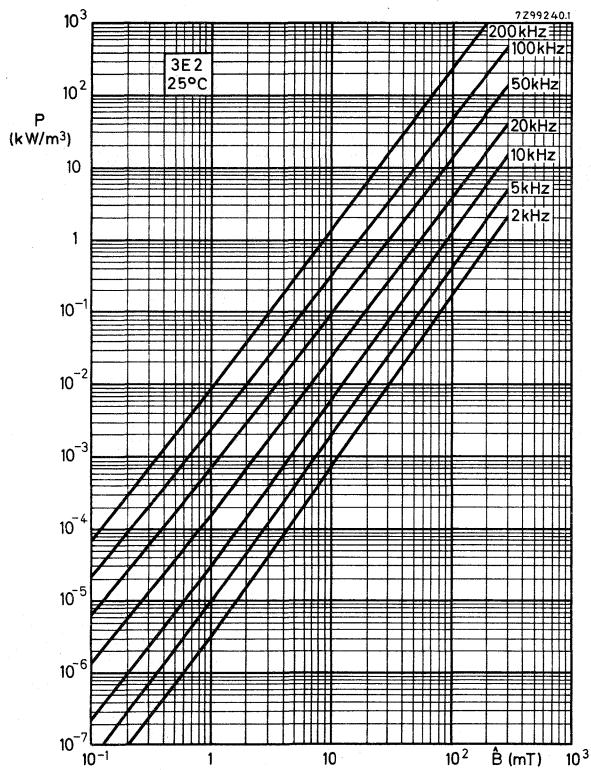
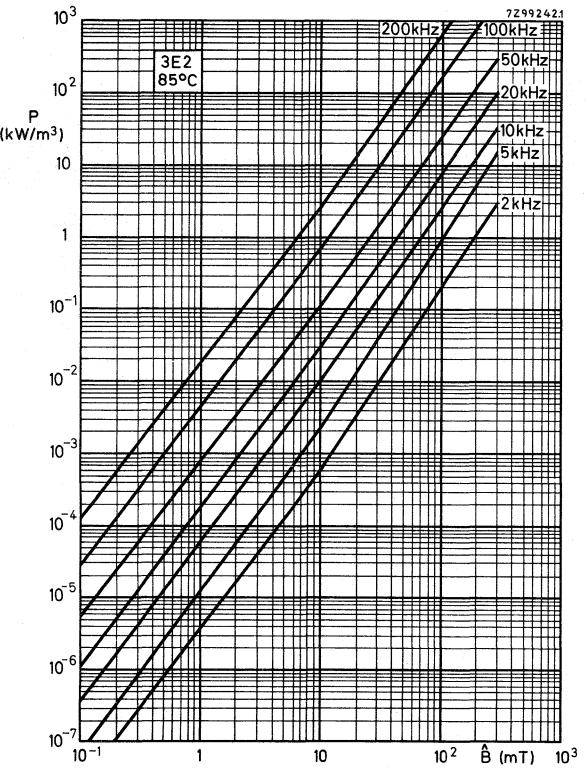



Characteristic curves

MnZn and  
NiZn ferrites

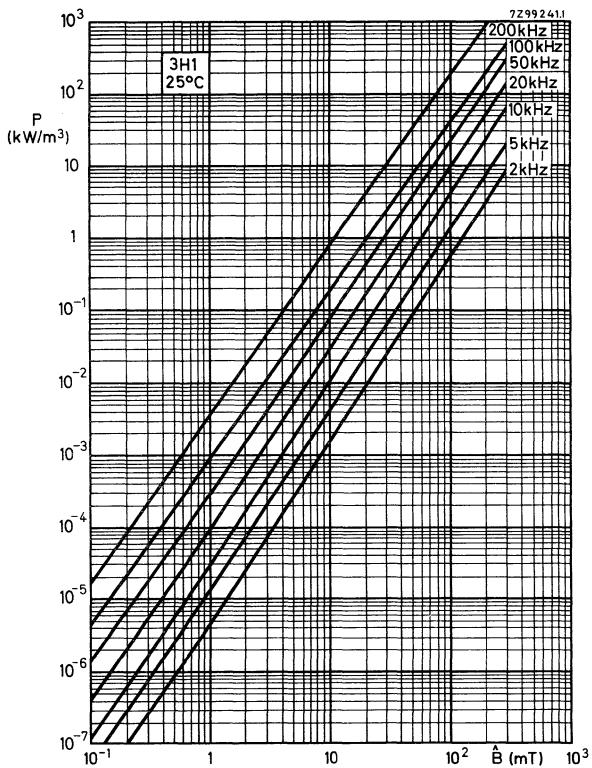
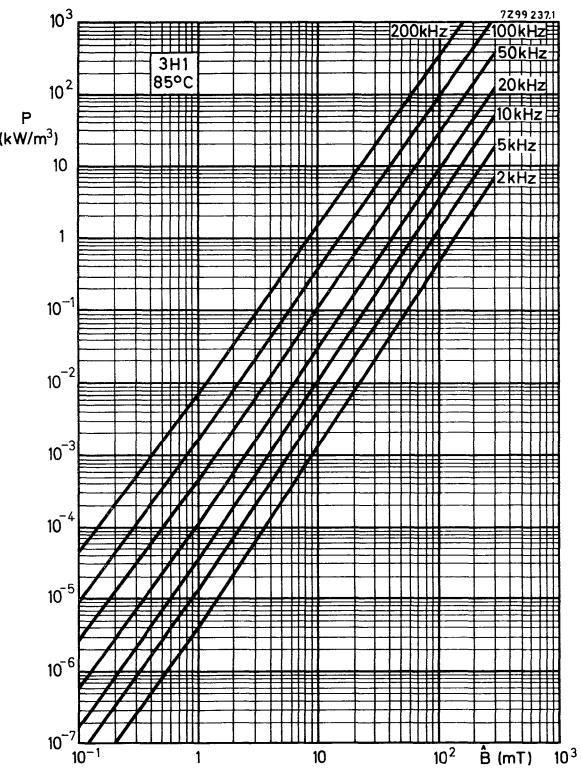


MnZn and  
NiZn ferrites

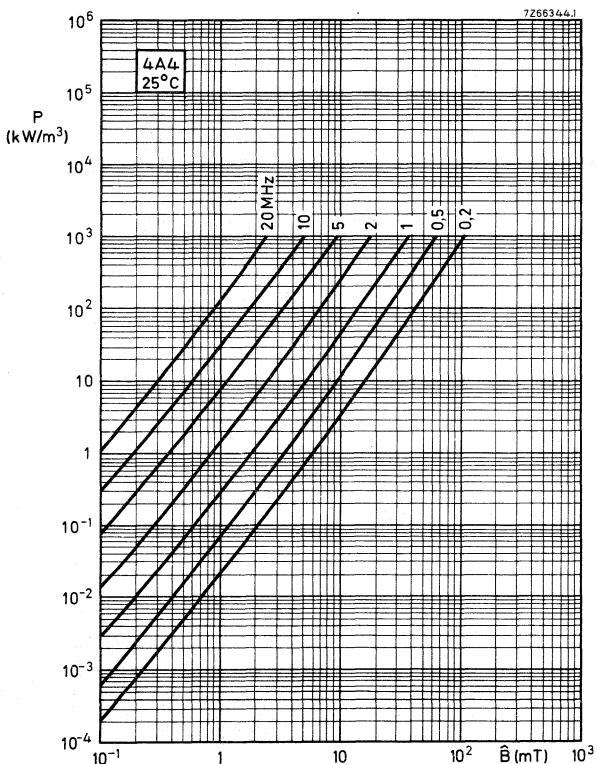
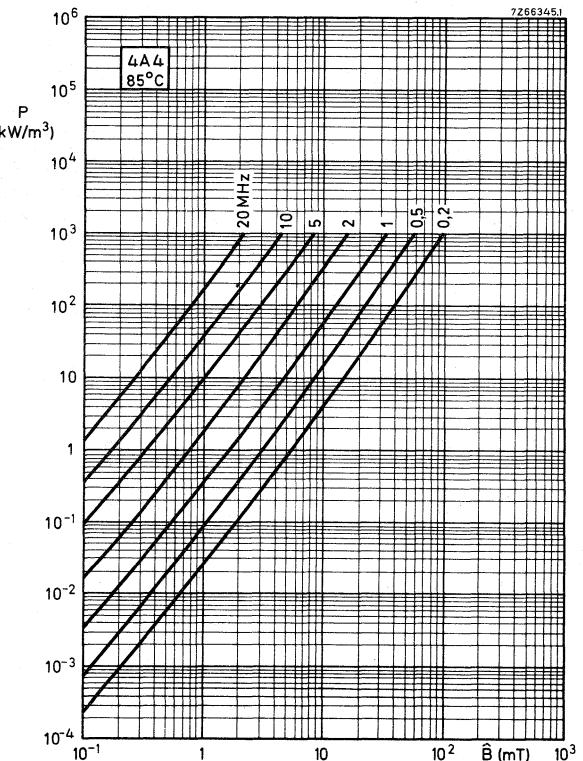


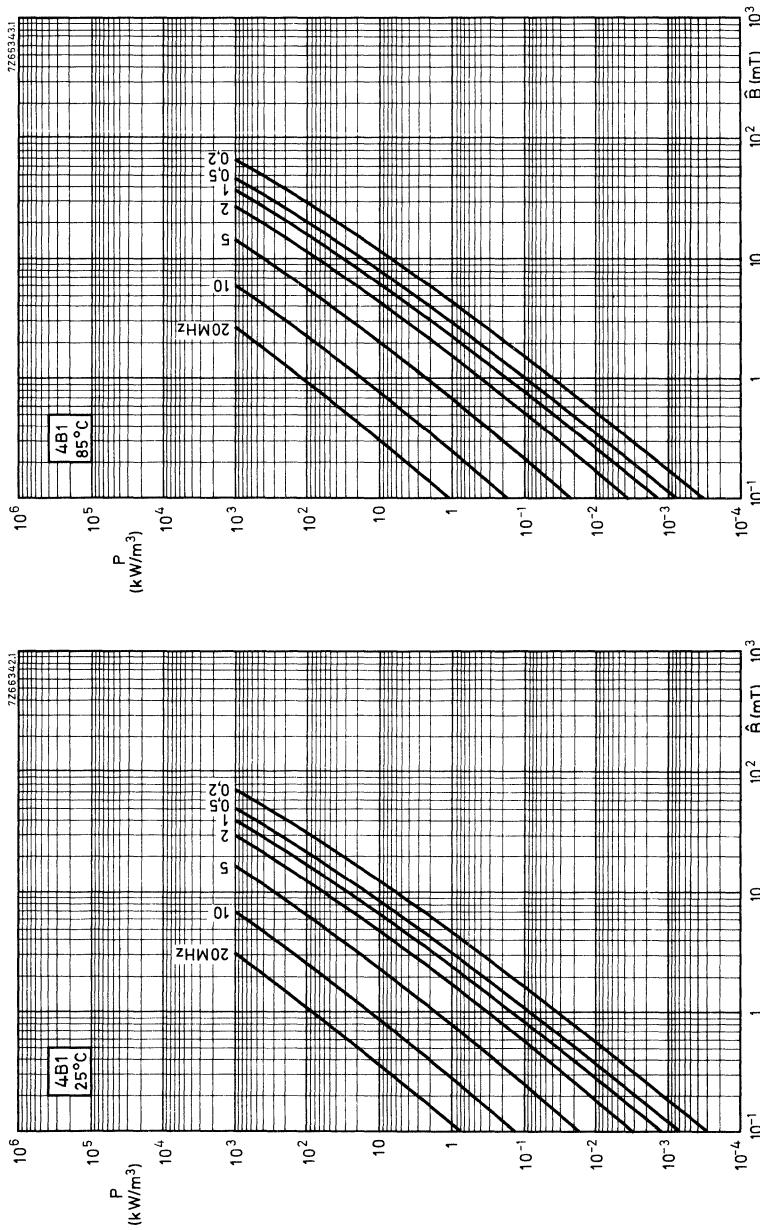



# MnZn and NiZn ferrites

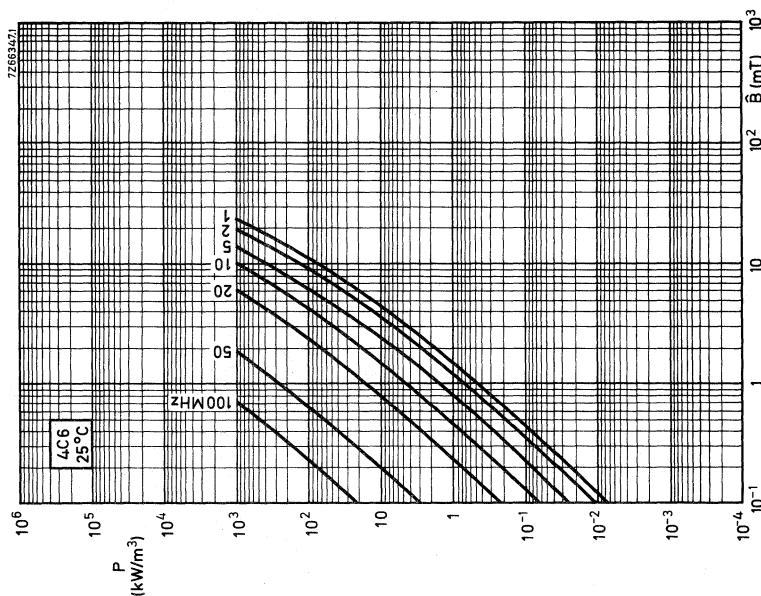
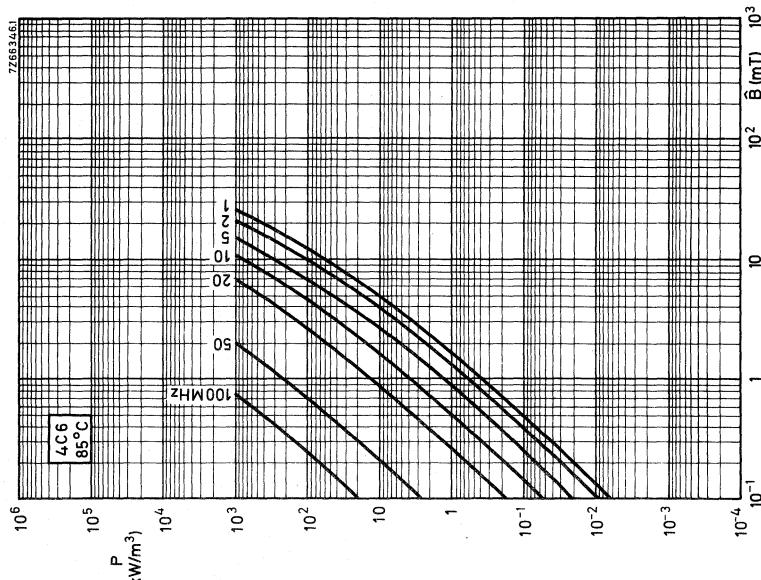


## Incremental permeability as a function of the field strength

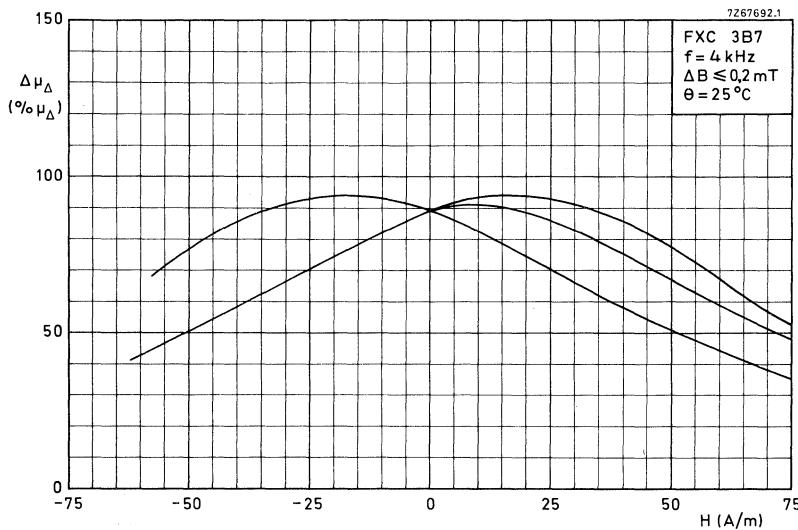
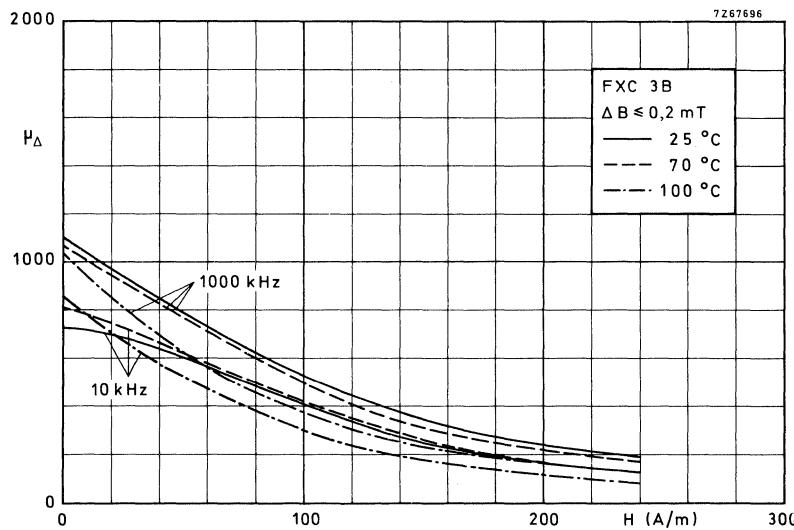



# MnZn and NiZn ferrites

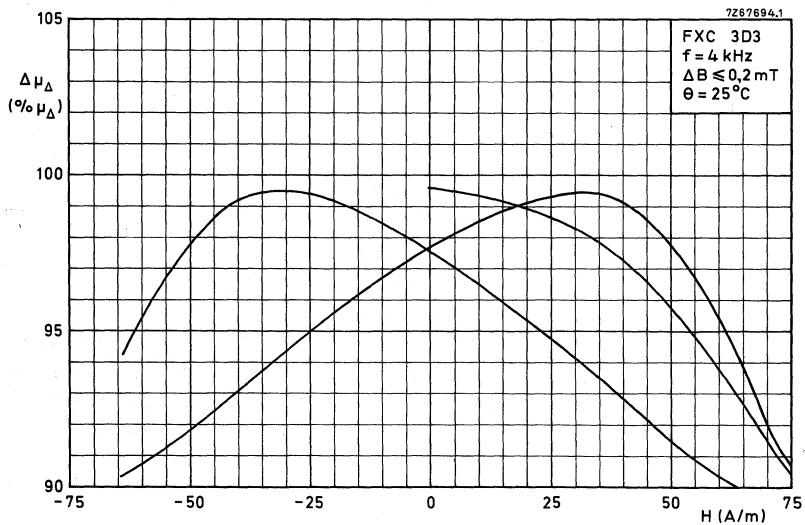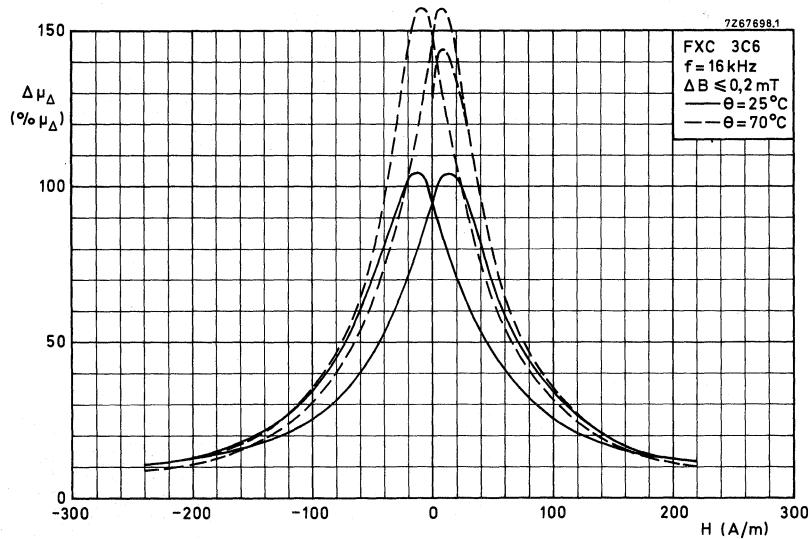


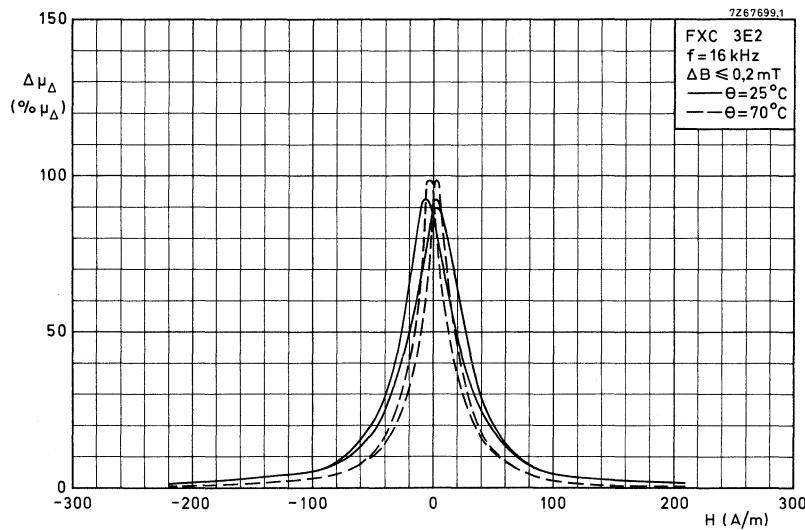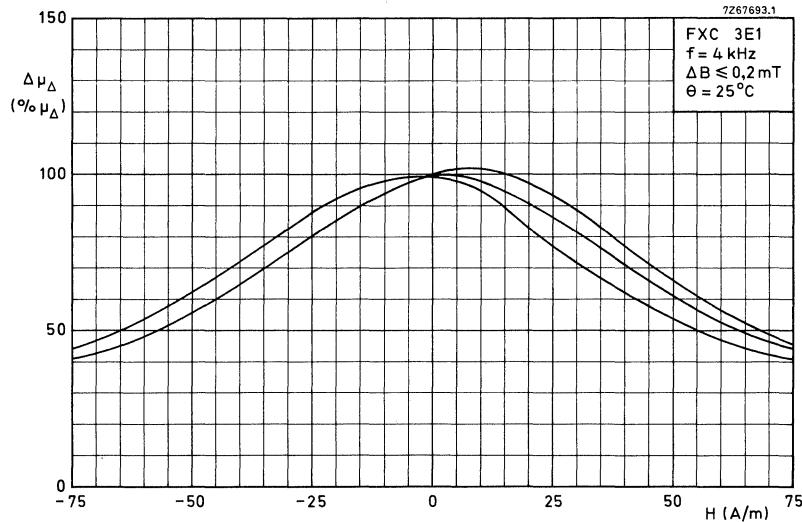

# MnZn and NiZn ferrites

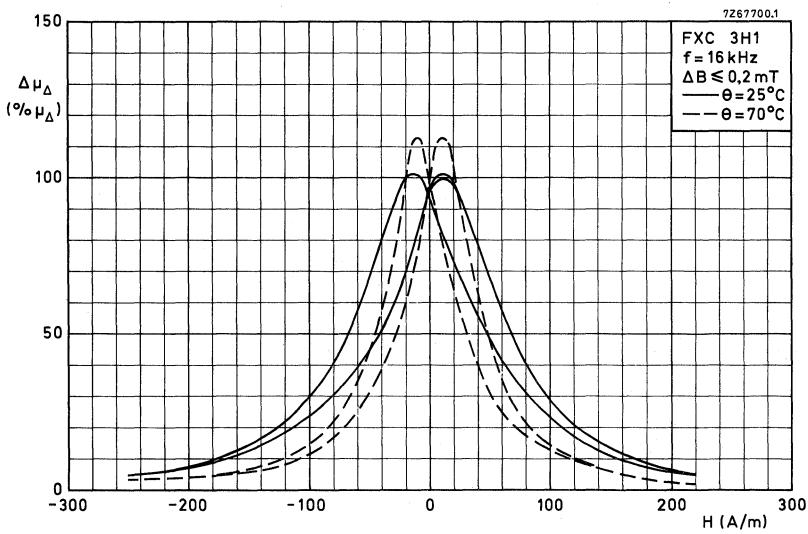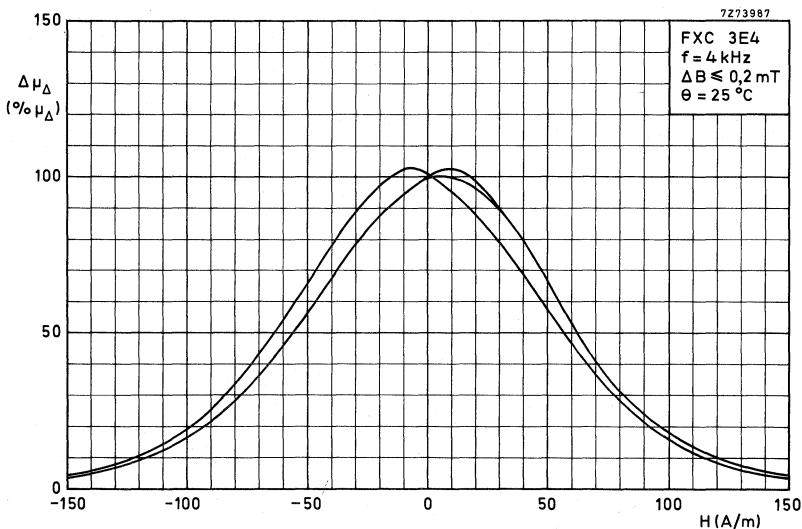


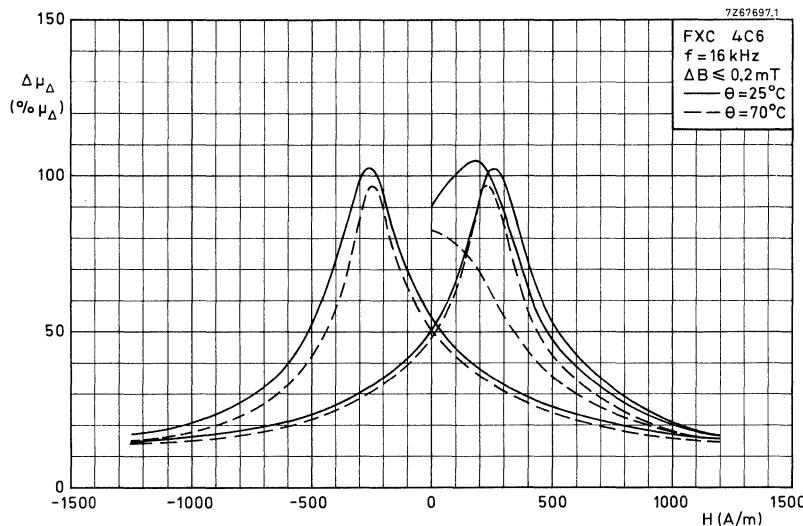

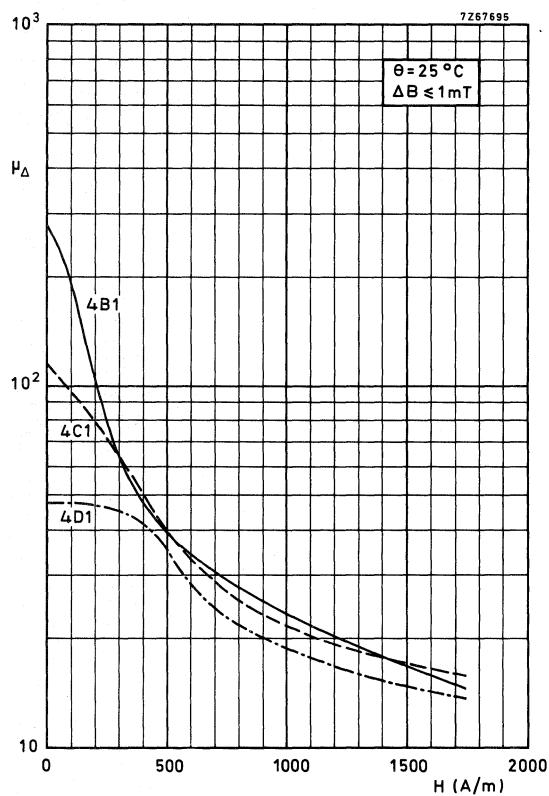

D.C. sensitivity

material grade: 3B8

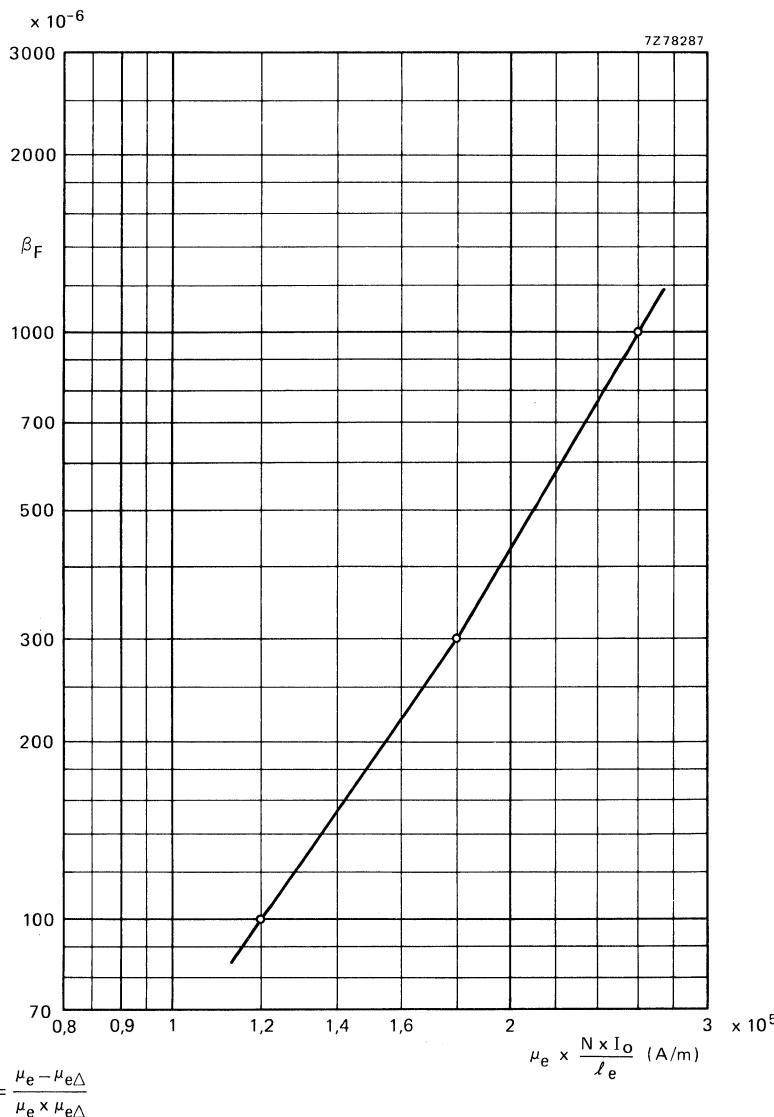

Inductance variation as a function of d.c. polarization. The measured values are situated in the area to the right of the curve.



**SECTION B**  
**YOKES RINGS**





## YOKE RINGS FOR USE IN DEFLECTION COILS FOR PICTURE TUBES

### SURVEY OF TYPES

application	grade	mass g	A mm	B mm	C mm	H mm	catalogue number	page
<b>B/W</b>								
90° (tiny vision)	2A2	62	47	37	29	26	3122 134 91680	59
110°	2A2	135	56,3	58	39,5	27,5	3122 134 91940	61
110°	3C2	135	56,3	58	39,5	26	3122 104 93840	54
110°	3C2	215	79	54	—	37	3122 134 90750	56
110° (tiny vision)	3C2	90	57		30,6	26,5	4313 020 35380	71
	3C2	196	74	54	38	37	4322 020 35070	70
90°	3C2	112	63	50	38	32	3122 134 90600	55
Data graphic display	3C2	364	94	58	46	54	3122 134 92030	62
<b>COLOUR</b>								
90°	2A2	235	92	60	48	46,5	3122 134 91610	58
90°	2A2	153	74	52	40	37	3122 134 92510	64
90° (39SW)	2A2	228	92	60	48	42	3122 134 92600	66
90° (51FS)	2A2	235	89	60	46,5	42	3122 134 92780	68
90° (36FS)	2A2	157	76	52	40	33	3122 134 93050	69
90°	2A2	268	84	60	48	42	3122 134 91440	57
90° (39SW)	2A2	225	92	66	51	36	3122 134 99370	70
110° (30AX)	3C2	505	138	73,5	60	576	3122 134 92500	63
110° (45AX)	3C2	367	113	65,5	49,5	44,8	3122 134 92750	67
data graphic display	3C2	285	92	64,2	52	48	3122 134 92590	65
data graphic display	3C2	760	132		51	87	3122 134 91850	60

The data on these yoke rings are arranged on the following pages in order of catalogue number.

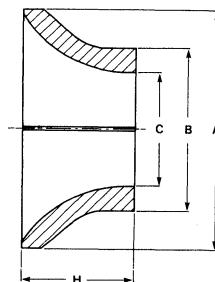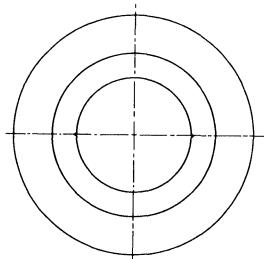


## YOKE RING FOR 110° B/W TUBES

- Material grade FXC 3C2
- Mass 135 g
- Catalogue number 3122 104 93840

Spring clips for assembling can be supplied, catalogue number 3122 101 06340.



Dimensions in mm

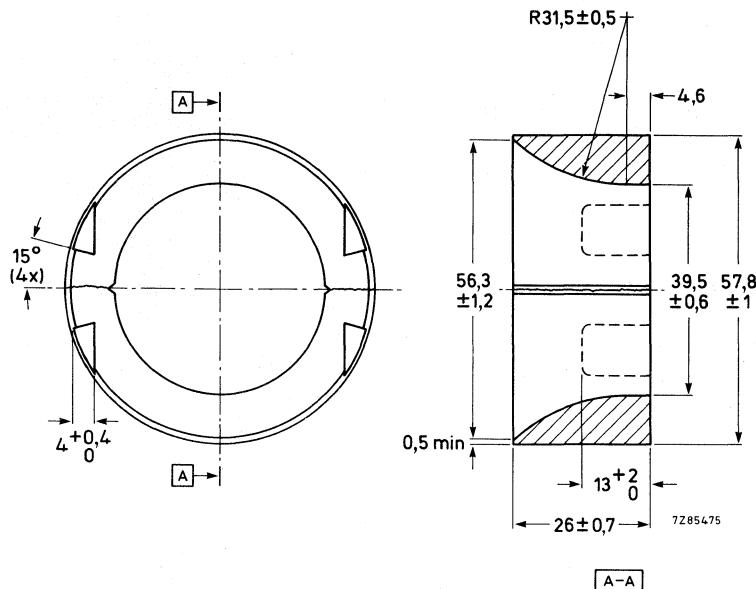

## YOKE RING FOR 90° B/W TUBES

- Material grade FXC 3C2
- Mass 112 g
- Catalogue number 3122 134 90600

Dimensions in mm

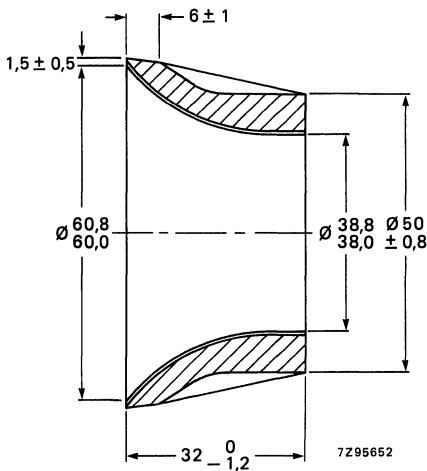
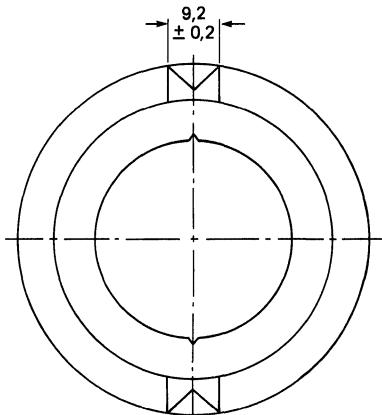


## YOKE RING FOR 110° B/W TUBES

- Material grade
- Mass
- Catalogue number

FXC 3C2  
215 g  
3122 134 90750

Dimensions in mm

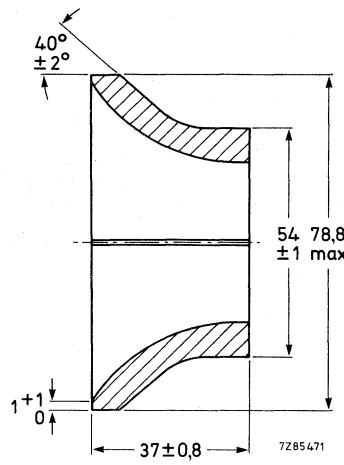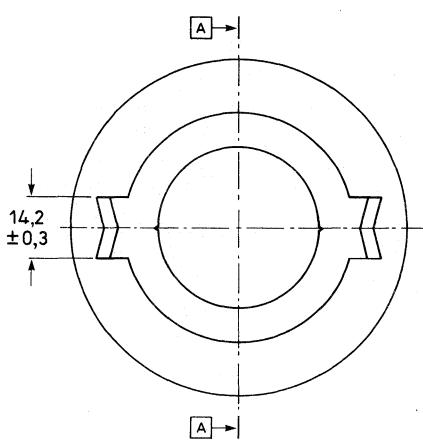


A-A

## YOKE RING FOR 90° HYBRID COLOUR TUBES

- Material grade 2A2
- Mass 268 g
- Catalogue number 3122 134 91440

Dimensions in mm

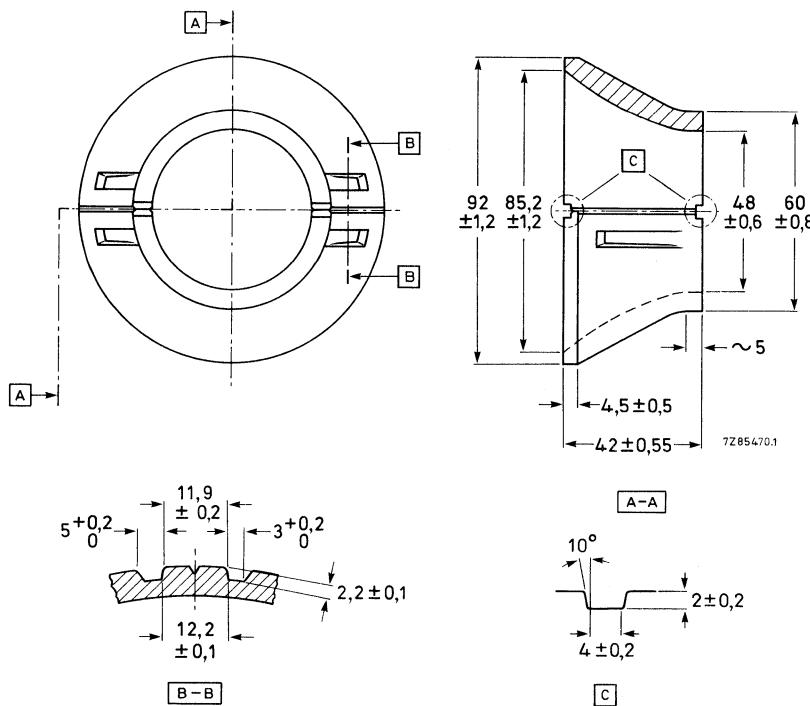


## YOKE RING FOR 90° COLOUR TUBES

- Material
- Mass
- Catalogue number

FXC 2A2  
235 g  
3122 134 91610


Dimensions in mm

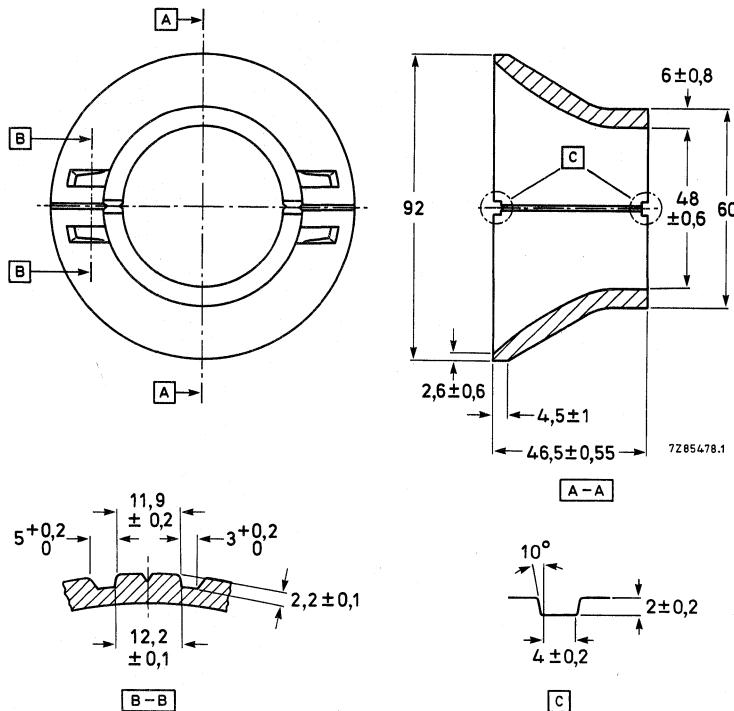

## YOKE RING FOR 90° B/W TINY VISION TUBES

- Material grade FXC 2A2
- Mass 62 g
- Catalogue number 3122 134 91680



Dimensions in mm

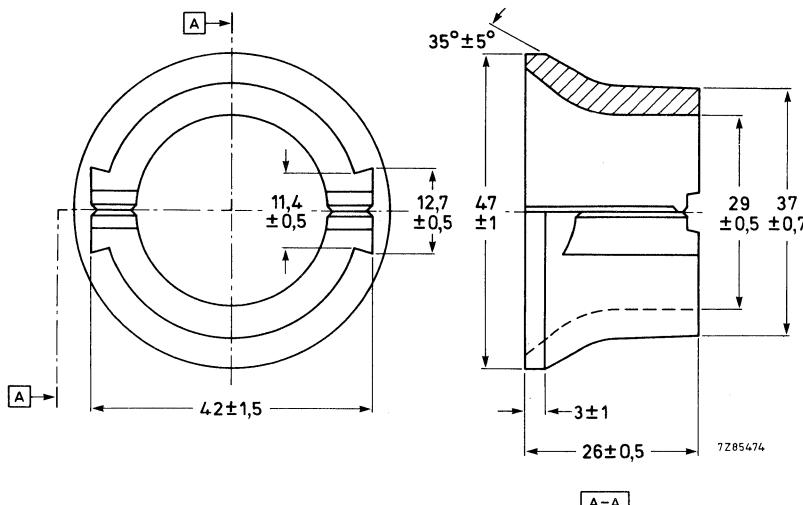

## YOKE RING FOR COLOUR DATA GRAPHIC DISPLAY TUBES

- Material FXC 3C2
- Mass 760 g
- Catalogue number 3122 134 91850


Dimensions in mm

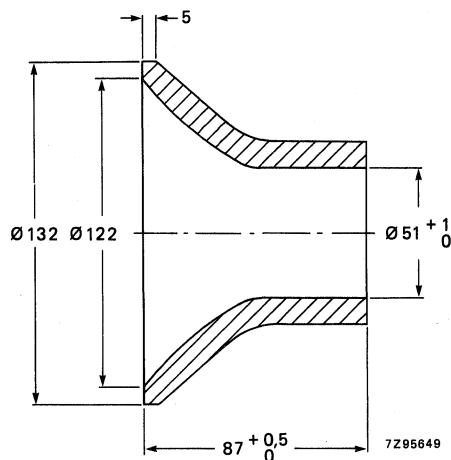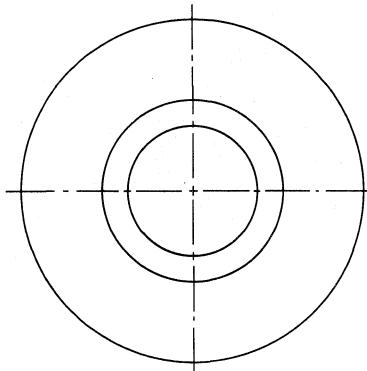

## YOKE RING FOR 110° B/W TUBES



- Material grade FXC 2A2
- Mass 135 g
- Catalogue number 3122 134 91940

Dimensions in mm

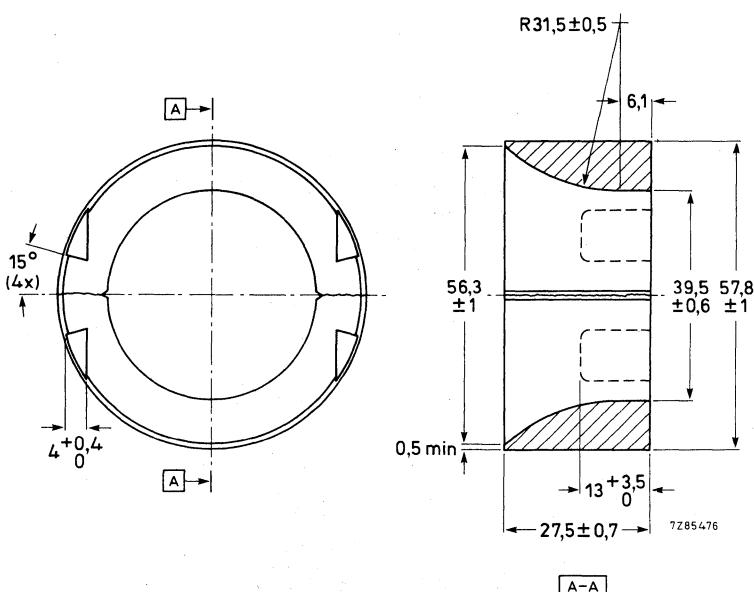

## YOKE RING FOR B/W DATA GRAPHIC DISPLAY TUBES


- Material grade FXC 3C2
  - Mass 364 g
  - Catalogue number 3122 134 92030 silanated
- Dimensions in mm

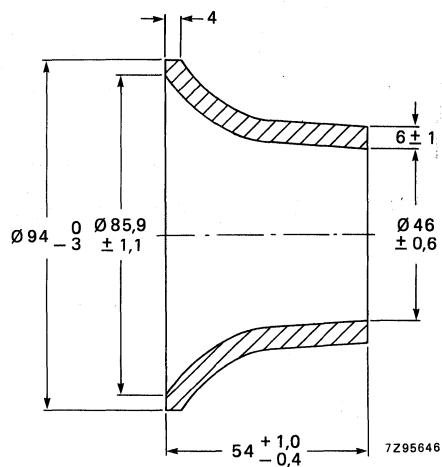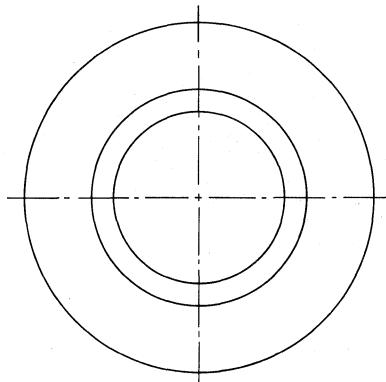

YOKE RING FOR 110° COLOUR TUBES  
30AX SYSTEM

- Material grade FXC 3C2
- Mass 505 g
- Catalogue number 3122 134 92500 silanated




Dimensions in mm

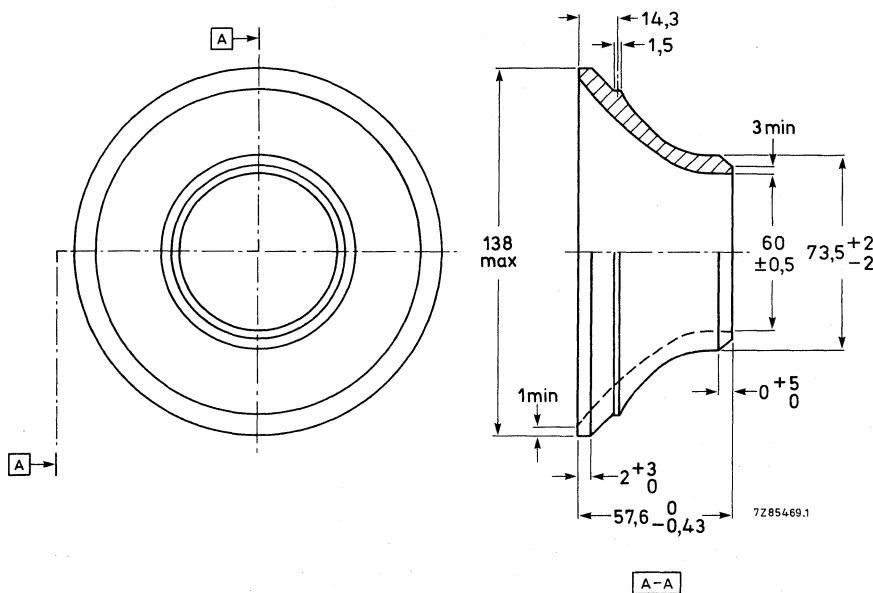

## YOKE RING FOR 90° COLOUR TUBES — MN

- Material grade
- Mass
- Catalogue number



FXC 2A2  
153 g  
3122 134 92510

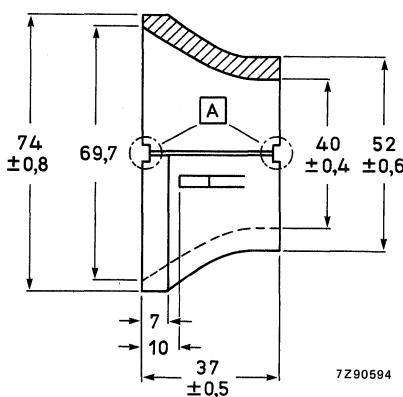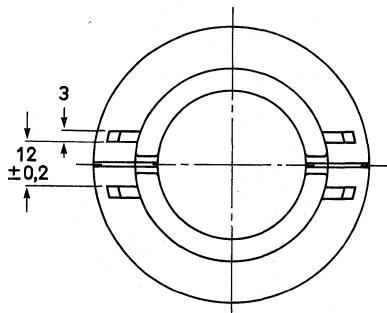

## YOKE RING FOR COLOUR DATA GRAPHIC DISPLAY TUBES


- Material FXC 3C2
- Mass 285 g
- Catalogue number 3122 134 92590 silanated

Dimensions in mm

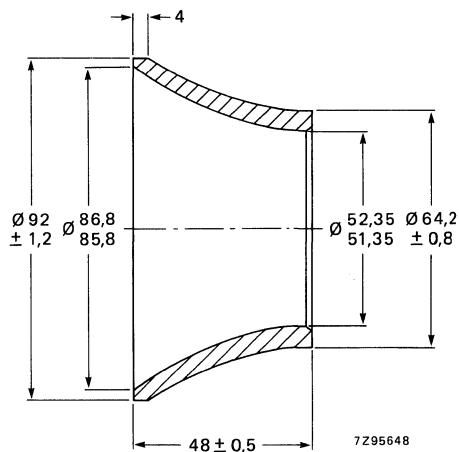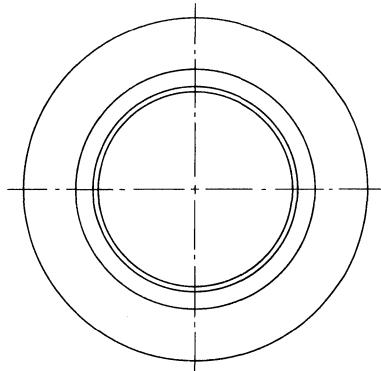

## YOKE RING FOR 90° COLOUR TUBES – 39SW



- Material grade FXC 2A2
  - Mass 228 g
  - Catalogue number 3122 134 92600 (4313 020 35400 export packed)
- Dimensions in mm

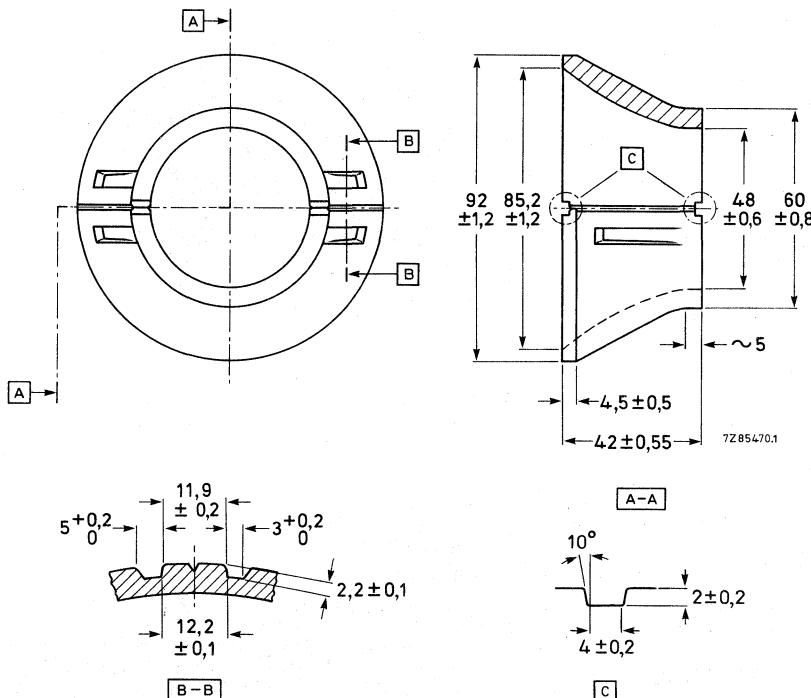

## YOKE RING FOR 110° COLOUR TUBES 45AX

- Material grade FXC 3C2
- Mass 367 g
- Catalogue number 3122 134 92750 silanated

Dimensions in mm

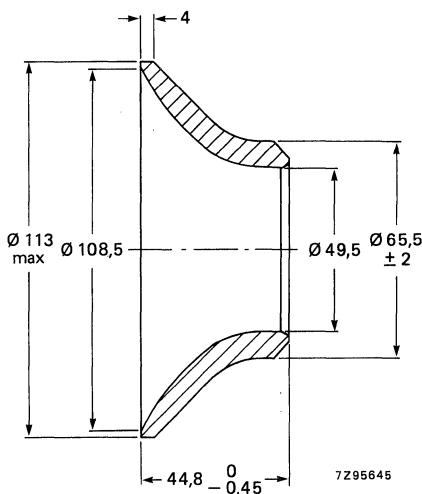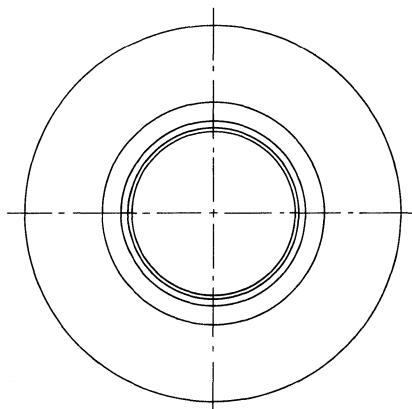

3122 134 92780

## YOKE RING FOR 90° COLOUR TUBES — 51FS



- Material grade
- Mass
- Catalogue number

FXC 2A2

235 g

3122 134 92780 (4313 020 35500 export packed)



Dimensions in mm

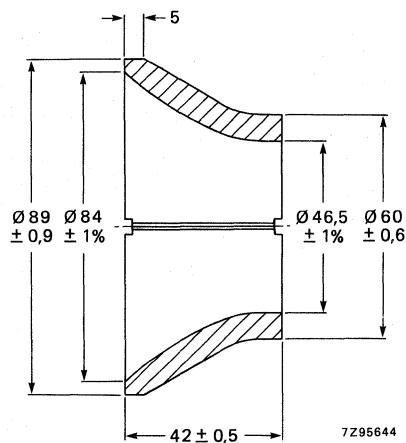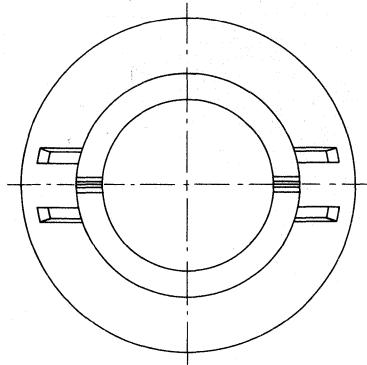

## YOKE RING FOR 90° COLOUR TUBES — 36FS

- Material grade FXC 2A2
- Mass 157 g
- Catalogue number 3122 134 93050

Dimensions in mm

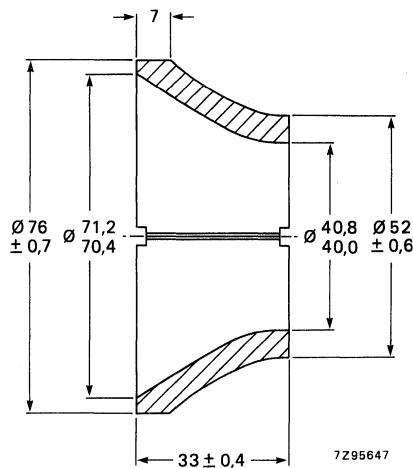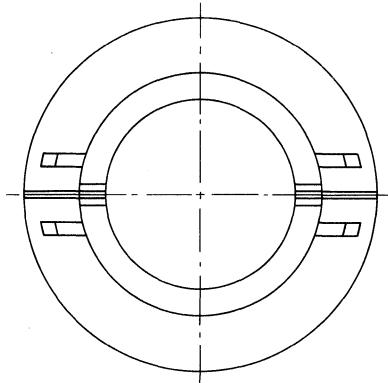

## YOKE RING FOR 90° COLOUR TUBES – 39SW



- Material grade
- Mass
- Catalogue number

FXC 2A2

225 g

3122 134 99370 (4313 020 35910 export packed)



Dimensions in mm

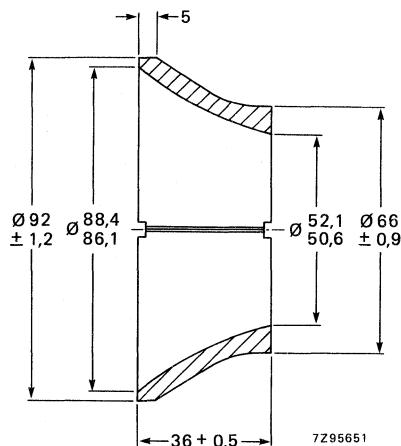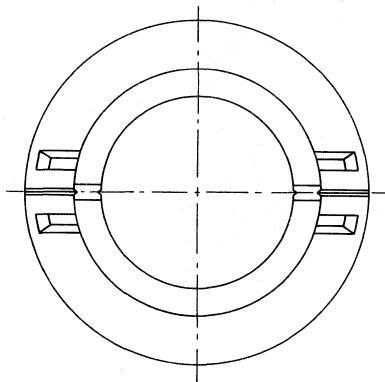

## YOKE RING FOR 110° B/W TINY VISION TUBES



- Material grade FXC 3C2
- Mass 90 g
- Catalogue number 4313 020 35380

Dimensions in mm

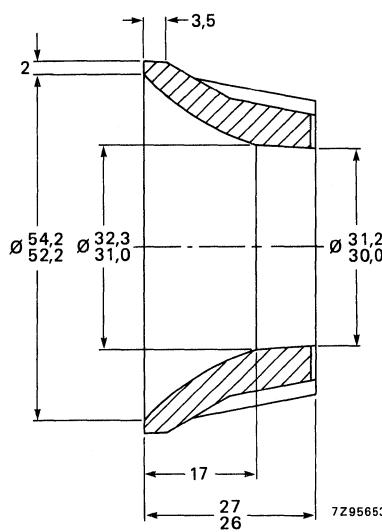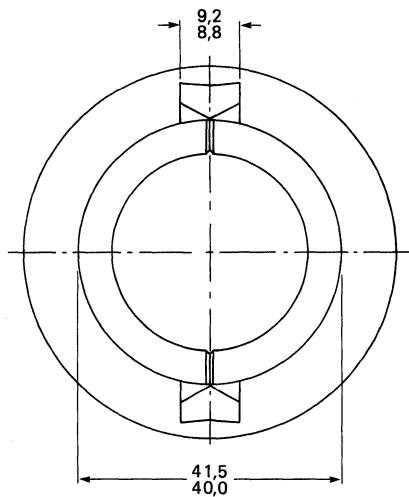

## YOKE RING FOR 90° B/W TUBES

- Material grade FXC 3C2
- Mass 196 g
- Catalogue number 4322 020 35070

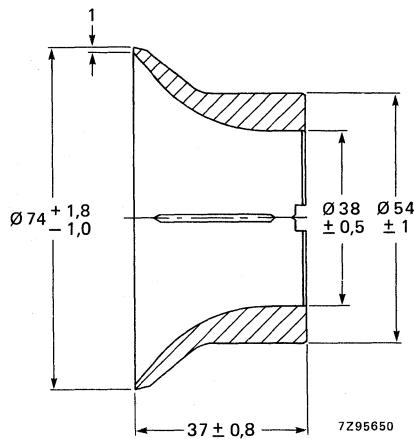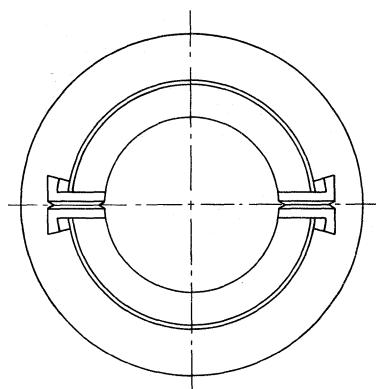

**SECTION C**  
**E/EC/ETD/U/I CORES**



## INTRODUCTION

### CORE TYPE AND MATERIAL GRADE SELECTION GUIDE

The range of applications of ferrite transformer and choke cores is very wide. This applications survey concentrates on the more popular, and more typical, applications so that these can be used as a guide to other, similar requirements. However, even where a clear indication in the Selection Guide is given for a given core and material, cost/performance trade-offs might be possible, especially where large quantities are involved. Intending users of ferrite cores are always recommended to consult us during equipment development, before a final core selection is made.

#### Using the selection guide

Starting with the paragraph Applications, below, find the application description that most closely resembles the intended application. Note the number or numbers of the application category. Proceed to the paragraph Application Categories and refer to the Category number obtained previously.

If the description of the application conditions fits the intended application, consult the tables or charts of core types indicated to select the most suitable core and material grade.

#### Applications

application	application category
Chokes, power suppression	1 3
Driver transformers	2
Line-output transformers	1
Matching transformers	2
Power-supply transformers, inverters	1
Converters	1
Switched-mode	1

#### Application categories

##### 1. High power, high flux density, minimum size

Preferred material: Ferroxcube 3C8.

The design of transformers where maximum throughput power is required in the minimum of volume requires careful balancing of core and winding dissipation. For details, refer to the section Cores for switched-mode power supplies. Selection charts for power transformer cores for switch-mode power supplies are also given in this section.

Ferroxcube 3C8 has been developed for optimum performance in power applications, and is the ideal material where transformer or choke volume is a principal consideration. All EC, E and U cores are available in Ferroxcube 3C8, but coil formers for U cores and some E cores are not listed here. Power-choke core selection and design is considered in detail in the section Power Choke Design.

Round-section U core type U64 in Ferroxcube 3C8 material was developed primarily for line-output transformers in colour TV receivers. A number of other round-section U cores suitable for line-output transformers is available.

Small, square-section U cores in Ferroxcube 3C8 material are especially suitable for small-power-supply applications, such as inverters. The effective magnetic dimensions of pairs of the cores are listed in the following table.

core type	$I_e$ (mm)	effective dimensions $A_e$ (mm <sup>2</sup> )	$V_e$ (mm <sup>3</sup> )
U10/8/3	38,4	8,63	331
U15/11/6	48	30	1 440
U20/16/7	68	56	3 800
U25/20/13	86	100	8 600
U30/25/16	111	157	17 400

Very large cores for transformers in the kilowatt power range can be assembled from larger, square-section U cores of types U93/52/30 and U100/57/25: either in combination with matching I cores, or by stacking. Please consult us on the properties of large stacks.

### 2. Minimum loss, low operating flux density

Preferred material: Ferroxcube 3E1.

A wide range of E cores, including DIN E cores, is available in Ferroxcube 3E1. These cores are also available with a ground air gap. The table below gives winding window area and induction factor  $A_L$  for the E cores with coil formers used in pairs. The induction factor  $A_L$  has a tolerance of 25% for cores selected at random and pressed together.

Small U cores in Ferroxcube 3C8 material often prove more attractive for driver transformers. These are listed under category 1.

core type	winding window area (mm <sup>2</sup> )	$A_L$ (nH)
EE20/20/5	27	2 405
EE30/30/7	80	3 330
EE42/42/15	178	7 555
EE55/55/21	250	11 937
EE65/65/13	394	15 450

### 3. Suppressor chokes

The small, square-section U cores listed under category 1 are ideal for use as cores for suppressor chokes in higher-current applications. Where there is a d.c. component of the line current, a spacer should be used. The data given in the section Power Chokes, together with curves in the data sheets should be used for selecting cores and designing suppressor chokes.

### CORES FOR SWITCHED-MODE POWER SUPPLIES

Ferroxcube grade 3C8/3C85 was developed specifically to meet the stringent demands placed on power supply chokes and transformers, especially those in switched-mode power supplies, operating at 10 kHz or higher. At these high frequencies the eddy current losses are very low due to the high bulk resistivity of Ferroxcube 3C8/3C85, whose permeability remains the same as at low frequencies. In general, therefore, this means a much smaller transformer can be designed than with laminated iron cores.

Ferroxcube 3C8/3C85 is a manganese-zinc ferrite which meets the main magnetic requirements for power transformer cores:

- high maximum flux density ( $B$ ) and high relative amplitude permeability ( $\mu_a$ ).
- high resistivity ( $\rho$ ) to ensure low eddy current losses.
- high Curie point, so that magnetic properties are retained at high temperature (up to 200 °C).
- in the operating temperature range (up to 100 °C), losses fall as temperature increases.

### Switched-mode power supply circuits

The basic arrangement of a switched-mode power supply (SMPS) is shown in Fig. 1. In this system, the power input is rectified and filtered and the resulting d.c. voltage is chopped at a high frequency by a switch. The chopped waveform is applied to the primary of a transformer and the secondary output is rectified and filtered to give the required d.c. output. The output voltage is sensed by a control circuit which supplies a correction signal to the drive circuit to vary the ON-OFF time of the switched waveform and compensate for any change at the output. This same system can operate from a battery or any other d.c. input.

There are numerous circuit designs that can be used to convert d.c. input voltage to the required d.c. output voltage. But some preliminary design selection will have to be made as to the type of converter circuit to use. Since the emphasis here is on the design of the magnetic components used in switched-mode power supplies, the many different designs are considered from a magnetics point of view.

Analysing available circuits this way, three broad basic converter designs can be distinguished, based upon the magnetic converting device: flyback, forward and push-pull converters.


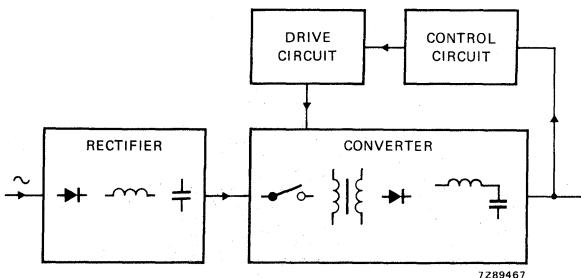


Fig. 1 Block diagram of switched-mode power supply.

*Flyback converter*

Figure 2 shows the basic circuit of a flyback converter and the associated waveforms. When the switch is closed (transistor conducts), the supply voltage is connected across the inductor and the output diode is non-conducting: current rises linearly, storing energy, until the switch is opened. When this happens the voltage across the inductor reverses and the stored energy is transferred into the output capacitor and load. By varying the conduction time of the transistor at a given frequency, the amount of energy stored in the inductor during each ON cycle can be controlled. This is a way of controlling and changing the output of a switched-mode power supply.

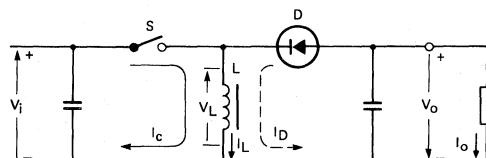

current flow  
—→ switch closed  
- - - → switch open

7289468

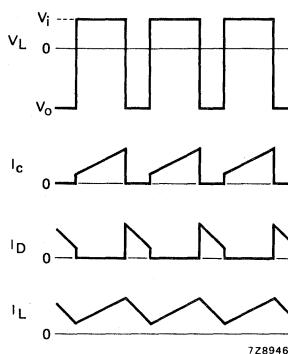


Fig. 2 Basic circuit of a flyback d.c. to d.c. converter with associated waveforms.

In Fig. 3, the basic circuit of Fig. 2 is developed into a practical circuit using an inductor with two windings. The progression from Fig. 3a via 3b to 3c can easily be understood. In a flyback converter the energy to be transferred to the output capacitor and load is first stored in the inductor. It is therefore possible to obtain line isolation by adding a secondary winding to the inductor. (Although an inductor with more than one winding appears in schematic diagrams as a transformer, it is referred to as an inductor in accordance with its function.) Another advantage of the flyback converter is the fact that no smoothing choke is required in the output circuit. This is important in high-voltage supplies and in power supplies with a number of output circuits (see Fig. 4). A disadvantage of this type of converter is that the output capacitor is charged only during the transistor OFF cycle. Hence the output capacitor ripple current is high when compared with the other types of converters. Another disadvantage of the flyback converter relates to the energy storage in the inductor. The inductor is driven in one direction only, which requires a larger core in a flyback design than for an equivalent design using a forward or push-pull converter.

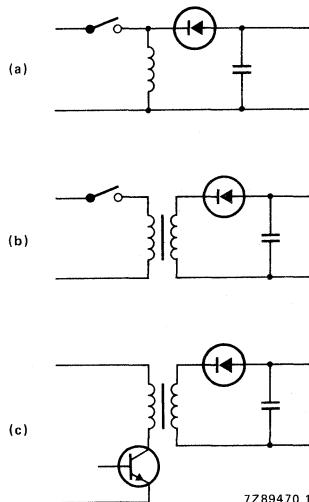


Fig. 3 Development of practical flyback converter circuit.

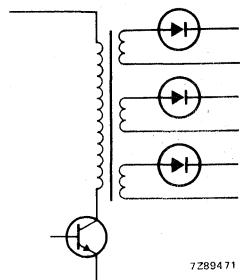


Fig. 4 Multiple output flyback converter circuit.

### Forward converter

Figure 5 gives the basic circuit of the forward converter, along with the associated voltage and current waveforms. When the switch is closed (transistor conducts), the current rises linearly and flows through the inductor into the capacitor and the load. During this ON cycle, energy is both transferred to the output and stored in the inductor  $L$ . When the switch is opened the energy stored in the inductor causes the current to continue to flow to the output via the diode.

As in the flyback converter, the amount of energy stored in the inductor can be varied by varying the ON-OFF cycles. This gives a method of controlling the output of the forward converter.

Figure 6 shows a more practical forward converter circuit with a line-isolation transformer. The need for a separate transformer for line isolation is an obvious disadvantage of this converter circuit when compared with the flyback converter. A major advantage of the forward converter in comparison with the flyback converter is the lower ripple voltage at the output. This is due to the fact that the high-frequency ripple current feeding into the smoothing capacitor is limited by the inductor. This advantage is of particular interest for low-voltage supplies.

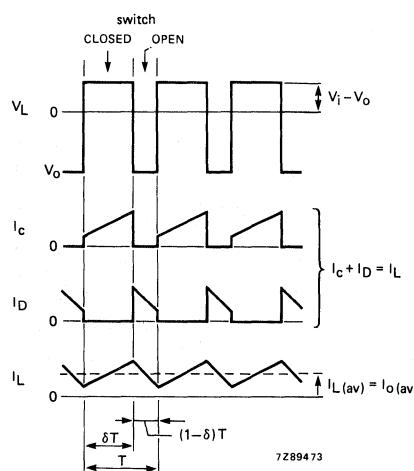
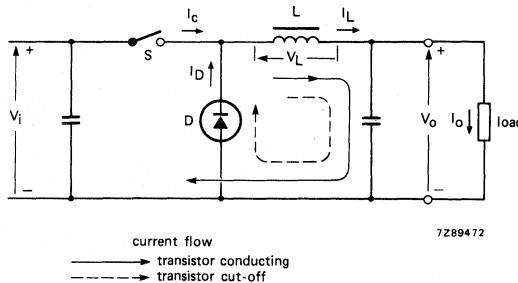


Fig. 5 Basic circuit of a forward d.c. to d.c. converter with associated waveforms.

Multiple outputs in a forward converter can be obtained by using more secondary windings on the transformer. Each of these windings, however, will have to have the two diodes, an inductor and capacitor. This method can cause regulation difficulties and is expensive.

Under certain conditions, a better approach is to use a combination of forward and flyback converters. (A dual output converter where this principle is demonstrated is shown in Fig. 7). Here the energy is stored in the inductor, to power another output. At the end of the transistor conduction cycle the voltage across the inductor is equal to the output voltage  $V_{o1}$ . Therefore, if  $V_{o1}$  is stabilized,  $V_{o2}$  will also be stabilized. The amount of energy that can be stored in the inductor is clearly limited. However, this circuit is a practical alternative in cases where a constant-load second output is required that is 30 per cent or less of the main output.

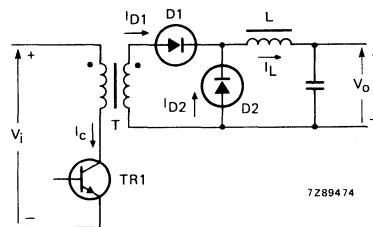


Fig. 6 Forward converter with line isolation transformer.

In Fig. 7 the transformer is shown with a tertiary winding and a diode in series. The purpose of the additional winding and diode is as follows: during the conduction cycle of the transistor, the magnetizing current increases linearly to some final value. As soon as the transistor is turned off, this magnetizing current is transferred, via the additional winding and diode, back to the d.c. supply. This demagnetizing winding should be tightly coupled with the primary winding to avoid voltage spikes during the switching of the transistors. The demagnetizing winding and diode ensure a return of the transformer's magnetic energy back to the d.c. supply and also limits the transistor collector voltage to twice the d.c. input voltage.



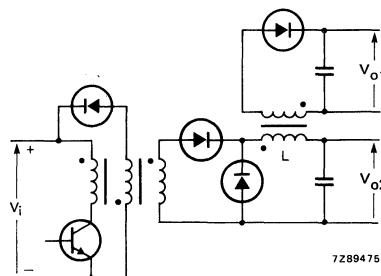



Fig. 7 Dual-output forward converter.

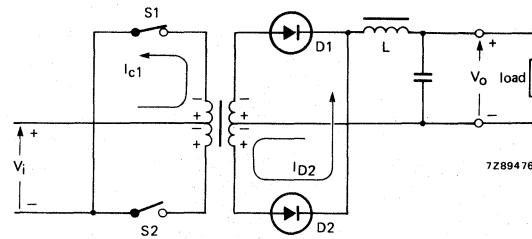

(a)

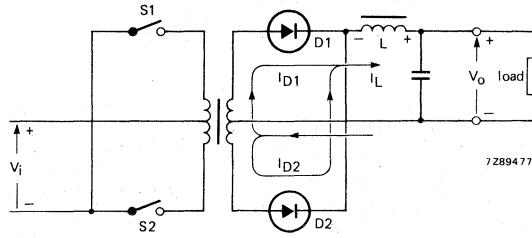

(b)

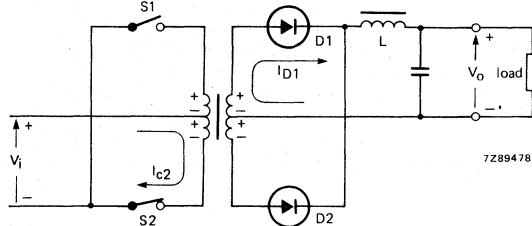

(c)

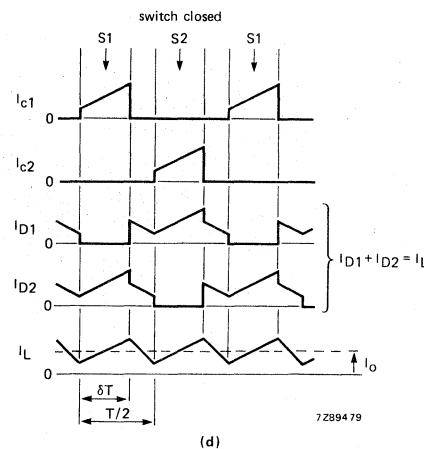


Fig. 8 Basic circuit of a push-pull d.c. to d.c. converter with associated waveforms.

*Push-pull converter*

Figure 8 gives the basic circuit of the push-pull converter, with voltage and current waveforms. The push-pull converter is, in fact, an arrangement of two forward converters operating in antiphase (push-pull action). With switch  $S_1$  closed (Fig. 8a) diode  $D_2$  conducts and energy is simultaneously stored in the inductor and supplied to the load. With  $S_1$  and  $S_2$  open (Fig. 8b), the energy stored in the inductor will continue to support the load current by the parallel diodes  $D_1$  and  $D_2$ , which are now acting as flywheel diodes. When switch  $S_2$  closes (Fig. 8c), diode  $D_1$  will continue to conduct, diode  $D_2$  will stop conducting and the process will repeat itself.

In Fig. 9 a practical push-pull converter circuit is shown. A push-pull converter circuit doubles the frequency of the ripple current in the output filter and, therefore, reduces the output ripple voltage. A further advantage of the push-pull operation is that the transformer core is excited alternately in both directions in contrast to both the forward and flyback converters. Therefore, for the same operating conditions and power throughput, a push-pull converter design can use a smaller transformer core.

Multiple outputs can be constructed by using several secondary windings, each with its own output diodes, inductor and smoothing capacitor. The method that relies on the energy stored in the output choke can also be used here (see Fig. 7, under Forward Converters).

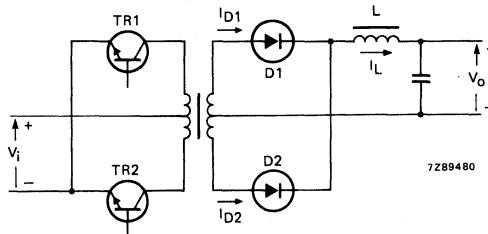


Fig. 9 Conventional push-pull converter circuit.

*Converter selection*

In each of the three basic converter designs there are several different circuit possibilities. In the flyback and forward converters, single and two-transistor designs can be used. If two transistors are used, they will switch simultaneously. This type of circuit preference is determined by the allowable collector-emitter voltage and collector current of the transistor. In push-pull converter designs, the primary of the transformer can be connected in several ways (see Fig. 10). Depending upon how the transformer primary is driven, it is possible to differentiate between single-ended (Fig. 10a), push-pull (Fig. 10b) and full-bridge circuits (Fig. 10c). Again, decisions on circuit details are determined by the transistor capabilities.

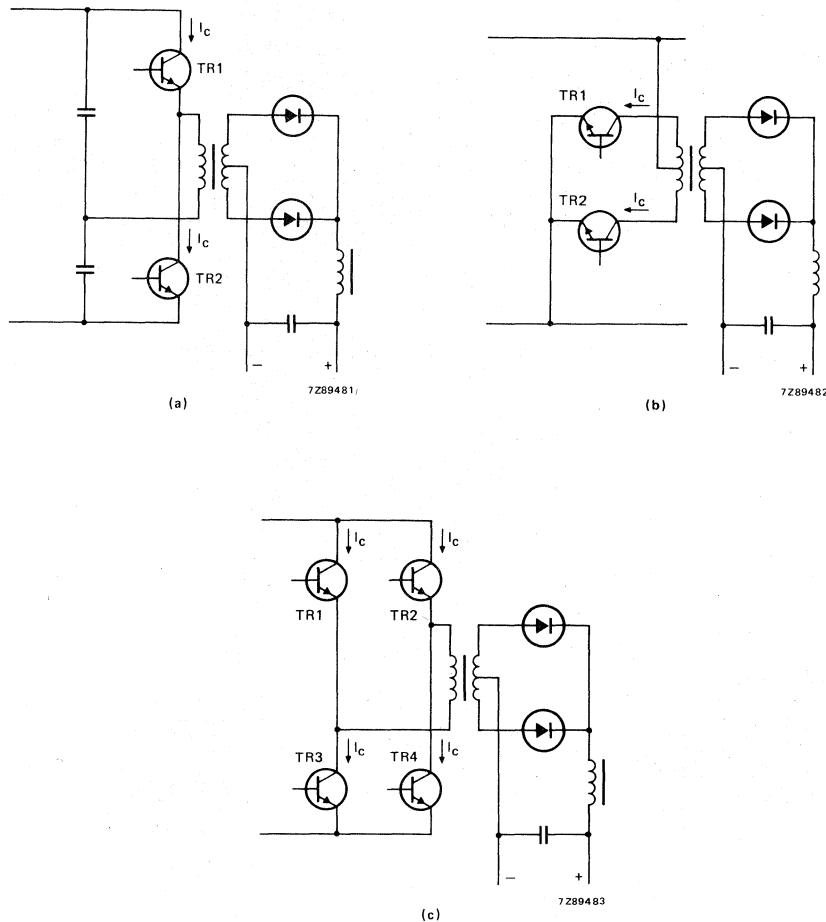


Fig. 10 Several push-pull converter circuits.

For a particular converter design, the first selection that should be considered is obviously the type of converter circuit. To aid in this initial converter circuit selection, Fig. 11 offers a rough guide to the type of converter, its output voltage and power capability. This selection has to be considered along with other requirements such as line isolation, ripple content, overall efficiency, multiple outputs, etc. Table 1 summarizes the most significant properties of a converter design. It shows the relative strengths and weaknesses of the three types of converters with regard to these characteristics.

For a high performance, high power, single output supply, where ripple requirement is well below 1%, the push-pull design is the obvious choice. For smaller power versions of this type of supply, the forward or double forward converter provides a useful alternative to the push-pull converter.

In high-voltage supplies, the flyback converter is the most suitable circuit and should be considered first.

In multiple-output supplies, again, the flyback converter is normally the first choice because it avoids the necessity of providing a number of output windings on the inductor, together with a single diode and capacitor for each.

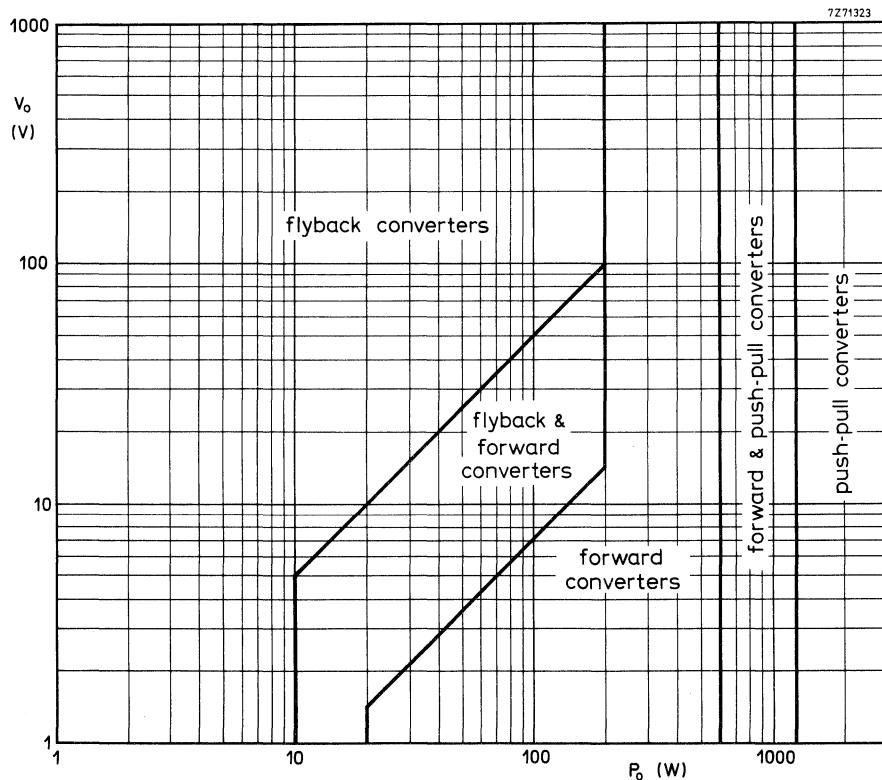


Fig. 11 Converter circuit selection as a function of output voltage and throughput power.

Table 1

	type of converter circuit		
	flyback	forward	push-pull
Circuit simplicity	+	0	-
Number of components	+	0	-
Drive circuitry	+	0	-
Output ripple	-	0	+
Choke volume	-	0	+
Transformer volume	not required	0	+
Mains isolation	+	-	+
High power	-	0	+
High voltage	+	0	0
Multiple outputs	+	0	0

+ Favourable

0 Average

-- Unfavourable

### Core selection curves

When designing a transformer, use the following charts to select a core whose indicated throughput power under the desired operating conditions is equal to, or greater than, the power required.

The power-handling capability of a given core is determined by its geometry and available winding area, which are fixed, and by the following factors which depend on the specific application.

### Winding configuration

In the derivation of the curves for three-winding transformers it has been assumed that each winding occupies one third of the winding area. This would apply when the third winding is bifilar wound with the primary and uses the same gauge of wire. However, because the third winding carries only magnetizing current in forward converters, or current spikes caused by leakage inductance in flyback converters, the current in the winding is normally low. Therefore, the third winding may be wound with thinner wire and may occupy less than one third of the winding area. In this case, the throughput power can be increased by up to about 20% when it would equal that for a two-winding curve.

When multiple secondaries are used to supply a number of different output-rectifier circuits, the total number of secondary windings should be regarded as a single secondary. The area of this single secondary should then be divided between the individual secondaries in proportion to the power to be delivered by each winding.

### Operating frequency

The preferred operating frequency of a switched-mode power supply is greater than 20 kHz to avoid audible noise from the transformer.

### Ambient temperature

Ambient temperature, together with the maximum core temperature (see next paragraph), determines the maximum temperature rise, which in turn fixes the permissible total power dissipation in the transformer. Curves of temperature rise versus power dissipation are included in the published data for each core. In the construction of the core selection curves, a maximum ambient temperature of 60 °C has been assumed. This allows a 40 °C temperature rise from the ambient to the centre of the transformer for a maximum core temperature of 100 °C.

### Core temperature

Core temperature determines the maximum flux density, or flux for a given core, to avoid saturation. Curves of maximum recommended flux against temperature are given in the published data for each core. In the construction of the core selection curves, a maximum core (hot spot) temperature of 100 °C has been assumed because this is acceptable for a wide range of applications and does not exceed the maximum temperature rating of generally-available enamelled wire.

### Flux density (see relevant graphs on following pages)

To avoid saturation in the cores the flux density in the minimum cross-section must not exceed the saturation flux density of the material at 100 °C. The allowable total flux is the product of this flux density and the bottom-limit minimum core area and must not be exceeded even under transient conditions: when a load is suddenly applied at the power supply output, and maximum duty factor occurs together with maximum supply voltage. Under steady-state conditions, where maximum duty factor occurs with minimum supply voltage, the flux is reduced from its absolute maximum permissible value by the ratio of the minimum-to-maximum supply voltage. (At all higher supply voltages the voltage control loop reduces the duty factor and keeps the steady-state flux constant.)

In the construction of the core selection curves, the minimum-to-maximum supply voltage ratio has been taken as 1 : 1,72, this being typical for most applications. The minimum supply voltage assumed in the curves is defined as that voltage which would correspond to a duty factor  $\delta$  of 0,5. If in practice the maximum duty factor is limited to less than 0,5, then the practical minimum supply voltage would be increased proportionately; for example, by 10% if  $\delta_{\max} = 0,45$ .

*Winding-window utilization*

In the construction of the core selection curves, the gaps of 4 mm on each side of the windings (see Figs 12 and 13) are to comply with IEC 435 mains isolation requirements. If these gaps are omitted, the maximum throughput power is increased to  $P'$  where:

$$P' = P \sqrt{\left(\frac{\text{full winding width}}{\text{full winding width} - 8 \text{ mm}}\right)}$$

that is, by about 25% for small cores and about 10% for large cores.

The maximum percentage of copper in the available winding area is generally about 50%, corresponding to windings of circular cross-section and insulation equal to 25% of the wire diameter.

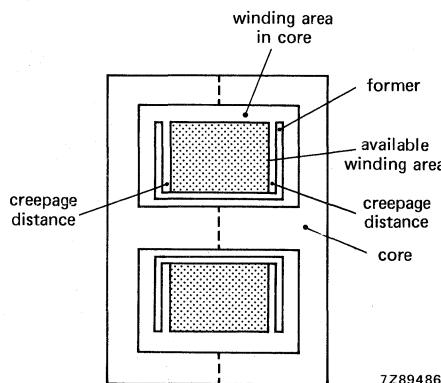


Fig. 12 To allow for creepage distance for 230 V mains isolation, a gap of 4 mm is left at each side of the winding.

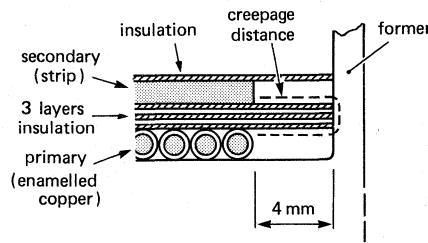


Fig. 13 Detailed section of winding showing how creepage distance is used.

*Ratio  $F_W/F_R$* 

The term  $F_W$  is the winding copper factor and is defined as:

$$F_W = \frac{A_{Cu}}{A_W} \quad \frac{\text{total cross-sectional area of copper}}{\text{available winding area}}$$

and  $F_R$  is defined as:

$$F_R = \frac{\text{a.c. resistance of winding}}{\text{d.c. resistance of winding}}$$

Both  $F_W$  and  $F_R$  depend on the conductor sizes and winding configuration employed in any particular transformer design, and these will depend on the required input and output voltages, etc. Achievable  $F_W/F_R$  ratios for normal solid wire and strip conductors depend on the particular transformer specification and can only be assessed for particular cases. However, the experience of a number of transformer designers, employing various cores and operating frequencies, has produced information on the values of  $F_W/F_R$  that can usually be achieved. This information has been used in the construction of the core-selection charts.

*Ratio  $\gamma$  (flyback converters)*

This is the ratio of minimum-to-maximum load current over which good output-voltage regulation is required, and over which duty factor remains roughly constant for a fixed input voltage.

*Push-pull converter balance*


Two sets of selection charts are given for push-pull converters. One applies to converters in which precautions have been taken to ensure balanced operation so that there is no d.c. component of core flux. Here the value of  $\alpha$  is taken as at least 1,72. The other applies to converter designs where there is a possibility of d.c. core polarization. The value of  $\alpha$  used, 3,44, allows for operation on one half of the hysteresis loop only and is thus a worst-case value.


*Using the selection charts*

These charts are intended as a guide only: the choke selection procedure, based on stored energy, should be used to make the choice of core. These charts can be used to check that choice. See 'Power choke design'.


On the charts, each core type is represented by a shaded area. The upper limit of this area is a curve of throughput power against frequency obtainable under the best possible conditions: no creepage distance, thus maximum winding window; flux density reduced below that for  $\alpha = 1,72$  at higher frequencies; and a ratio of  $F_W/F_R = 0,5$ , which is just attainable at the lower frequencies with bunched (Litz) wire windings. The lower limit of the core area is a curve of throughput power against frequency for a basic transformer design: simple, but optimized, solid-wire windings, 8 mm creepage distance for IEC mains isolation, and optimum flux density sweep is assumed.


To select the best core for the application, draw a line on the chart for the desired converter type at the required throughput power. Possible cores for the transformer are those for which this power line is within or below the operating area at the desired operating frequency. The proximity of the core operating point to the upper boundary of its area will depend on the degree to which the design is to be elaborated.

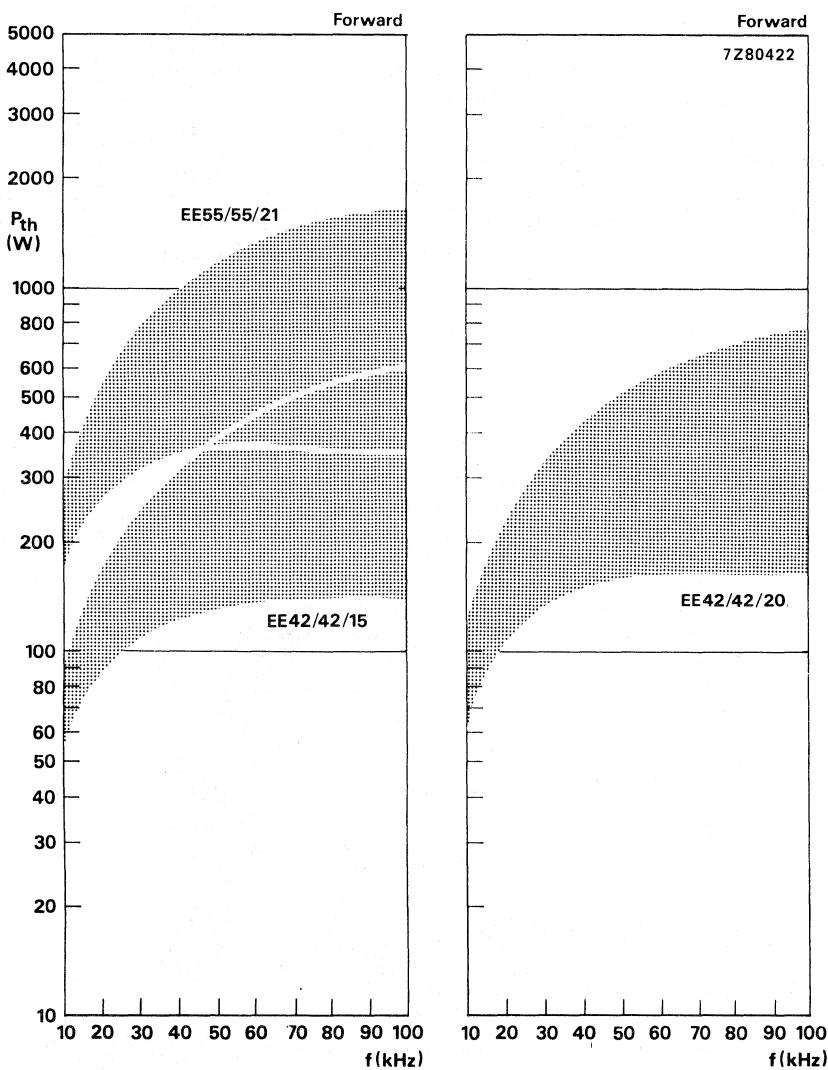

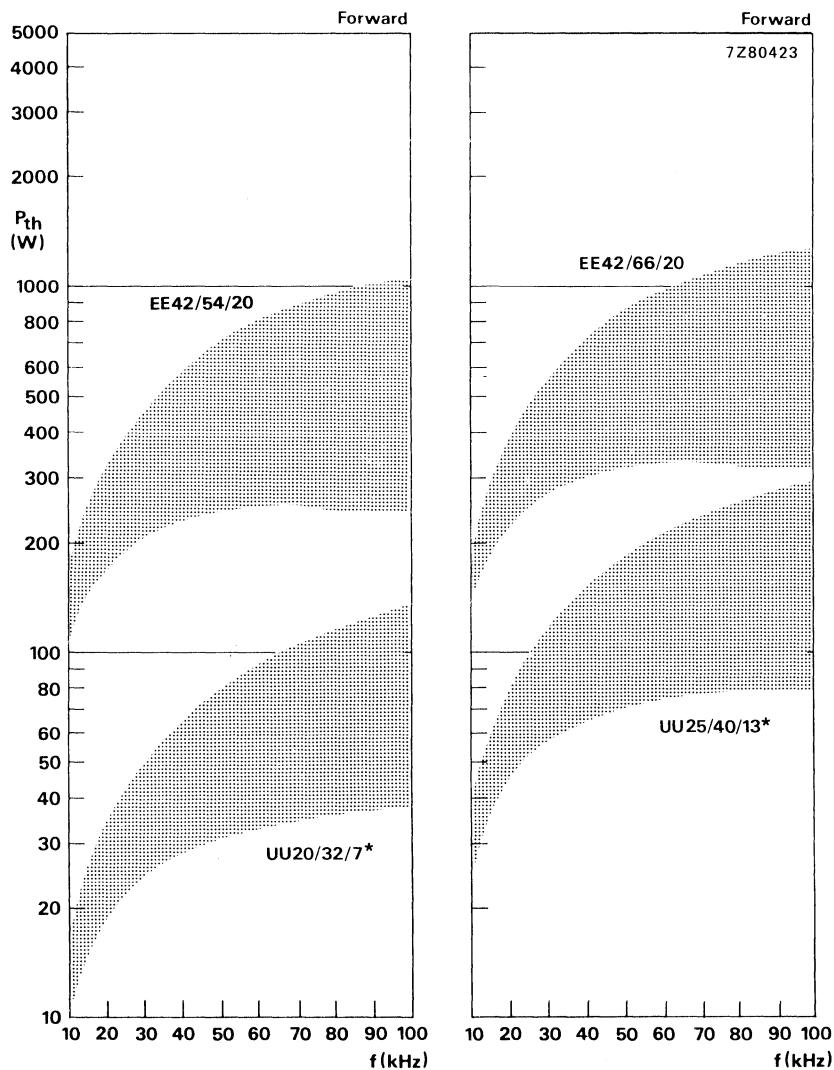



\* Without creepage allowance.

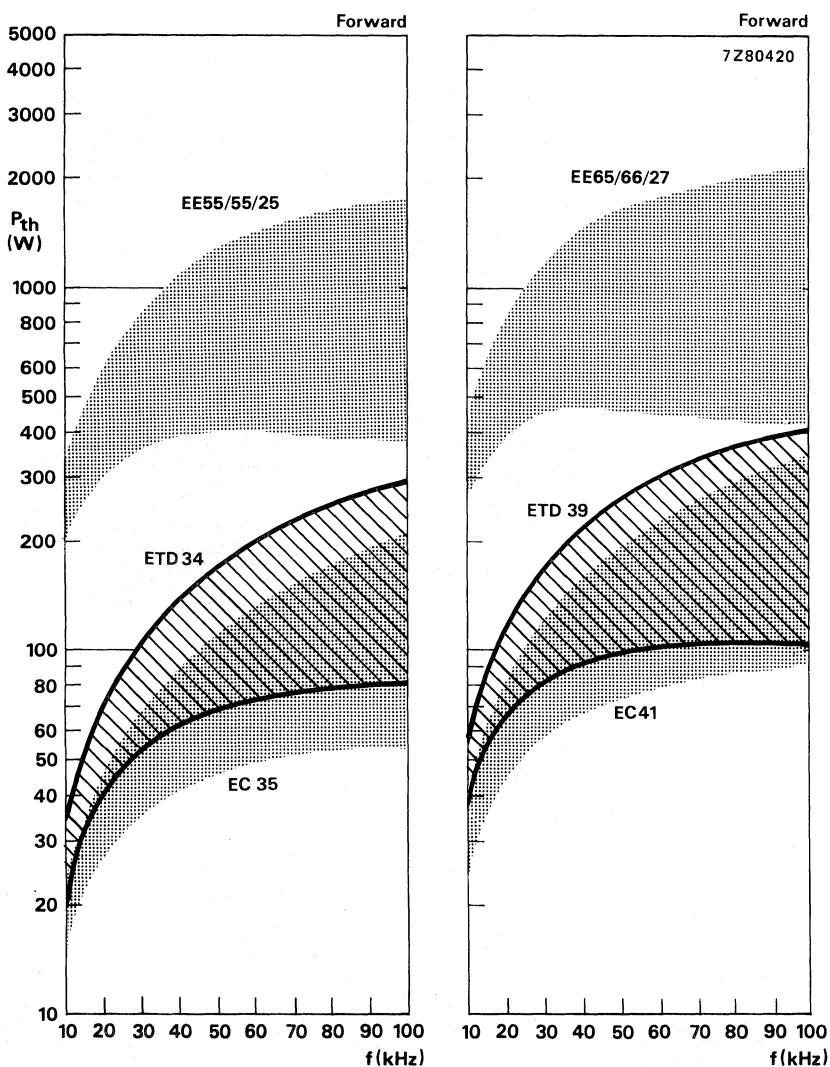

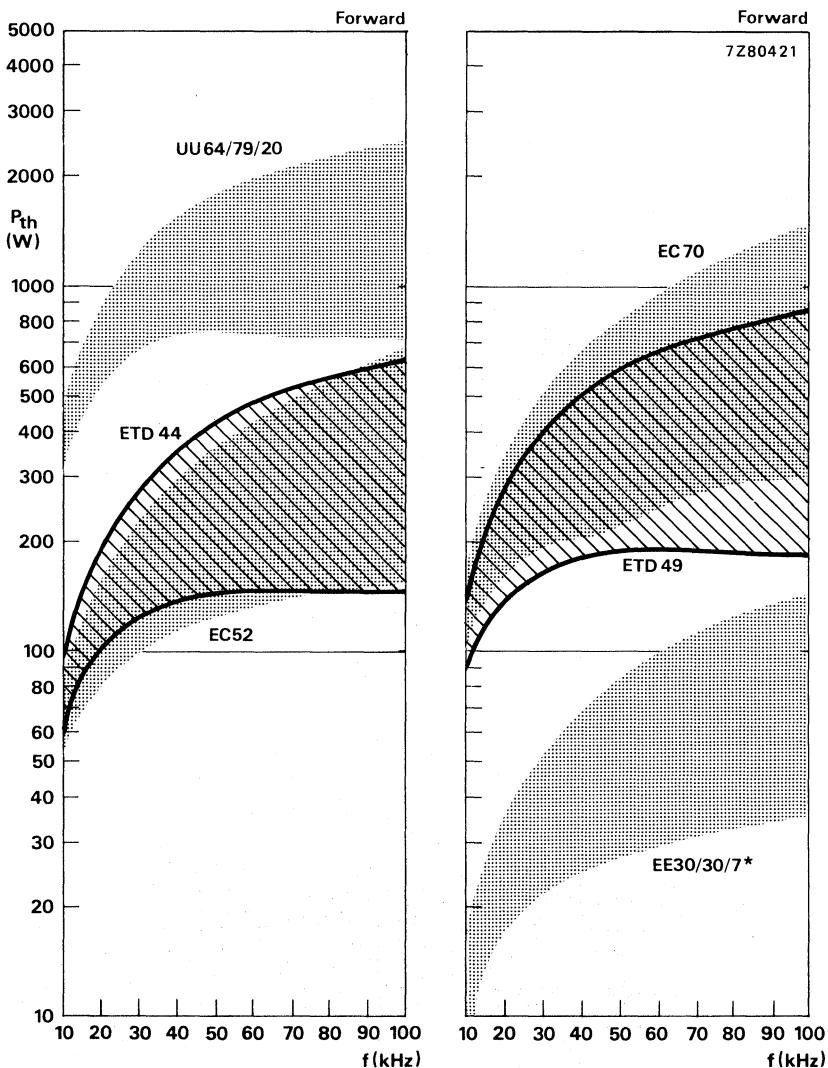



\* Without creepage allowance.

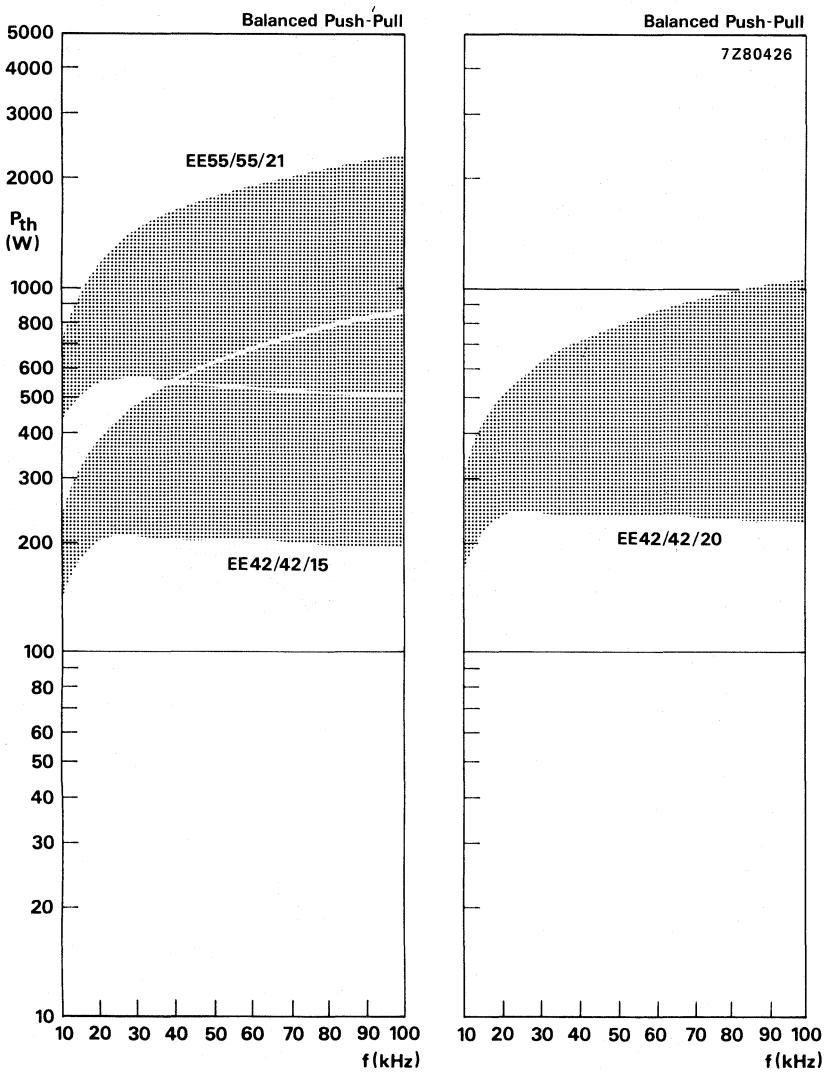

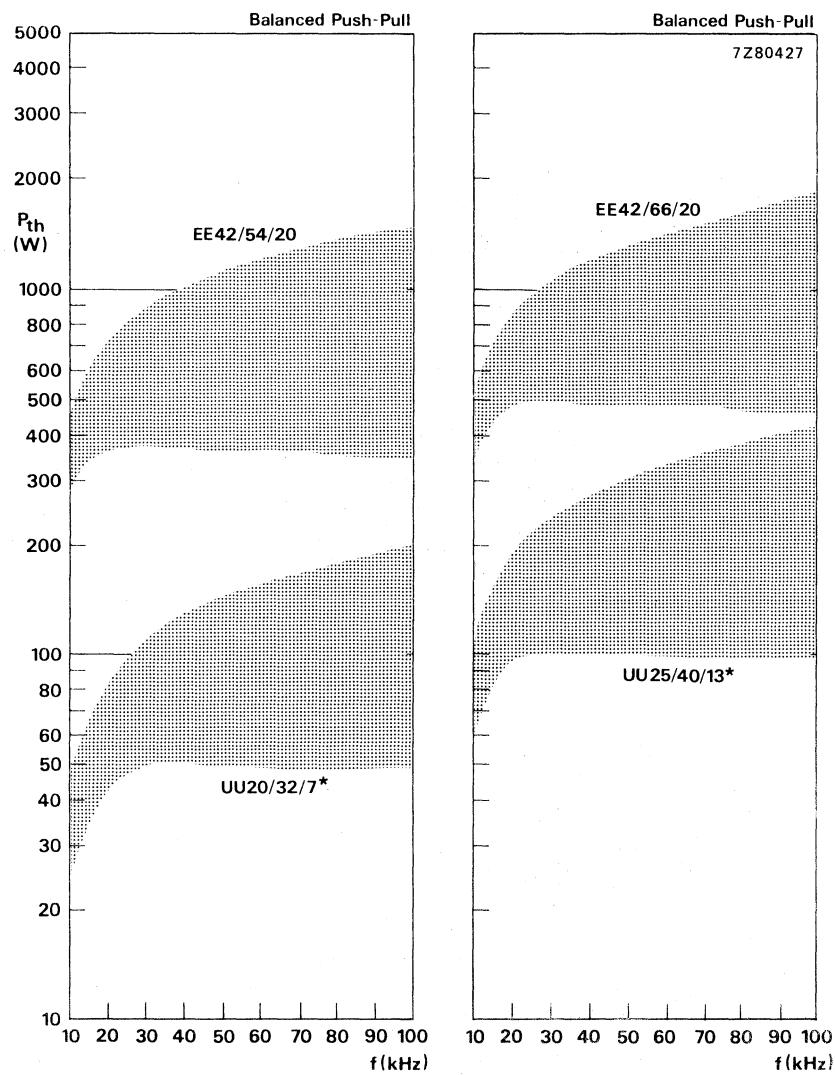



\* Without creepage allowance.

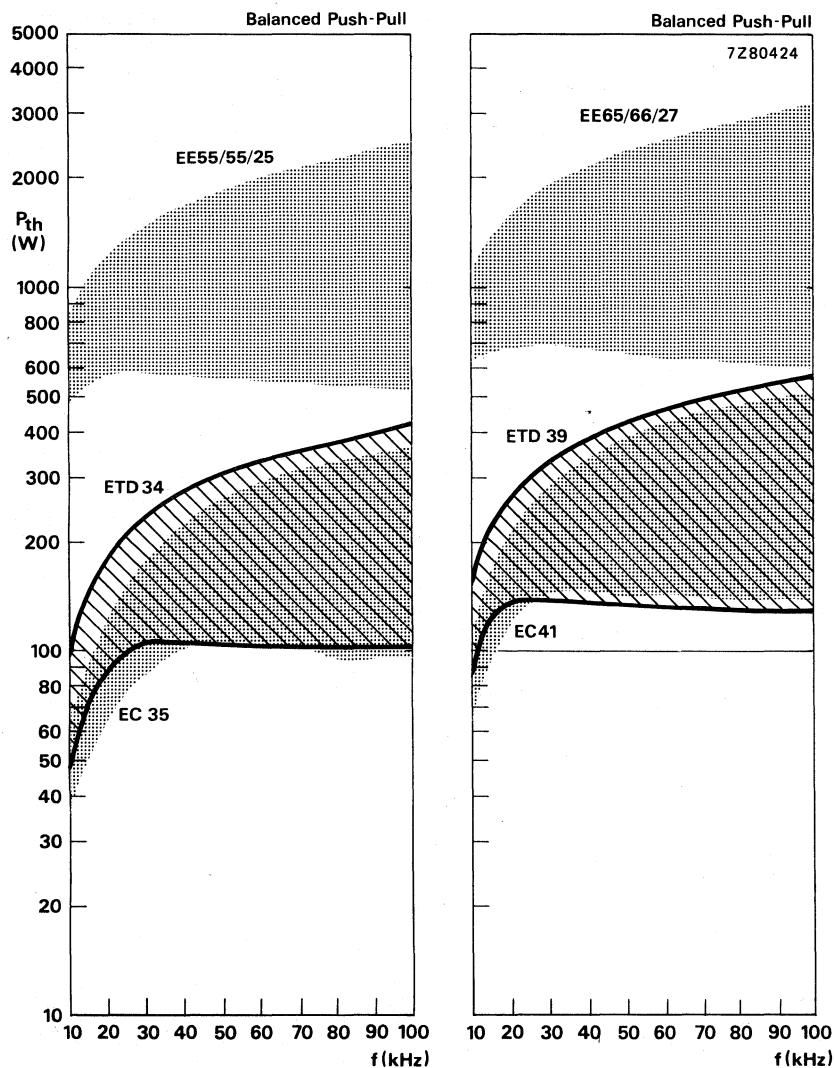

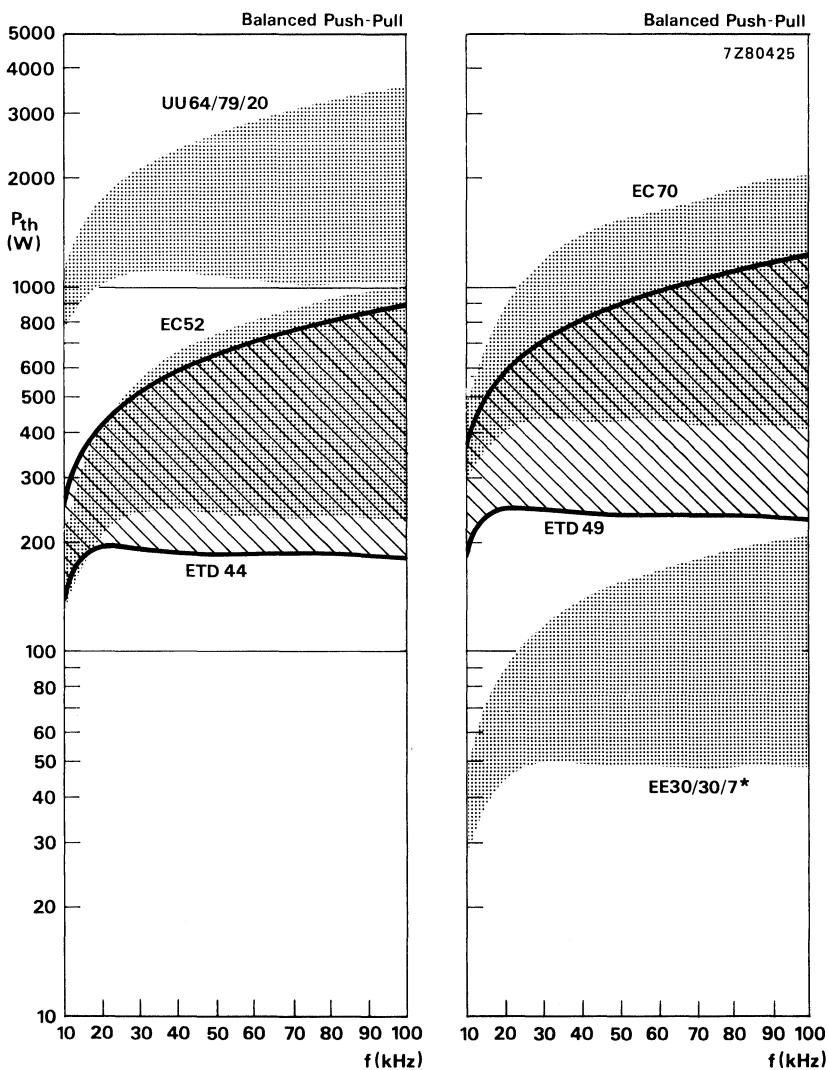



\* Without creepage allowance.

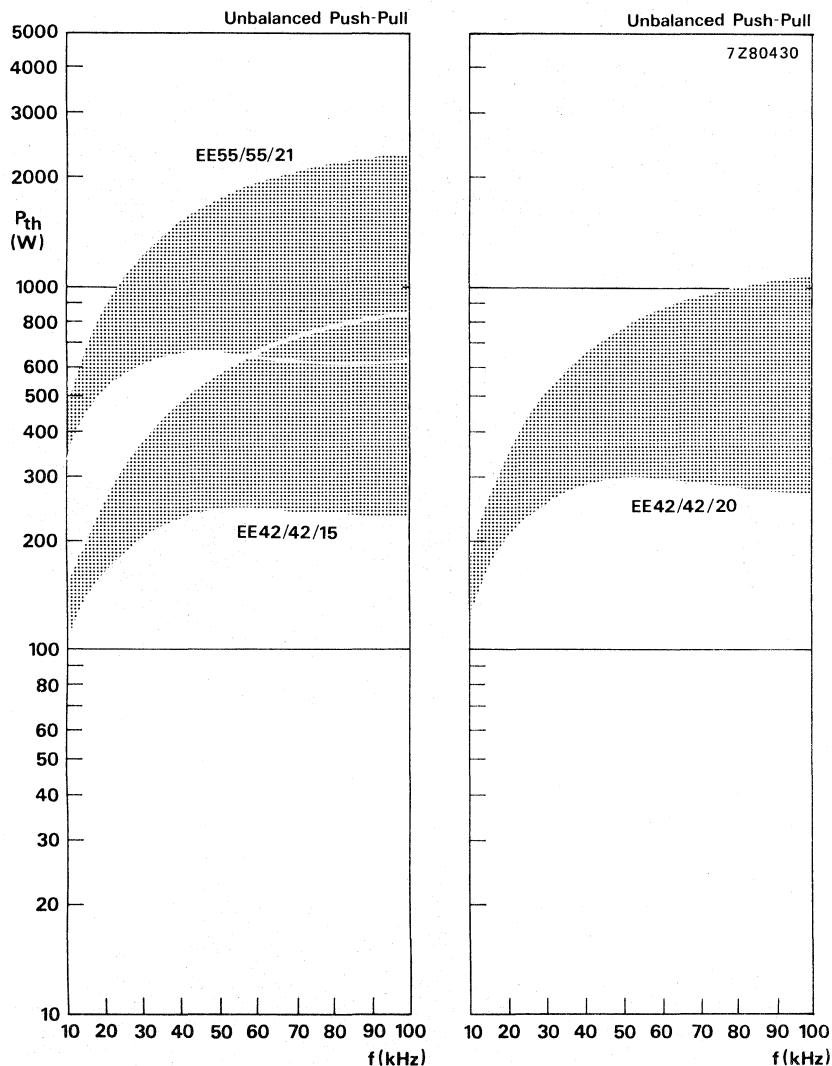

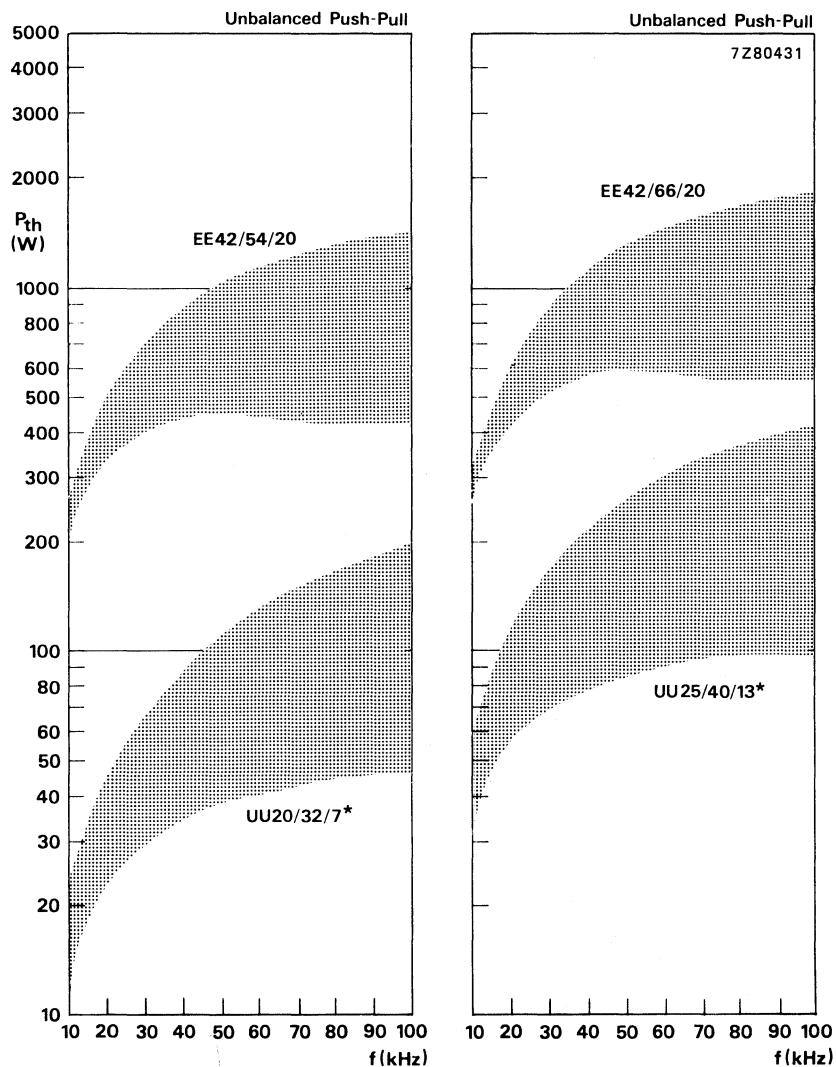



\* Without creepage allowance.

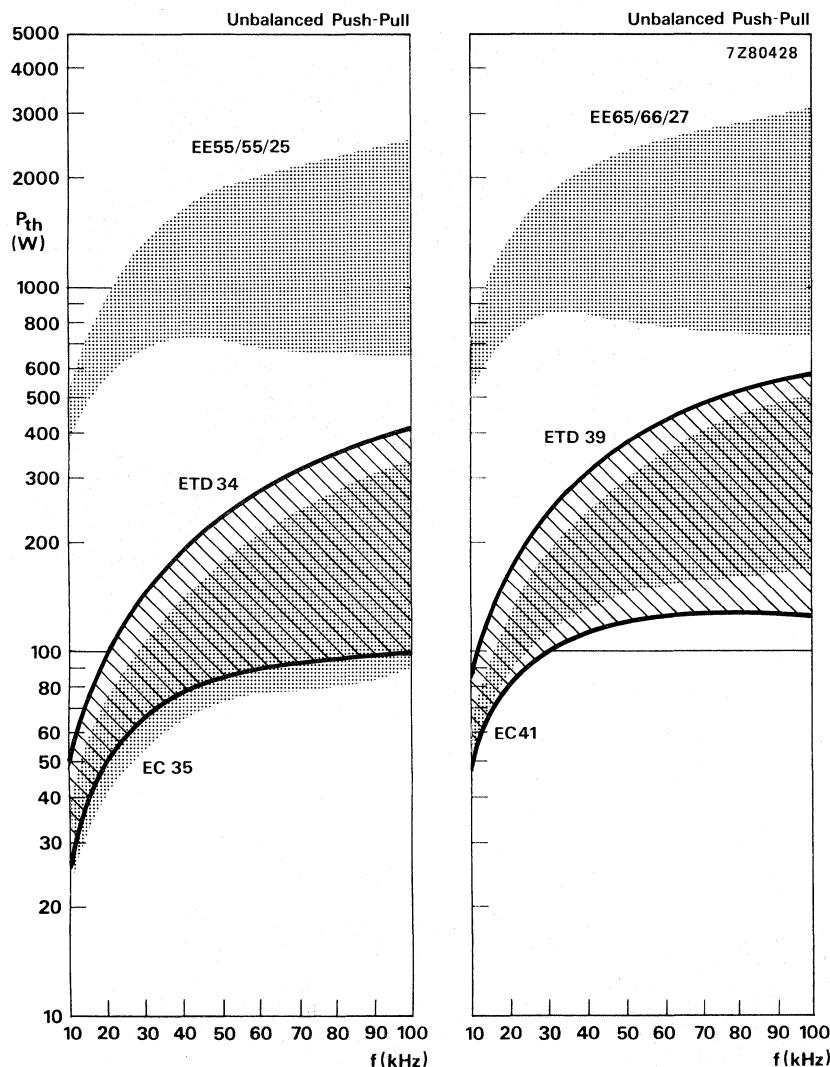

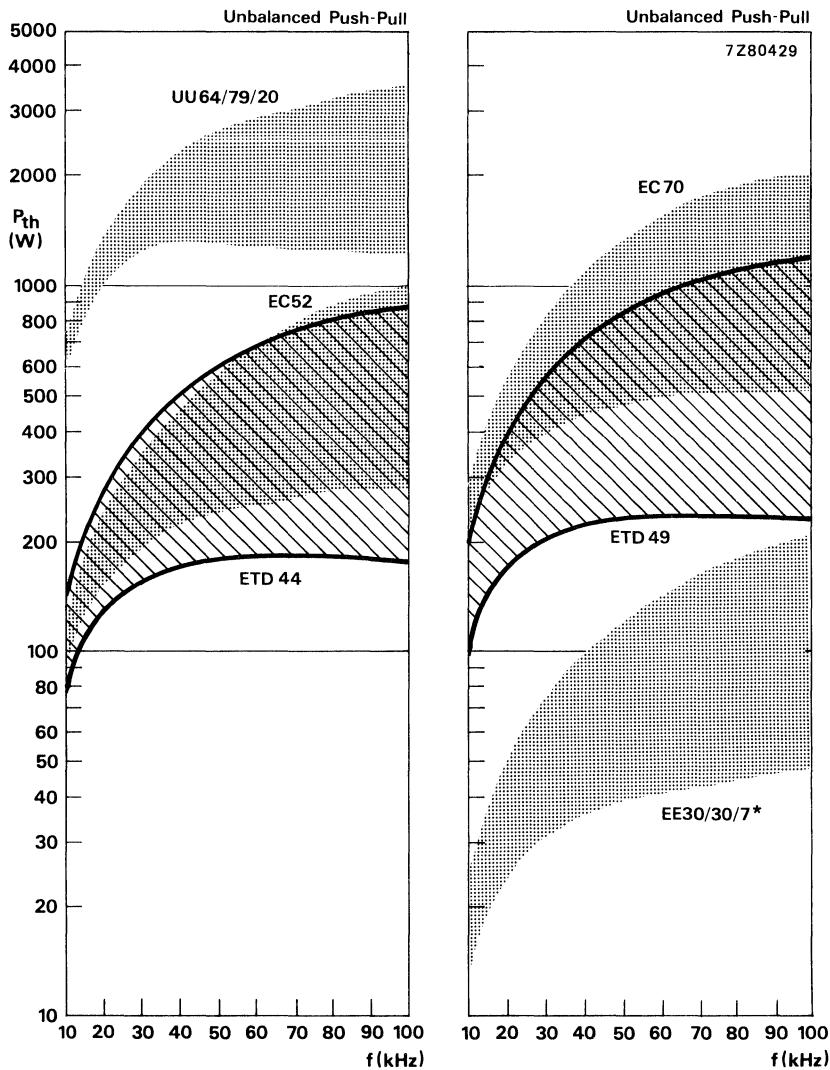



\* Without creepage allowance.

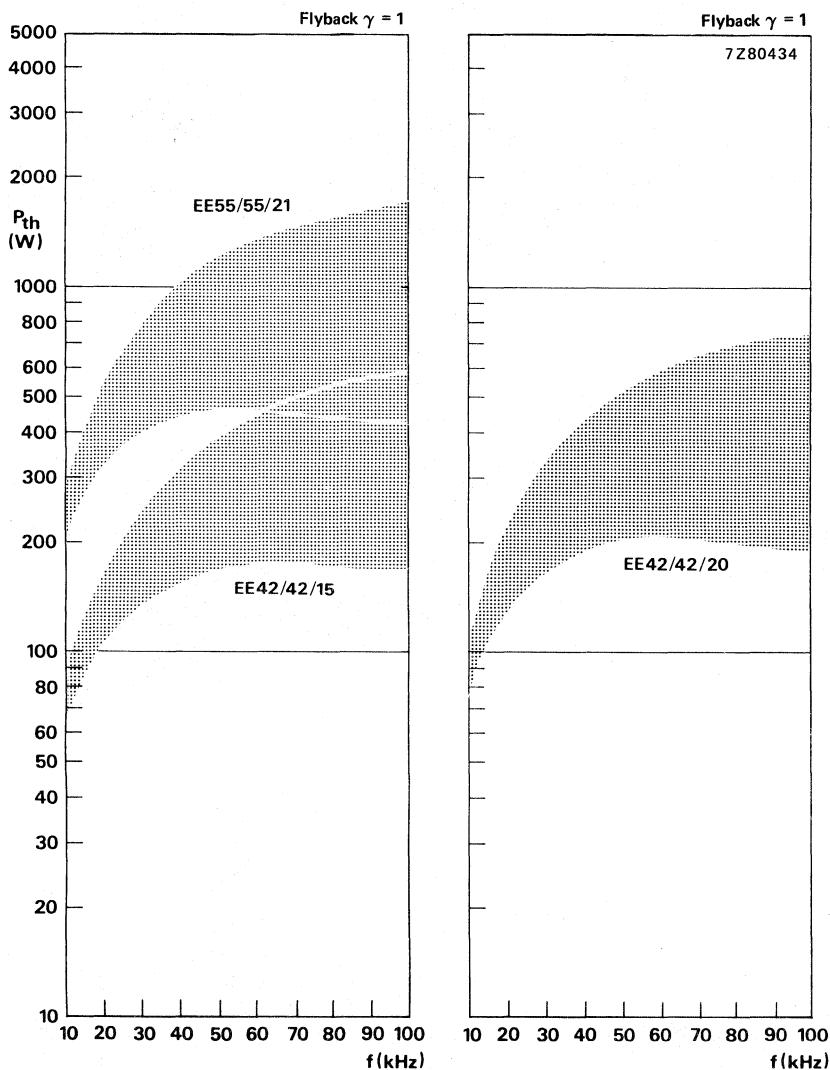

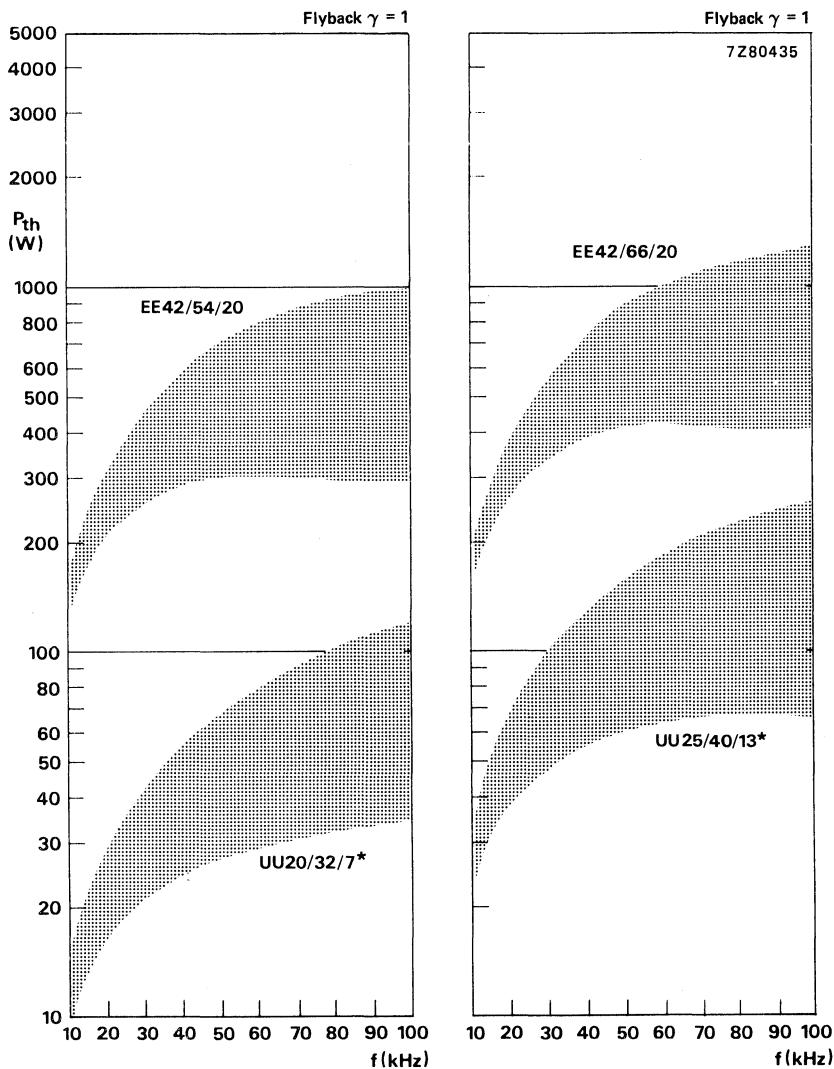



\* Without creepage allowance.

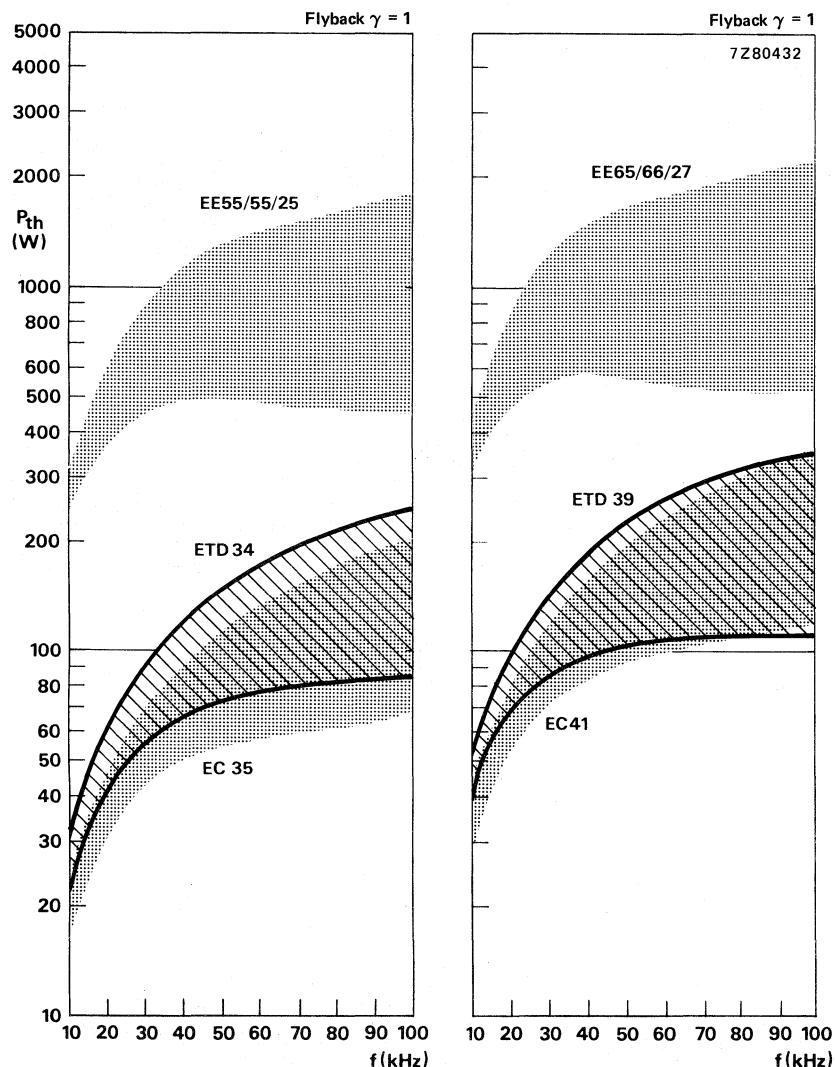

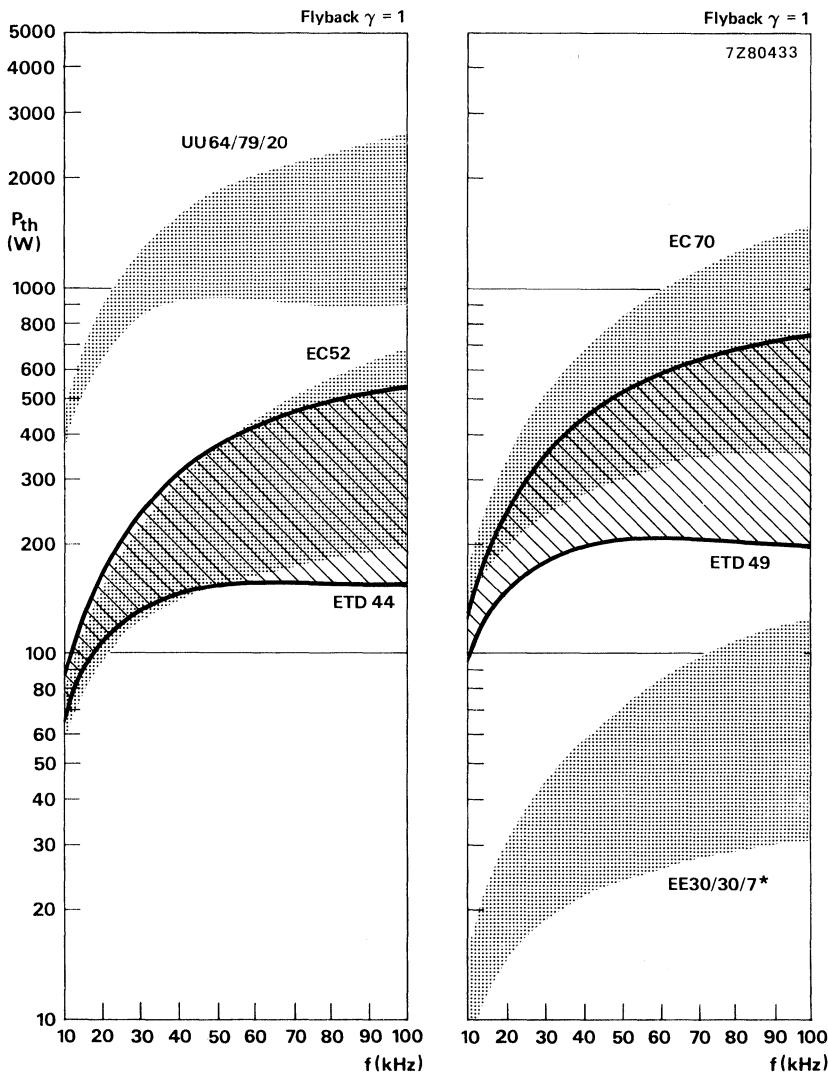



\* Without creepage allowance.

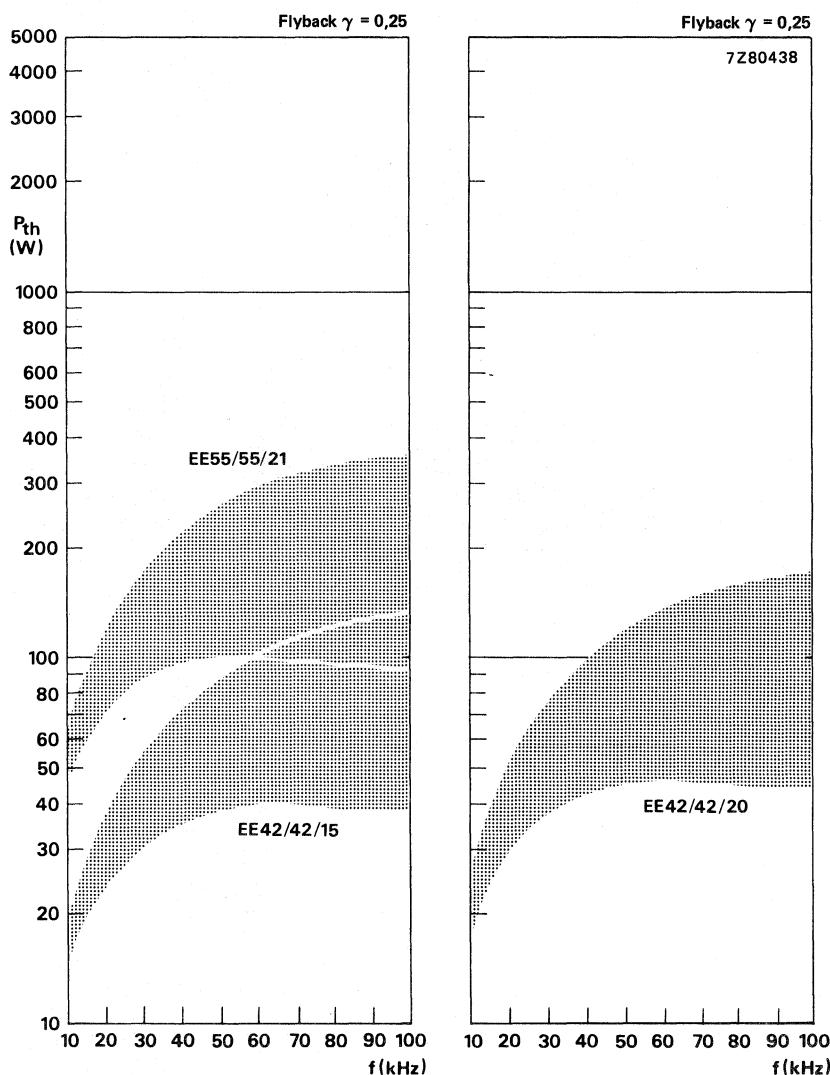

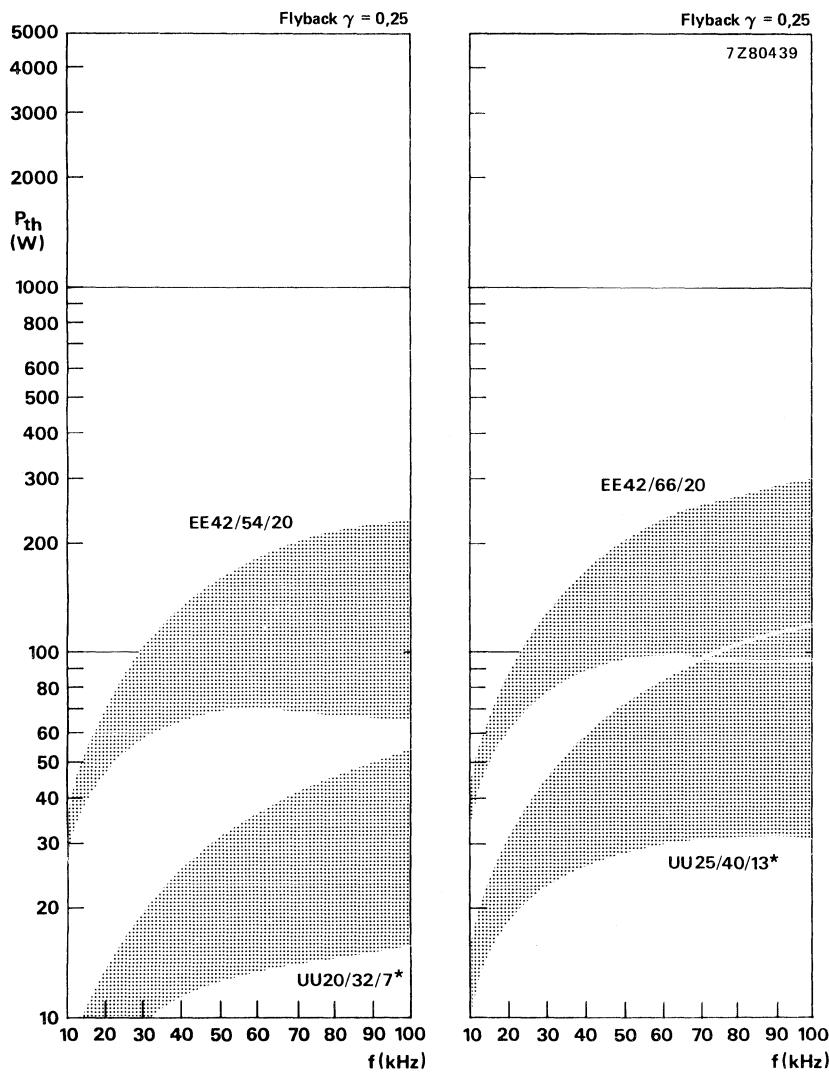

\* Without creepage allowance.

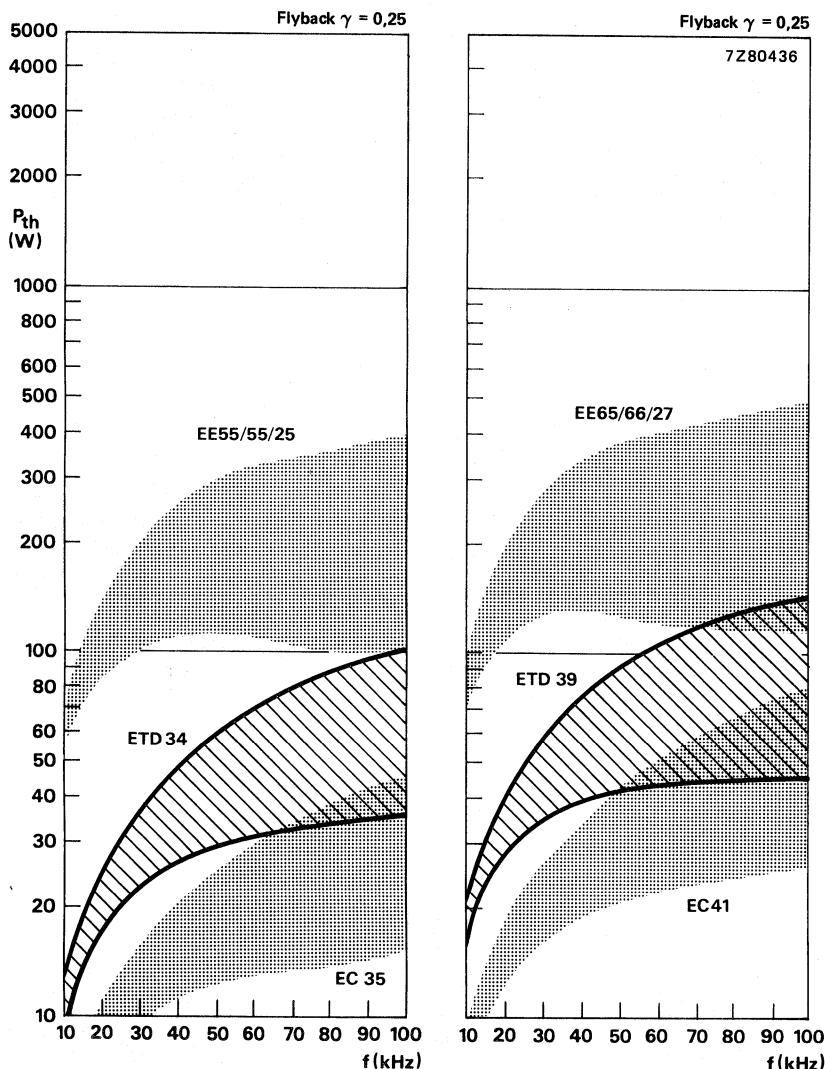


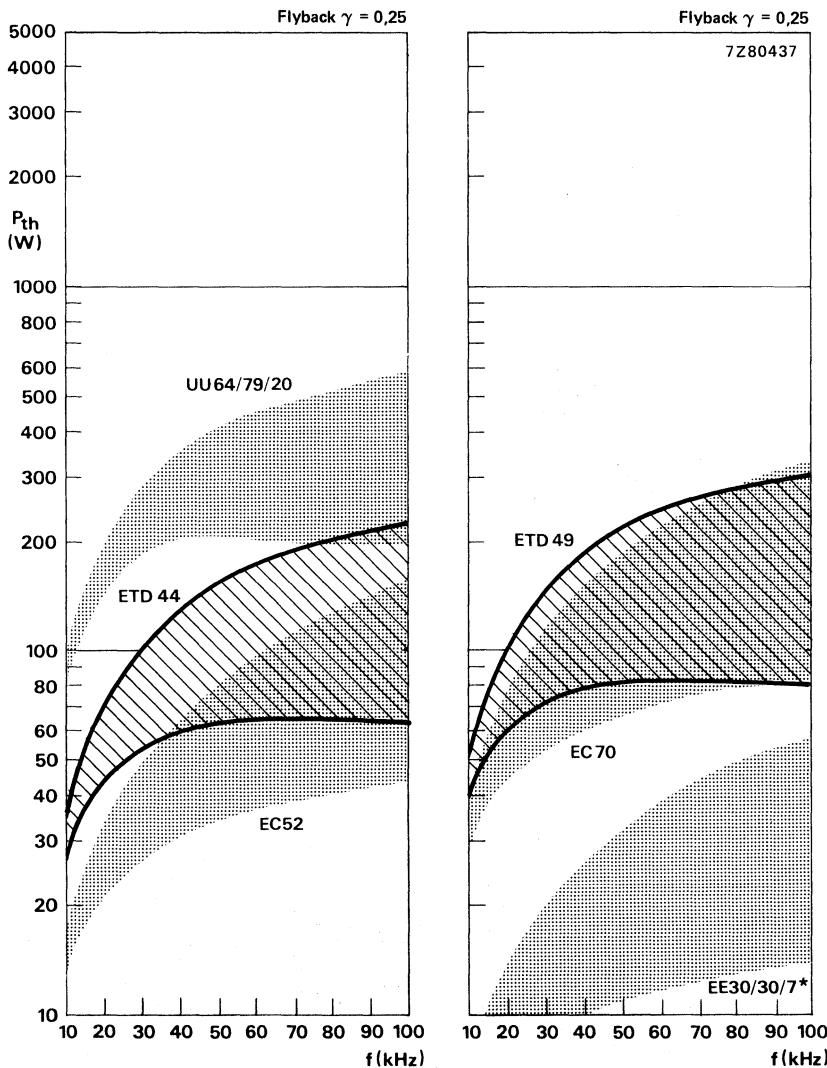

\* Without creepage allowance.


*Optimum flux density*

Optimum flux density excursion (half the peak-to-peak value) giving maximum throughput power for a variety of cores for SMPS applications.

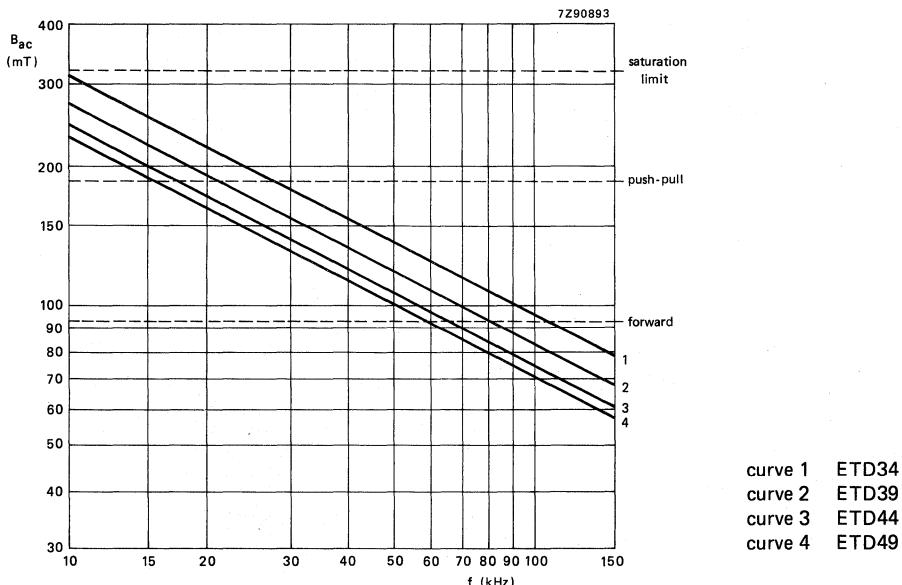


The two lower broken horizontal lines in the graphs indicate the maximum flux values for converters without feed forward, to allow for transient conditions. The intersections of these horizontal lines with the optimum-sweep curves gives the transition frequencies\* for the respective cores.

\* Transition frequency is the frequency at which the design changes from 'saturation limited' to 'core loss limited'.

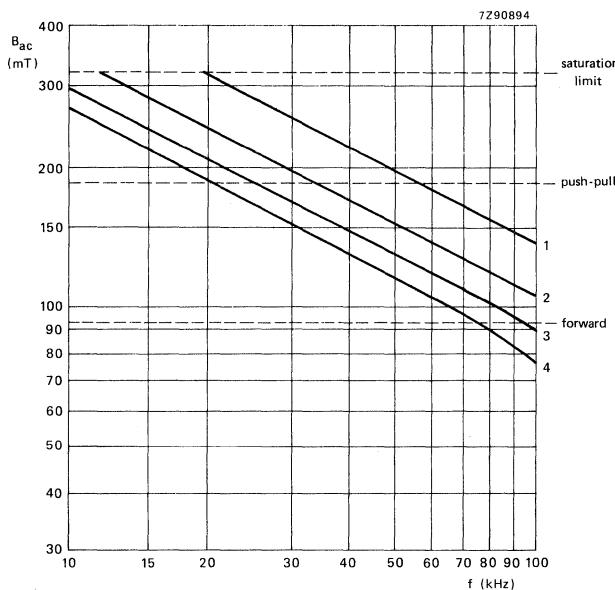

1. UU15/22/6  
EE20/20/5
2. UU20/32/7  
EE25/25/7  
EE30/30/7
3. UU25/40/13
4. UU30/50/16

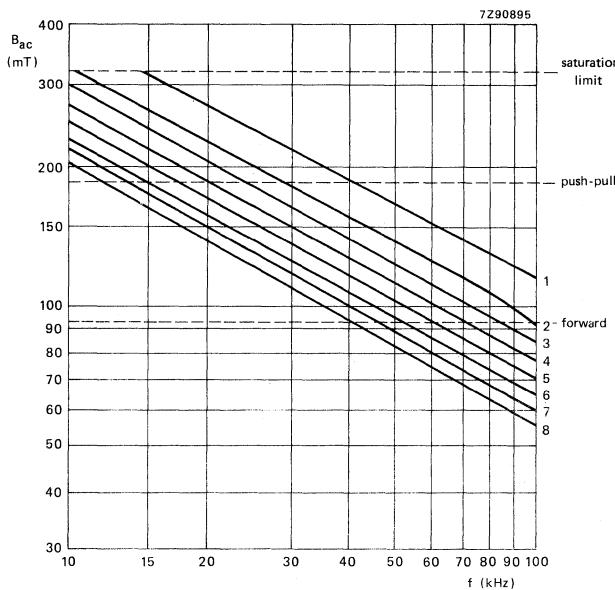

1. EC35
2. EC41, EC52
3. EE42/42/15
4. EC70
5. EE42/42/20  
EE42/54/20  
EE42/66/20
6. EE55/55/21
7. EE55/55/25  
UU64/79/20
8. EE65/66/27

### POWER CHOKE DESIGN

Ferroxcube grade 3C8 is the natural choice for cores for power chokes operating at ultrasonic frequencies, such as those in switched-mode power supplies (SMPS). The data for the cores in this section include design charts that greatly simplify the design of these power chokes. Starting with the peak current  $I_M$  (Fig. 14) that the choke shall pass without saturating the core, and the minimum inductance required  $L_{min}$  the designer obtains all the information required for the construction of the choke directly. Core size, spacer thickness, number of turns, and winding geometry are derived in straightforward procedures. Note that the magnetic properties of the core do not enter into the design process. The ratio of the a.c. and d.c. current components may be small (smoothing chokes) to large (push-pull converter chokes). Parameter spreads due to manufacturing and temperature variations are taken into account in the construction of the design charts. The design procedures allow for spacer tolerances.

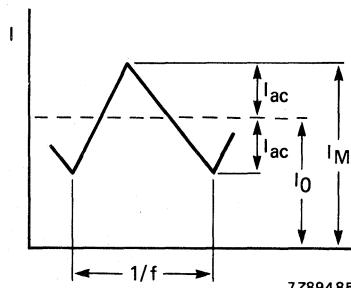


Fig. 14 Choke waveform showing symbols for currents are full load.

#### Operating conditions

The charts are constructed for cores of Ferroxcube 3C8 operating at a hot-spot temperature of 100 °C. Operation at lower temperatures leads neither to core saturation nor to inductances lower than  $L_{min}$ . The design peak flux density is 0,32 T. However, the charts can be used for a lower value  $B_M$  by designing for a peak current  $0,32 I_M/B_M$ .

#### Applications

For the purposes of this design process, applications are divided into three classes:

I     $I_{ac}/I_0 < 0,3$

Examples: smoothing chokes, and converter chokes in flyback-type SMPS without complete demagnetization.

II     $I_{ac}/I_0 \approx 1$

Example: flyback-converter chokes with complete demagnetization (ringing-choke converters).

III     $I_{ac}/I_0 > 2$

Example: converter chokes in push-pull-type SMPS (symmetrical excitation) as used for fluorescent-lighting.

Core loss rather than saturation is usually the limiting factor in this class of application. Thus, the peak flux density must be lower than 0,32 T by an amount that depends on operating frequency.

The special treatment of class III designs given in the following procedures generally yield satisfactory results.

**Core selection**

The cores are grouped according to shape: EC, EE, ETD, UI, UU.


**Selection procedure**

- Knowing the values of peak choke current  $I_M$  and minimum required inductance  $L_{min}$ , calculate the value of  $I_M^2 L_{min}$ .
- Choose — at least provisionally — the shape of core (EE, EC, ETD, UU or UI) and draw a horizontal line  $I_M^2 L_{min}$  across the selection chart for that core shape. For class II designs at frequencies beyond 40 kHz use a value of  $I_M^2 L_{min}$  equal to  $f/40$  times the actual value of  $I_M^2 L_{min}$ , for class III designs at frequencies beyond 10 kHz use a value of  $I_M^2 L_{min}$  equal to  $0,1 f$  times the actual value of  $I_M^2 L_{min}$ , where  $f$  is the operating frequency in kHz.
- A core whose curve intersects this horizontal line can be used for the application. The spacer thickness or centre pole gap size corresponding to the intersection is only an indication of the final value.


**Effect of core size**

Where, as is usual, more than one core could be used, the final choice may be governed by the consideration that operation near the right-hand end of the curves carries the risk of overheating.


Selection of a larger core will generally result in a more conservative, efficient design than one based on a core that is marginally large enough.

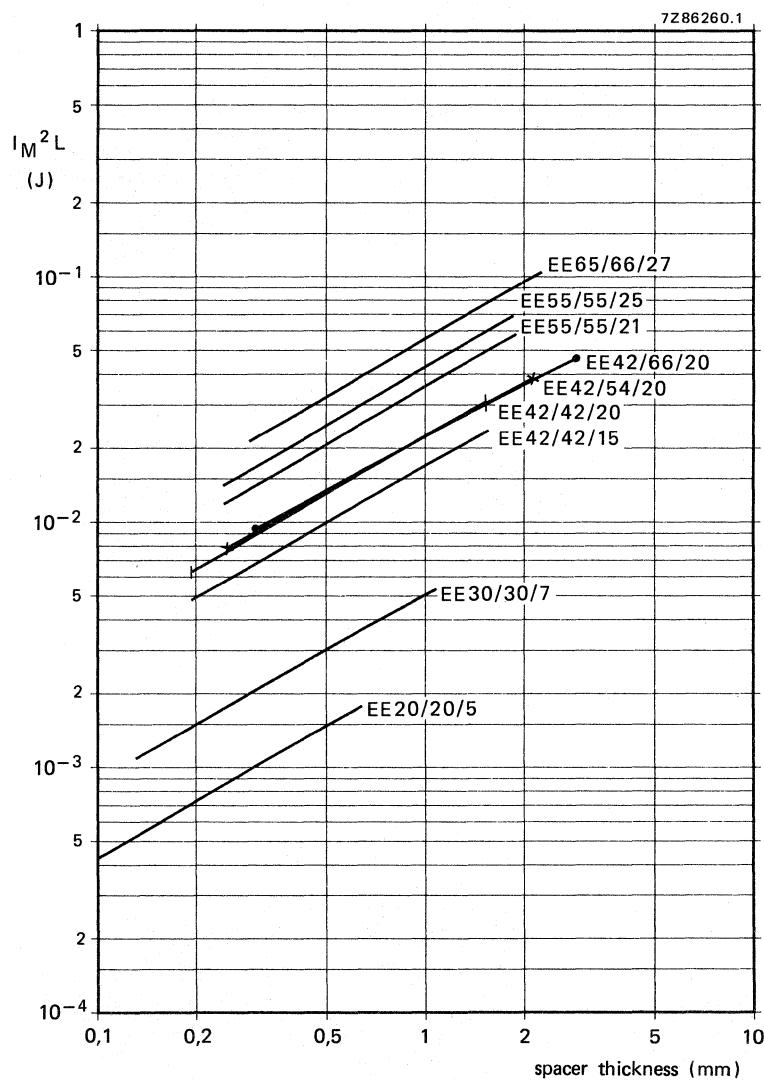


Choke core selection chart for EE cores.

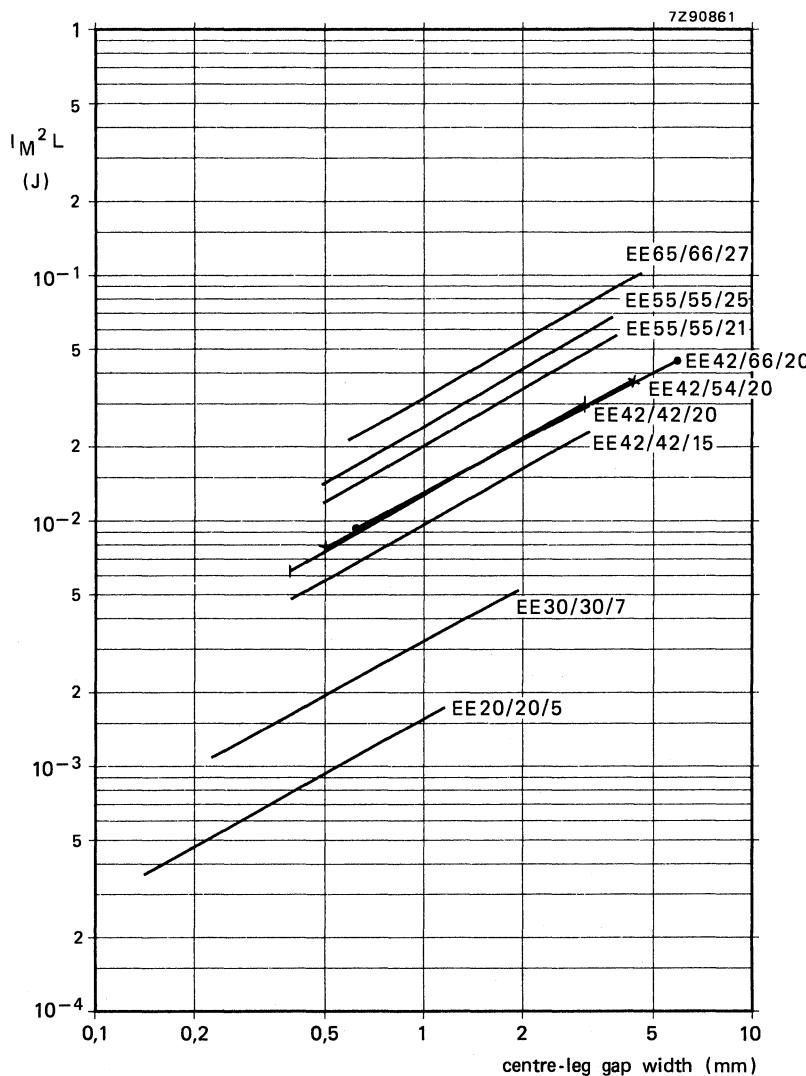

Choke core selection chart for EE cores.

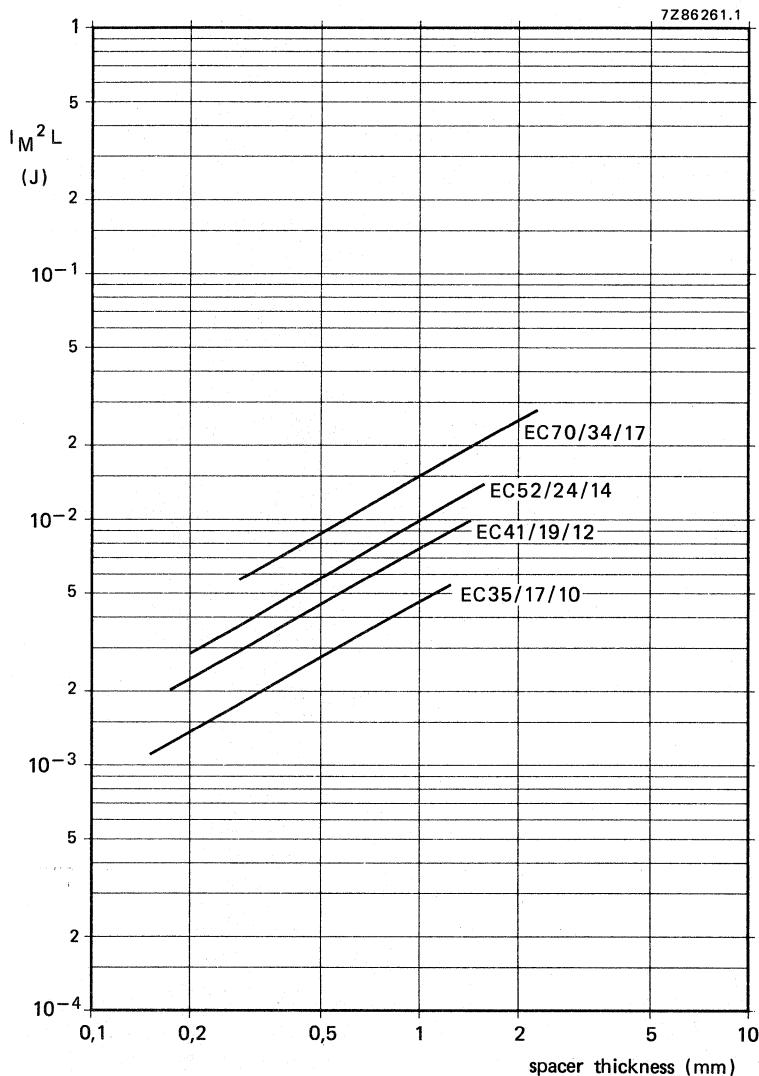


Choke core selection chart for EC cores.

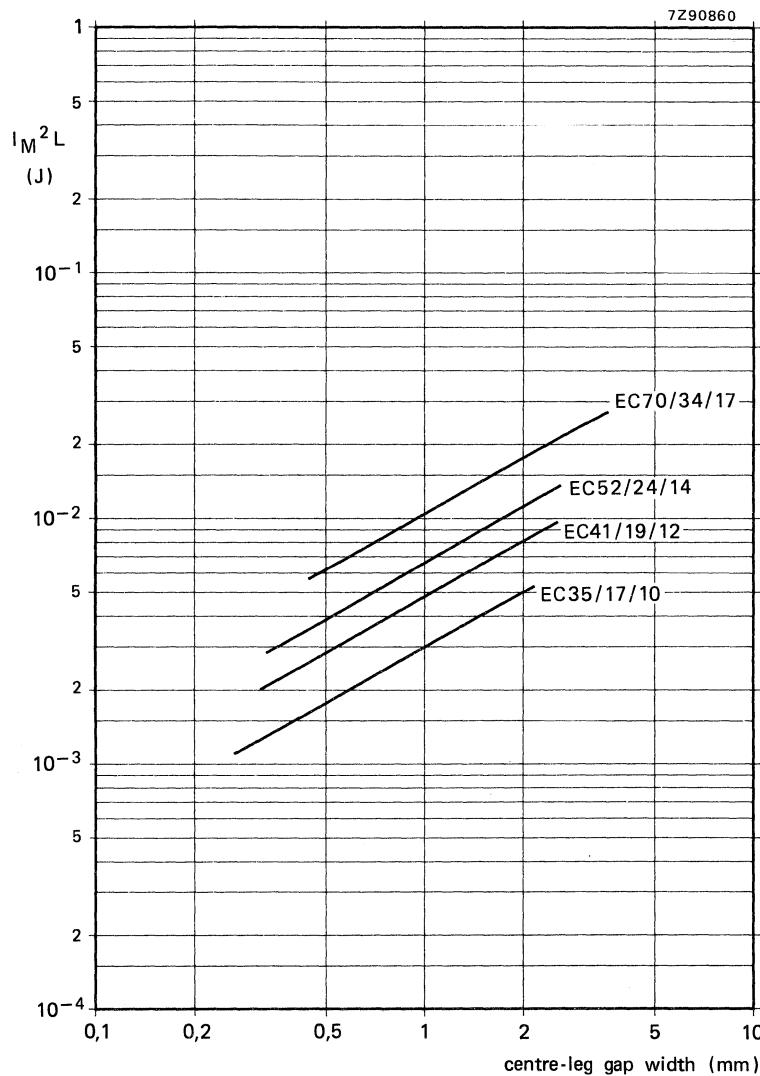


Choke core selection chart for EC cores.




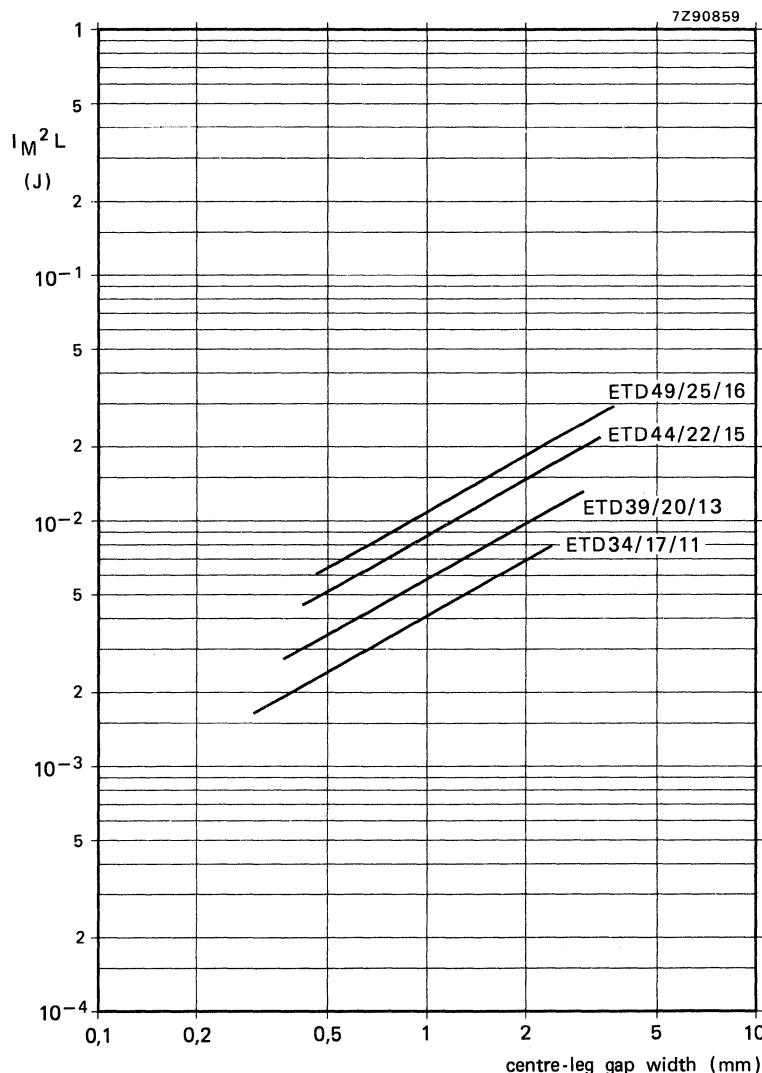

Choke core selection chart for ETD cores.

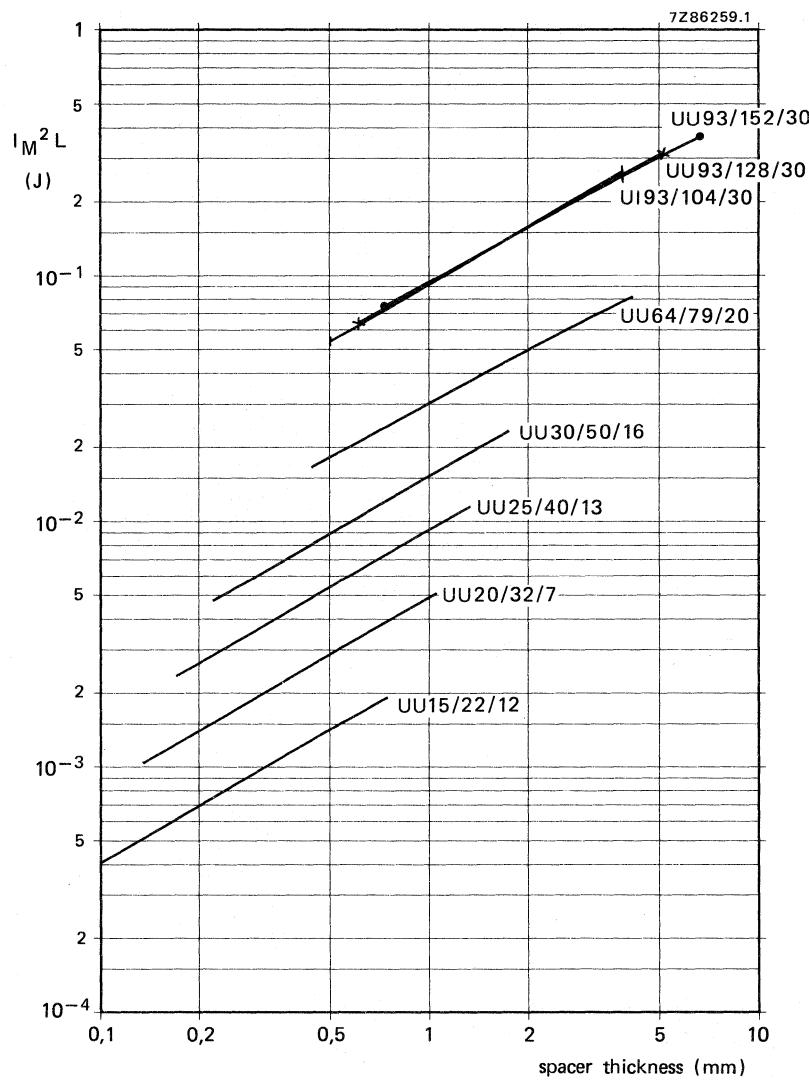

Choke core selection chart for UU/UI cores.

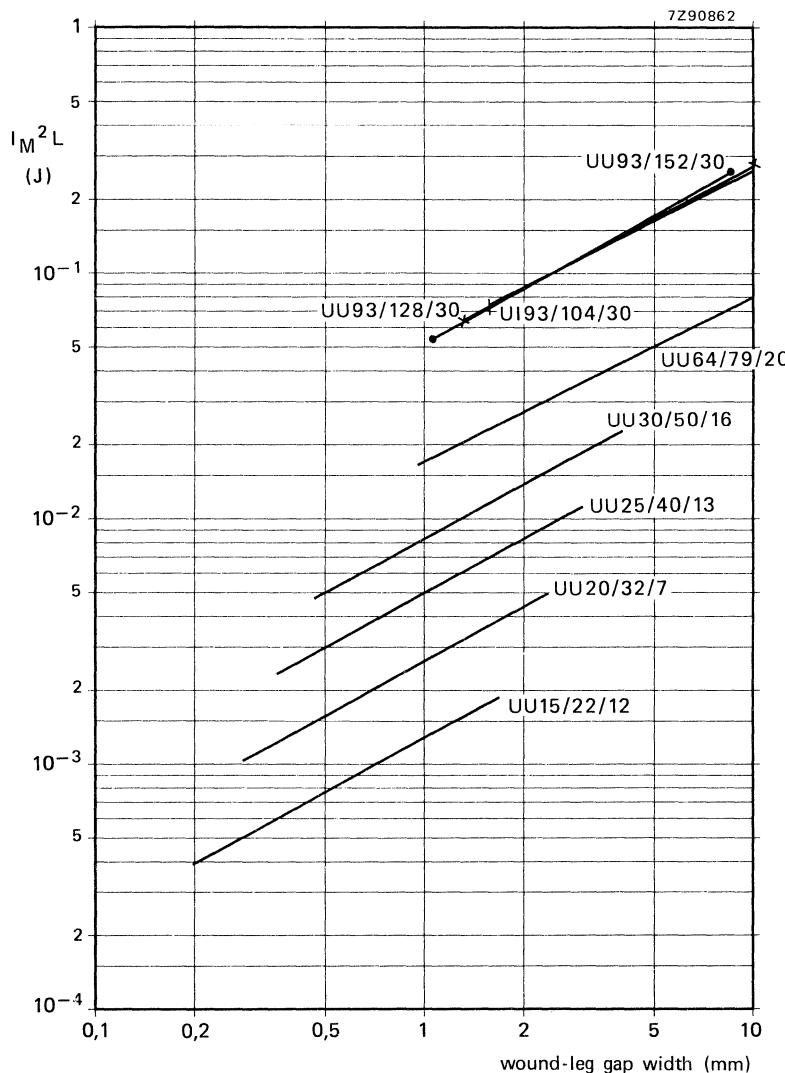

Choke core selection chart for UU/UI cores.

**Gap size (spacer thickness or centre leg gap width) and number of turns**

For ETD cores consult the tables given on the relevant pages. For the other cores turn to the data for the core type selected and refer to the chart giving  $(I_M^2 L)_{\max}$  and  $A_L$  as functions of gap sizes.

(Note:  $A_L$  for these power cores is the inductance factor in henry.)

The charts comprise a pair of curves of  $(I_M^2 L)_{\max}$  and  $A_L$  for each of the three application classes. Use the pair of curves for the appropriate class of application in the following design procedure.

1. On the chart, draw the horizontal line  $I_M^2 L_{\min}$ , as used for core selection, see under 'Core selection'.

The working point of the core must lie above this line and below the  $(I_M^2 L)_{\max}$  curve for the core. That is, between lines SQ and SP in Fig. 15.

2. Select a suitable gap size, nominal width  $s$ . Draw vertical lines  $s_{\min}$  and  $s_{\max}$  on the chart, where  $s_{\max} - s_{\min}$  is the tolerance field on the centre pole gap size or thickness of the spacer and the associated adhesive films. (Epoxy adhesive films vary in thickness from about 10  $\mu\text{m}$  to about 20  $\mu\text{m}$ .) Ensure that the horizontal distance between the intersection and  $s_{\min}$  (a in Fig. 15) is greater than the distance from  $s_{\min}$  to  $s_{\max}$  (b in Fig. 15).

3. For  $s_{\min}$ , read values of  $(I_M^2 L)_{\max 1}$  and  $A_{L 1}$  from the chart. The maximum number of turns allowed to avoid saturation is

$$N_{\max} = \sqrt{\frac{(I_M^2 L)_{\max 1}}{I_M^2 A_{L 1}}}$$

for class II beyond 40 kHz,

$$N_{\max} = \sqrt{\frac{(I_M^2 L)_{\max 1}}{f/40 \times I_M^2 A_{L 1}}},$$

for class III beyond 10 kHz,

$$N_{\max} = \sqrt{\frac{(I_M^2 L)_{\max 1}}{0,1 f \times I_M^2 A_{L 1}}},$$

where  $f$  is expressed in kHz.

Note: The upper left-hand corner of the shaded area of the figure is the most critical point regarding number of turns and core saturation.

4. For  $s_{\max}$ , read the value of  $A_{L 2}$ . The minimum number of turns, for inductance  $L_{\min}$ , is


$$N_{\min} = \sqrt{\frac{L_{\min}}{A_{L 2}}}$$

Note: The lower right-hand corner of the shaded area is the most critical for number of turns and  $L_{\min}$ .

5. Select an integral number of turns  $N$  between  $N_{\min}$  and  $N_{\max}$ .

Note: If  $a$  was taken to be only marginally greater than  $b$  (see Fig. 15), the design attempt might fail since such an integer would not exist. Taking  $a < b$  makes  $N_{\max} < N_{\min}$ .

6. Establish the winding geometry using the winding-design procedure, given later.

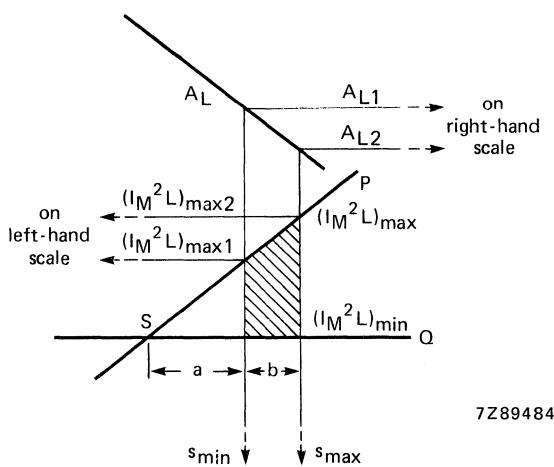

7Z89484

Fig. 15 Graphical design process using core design charts.

### Winding design

Because the eddy-current losses in a winding carrying a.c. increase rapidly with conductor size (for wire, with  $d^4$ , whereas d.c. loss increases with  $d^{-2}$ ), there is a certain "ideal" conductor size for minimum loss. This may set an upper limit to conductor size at the ultrasonic frequencies at which SMPS chokes operate. The procedures that follow allow the ideal number of layers and wire size, or the thickness of strip, to be determined for chokes with an operating-current waveform of the form shown (Fig. 14). They also indicate the course of action when the available winding window will not accommodate the ideal winding.

Copper conductors are assumed; operating temperature is 100 °C, so that conductor resistivity is 1/45 Ωmm<sup>2</sup>/m (30% higher than that at 20 °C). Symbols used in the formulae are as follows. (Note: subscript id indicates an ideal (lowest loss) value).

$b_w$	mm	winding (layer) breadth
$d$	mm	nominal wire diameter
$d_o$	mm	overall wire diameter
$f$	kHz	frequency
$f_e$	kHz	effective frequency (see text)
$F_R$	—	resistance factor $R_{ac}/R_{dc}$
$h$	mm	thickness of foil conductor
$H$	mm	winding height
$H_a$	mm	available winding height
$i$	mm	thickness of interleaving
$I_e$	A	r.m.s. current at full load
$I_0$	A	d.c. component of current at full load (see Fig. 14)
$I_{ac}$	A	a.c. component of current at full load (see Fig. 14)
$I_M$	A	peak value of current at full load (see Fig. 14)
$N$	—	number of turns in a winding
$p$	—	number of layers
$P_w$	W	winding loss
$R_{ac}$	Ω	a.c. resistance
$R_{dc}$	Ω	d.c. resistance

#### Effective frequency $f_e$ and effective current $I_e$

For sinusoidal currents, effective frequency  $f_e$  is equal to actual frequency  $f$ . This remains the case for small amounts of waveform distortion and small d.c. components.

For the waveform shown in Fig. 14, and provided that the rise and fall times are between 15% and 85% of the repetition period,

$$f_e = \frac{1,3f}{\sqrt{\{1 + 3(I_0/I_{ac})^2\}}}.$$

In designs for applications in class I,  $f_e$  may be only a few kilohertz. Eddy-current effects are then negligible and windings can be designed as if they carry d.c. Use the correct value of d.c. resistivity (given below).

For the waveform shown,

$$I_e^2 = I_0^2 + I_{ac}^2/3.$$

but for sinusoidal currents with a significant d.c. component

$$I_e^2 = I_0^2 + I_{ac}^2/2.$$

*Multi-layer wire windings (solid round wire)*

It is assumed that all layers have equal breadth; a difference in number of turns per layer of one is permitted where N/p is not an integer.

1.  $d_{id} = 2,6 \{b_w/(Nf_e)\}^{1/2}$ .
2. Select the nearest standard wire size (for d and  $d_o$ ) from a table such as that for IEC grade-1 winding wires.
3.  $P_{id} = N / \{ (b_w/d_o) - 1 \}$ . Note: this expression is valid only for  $d_o$  from step 2.
  - If  $p_{id} \geq 1,5$ , and current density in wire  $d_{id}$  is too high, make a new design using a larger core.
  - If  $p_{id} \leq 1,5$ , consider a foil or strip winding.
  - If  $p_{id} \leq 1$ , the expression for  $d_{id}$  in step 1 is not valid: go to the single-layer winding procedure.
  - Find p by rounding  $p_{id}$  to the next highest integer. Due to this rounding, there will be some space between turns.
4.  $H = p(d_o + i)$ .
5. If H exceeds  $H_a$ , or if current density is low:
  - reduce p by one layer,
  - select thickest wire for which  $d_o \leq pb_w/(N + p)$ ,
  - repeat from step 4, even if  $p = 1$ .
6.  $F_R = 1 + \frac{1}{2}(d/d_{id})^6$ . Note:  $F_R = 1,5$  for  $d = d_{id}$ ;  $F_R \approx 1$  if  $d/d_{id} < 0,7$ .
7.  $P_w = I_e^2 R_{ac} = I_e^2 F_R R_{dc}$ . Note: d.c. wire resistance  $0,0283/d^2 \Omega/m$ . For  $I_e$ , see previous page.

*Single-layer wire windings (solid round wire)*

1. Select thickest wire for which  $d_o \leq b_w/(N + 1)$ .
2.  $F_R = 0,33 d_e^{1/2} N / (N + 1)$ . Note: valid only if  $p_{id} \leq 1$  (see above).
3.  $P_w = I_e^2 R_{ac} = I_e^2 F_R R_{dc}$ . Note: wire resistance  $0,0283/d^2 \Omega/m$ . For  $I_e$  see previous page.

*Bunched (Litz) wire windings*

Eddy-current effects negligible: no special design procedure required. Copper density and thermal conductivity of winding low. Might be attractive if the ideal solid-conductor winding fills less than half the available height. Remember the 30% higher resistance at 100 °C.

*Foil or strip windings*

Here  $b_w$  is the width of the strip.

1.  $h_{id} = 3,1 (Nf_e)^{-1/2}$ .
2.  $h_{min} = 0,8 h_{id} \sqrt{N}$ .
3.  $h_{max} = (H_a/N) - i$  (choose a value for i that is appropriate to a strip of thickness about  $H_a/N$ ). If  $h_{max} < h_{min}$ , try a wire winding.
4. Select from available materials a conductor of thickness h such that  $h_{min} < h < h_{max}$ . Aim for  $h = h_{id}$ .
5.  $F_R = 1 + (h/h_{id})^4/3$ . For  $h = h_{id}$ ,  $F_R = 1,33$ . For  $h < 0,6h_{id}$ ,  $F_R \approx 1$ .
6.  $P_w = I_e^2 R_{ac} = I_e^2 F_R R_{dc}$ . Resistance of foil is  $1/(45b_w h) \Omega/m$ . For  $I_e$  see previous page.

**Reference**

Jongsma, J. 1978. Minimum-loss transformer windings for ultrasonic frequencies. *E.A.B.* 35: 146 – 163 (no. 3) and 211 – 226 (no. 4).

## E CORES (without air gap)\*

type number	material grade FXC 3C8	material grade FXC 3E1
	catalogue number of one core	catalogue number of one core
→ E13/7/4 (EF 12,6)	4312 020 34470	
E20/10/5	● 4312 020 34070	● 4322 020 34830
E25/13/7	4312 020 34020	
EI25/25/7	3122 134 90960	
E30/15/7	4312 020 34550	4322 020 34840
E42/21/15	● 4312 020 34110	● 4322 020 34850
I42/7/15		4322 020 37320
E42/21/20	● 4312 020 34120	
E42/33/20	4312 020 34190	
E55/28/21	● 4312 020 34100	● 4322 020 34900
E55/28/25	3122 134 90210	
E65/32/13		
E65/32/27	● 4312 020 34380	● 4322 020 34910

## EC CORES (without air gap)\*

type number	material grade FXC 3C8
	catalogue number of one core
EC35/17/10	● 4322 020 52500
EC41/19/12	● 4322 020 52510
EC52/24/14	● 4322 020 52520
EC70/34/17	● 4322 020 52530

## ETD CORES

type number	gap width mm	nominal $A_L$ nH	catalogue number	
			grade 3C8	grade 3C85
ETD34/17/11	≥ 0	2500 ± 25%	● 4312 020 37000	● 4312 020 37200
	0,1 ± 0,02	800	4312 020 37010	4312 020 37210
	0,2 ± 0,03	480	4312 020 37020	4312 020 37220
	0,5 ± 0,05	230	4312 020 37030	4312 020 37230
	1,0 ± 0,1	140	4312 020 37040	4312 020 37240
ETD39/20/13	≥ 0	2800 ± 25%	● 4312 020 37050	● 4312 020 37250
	0,1 ± 0,02	1000	4312 020 37060	4312 020 37260
	0,2 ± 0,03	600	4312 020 37070	4312 020 37270
	0,5 ± 0,05	295	4312 020 37080	4312 020 37280
	1,0 ± 0,1	170	4312 020 37090	4312 020 37290

● Preferred types.

\* Cores with air gap are available on request.

## ETD CORES (continued)

type number	gap width mm	nominal A <sub>L</sub> nH	catalogue number	
			grade 3C8	grade 3C85
ETD44/22/15	≥ 0	3500 ± 25%	● 4312 020 37100	● 4312 020 37300
	0,2 ± 0,03	800	4312 020 37110	4312 020 37310
	0,5 ± 0,05	400	4312 020 37120	4312 020 37320
	1,0 ± 0,1	230	4312 020 37130	4312 020 37330
	1,5 ± 0,15	170	4312 020 37140	4312 020 37340
ETD49/25/16	≥ 0	4000 ± 25%	● 4312 020 37150	● 4312 020 37350
	0,2 ± 0,03	1000	4312 020 37160	4312 020 37360
	0,5 ± 0,05	480	4312 020 37170	4312 020 37370
	1,0 ± 0,1	270	4312 020 37180	4312 020 37380
	2,0 ± 0,2	150	4312 020 37190	4312 020 37390


## U AND I CORES

type number	material grade FXC 3C8	
	catalogue number of one core	
U10/8/3	● 3122 134 91160	
U15/11/6	● 3122 134 90690	
	3122 134 90730	
I15/3/3	● 3122 134 90200	
U20/16/7	3122 134 90720	
	● 3122 134 90460	
I20/6/5	3122 134 90620	
U25/20/13	● 3122 134 90760	
I25/7/7		
U30/25/16		
I46/10/11		
U37/25/18	4312 020 34740	
U37/29/18	4312 020 33710	
U46/33/11	3122 104 90480	
	3122 104 90470	
I58/13/16		
U52/27/11	● 3122 134 90480	
U57/28/16	4312 020 33190	
U58/45/16	3122 104 94760	
	3122 104 94770	
U64/40/20	3122 134 91390	
U70/33/17	3122 104 93950	
I93/28/30		
U93/52/30	4312 020 33580	
U93/76/30	4312 020 33570	
	4312 020 33590	
U93/76/16	4312 020 33550	
I93/28/16	4312 020 33560	
U100/57/25	4312 020 33600	
I100/25/25	4312 020 33610	

The data on these cores are arranged on the following pages in order of type number.

- Preferred types.

## E-CORE

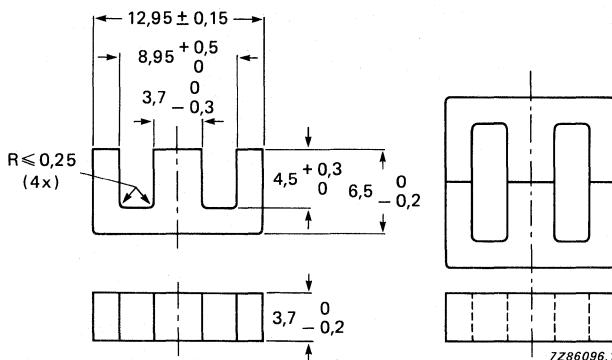

Dimensions according to DIN 41985

Mass approx. 0,9 g

### MAGNETIC DATA

Guaranteed values measured at 16 kHz for a core pair EE13/13/4, pressed together with a force of 30 N.

grade	temperature °C ± 5	induction $\hat{B}$ (mT)	field strength $\hat{H}$ (A/m)	catalogue number of one E core
3C8	25 105	≥ 140 ≥ 330	50 250	4312 020 34470

Magnetic dimensions

$$l_e = 29,6 \text{ mm}$$


$$A_e = 13 \text{ mm}^2$$

$$V_e = 384 \text{ mm}^3$$

$$\text{Inductance factor } A_L \quad \text{at } f < 10 \text{ kHz}, \theta = 25^\circ \text{C}, \hat{B} < 0,1 \text{ mT} : \quad 800 \quad +30\% \quad -20\%$$

The core is available with air gap on request.

## E-CORES

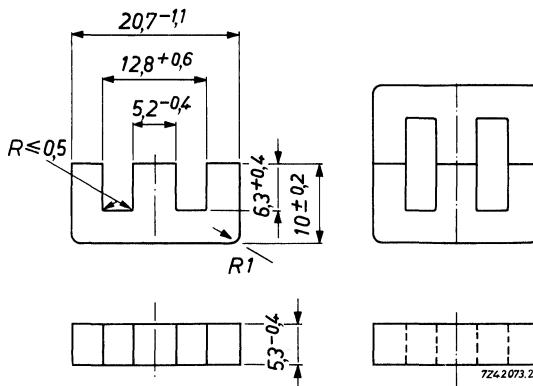

Dimensions according to DIN 41295

Mass approx. 4 g

## MAGNETIC DATA

Guaranteed values for a core pair EE20/20/5, pressed together with a force of 55 N, air gap  $\Delta = 0$ .

	freq. kHz	temperature °C	$\hat{B}$ mT	grade 3E1	grade 3C8
$A_L$	100	$25 \pm 10$	$\leq 0,1$	1920 to 2890	$1300 \pm 25\%$ ←
$\mu_e$	100	$25 \pm 10$	$\leq 0,1$	2100 to 3155	
$\mu_e$	100	23 to 70	$\leq 0,1$	$\geq 2100$	
$\tan \delta$					
$\frac{\tan \delta}{\mu_i} \times 10^6$	4	$25 \pm 10$	$\leq 0,1$	$\leq 2,5$	
$\mu_i$	100	$25 \pm 10$	$\leq 0,1$	$\leq 20$	
	500	$25 \pm 10$	$\leq 0,1$	$\leq 200$	
$\eta_B \times 10^3$	4	$25 \pm 10$	1,5 to 3	$\leq 1,8$	
P(W)	16	25	200		$\leq 0,3$
	16	100	200		$\leq 0,25$
$\hat{H}$ (A/m)	16	100	$\geq 275$		250

Catalogue number of one E core without air gap\*, grade 3E1 • 4322 020 34830  
3C8 • 4312 020 34070

Magnetic dimensions, according to IEC 205:

$$l_e = 42,8 \text{ mm}$$

$$C_1 = \sum \frac{1}{A} = 1,37 \text{ mm}^{-1}$$

$$A_e = 31,2 \text{ mm}^2$$

$$V_e = 1340 \text{ mm}^3$$



\* The cores are available with air gap on request.

• Preferred type.

## COIL FORMERS


for shell type transformer EE20/20/5 (M20)

Without pins.

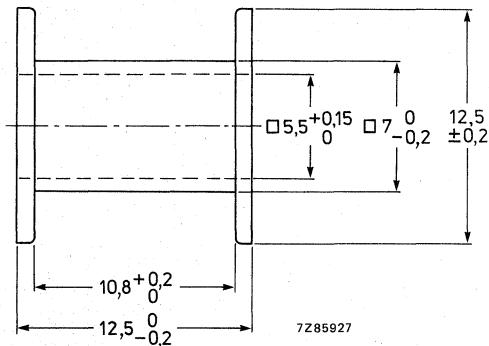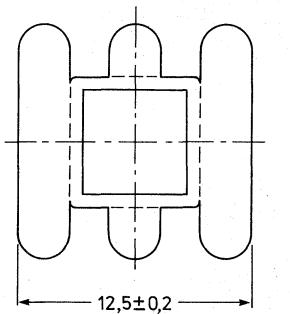


catalogue number	4312 021 28430
→ material	polyamide 6,6, glass fibre reinforced
minimum window area	27 mm <sup>2</sup>
mean length of turn	38 mm
approximate mass	0,5 g
maximum working temperature	130 °C

With 8 soldering pins.

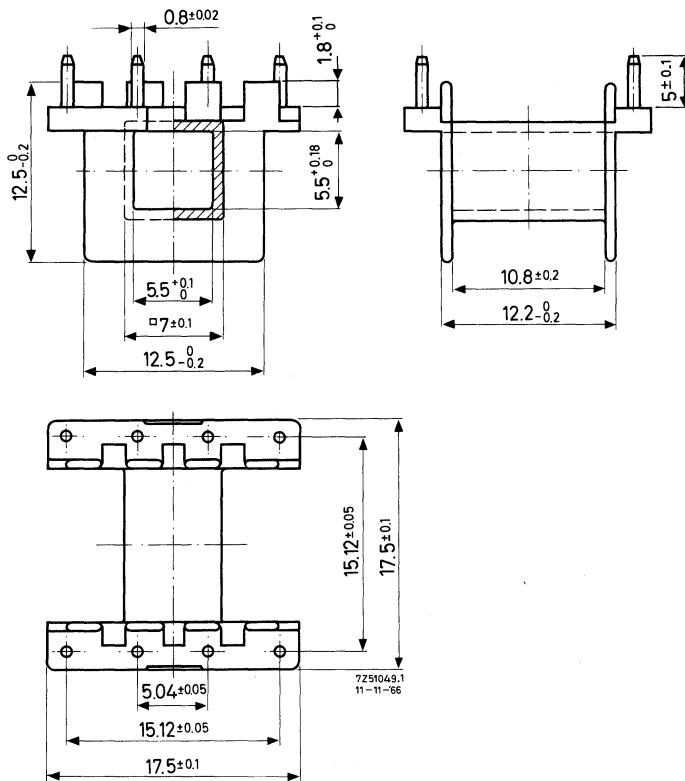


catalogue number	4322 021 20240
material	phenolformaldehyde reinforced with glass fibre; brass dip-solder pins
minimum window area	27 mm <sup>2</sup>
mean length of turn	38 mm
approximate mass	3 g
maximum temperature for dip-soldering during 5-6 s	280 °C
maximum working temperature	130 °C

The coil former fits a shell type transformer EE20/20/5 (M20). The soldering pins will fit printed-wiring boards with a grid of 0,1 inch as well as 2,5 mm. The pin length is sufficient for a board thickness of up to 3 mm. The board should be provided with holes of  $1,3 \pm 0,1$  mm diameter.

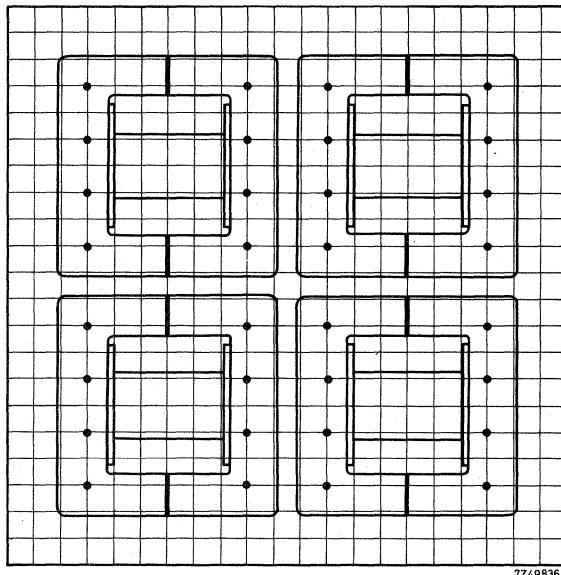


With 6 soldering pins.

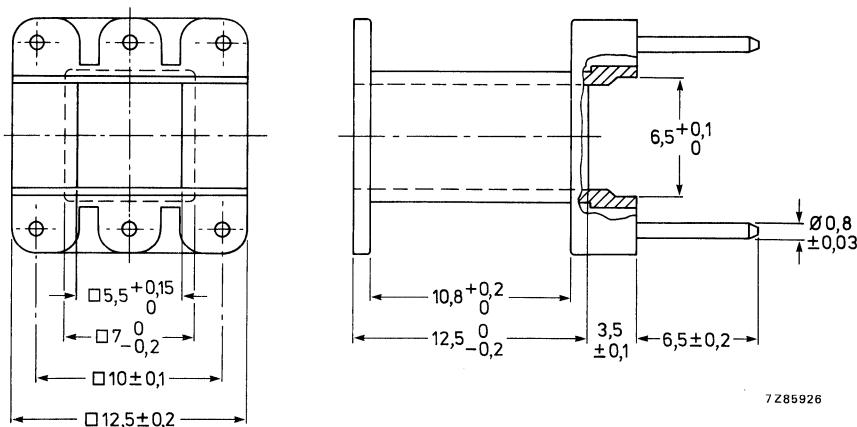

catalogue number	4322 021 20290
material	polyamide 6,6, glass fibre reinforced; copper nickel soldering pins
minimum window area	27 mm <sup>2</sup>
mean length of turn	38 mm
approximate mass	3 g
maximum working temperature	130 °C

The coil former fits a shell type transformer EE20/20/5 (M20). The soldering pins will fit printed-wiring boards with a grid of 0,1 inch as well as 2,5 mm. The pin length is sufficient for a board thickness of up to 3 mm. The board should be provided with holes of  $1,3 \pm 0,1$  mm diameter.

## MOUNTING PARTS

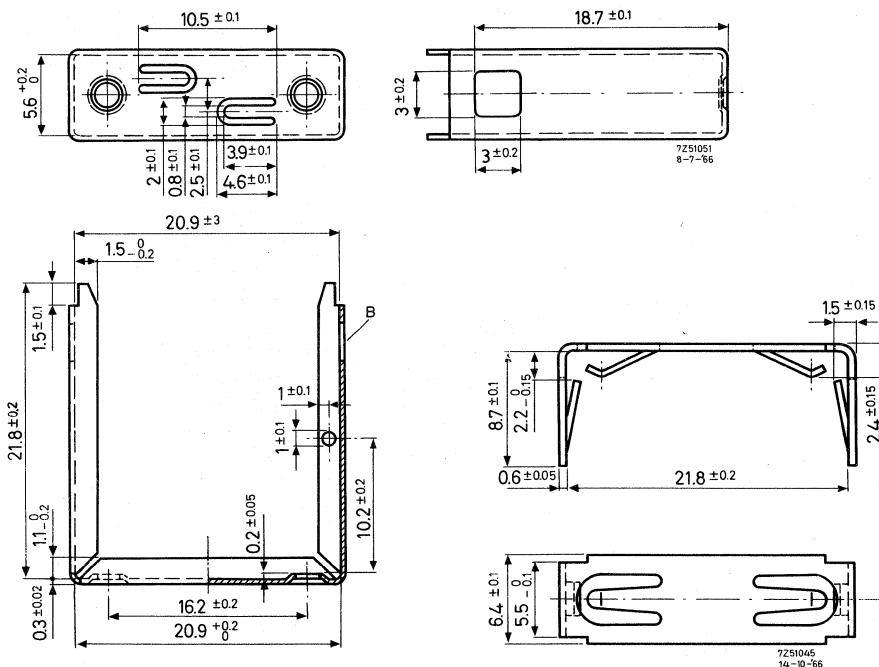


(1). Clasp 4322 021 20160.  
Material: brass, tin-plated.

(2). Spring 4322 021 20220.  
Material: phosphor-bronze, tin-plated.


The construction is mounted by pushing the spring over the clasp in such a way that the lips A of the spring catch in the square holes B of the clasp. The mechanical pressure, required to keep the two E-cores together is exercised by means of two lips on top of the spring. No special tool is required for mounting the construction.

The construction can be used in the horizontal and vertical positions. If the construction is used in the vertical position, the lips C of the clasp must be bent. The dimensions and mutual distance of these lips are chosen in such a way that they fit printed-wiring boards with a grid of 0,1 " as well as those with a grid of 2,50 mm. If used in a horizontal position the clasp can be earthed by means of a copper wire soldered in hole D.

## CHARACTERISTIC CURVES

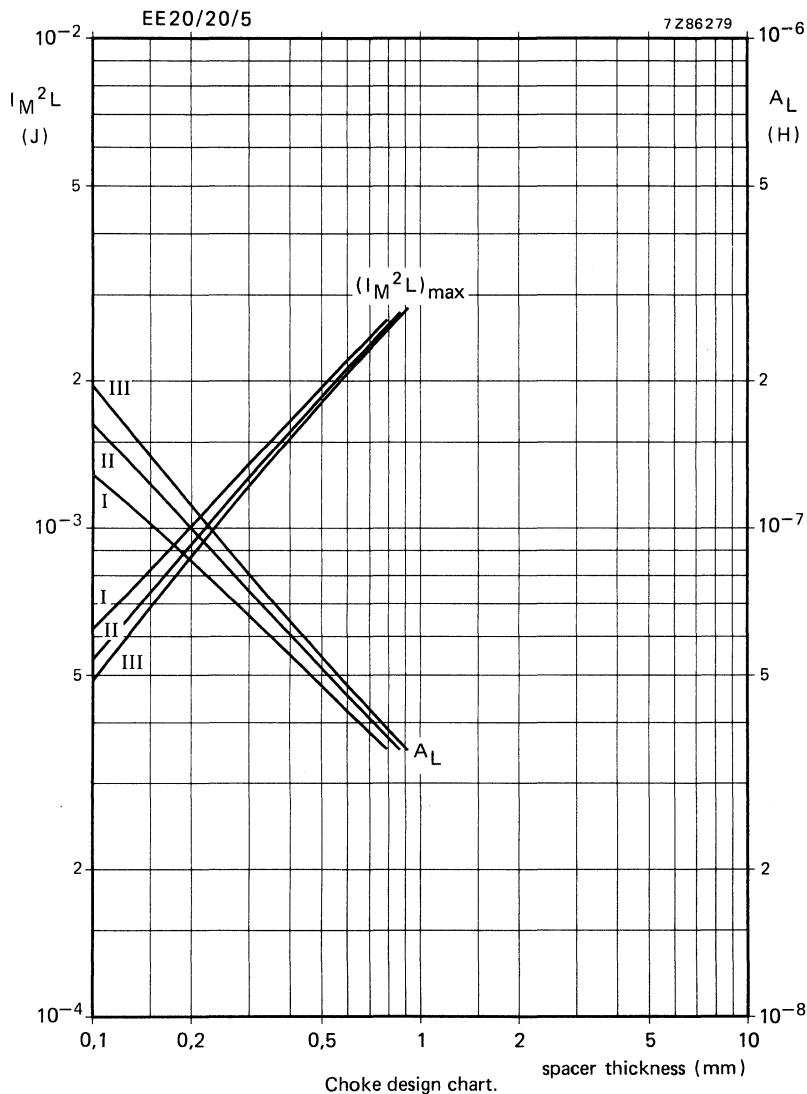


For application classes I, II and III see 'Power choke design' in the Introduction.

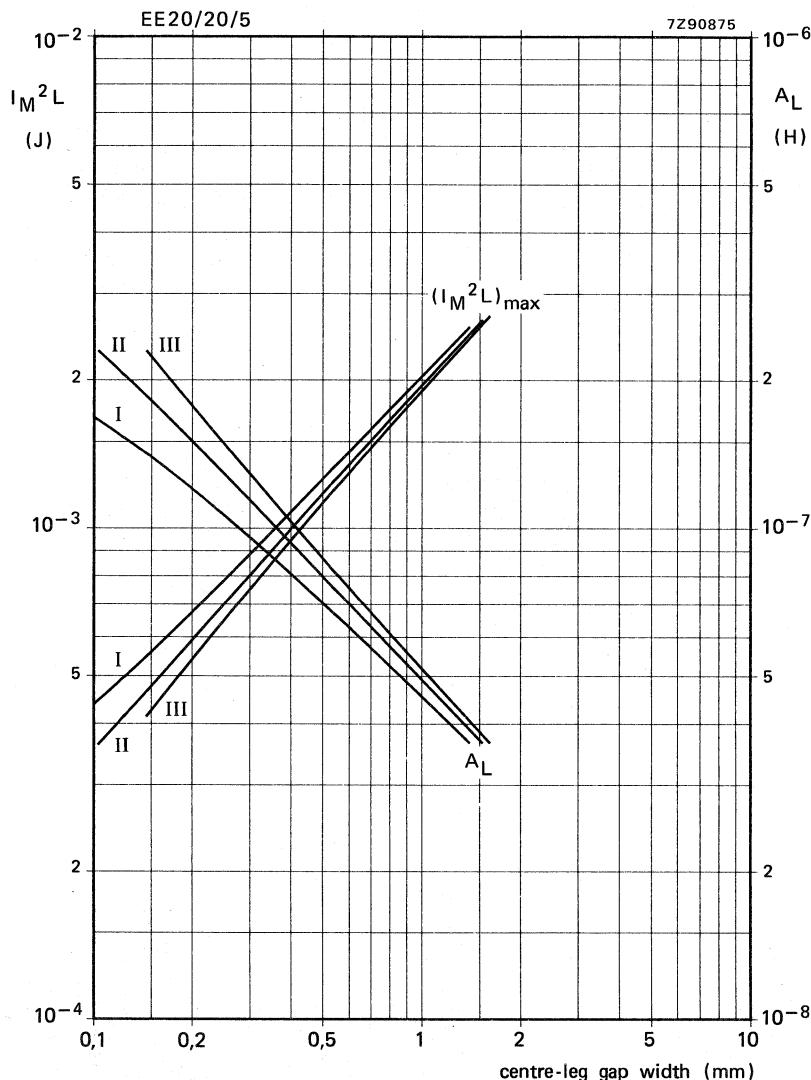

Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.

## E-CORES

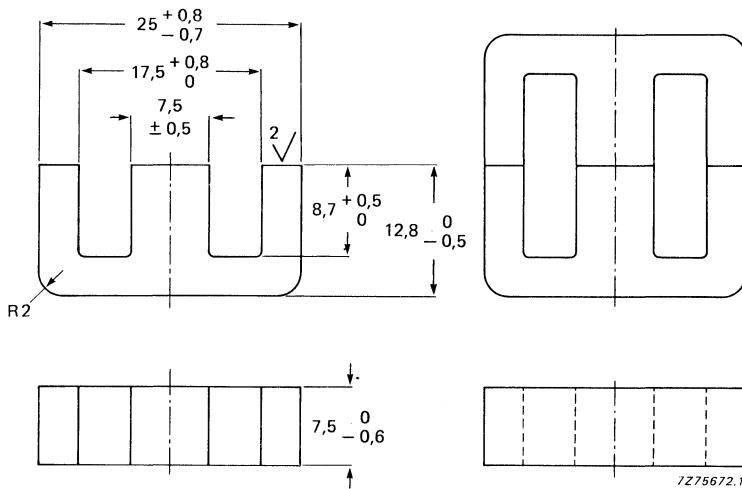

Dimensions according to DIN 41985

Mass 8,1 g

#### MAGNETIC DATA

Guaranteed values measured at 16 kHz for a core pair EE25/25/7, pressed together with a force of 60 N.

grade	temperature °C	induction $\hat{B}$ (mT)	field strength $\hat{H}$ (A/m)	losses W	catalogue number of one E-core
3C8	25 100 100	200 $\geq 330$ 200	250	$\leq 0,4$ $\leq 0,35$	● 4312 020 34020

Magnetic dimensions, according to IEC 205:

$$l_e = 57,5 \text{ mm}$$


$$A_e = 52,5 \text{ mm}^2$$

$$C_1 = \sum \frac{l_e}{A_e} = 1,095 \text{ mm}^{-1}$$

$$V_e = 3020 \text{ mm}^3$$

$$A_L = 1750 \pm 25\% \text{ at } f = 10 \text{ kHz; } \theta = 25^\circ \text{C; } \hat{B} \leq 0,1 \text{ mT}$$

- Preferred type.

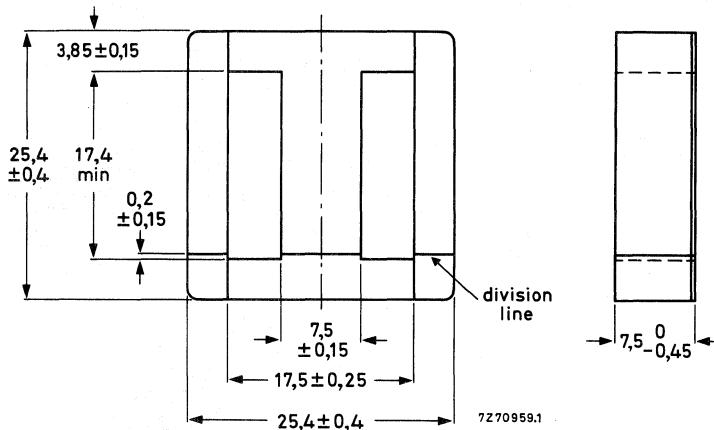**MAGNETIC DATA**

Guaranteed values measured at 16 kHz, for an E-and an I core pressed together with a force of 60 N.

grade	temperature °C	B mT	H A/m	losses W	catalogue number
3C8	25 25 100	$\geq 200$ $\geq 380$ $\geq 100$	250 50	$\leq 0,65$	3122 134 90960

**Magnetic dimensions**

$$l_e = 57,5 \text{ mm}$$


$$A_e = 52,5 \text{ mm}^2$$

$$V_e = 3020 \text{ mm}^3$$

## COIL FORMERS


for shell type transformers EE25/25/7  
and EI25/25/7

With 6 soldering pins.

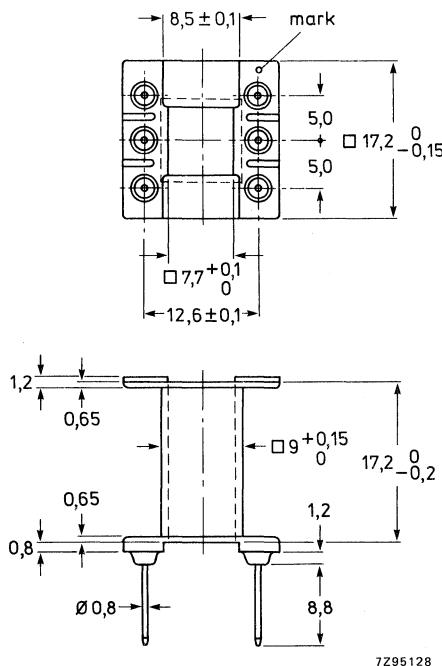




catalogue number	4312 021 28540
material	polyamide 6,6 glass fibre reinforced
minimum window area	61 mm <sup>2</sup>
mean length of turn	49 mm
approximate mass	4 g
maximum working temperature	130 °C

With 8 soldering pins.

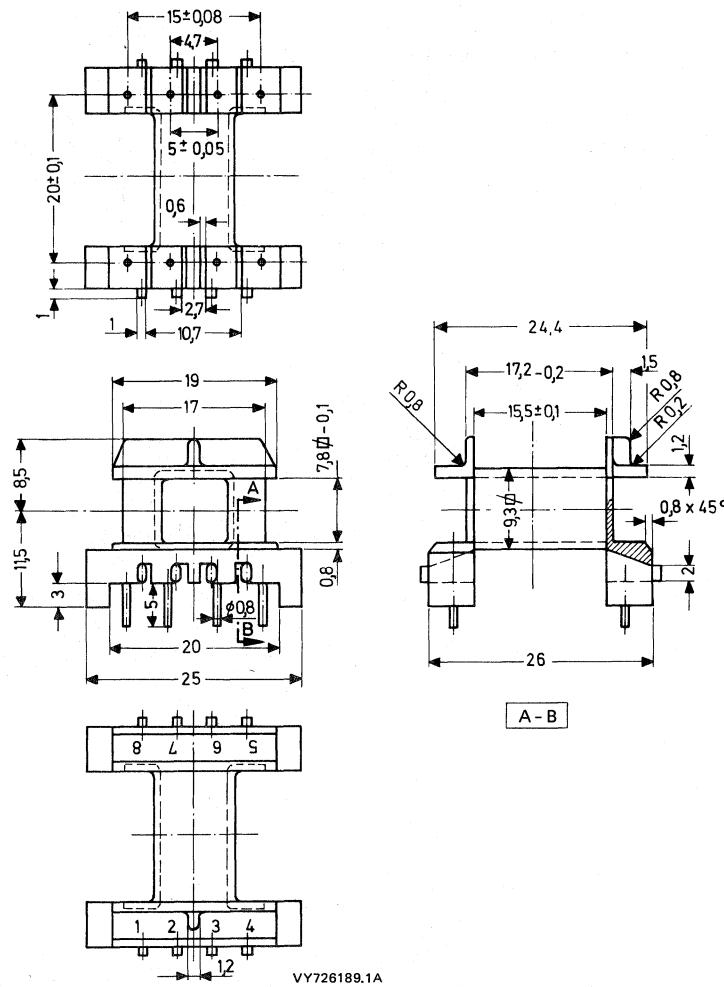

catalogue number	4312 021 28750
material	polyamide 6,6 glass fibre reinforced
soldering pins	phosphor bronze dip-soldered
minimum window area	61 mm <sup>2</sup>
mean length of turn	49 mm
approximate mass	4 g
maximum working temperature	130 °C

## MOUNTING PARTS

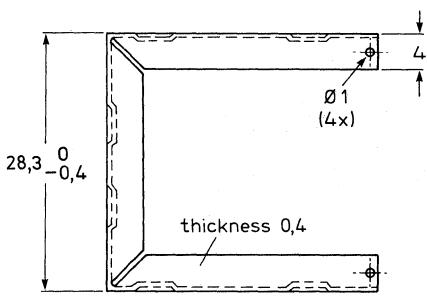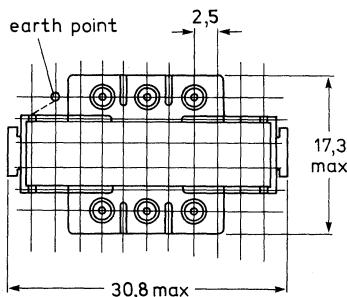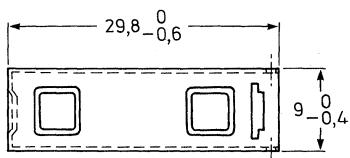


7Z95130


Clasp.

material: nickel plated steel


catalogue number: 4312 021 26120

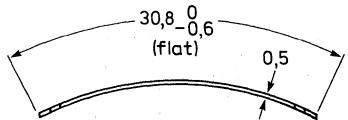

7Z95127

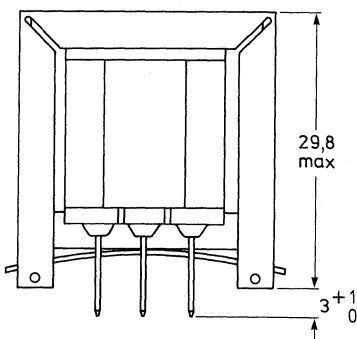

Maximum dimensions of the set.




7Z95129

Spring.

material: stainless steel

catalogue number: 4312 021 26190

## E-CORES

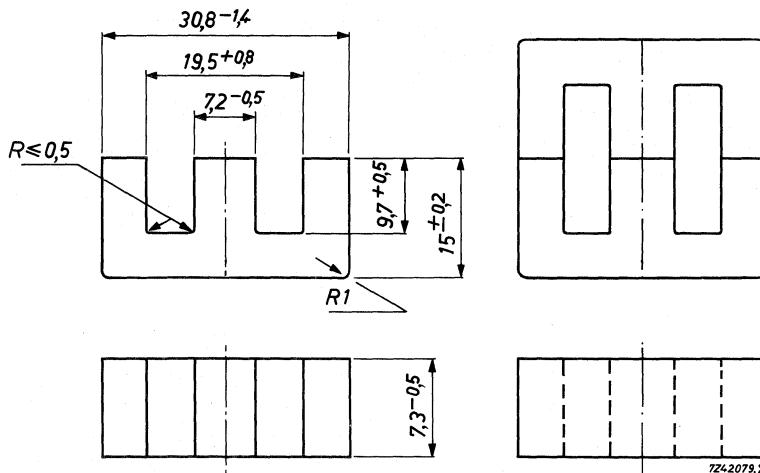

Dimensions according to DIN 41295

Mass approx. 11 g

## MAGNETIC DATA

Guaranteed values for a core pair EE30/30/7, pressed together with a force of 110 N, air gap  $\Delta = 0$ 

	freq. kHz	temperature °C	$\hat{B}$ mT	grade	
				3E1	3C8
→ A <sub>L</sub>	100	25 ± 10	≤ 0,1	2660 to 4000	1900 ± 25%
$\mu_e$	100	25 ± 10	≤ 0,1	2375 to 3565	
$\mu_e$	100	23 to 70	≤ 0,1	≥ 2375	
$\tan \delta$ $\mu_i$ × 10 <sup>6</sup>	4	25 ± 10	≤ 0,1	≤ 2,5	
	100	25 ± 10	≤ 0,1	≤ 20	
	500	25 ± 10	≤ 0,1	≤ 200	
$\eta_B \times 10^3$	4	25 ± 10	1,5 to 3	≤ 1,8	
P (W)	16	25	200		≤ 0,48
	16	100	200		≤ 0,44
$\hat{H}$ (A/m)	16	100	≥ 330		250

Catalogue numbers of one E-core without air gap:<sup>\*</sup>

Ferroxcube grade 3E1 • 4322 020 34840

3C8 • 4312 020 34550

Magnetic dimensions according to IEC 205:

$$l_e = 66,9 \text{ mm}$$

$$A_e = 59,7 \text{ mm}^2$$

$$C1 = \sum \frac{1}{A} = 1,12 \text{ mm}^{-1}$$


$$V_e = 4000 \text{ mm}^3$$

\* Cores with air gap are available on request.

• Preferred type.


## COIL FORMERS

for shell type transformer EE30/30/7 (M30)

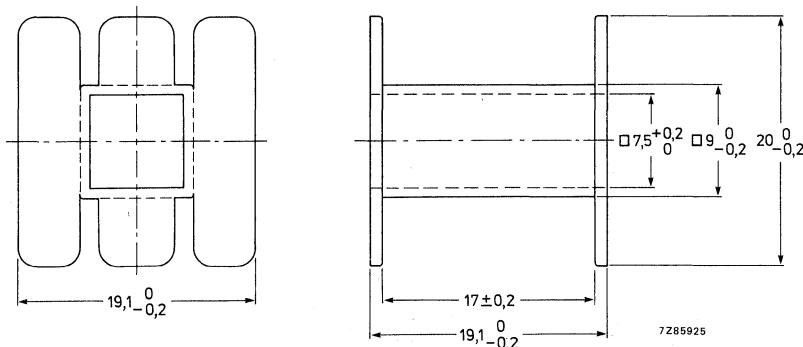


catalogue number	4312 021 28550
material	polyamide 6,6 glass fibre reinforced
minimum window area	80 mm <sup>2</sup>
mean length of turn	56 mm
approximate mass	1,3 g
maximum working temperature	130 °C

With soldering pins.

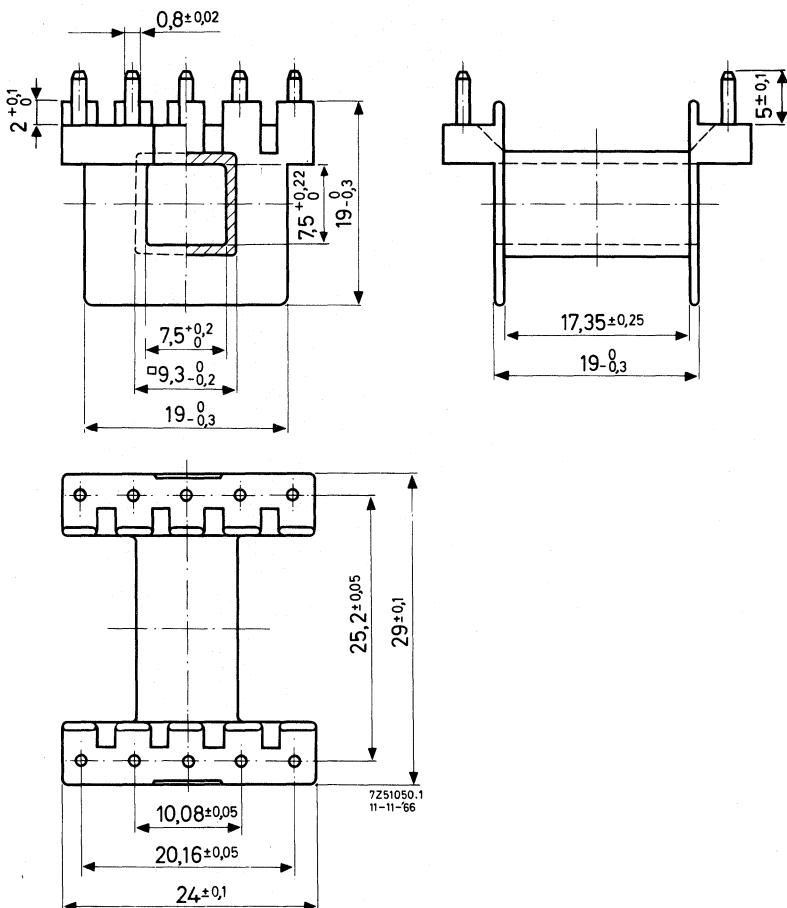


catalogue number	4322 021 20250
material	phenolformaldehyde reinforced with glass fibre; brass dip-solder pins
minimum window area	$80 \text{ mm}^2$
mean length of turn	$56 \text{ mm}$
approximate mass	$3 \text{ g}$
maximum temperature for dip-soldering during 5-6 s	$280 \text{ }^\circ\text{C}$
maximum working temperature	$130 \text{ }^\circ\text{C}$

The coil former fits a shell type transformer EE30/30/7 (M30). The soldering pins will fit printed-wiring boards with a grid of 0,1 inch as well as 2,5 mm. The pin length is sufficient for a board thickness up to 3 mm. The board should be provided with holes of  $1,3 \pm 0,1$  mm diameter.

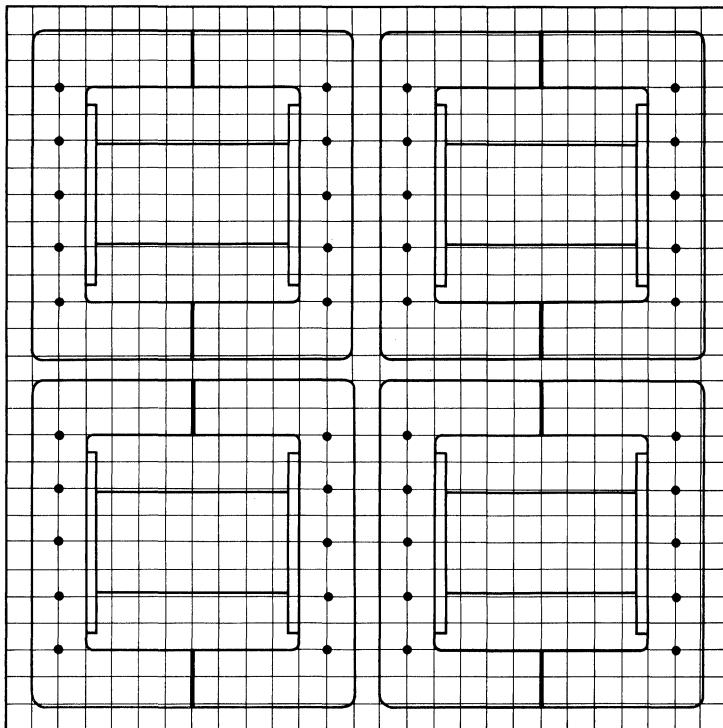

## MOUNTING PARTS

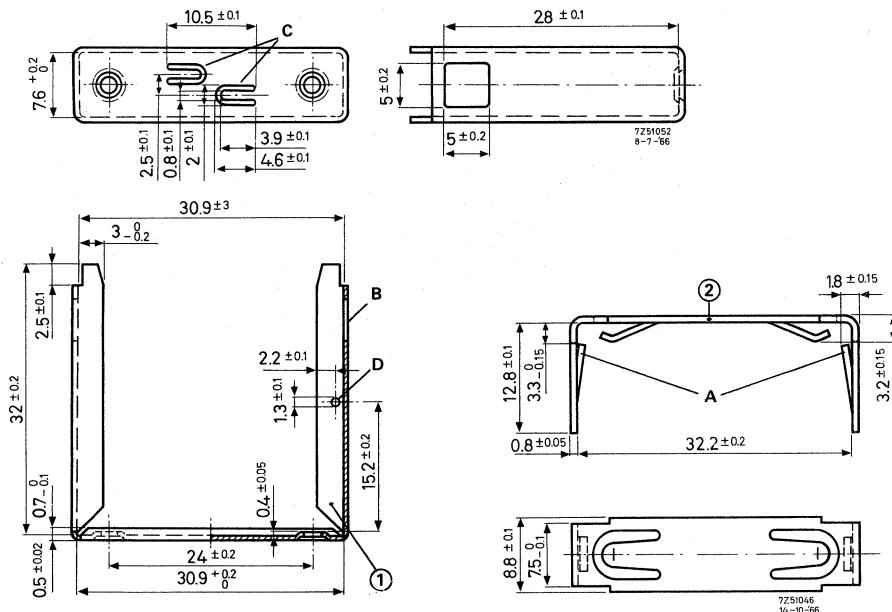

(1). Clasp 4322 021 20170

Material: brass, tin-plated.


(2). Spring 4322 021 20230

Material: phosphor-bronze, tin-plated.


The construction is mounted by pushing the spring over the clasp in such a way that the lips A of the spring catch in the square holes B of the clasp. The mechanical pressure, required to keep the two E-cores together is exercised by means of two lips on top of the spring. No special tool is required for mounting the construction.

The construction can be used in the horizontal and vertical positions. If the construction is used in the vertical position, the lips C of the clasp must be bent. The dimensions and mutual distance of these lips are chosen in such a way that they fit printed-wiring boards with a grid of 0,1" as well as those with a grid of 2,50 mm. If used in a horizontal position the clasp can be earthed by means of a copper wire soldered in hole D.

## CHARACTERISTIC CURVES

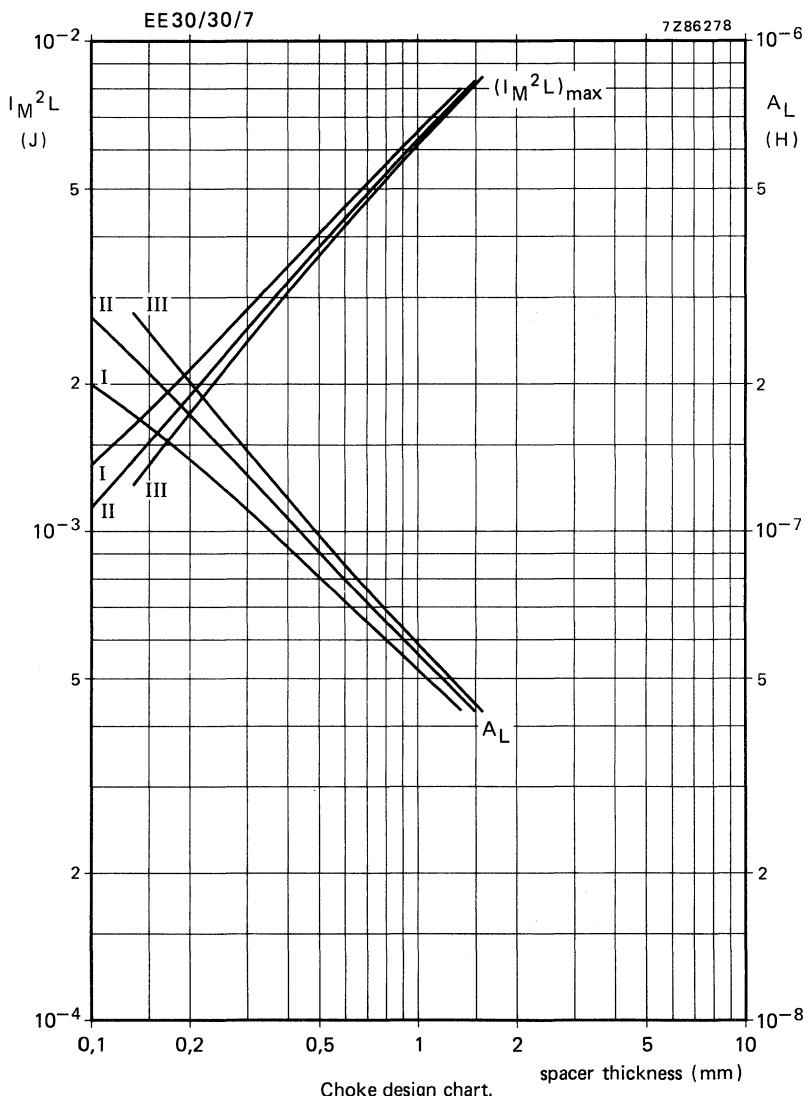

For application classes I, II and III see 'Power choke design' in the Introduction.

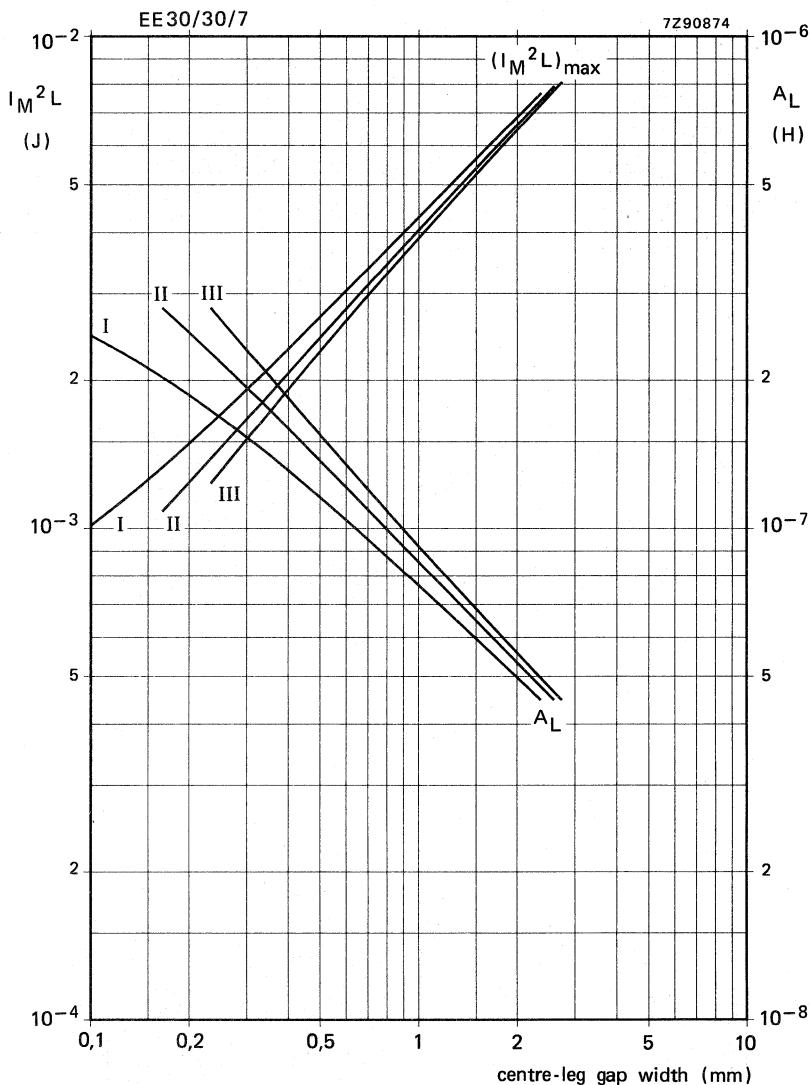


Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.

## E- AND I-CORES

Dimensions according to DIN 41295.

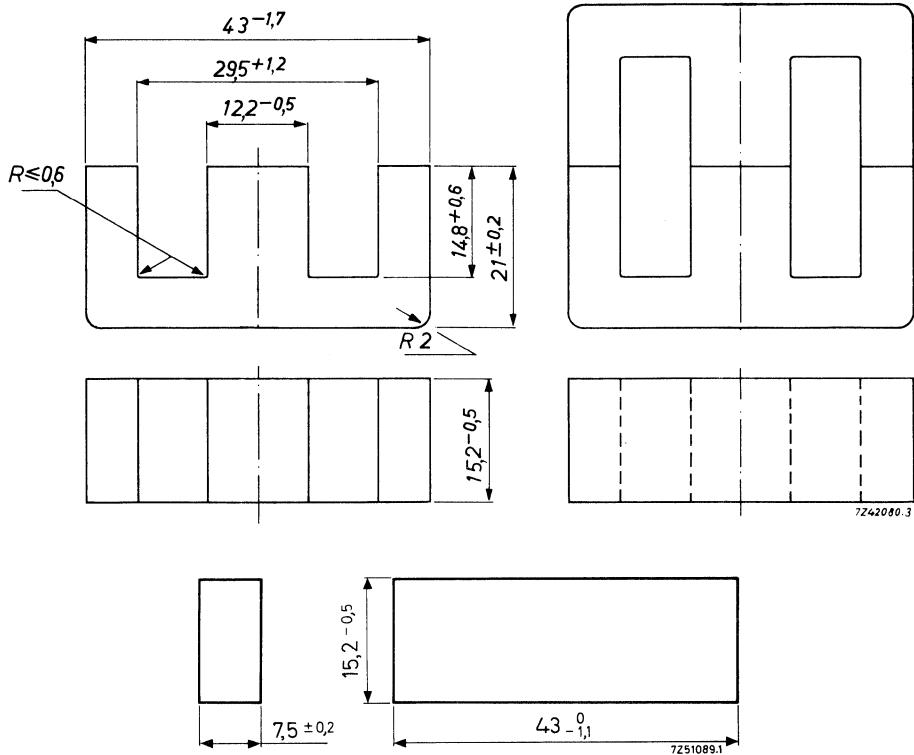

Mass approx. 42 g

**Catalogue numbers**

Ferroxcube grade

Catalogue number of E-core, without air gap\*

Catalogue number of I-core

3E1

• 4322 020 34850  
4322 020 37320

3C8

• 4312 020 34110

\* Cores with air gap are available on request.

• Preferred type.

A transformer core can be built up by combining an even number of E-cores. A shape that is often chosen is the shell type transformer EE42/42/15 composed of two cores type E42/21/15 or the E-I combination EI42/29/15.

Magnetic dimensions according to IEC 205:

		EE42/42/15	EI42/29/15
Effective magnetic path length	$l_e$	= 97,0 mm	67,2 mm
Effective cross-sectional area	$A_e$	= 182 mm <sup>2</sup>	183 mm <sup>2</sup>
Core constant	$C_1 = \sum \frac{l_e}{A_e} =$	0,534 mm <sup>-1</sup>	0,367 mm <sup>-1</sup>
Effective core volume	$V_e$	= 17600 mm <sup>3</sup>	12300 mm <sup>3</sup>

#### MAGNETIC DATA

Guaranteed values for a core pair EE42/42/15 or EI42/29/15, pressed together with a force of 280 N, air gap  $\Delta = 0$ .

#### Magnetic properties at $25 \pm 10$ °C for grade 3E1

	EE42/42/15	EI42/29/15
$\mu_e$	= 2570-3855*	2400-3600
$A_L$	= 6040-9070	8210-12320

At 4 kHz and  $\hat{B}$  between  
1,5 and 3 mT

$$\eta_B \times 10^3 \leq 1,8 \text{ T}^{-1}$$

at 4 kHz and  $\hat{B} \leq 0,1 \text{ mT}$

$$\frac{\tan \delta}{\mu_i} \times 10^6 \leq 2,5$$

At 100 kHz and  $\hat{B} \leq 0,1 \text{ mT}$

$$\frac{\tan \delta}{\mu_i} \times 10^6 \leq 20$$

#### Magnetic properties for grade 3C8

At 16 kHz,  $B = 200 \text{ mT}$  and  $\theta = 100$  °C

$$P \leq 2 \text{ W}$$

→ At 16 kHz,  $B \geq 330 \text{ mT}$  and  $\theta = 100$  °C

$$\hat{H} = 250 \text{ A/m}$$

At 16 kHz,  $B \geq 90 \text{ mT}$  and  $\theta = 100$  °C

$$\hat{H} = 50 \text{ A/m}$$


→  $A_L = 3900 \pm 25\%$  at  $f = 10 \text{ kHz}$ ,  $\theta = 25$  °C,  $\hat{B} \leq 0,1 \text{ mT}$

\* In the temperature range + 23 to + 70 °C  $\mu_e \geq 2575$ .

## COIL FORMERS

for shell type transformer EE42/42/15 (M42)


Without soldering pins.

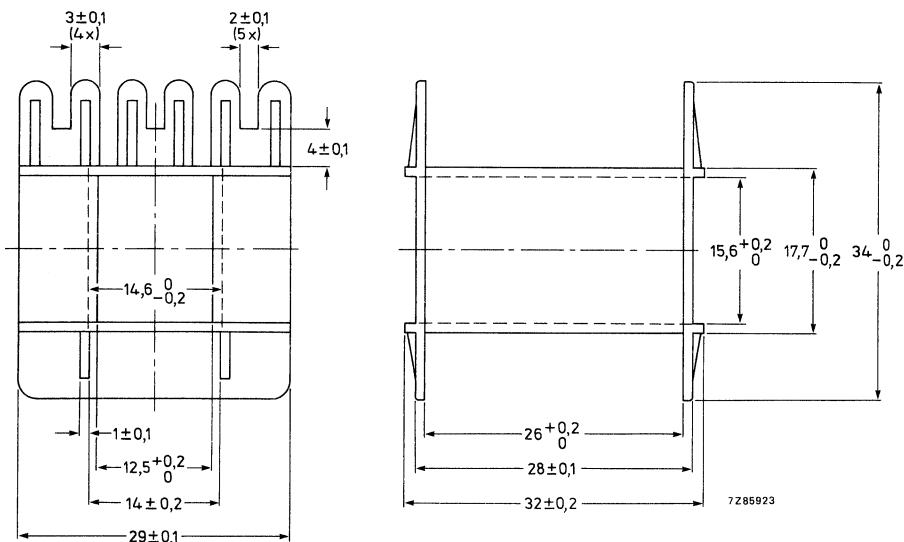

catalogue number	4312 021 28620
material	polyamide 6,6 glass fibre reinforced
minimum window area	178 mm <sup>2</sup>
mean length of turn	93 mm
approximate mass	4 g
maximum working temperature	130 °C


The dimensions are practically according to German specification DIN 41305.

With 10 soldering pins.

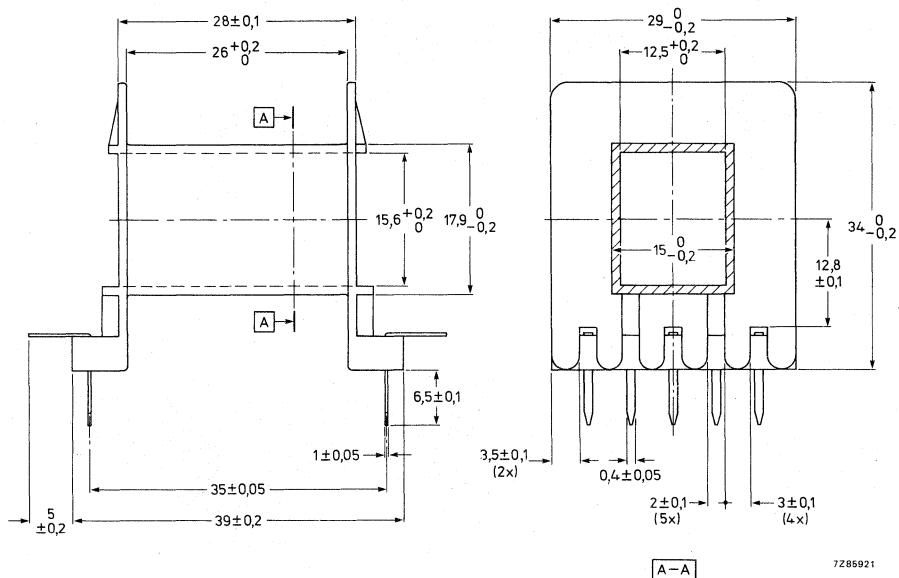


A-A

7285921

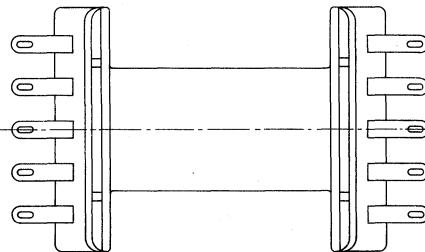


catalogue number	4322 021 31830
material	reinforced polyamide with brass dip-soldered pins
minimum window area	178 mm <sup>2</sup>
mean length of turn	93 mm
approximate mass	4 g
maximum working temperature	130 °C

The coil former fits a shell type transformer EE42/42/15 (M42). The soldering pins will fit printed-wiring boards with a grid of 0,1 inch as well as 2,5 mm. The pin length is sufficient for a board thickness of up to 3 mm. The board should be provided with holes of  $1,3 \pm 0,1$  mm diameter.

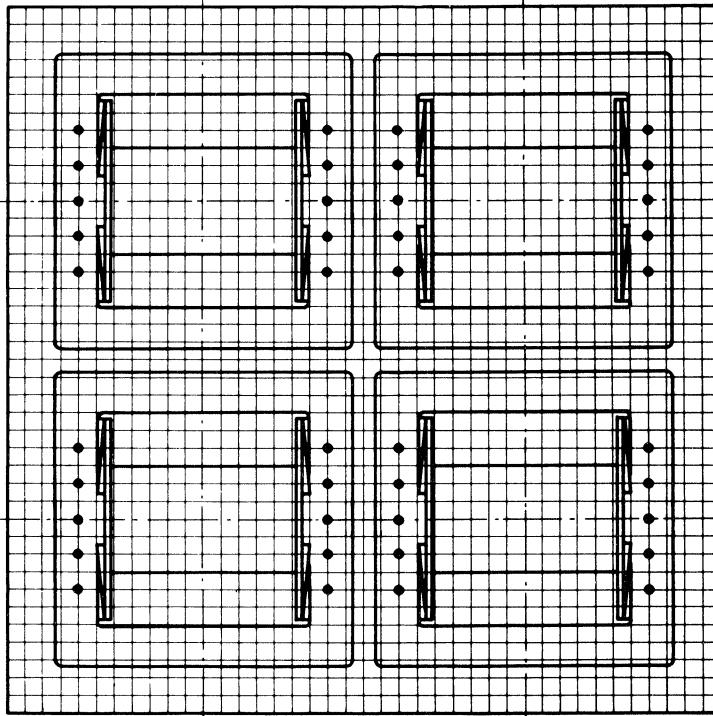

7Z99308.1

## MOUNTING PARTS

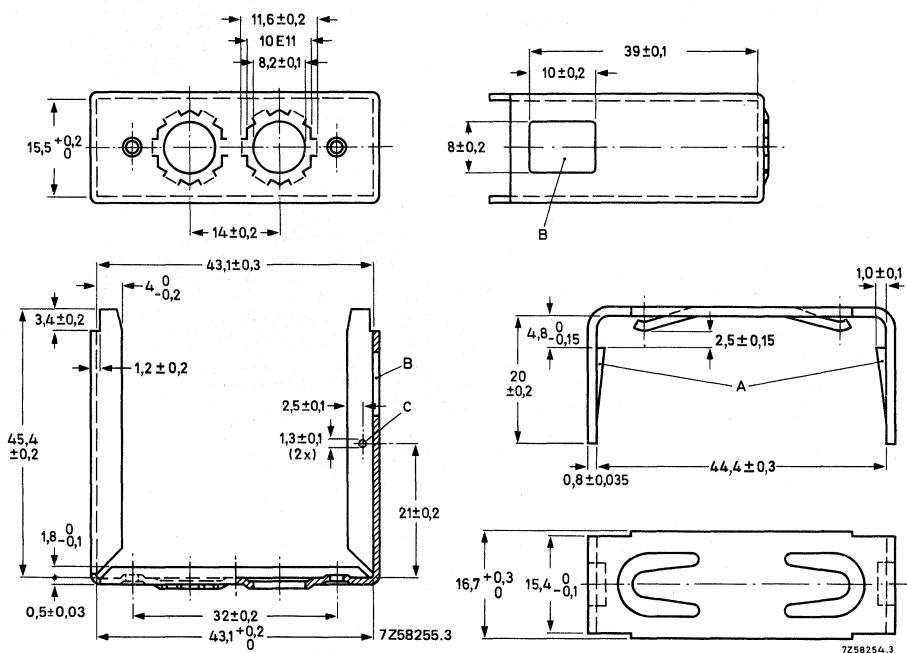


Clasp 4322 021 31910  
Material: chromium nickel steel.

Spring 4322 021 31920  
Material: chromium nickel steel.

The construction is mounted by pushing the spring over the clasp in such a way that the lips A of the spring catch in the square holes B of the clasp. The mechanical pressure, required to keep the two E-cores together is exercised by means of two lips on top of the spring. No special tool is required for mounting the construction.


The construction can be used in the horizontal and vertical positions. If the construction is used in the vertical position, two fixing bushes 4322 021 30720 with nuts 4322 021 30710 must be applied in the holes of the clasp. If used in a horizontal position the clasp can be earthed by means of a copper wire soldered in hole C.

## CHARACTERISTIC CURVES

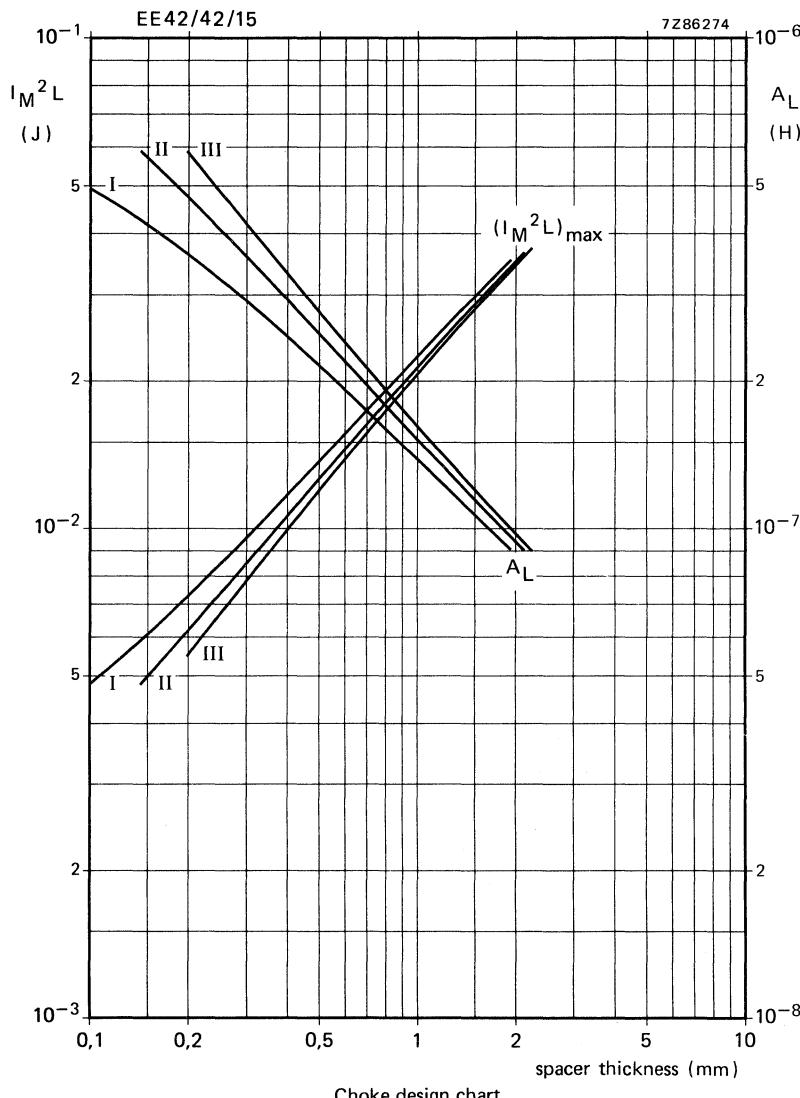

Choke design chart.


For application classes I, II and III see 'Power choke design' in the Introduction.

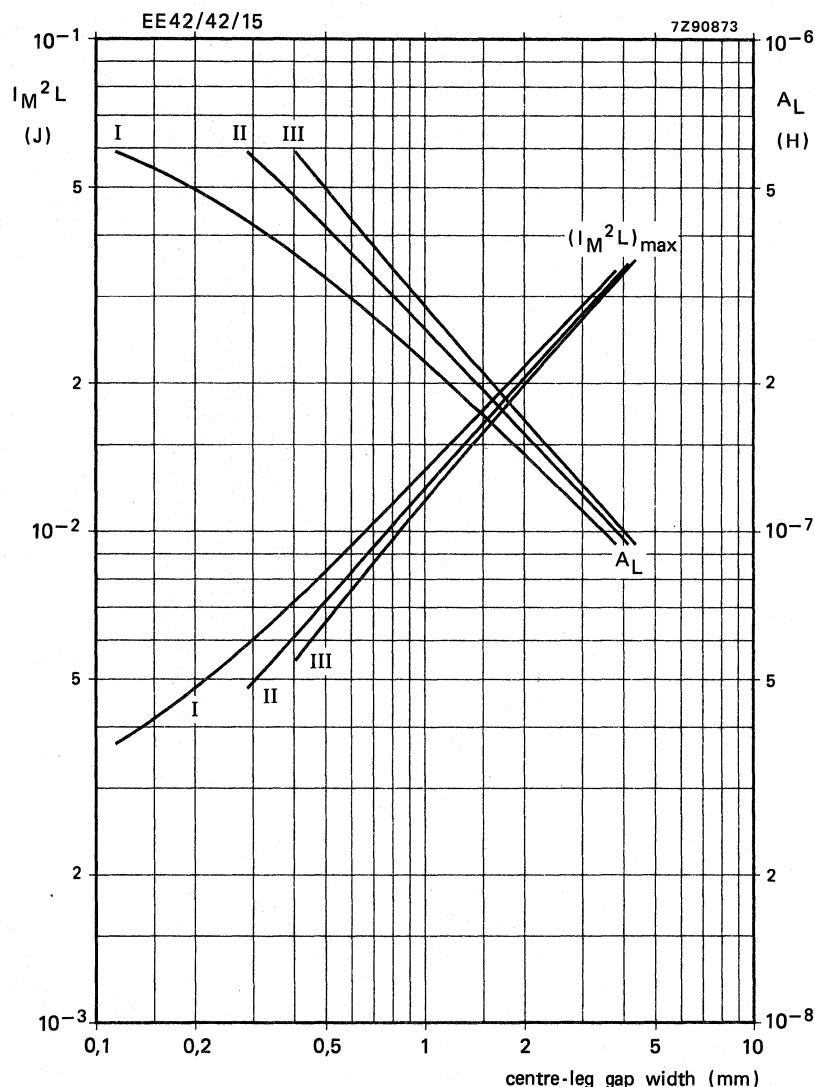

Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.

## E-CORES

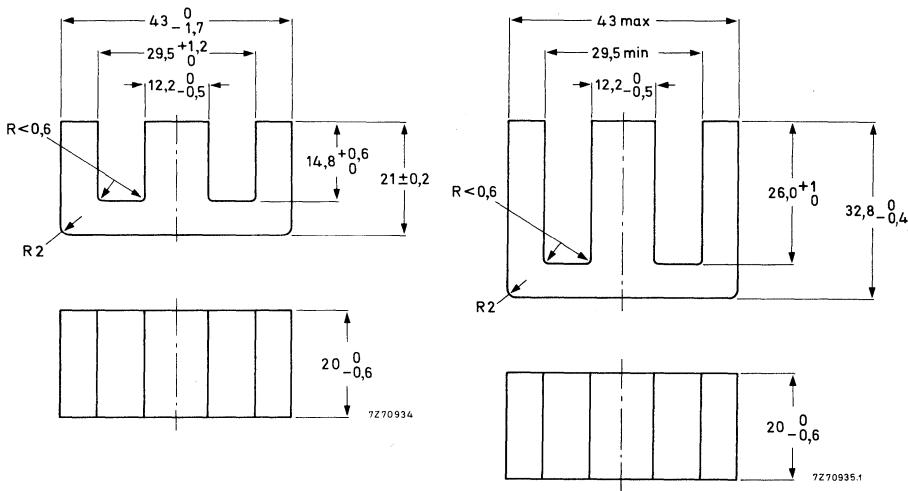

E42/21/20

Mass 56 g

E42/33/20

Mass 82 g

### Catalogue numbers

Ferroxcube grade 3C8

Catalogue number of core E42/21/20 without air gap\*

Catalogue number of core E42/33/20 without air gap\*

Catalogue number of combination of cores E42/21/20 + E42/33/20

• 4312 020 34120

4312 020 34190

4312 020 34170

### SHELL TYPE TRANSFORMERS EE42/42/20 AND EE42/54/20

A transformer core can be built up by combining an even number of E-cores. Shapes that are often chosen are the shell type transformer EE42/42/20 composed of two cores E42/21/20, and shell type transformer EE42/54/20 composed of one core E42/21/20 and one core E42/33/20.

- Preferred type.

\* Cores with air gap are available on request.

Magnetic dimensions according IEC 205:

	EE42/42/20	EE42/54/20
$I_e$	= 98 mm	122 mm
$A_e$	= 236 mm <sup>2</sup>	236 mm <sup>2</sup>
$C_1 = \sum \frac{I_e}{A_e}$	= 0,415 mm <sup>-1</sup>	0,517 mm <sup>-1</sup>
$V_e$	= 23100 mm <sup>3</sup>	28800 mm <sup>3</sup>

### MAGNETIC DATA


At  $f = 16$  kHz,  $\hat{B} = 200$  mT,  $\theta = 25^\circ\text{C}$   
 $\theta = 100^\circ\text{C}$

At  $f = 16$  kHz,  $\hat{B} \geq 90$  mT,  $\theta = 100^\circ\text{C}$   
 $\hat{B} \geq 315$  mT,  $\theta = 100^\circ\text{C}$


At  $f = 10$  kHz,  $\hat{B} \leq 0,1$  mT,  $\theta = 25^\circ\text{C}$

	EE42/42/20	EE42/54/20
P	$\leq 3,5$ W	$\leq 3,2$ W
P	$\leq 2,6$ W	$\leq 3,2$ W
$\hat{H}$	= 50 A/m	
$\hat{H}$	= 250 A/m	250 A/m
$A_L$	= $5000 \pm 25\%$	$3600 \pm 25\%$



## CHARACTERISTIC CURVES

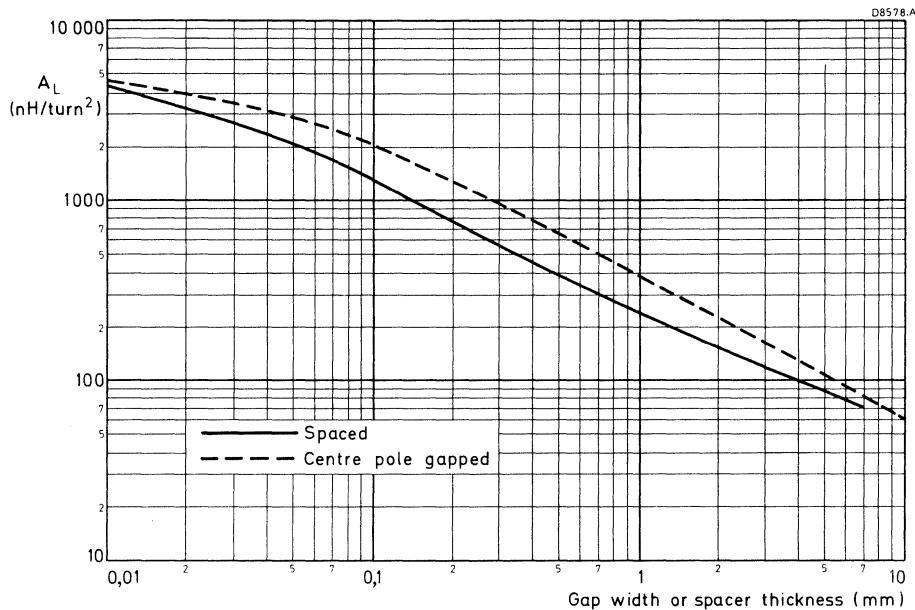


$A_L$  based on a typical initial permeability of 2000 as a function of spacer thickness.

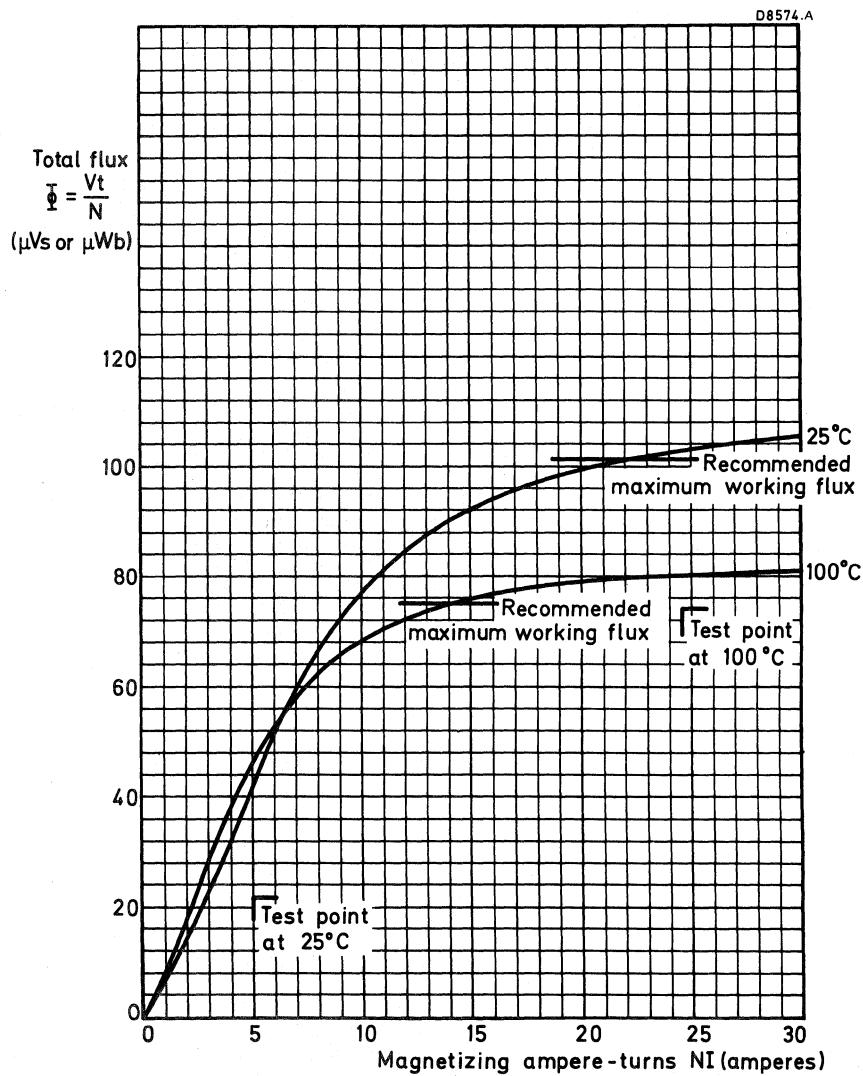


Typical magnetization curves for a pair of cores, in 3C8, with ambient temperature as parameter.

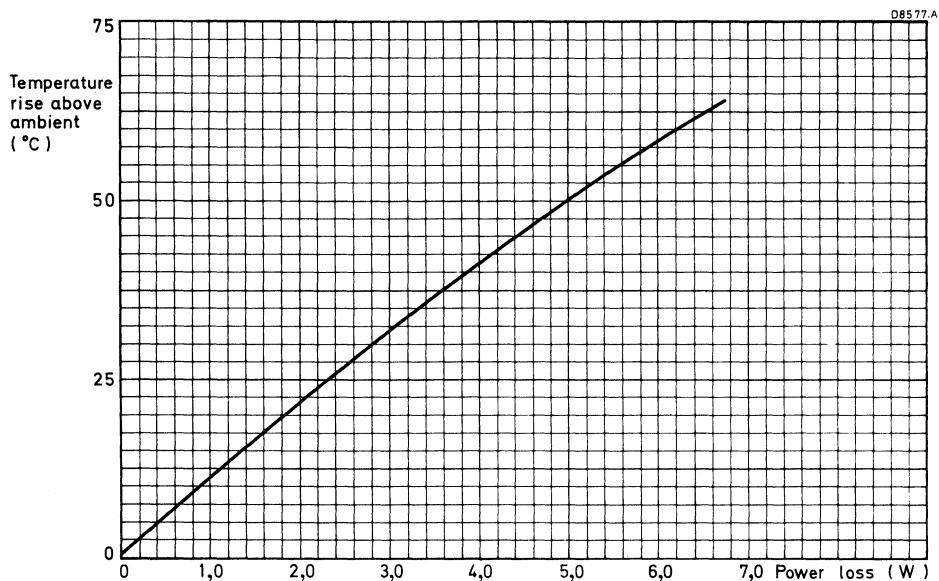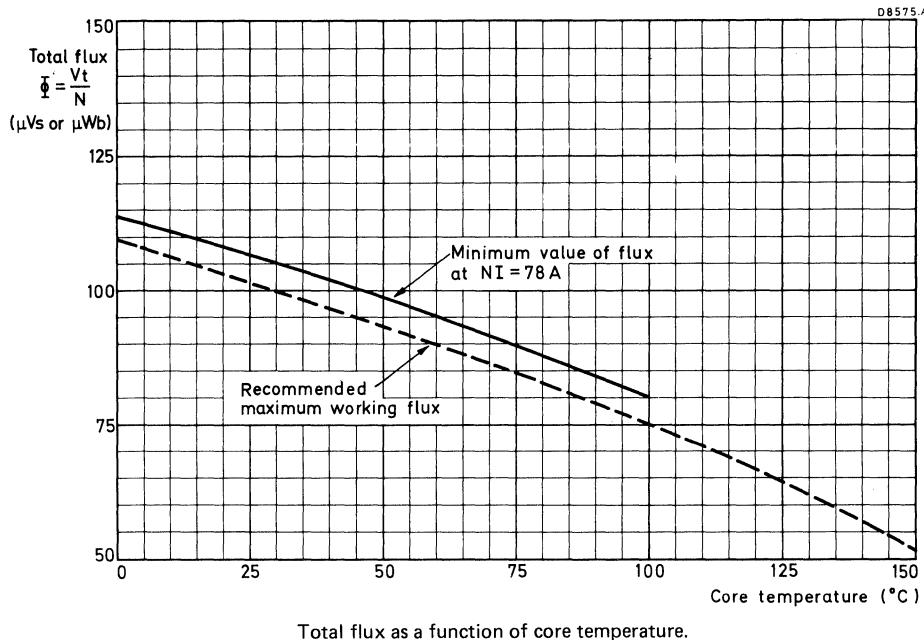

Typical transformer temperature rise as a function of total transformer loss in free air conditions.

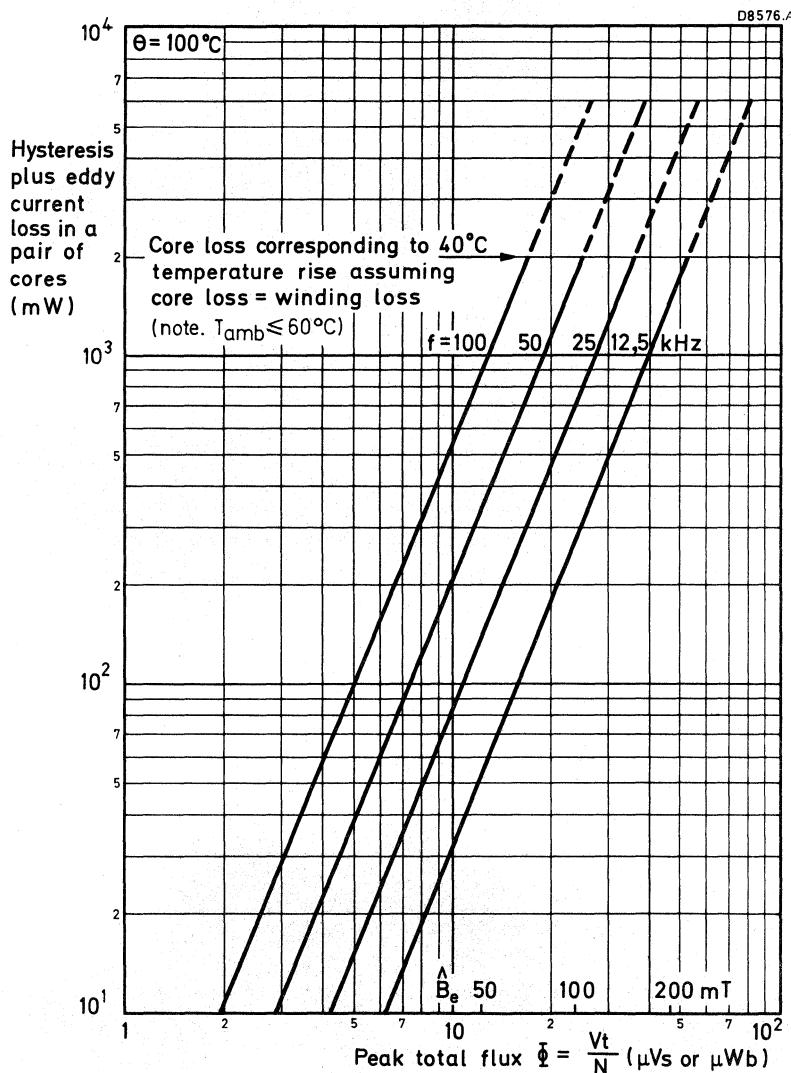


Core loss as a function of total flux at  $100^\circ\text{C}$  with frequency as parameter.

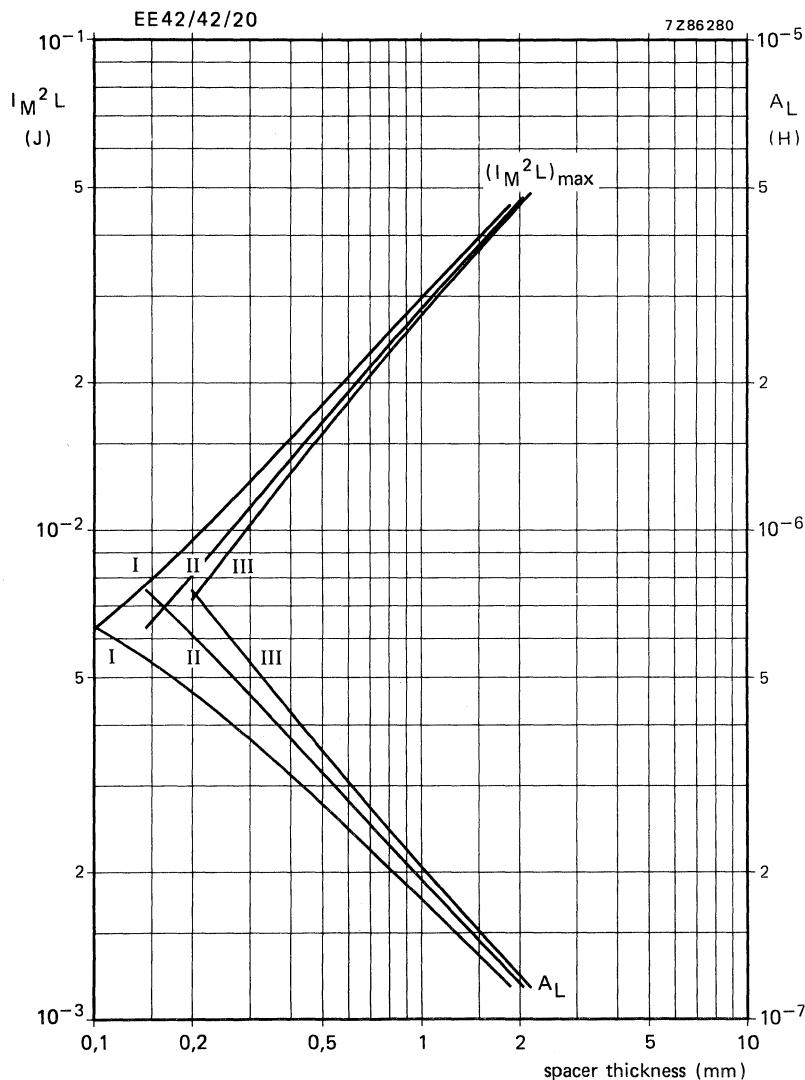


Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.

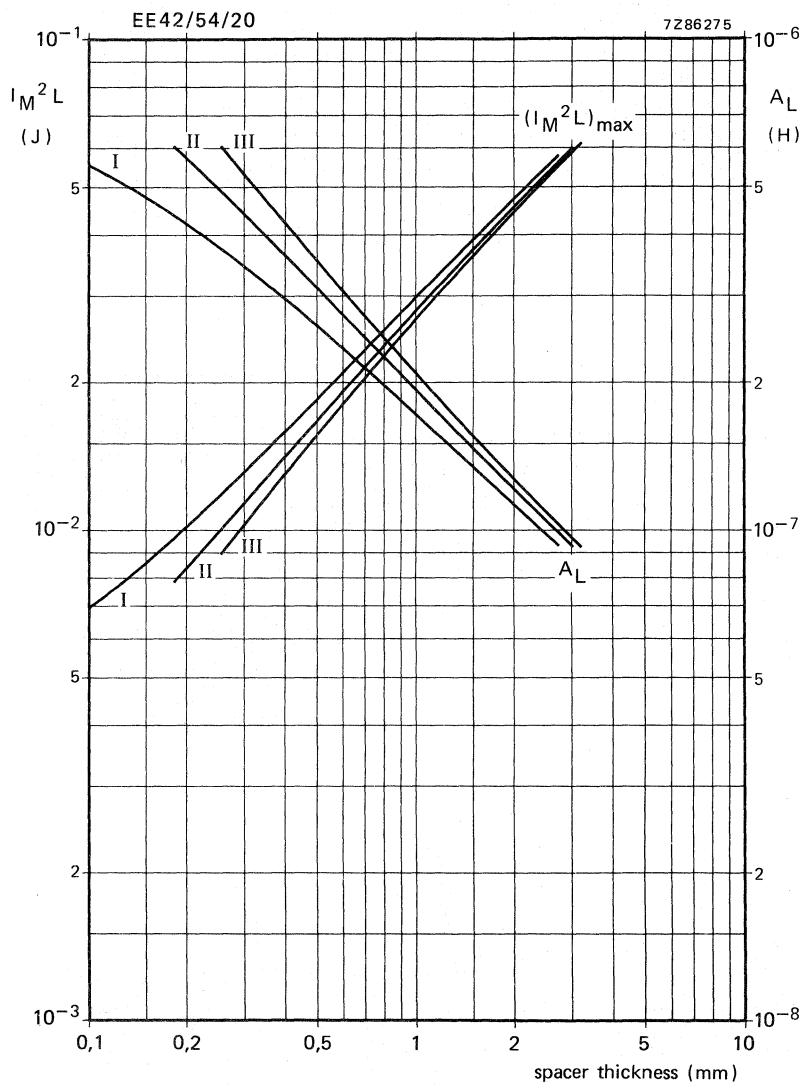


Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.

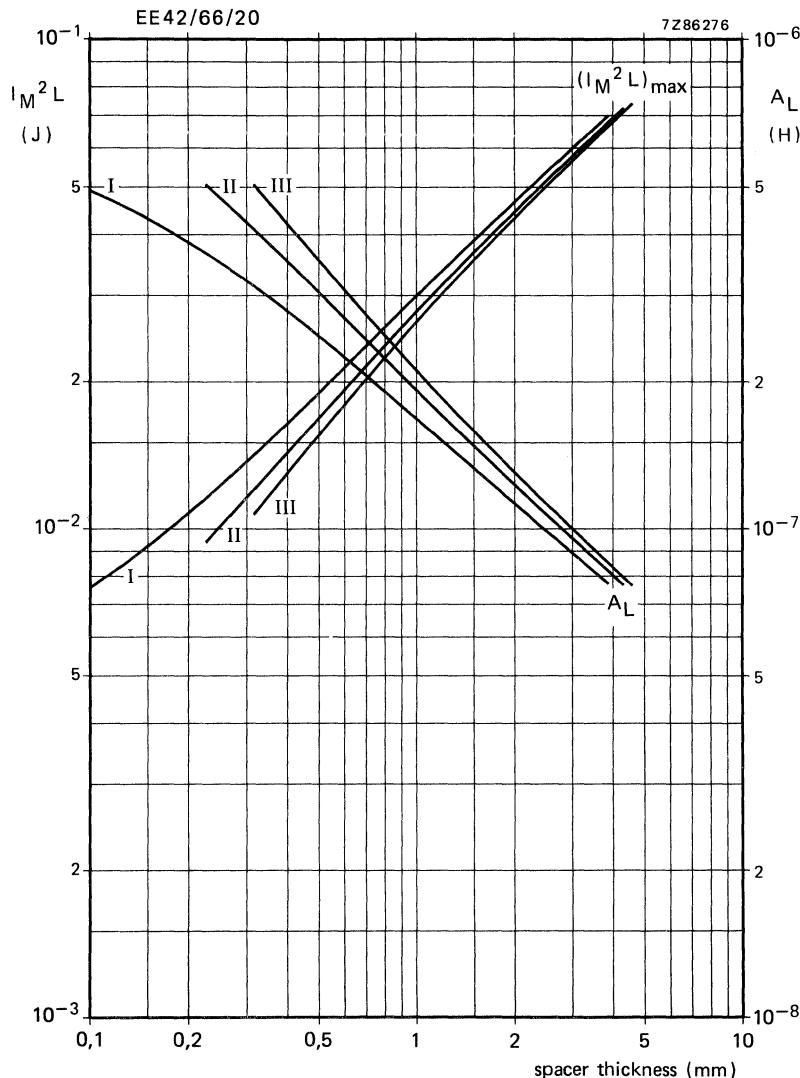


Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.

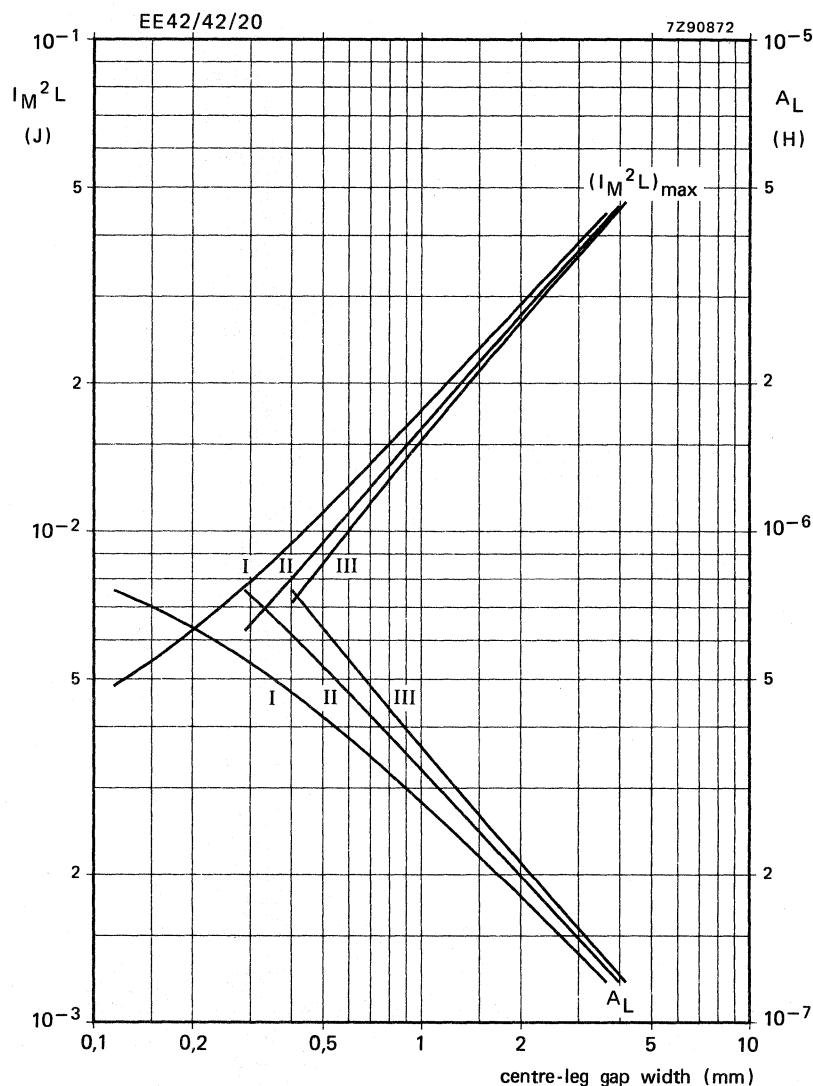


Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.

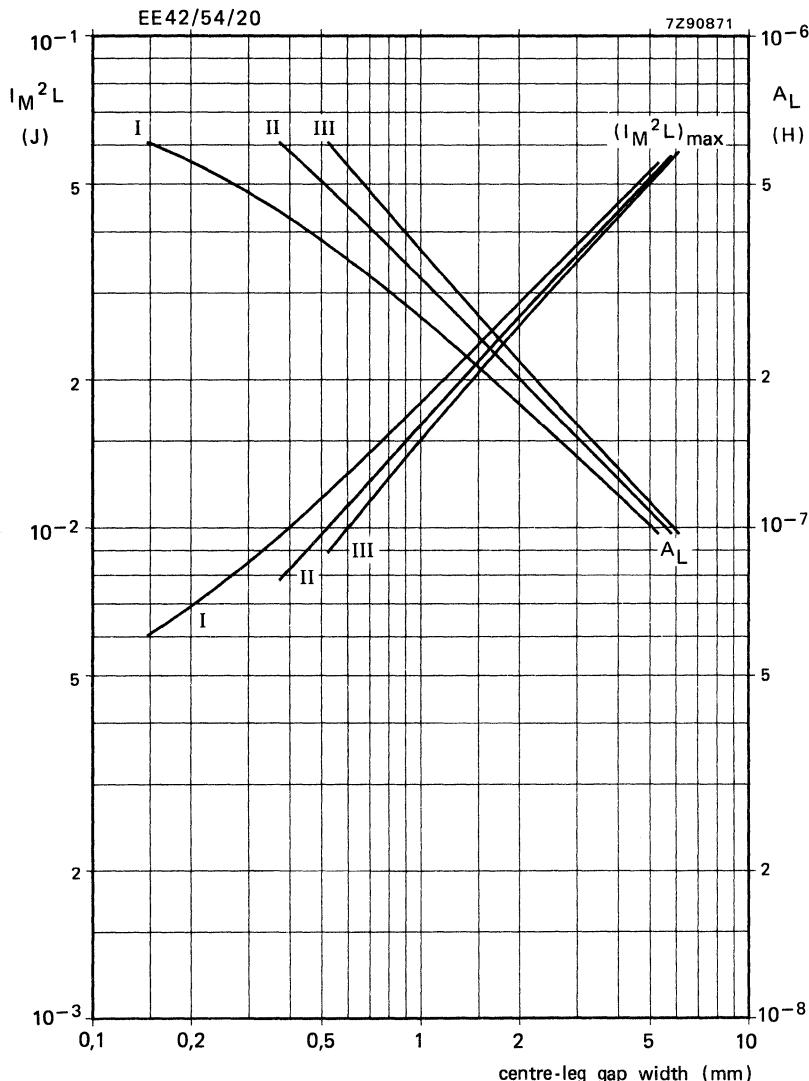

Choke design chart.


For application classes I, II and III see 'Power choke design' in the Introduction.

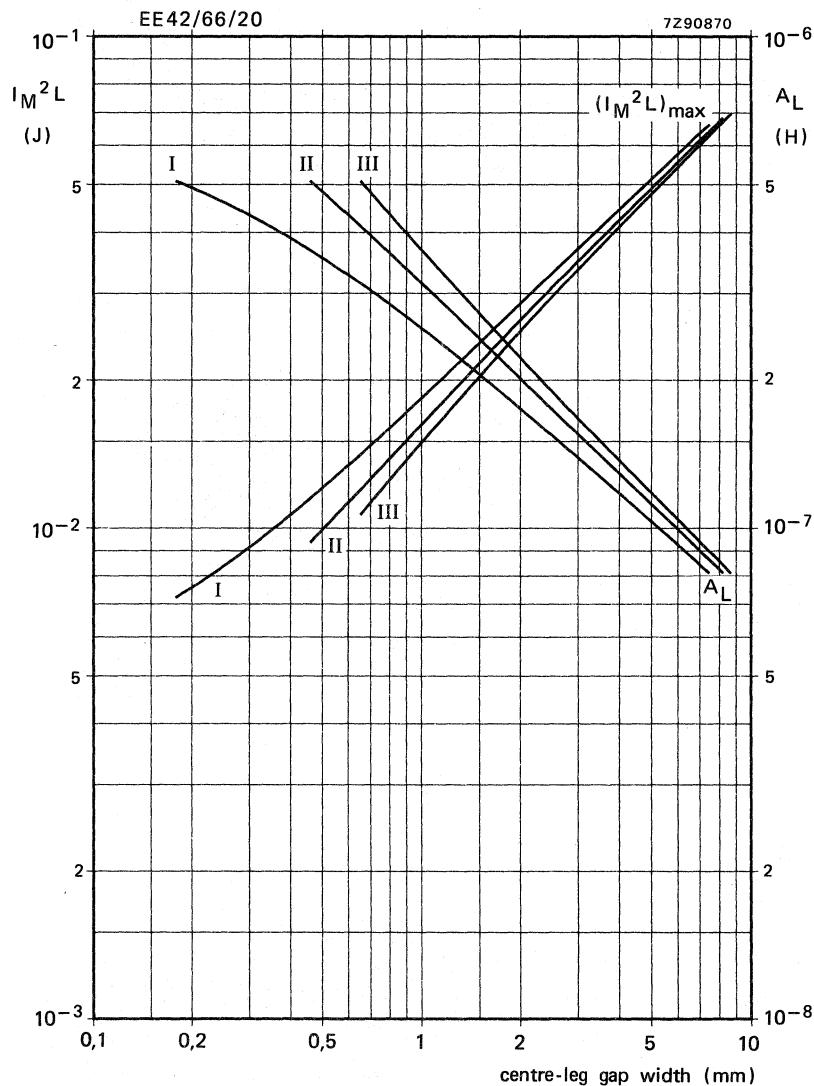

Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.

## E-CORES

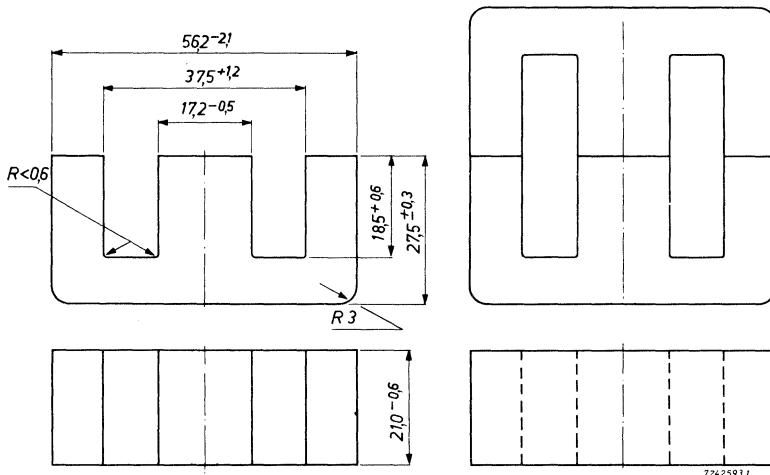

7242593/1

The dimensions are according to DIN 41295.

Mass               approx. 115 g

#### Catalogue numbers

Ferroxcube grade 3E1, no air gap\*  
Ferroxcube grade 3C8, no air gap\*

- 4322 020 34900
- 4312 020 34100

#### SHELL TYPE TRANSFORMER EE55/55/21

A transformer core can be built up by combining an even number of E-cores. A shape that is often chosen is the shell type transformer EE55/55/21 composed of two cores type EE55/28/21.

\* Cores with air gap are available on request.

● Preferred type.

Magnetic dimensions according to IEC 205:

$$l_e = 123 \text{ mm}$$

$$A_e = 354 \text{ mm}^2$$

$$C_1 = \sum \frac{l_e}{A_e} = 0,348 \text{ mm}^{-1}$$


$$V_e = 43700 \text{ mm}^3$$

### MAGNETIC DATA

Guaranteed values for a core pair EE55/55/21, pressed together with a force of 550 N, air gap  $\Delta = 0$ .

	freq. kHz	temp. °C	$\hat{B}$ mT	grade	
				3E1	3C8
→ AL	100	$25 \pm 10$		9545 to 14330	$6300 \pm 25\%$
$\mu_e$	100	$25 \pm 10$		2645 to 3970	
$\eta_B \times 10^3$	4	$25 \pm 10$	1,5 to 3	$\leq 2,5$	
P (W)	16	25	200		$\leq 5,5$
	16	100	200		$\leq 5,0$
$\hat{H}$ (A/m)	16	100	315		250

## CHARACTERISTIC CURVES

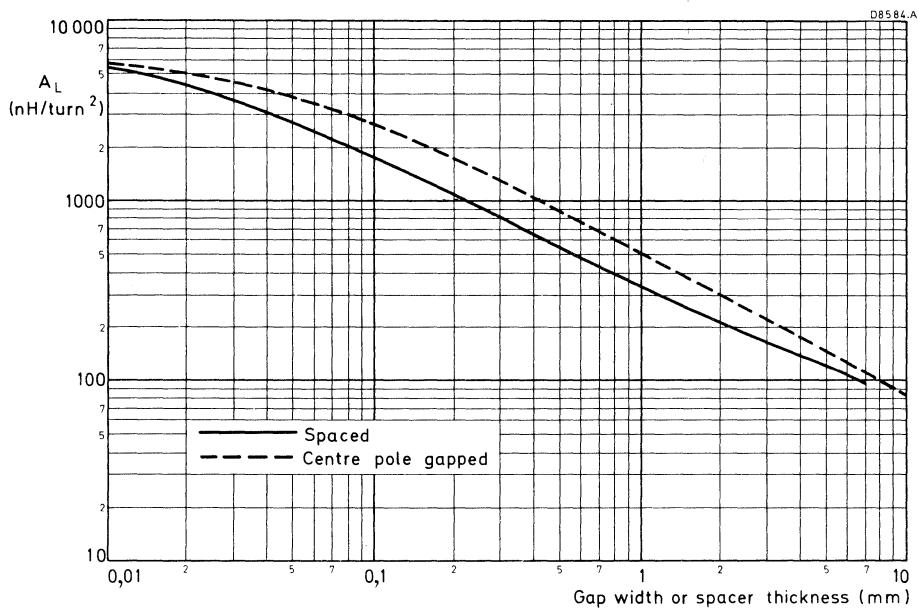

$A_L$  based on a typical initial permeability of 2000 as a function of spacer thickness.

D8580.A

Total flux  
 $\Phi = \frac{Vt}{N}$   
( $\mu$ Vs or  $\mu$ Wb)

200

150

100

50

0

0

10

20

30

40

Magnetizing ampere-turns NI (amperes)



25°C

100°C


Recommended  
maximum working flux


Test point  
at 100°C

Typical magnetization curves for a pair of cores with ambient temperature as parameter, FXC 3C8.

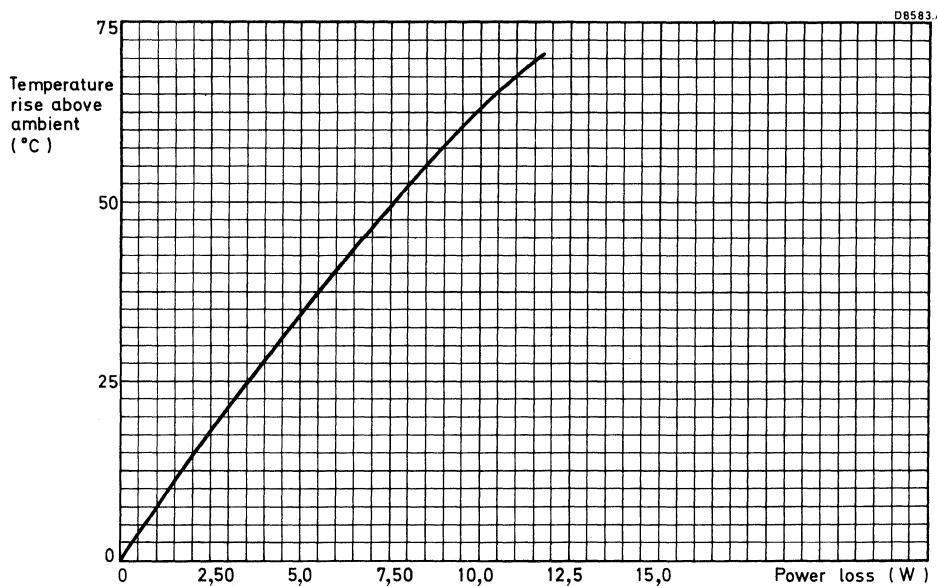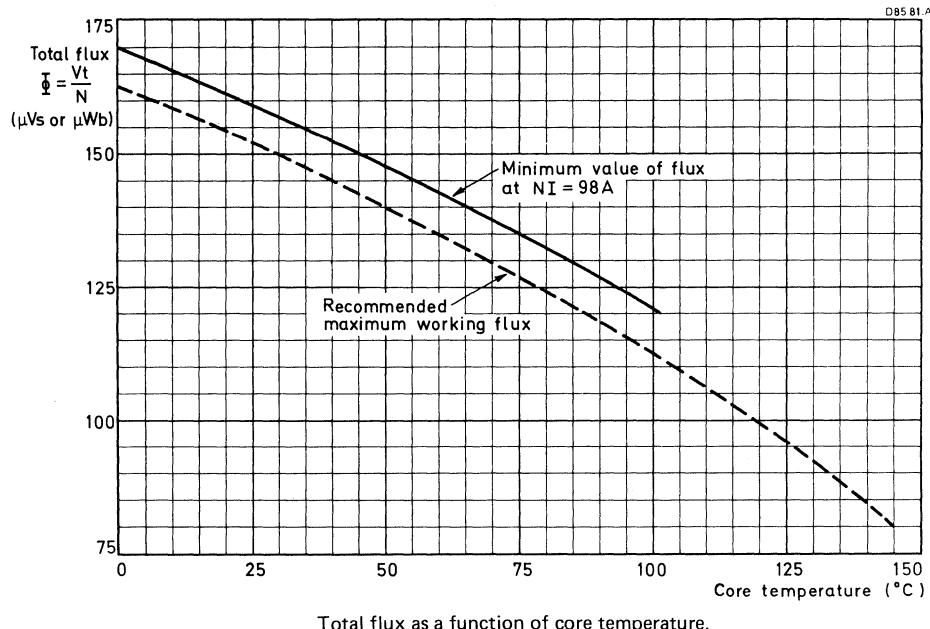


Typical transformer temperature rise as a function of total transformer loss in free air conditions.

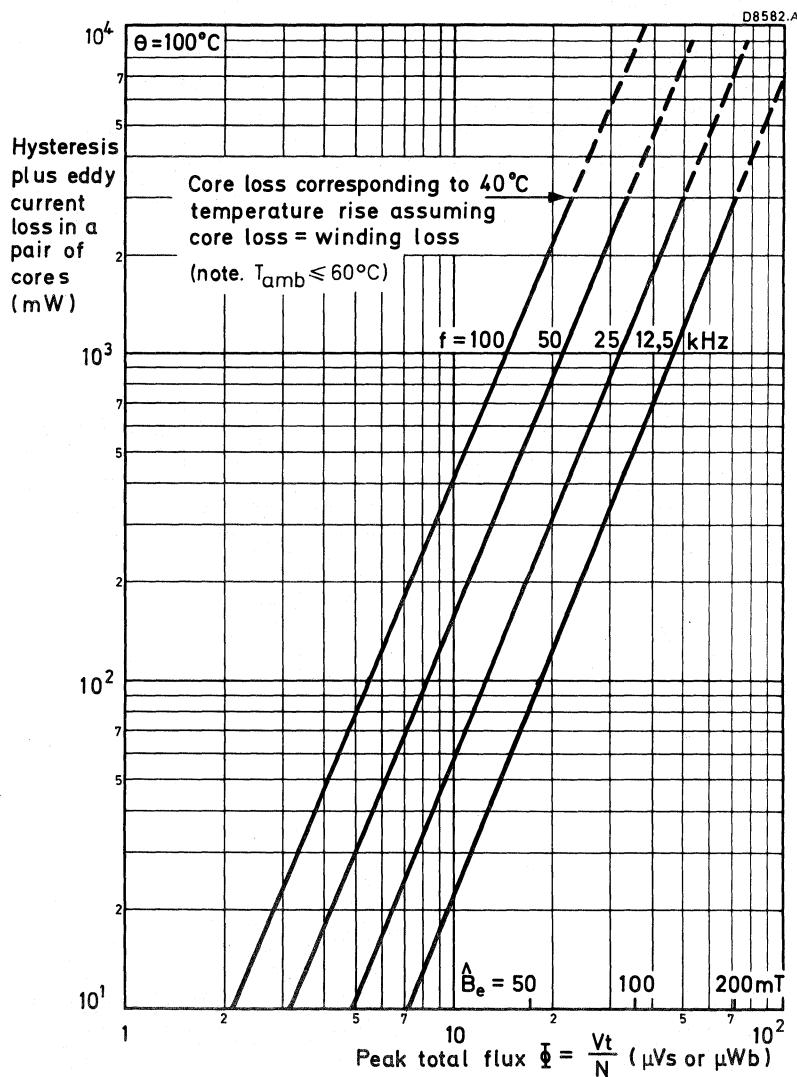Core loss as a function of total flux at  $100^\circ\text{C}$  with frequency as parameter, FXC 3C8.

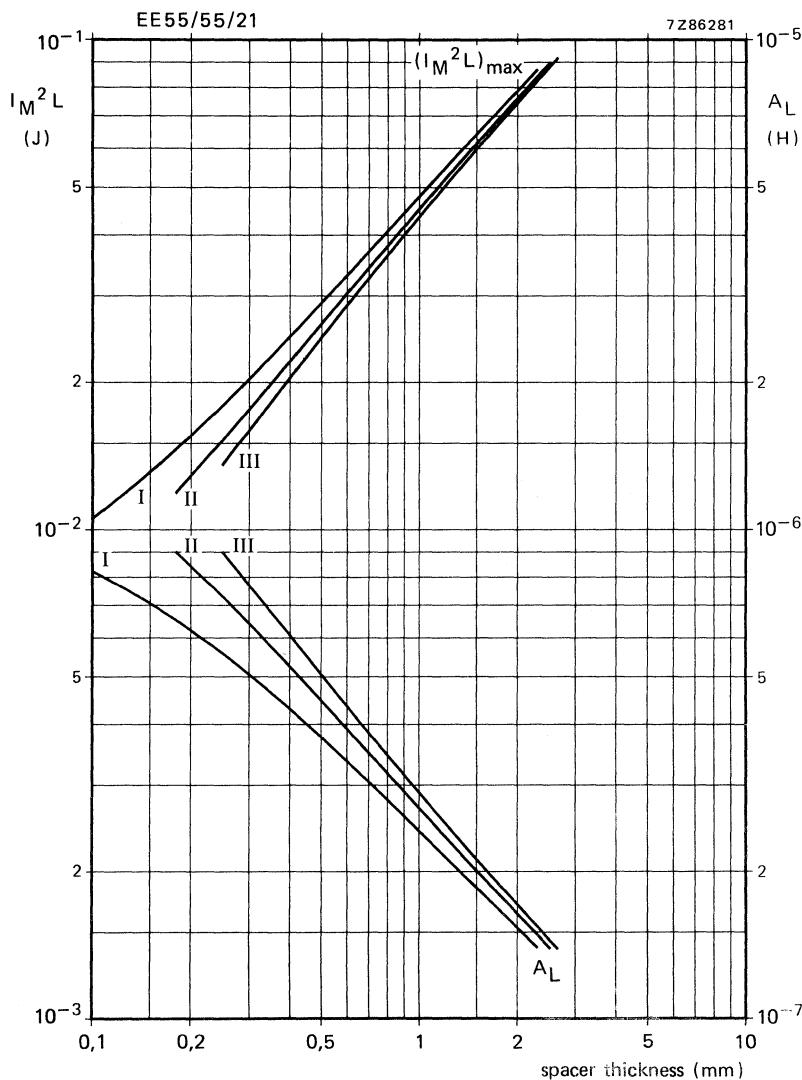

Choke design chart.

For application classes I, II and III see 'Power choke design' in the introduction.

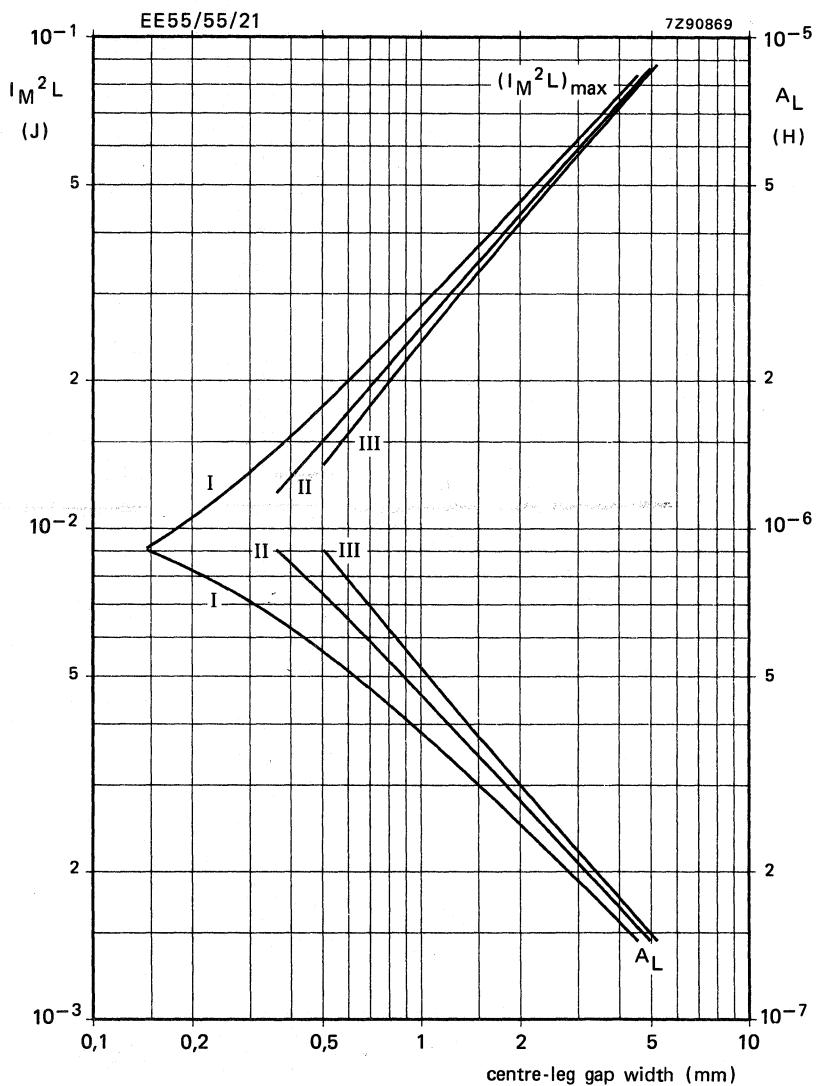


Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.

## COIL FORMER



for shell type transformer EE55/55/21

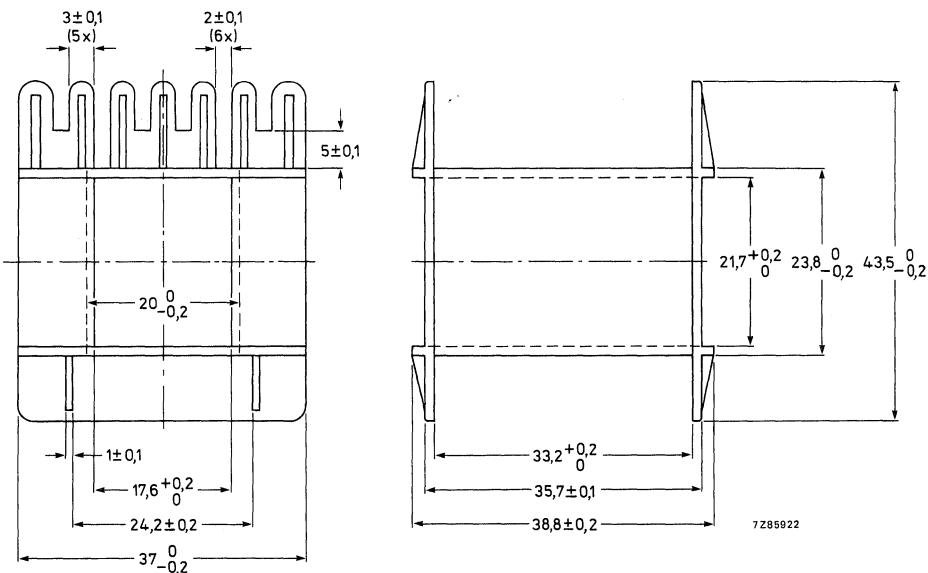

catalogue number	4312 021 28710
material	polyamide 6,6 glass fibre reinforced
minimum window area	250 mm <sup>2</sup>
mean length of turn	116 mm
approximate mass	9 g
maximum working temperature	130 °C


The dimensions are according to German specification DIN 41305.

## MOUNTING PARTS

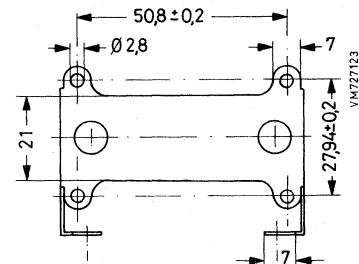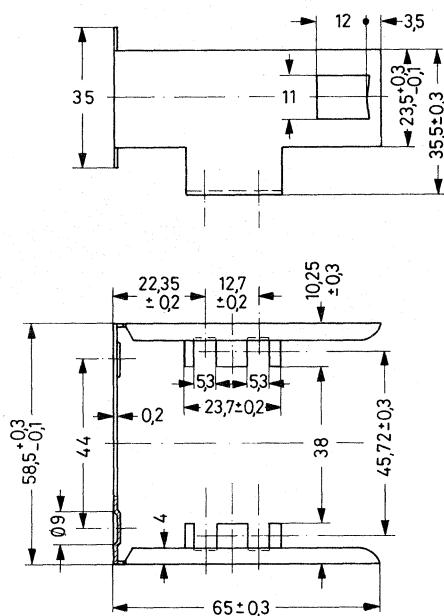

Clasp.





Material: zinc plated steel, bichromated.  
Catalogue number: 4312 021 26090

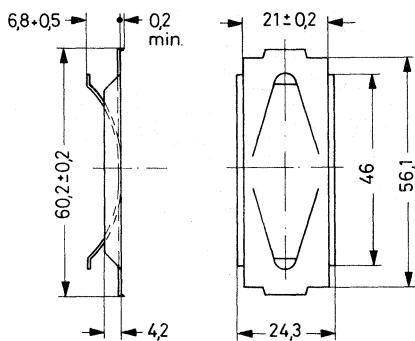

Spring.

Material: zinc plated stainless steel, bichromated.  
Catalogue number: 4312 021 26130

## E-CORES

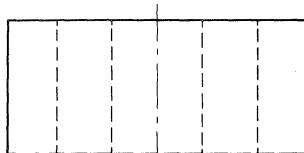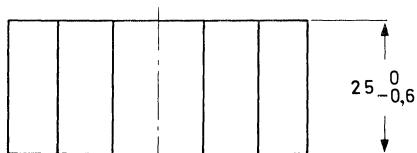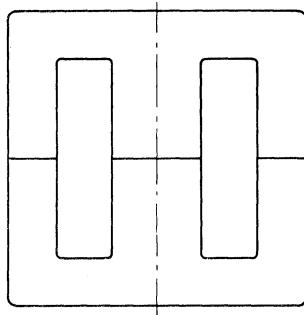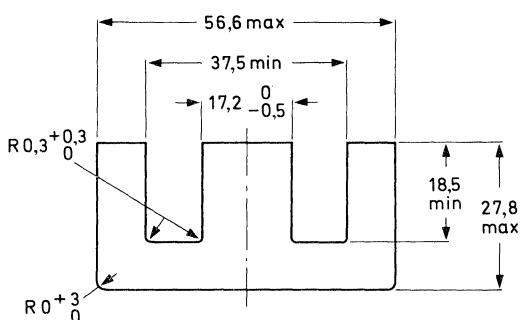

Mass approx. 130 g

7270933

#### Catalogue numbers

Ferrocube grade 3C8

Catalogue number of E-core without air gap\*

3122 134 90210

#### SHELL TYPE TRANSFORMER EE55/55/25

A transformer core can be built up by combining an even number of E-cores. A shape that is often chosen is the shell type transformer EE55/55/25 composed of two cores type EE55/28/25.

Magnetic dimensions according to IEC 205:

$$l_e = 123 \text{ mm}$$

$$A_e = 420 \text{ mm}^2$$

$$C_1 = \sum \frac{l_e}{A_e} = 0,293 \text{ mm}^{-1}$$

$$V_e = 52000 \text{ mm}^3$$

#### Magnetic properties; $\Delta = 0$

At  $f = 16 \text{ kHz}$ ,  $B = 200 \text{ mT}$ ,  $\theta = 25^\circ\text{C}$

$$\theta = 100^\circ\text{C}$$

At  $f = 16 \text{ kHz}$ ,  $B \geq 315 \text{ mT}$ ,  $\theta = 100^\circ\text{C}$


$$P \leq 6,2 \text{ W}$$

$$P \leq 5,7 \text{ W}$$



$$H = 250 \text{ A/m}$$

\* Cores with air gap are available on request.


## CHARACTERISTIC CURVES

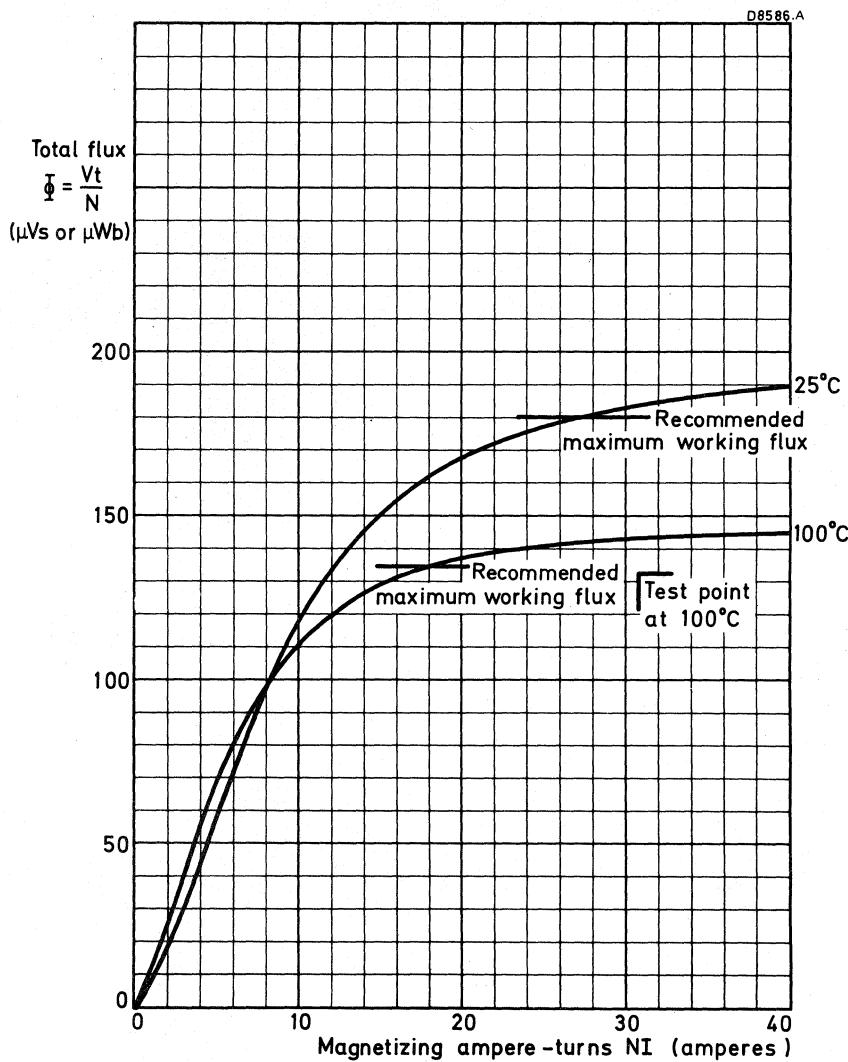


Typical magnetization curves for a pair of cores with ambient temperature as parameter.

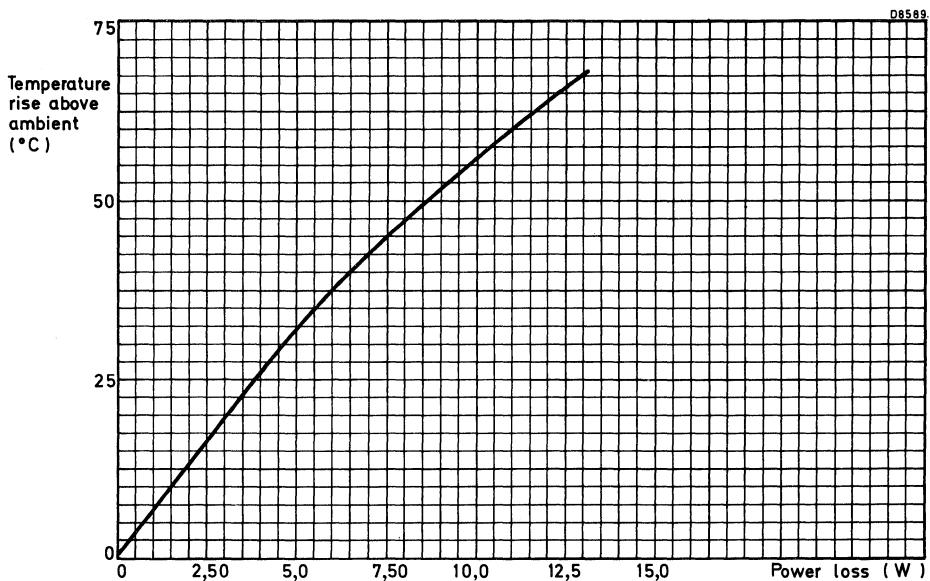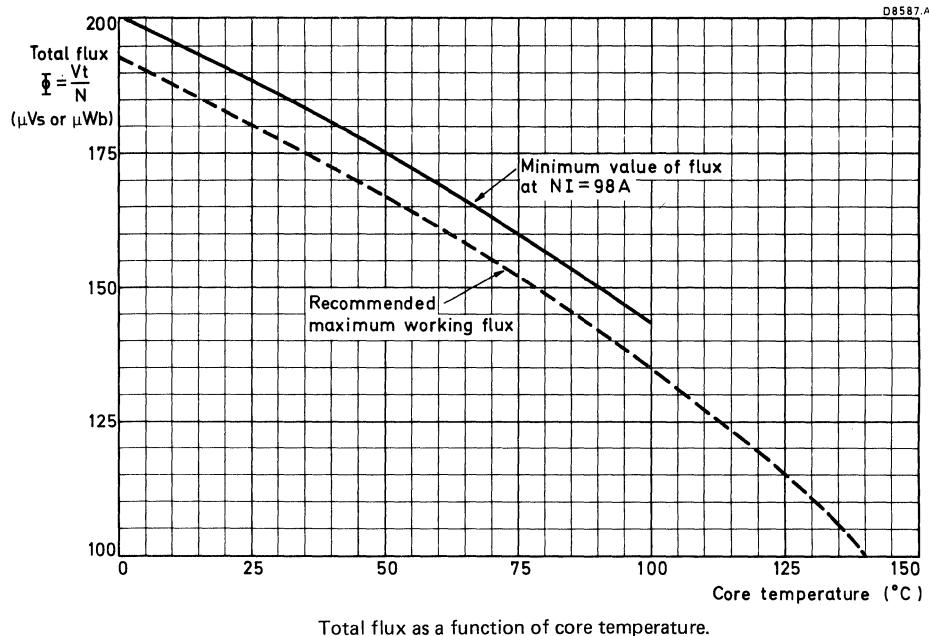


Typical transformer temperature rise as a function of total transformer loss in free air conditions.

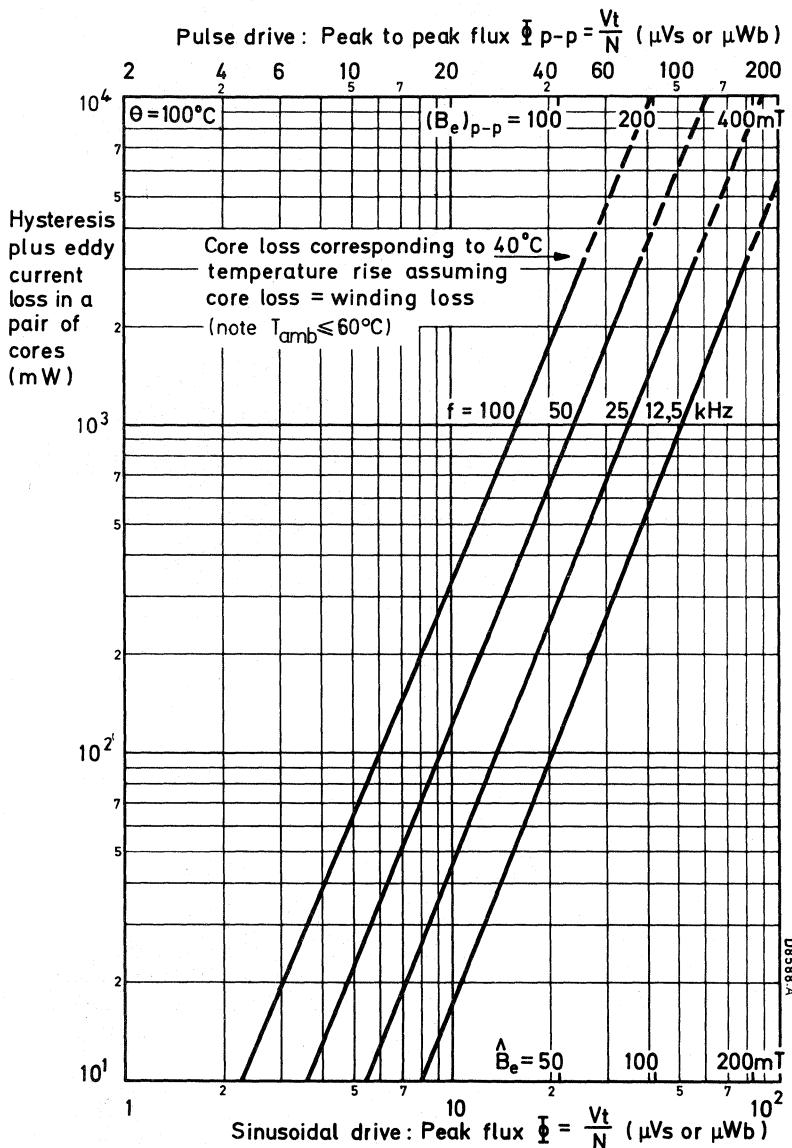

Core loss as a function of total flux at  $100^\circ C$  with frequency as parameter.

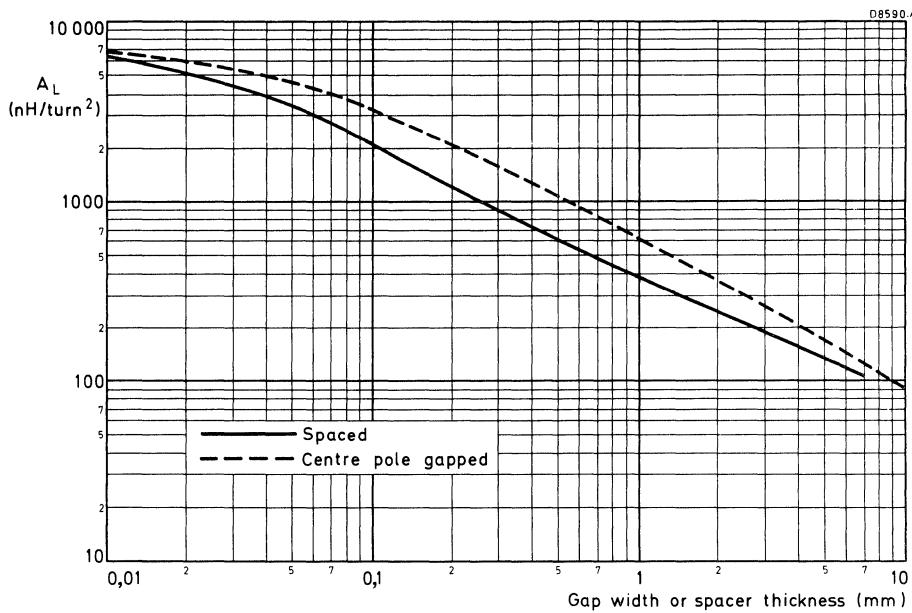


$A_L$  based on a typical permeability of 2000 as a function of spacer thickness.

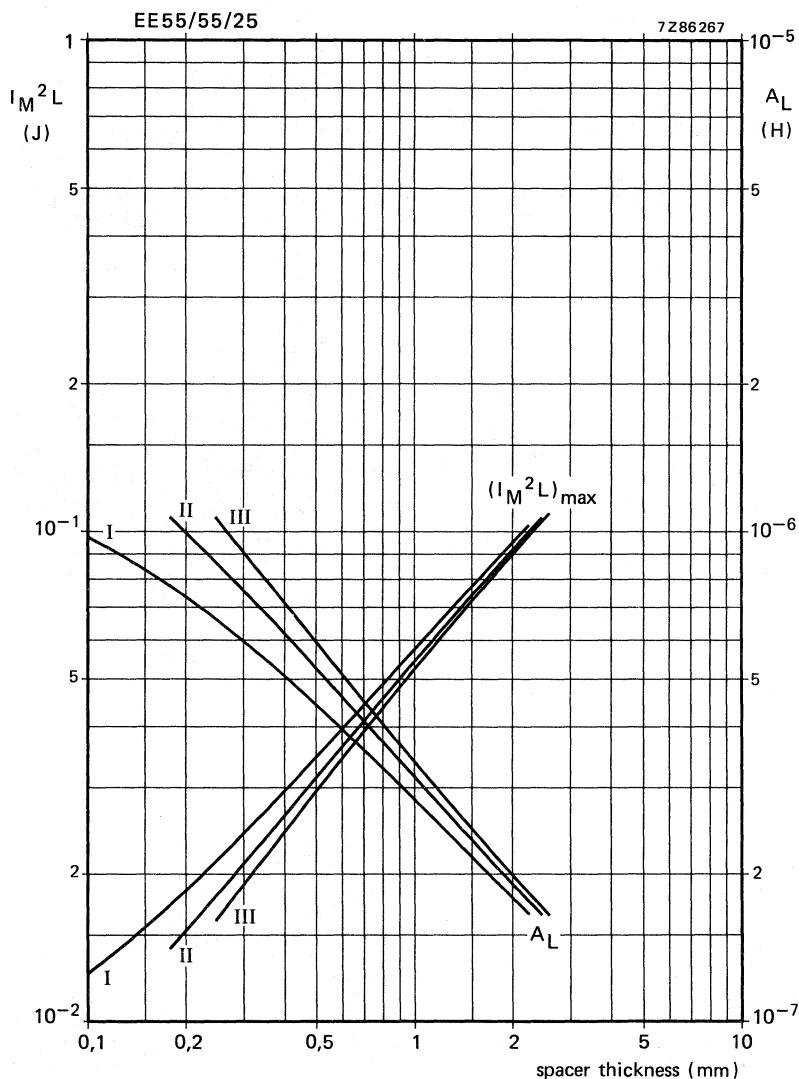

Choke design chart.



For application classes I, II and III see 'Power choke design' in the Introduction.

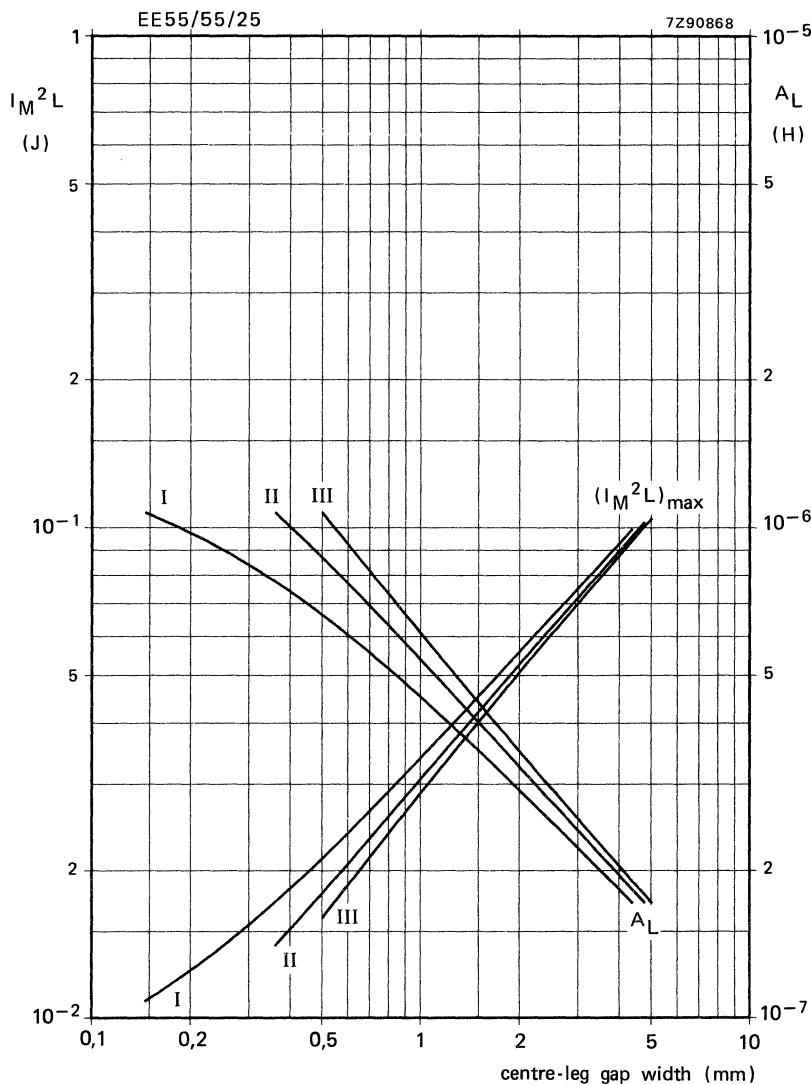

Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.

## E-CORES

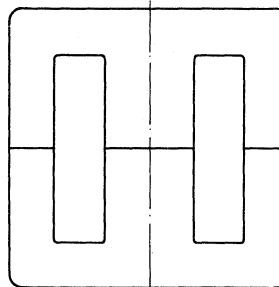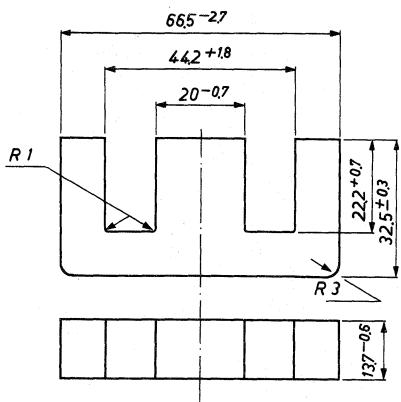

7242082

The dimensions are according to DIN 41295

Mass approx. 103 g

#### Catalogue number

Ferroxcube grade 3E1

Catalogue number of E-core • 4322 020 34910

#### SHELL TYPE TRANSFORMER 65/65/27

A transformer core can be built up by combining an even number of E-cores. A shape that is often chosen is the shell type transformer 65/65/27 composed of four cores type E65/32/13.

Magnetic dimensions according to IEC 205:

$$l_e = 147 \text{ mm}; A_e = 532 \text{ mm}^2; C_1 = \sum \frac{l_e}{A_e} = 0,275 \text{ mm}^{-1}; V_e = 78200 \text{ mm}^3$$

#### MAGNETIC DATA





Guaranteed values for a combination of four E-cores, pressed together with a force of 400 N, air gap  $\Delta = 0$ . \*

	freq. kHz	temp. °C	$\hat{B}$ mT	
$A_L$	100	$25 \pm 5$		12355 to 18545
$\mu_e$	100	$25 \pm 5$		2705 to 4060
$\eta_B \times 10^3$	4	$25 \pm 5$	1,5 to 3	$\leq 4,3$

\* Cores with air gap are available on request.

• Preferred type.

## E-CORES

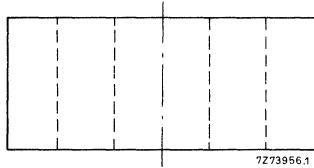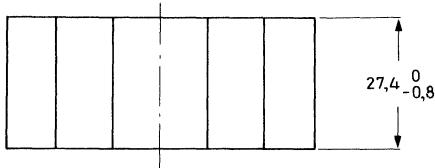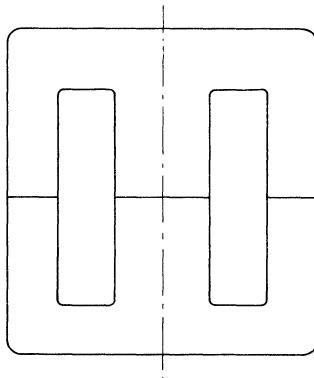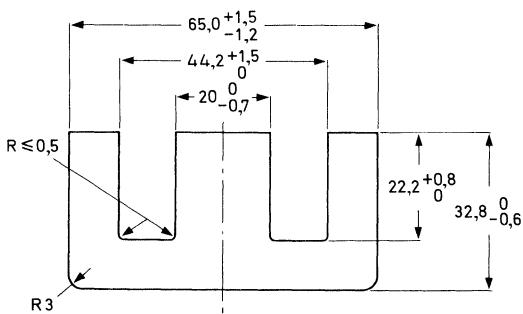

Mass

approx. 203 g

Ferroxcube grade

3C8

Catalogue number of E-core, without air gap\*

• 4312 020 34380

## SHELL TYPE TRANSFORMER EE65/66/27

A transformer core can be built up by combining an even number of E-cores. A shape that is often chosen is the shell type transformer EE65/65/27 composed of two cores type E65/32/27.

Magnetic dimensions according to IEC 205:

$$l_e = 147 \text{ mm}$$

$$A_e = 532 \text{ mm}^2$$

$$C_1 = \sum \frac{l_e}{A_e} = 0,275 \text{ mm}^{-1}$$

$$V_e = 78200 \text{ mm}^3$$

**Magnetic properties;  $\Delta = 0$**

At  $f = 16 \text{ kHz}$ ,  $\hat{B} = 200 \text{ mT}$ ,  $\theta = 25^\circ\text{C}$   
 $\theta = 100^\circ\text{C}$

$$\begin{aligned} P &\leqslant 9,5 \text{ W} \\ P &\leqslant 8,7 \text{ W} \\ \hat{H} &= 250 \text{ A/m} \end{aligned}$$

At  $f = 16 \text{ kHz}$ ,  $\hat{B} \geq 315 \text{ mT}$ ,  $\theta = 100^\circ\text{C}$

At  $f = 10 \text{ kHz}$ ,  $\hat{B} \leq 0,1 \text{ mT}$ ,  $\theta = 25^\circ\text{C}$


$$A_L = 8000 \begin{array}{l} +30\% \\ -20\% \end{array}$$

\* Cores with air gap are available on request.



● Preferred type.

## CHARACTERISTIC CURVES


Note: The curves shown on the following pages represent typical characteristics for a pair of E65 cores in 3C8.

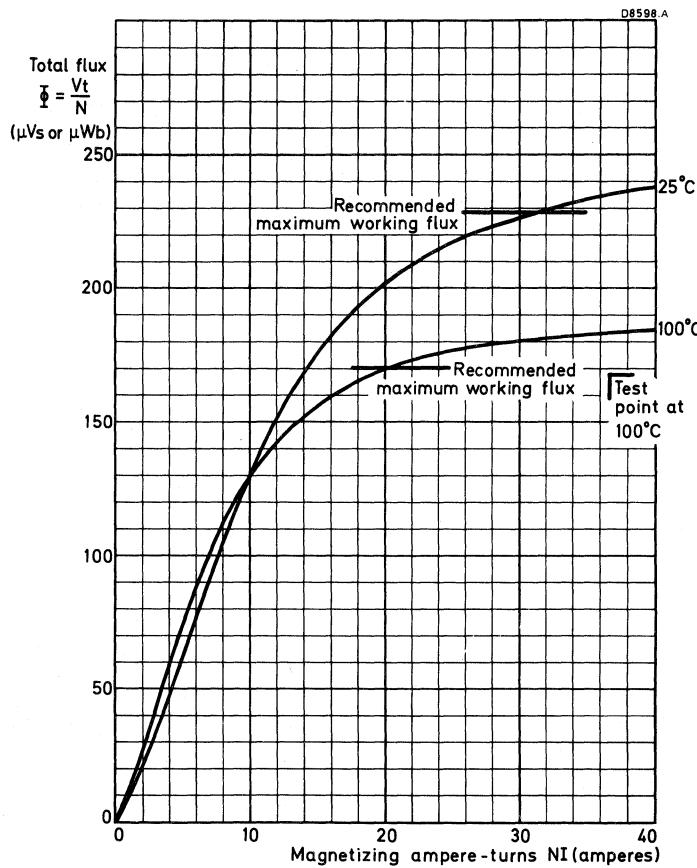


Typical magnetization curves for a pair of cores with ambient temperature as a parameter.

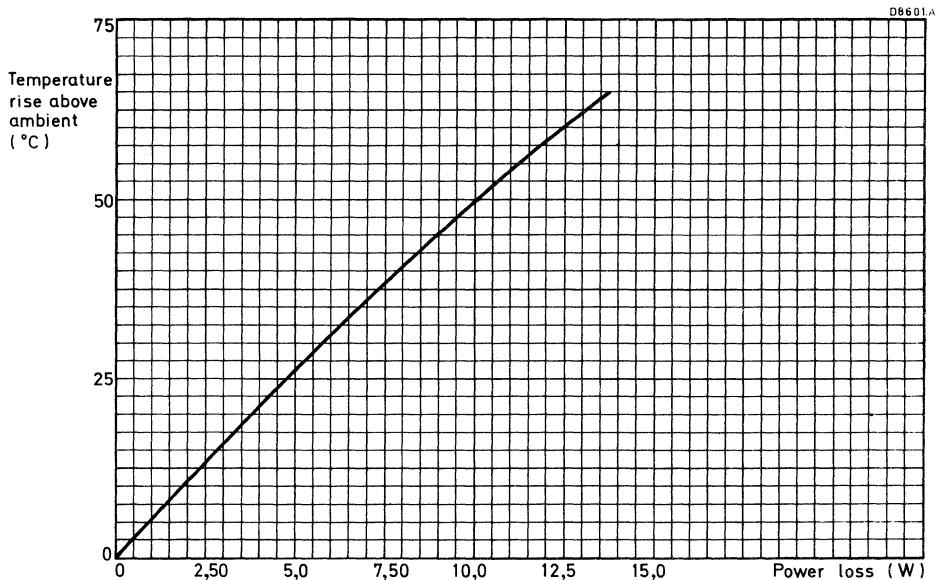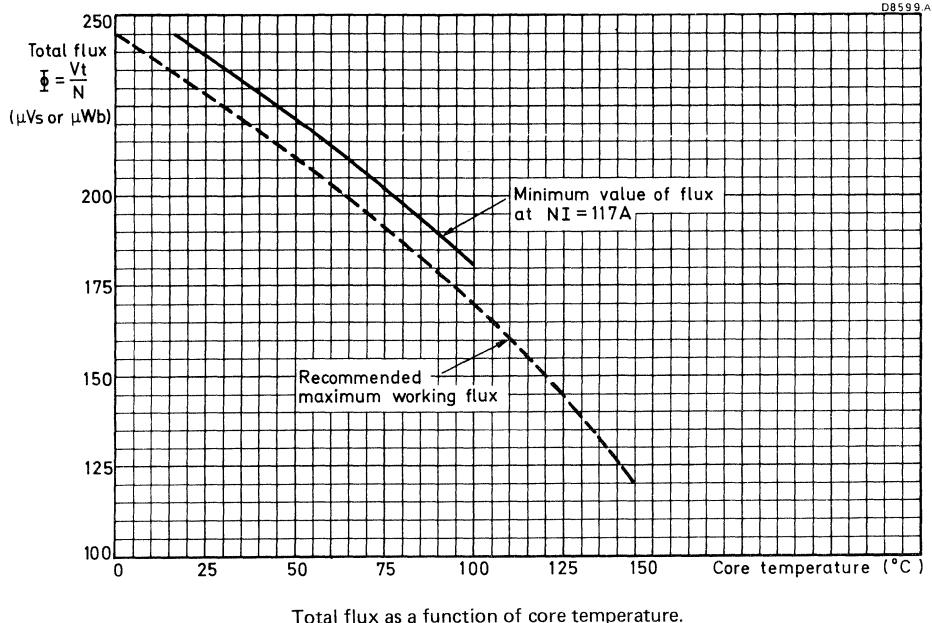


Typical transformer rise as a function of total transformer loss in free air conditions.

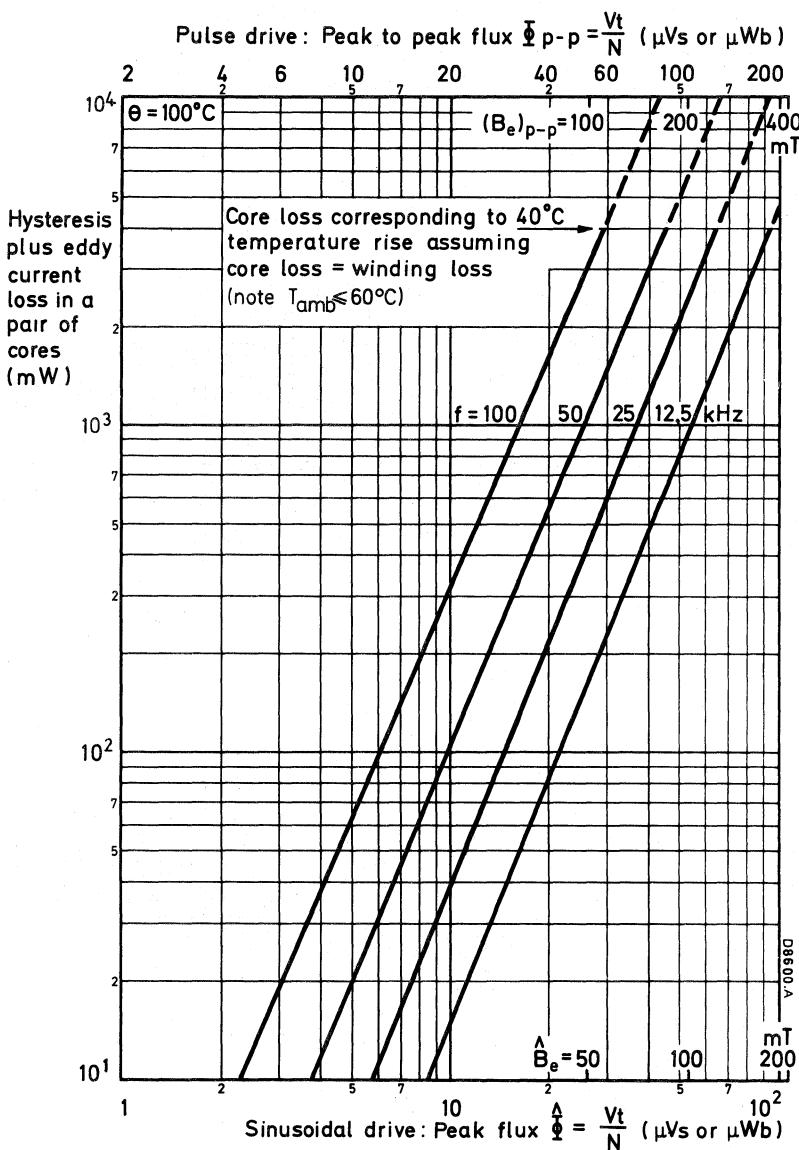

Core loss as a function of total flux at  $100^\circ C$  with frequency as parameter.

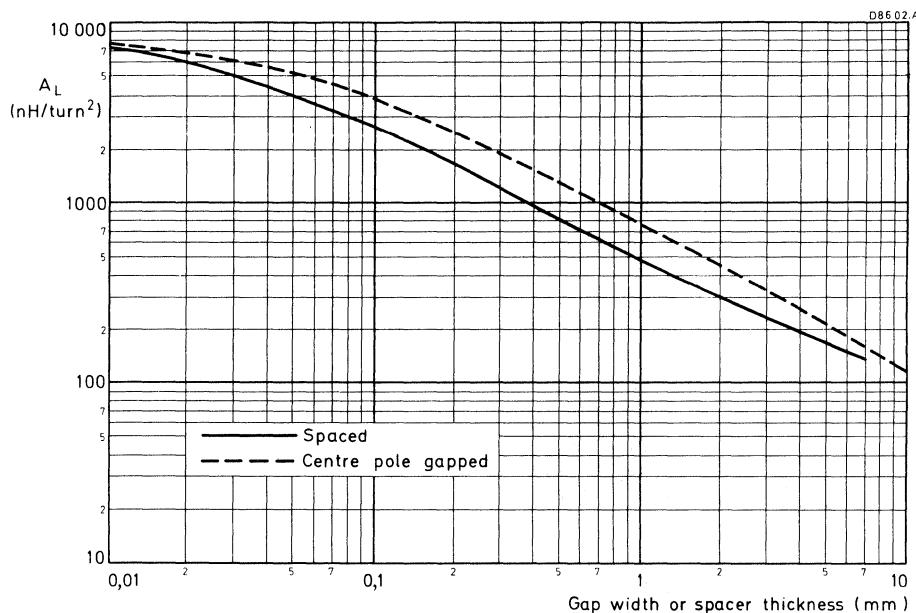


$A_L$  based on a typical initial permeability of 2000 as a function of spacer thickness.

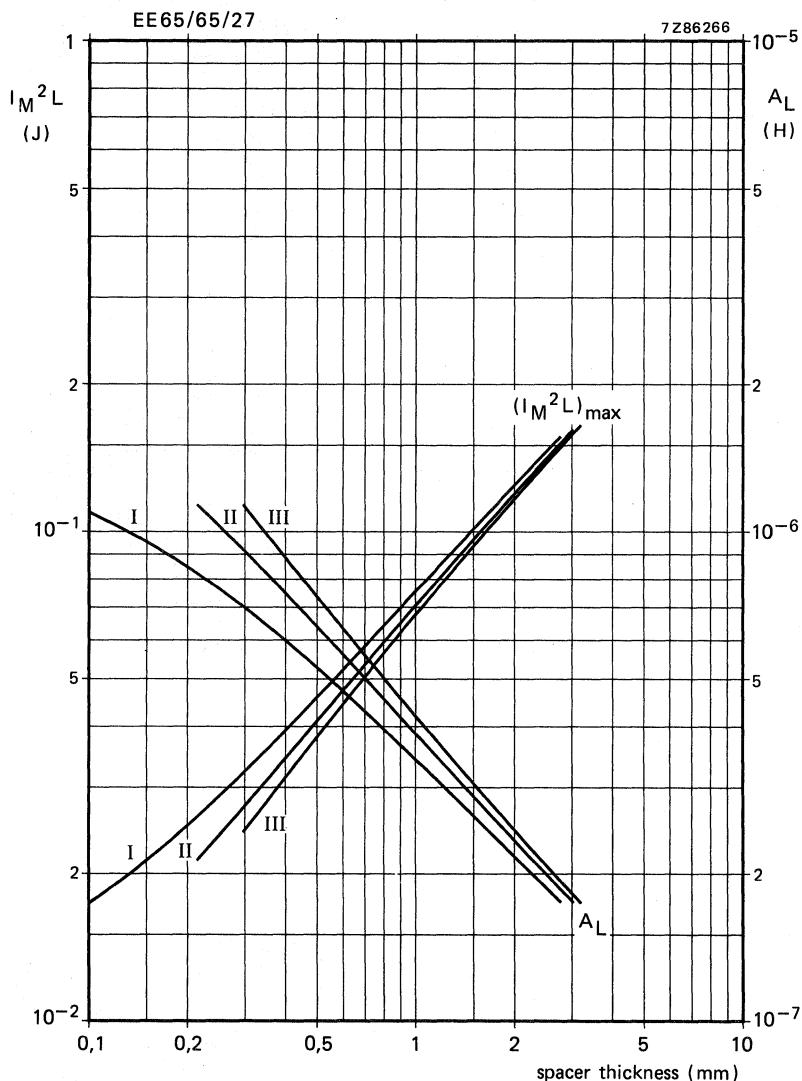

Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.

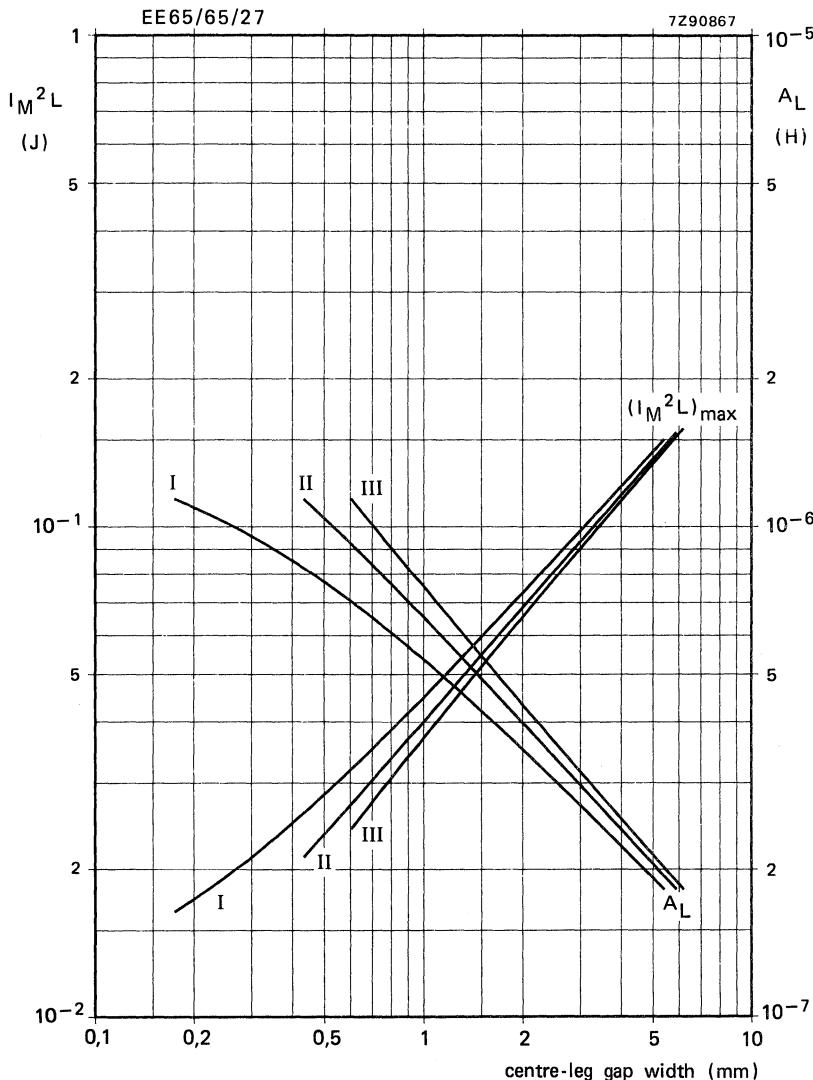


Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.



## COIL FORMER



for shell type transformer 65/65/27 (M65)

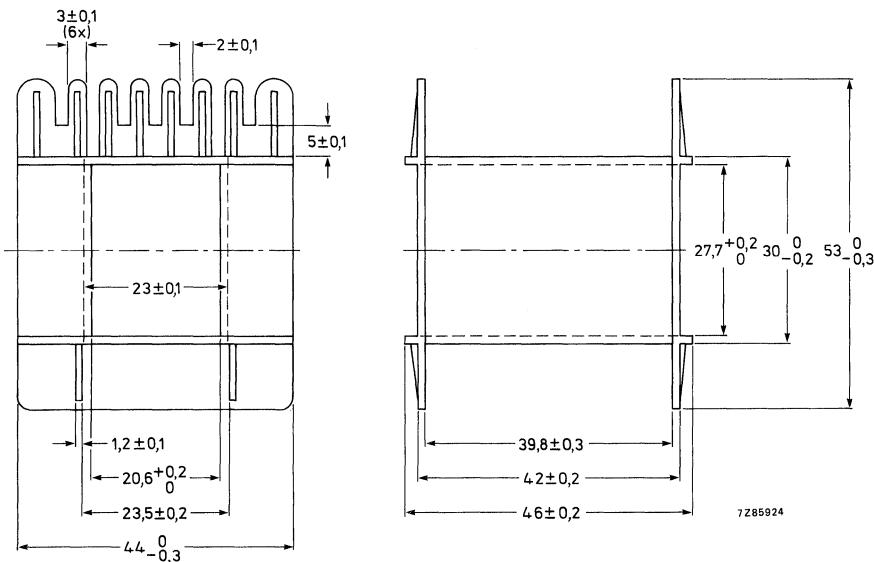

catalogue number	4312 021 28720
material	polyamide 6,6 glass fibre reinforced
minimum window area	394 mm <sup>2</sup>
mean length of turn	150 mm
approximate mass	13 g
maximum working temperature	130 °C


The dimensions are according to German specification DIN 41305.

## MOUNTING PARTS

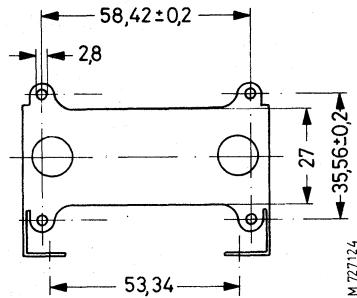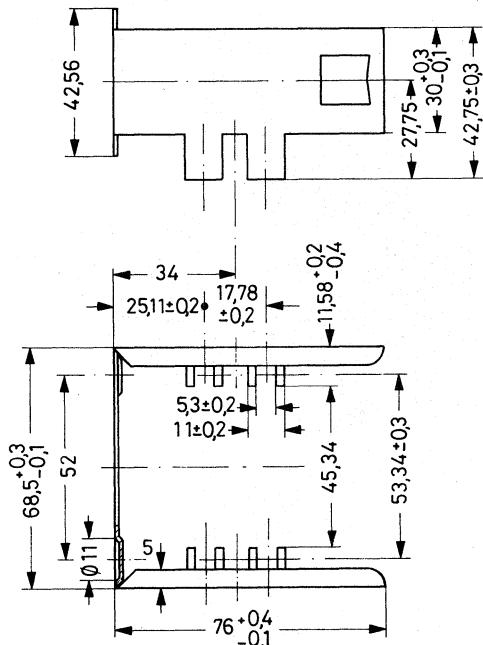

Clasp.


Material: zinc plated steel, bichromated.  
Catalogue number: 4312 021 26110

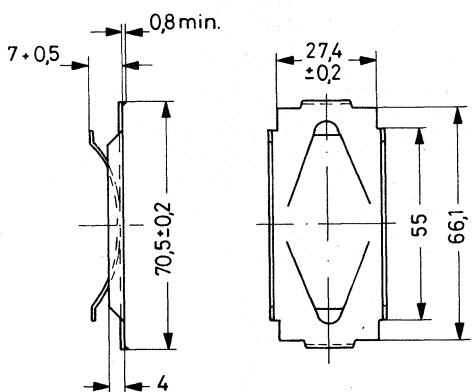

Spring.

Material: zinc plated stainless steel,  
bichromated.  
Catalogue number: 4312 021 26140

## EC-CORE

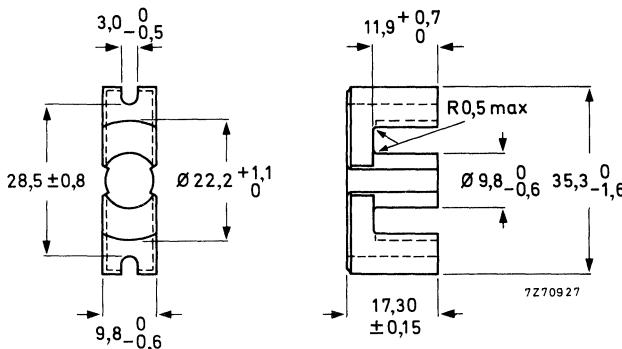

Mass

approx. 18 g

Ferrocube grade

3C8

Catalogue number of EC-core without air gap\*

● 4322 020 52500

## DIMENSIONAL PARAMETERS FOR A PAIR OF CORES

(Assuming nominal dimensions, unless otherwise stated).

Core constant\*\*

$$C_I = 0,918 \text{ mm}^{-1}$$

Minimum cross-sectional centre pole area

$$A_{CPmin} = 66,5 \text{ mm}^2$$

Cross-sectional centre pole area

$$A_{min} = 71,0 \text{ mm}^2$$

Back and leg cross-sectional area

$$A_b = 96,0 \text{ mm}^2$$

Centre pole volume

$$V_{CP} = 1740 \text{ mm}^3$$

Back and leg volume

$$V_b = 6040 \text{ mm}^3$$

Total core volume

$$V_f = 7780 \text{ mm}^3$$

Effective magnetic path length\*\*

$$l_e = 77,4 \text{ mm}$$

Effective cross-sectional area\*\*

$$A_e = 84,3 \text{ mm}^2$$

Effective core volume\*\*

$$V_e = 6530 \text{ mm}^3$$

\* Cores with air gap are available on request.

\*\* According to IEC 205.

● Preferred type.


**MAGNETIC PROPERTIES FOR A PAIR OF CORES WITHOUT AIR GAP**Relative amplitude permeability ( $\mu_a$ )at  $\theta = 100^\circ\text{C}$ ,  $\hat{B} = 320 \text{ mT}$  in  $A_{CP\min}$  $> 1000$ Permissible induction in centre pole ( $\hat{B}$ )with min. cross-sectional area, at  $\theta = 100^\circ\text{C}$  $\leq 320 \text{ mT}$ Resistivity ( $\rho$ ), measured with d.c. current $\geq 1 \Omega\text{m}$ 

Curie point

 $\geq 200^\circ\text{C}$ Effective total core loss ( $P$ ) referred to  $A_e$ at  $f = 25 \text{ kHz}$ ,  $\theta = 100^\circ\text{C}$ ,  $\hat{B} = 160 \text{ mT}$  $\leq 1,1 \text{ W}$ Inductance factor  $A_L$  at→  $f < 10 \text{ kHz}$ ,  $\theta = 25^\circ\text{C}$ ,  $\hat{B} < 0,1 \text{ mT}$   $2100 \pm 25\%$

## COIL FORMERS

Style 1

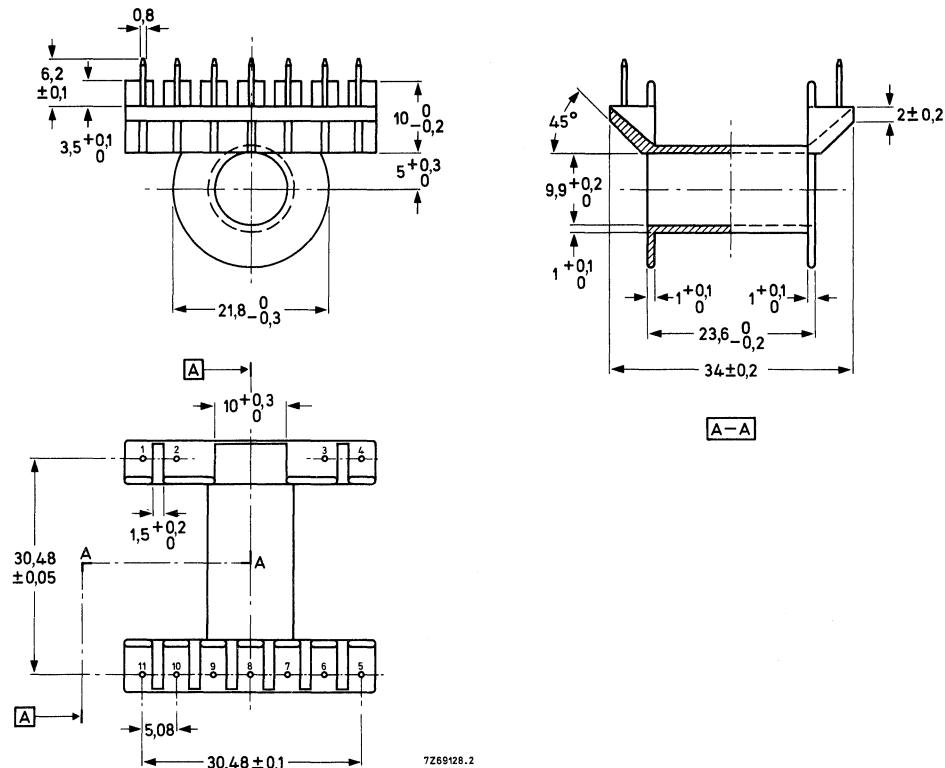

7269128.2

**Material**

phenolformaldehyde reinforced with glass fibre; brass dip-solder pins

**Mounting**

horizontal

**Minimum window area**97,5 mm<sup>2</sup>**Mean length of turn**

50 mm

**Mass**

approx. 6 g


**Maximum temperature**

140 °C


**Catalogue number (coil former with pins)**

4322 021 33410

## Style 2

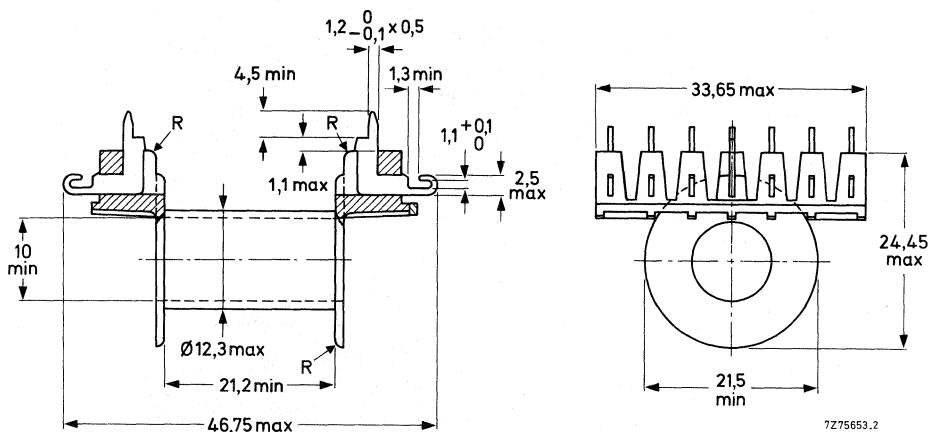

Tag arrangement

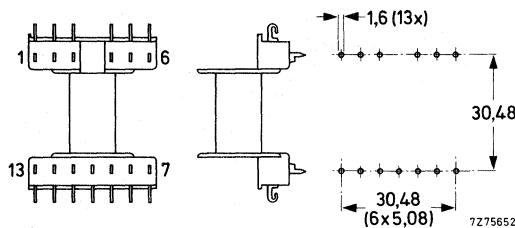

## Material

polyteraphthalate, glass fibre reinforced, 13 solder-plated brass tags are inserted.

## Mounting

horizontal

## Minimum window area

97 mm<sup>2</sup>

## Mean length of turn

53 mm

## Mass

7 g

## Flammability


according to UL 94 V-0

## Catalogue number \*

4322 021 33310

\* Catalogue number of coil former, style 2, without tags: 4322 021 33000.


## MOUNTING PARTS

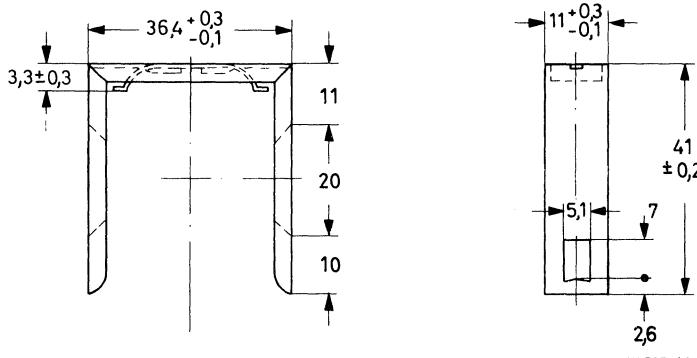

Clasp.

Material: zinc plated steel, bichromated.

Catalogue number: 4312 021 26010

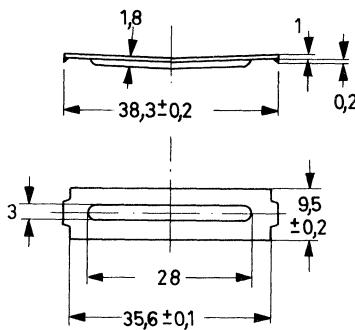


Spring.


Material: zinc plated steel, bichromated.

Catalogue number: 4312 021 26150


## CHARACTERISTIC CURVES

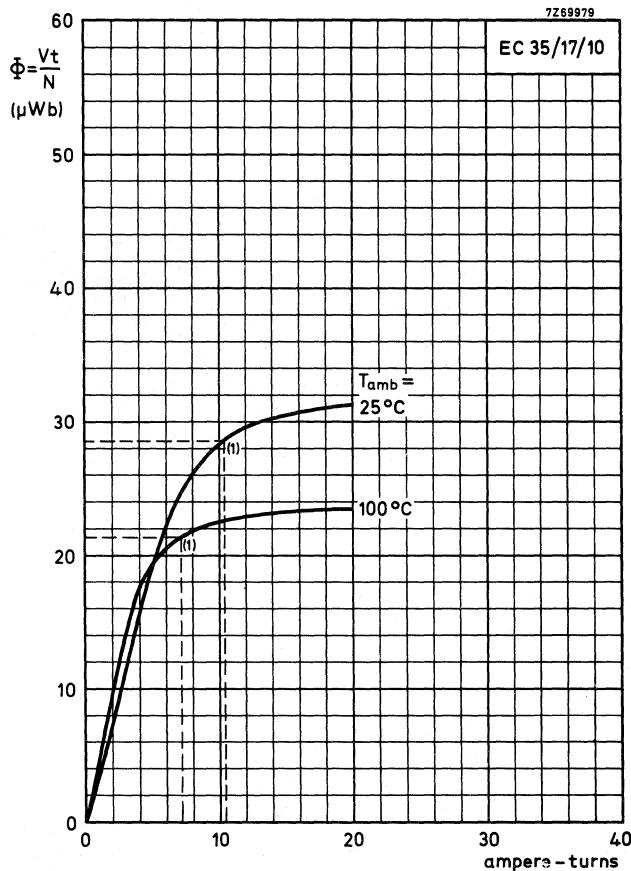


(1) Recommended maximum working flux.  
Total flux as a function of ampere-turns.

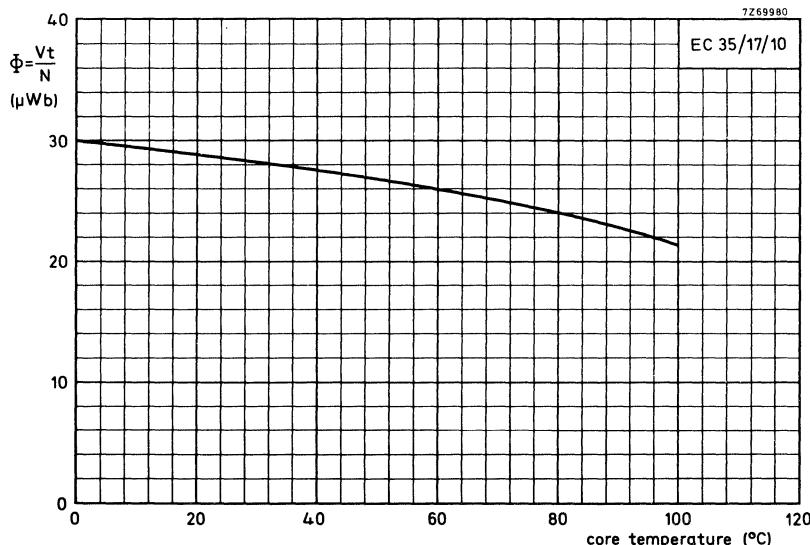


Recommended maximum working flux as a function of core temperature.

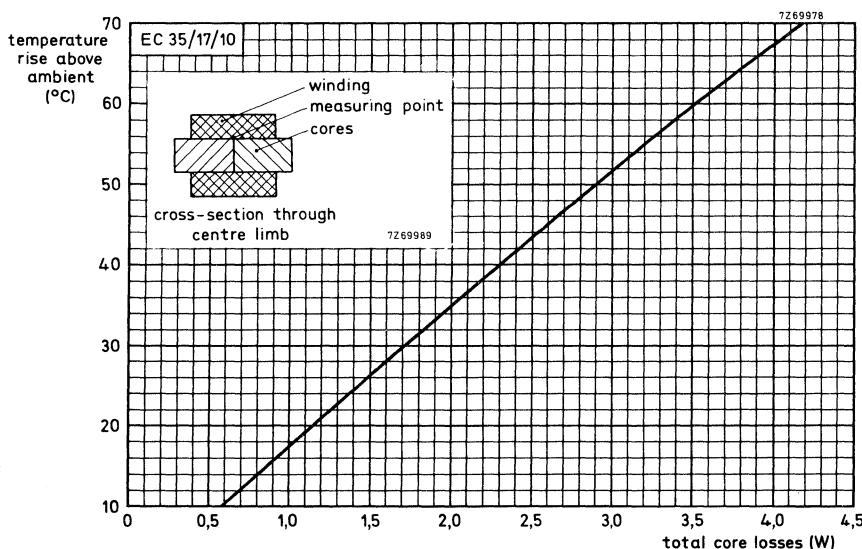


Transformer temperature rise as a function of total core losses, in free air conditions, without heatsink.

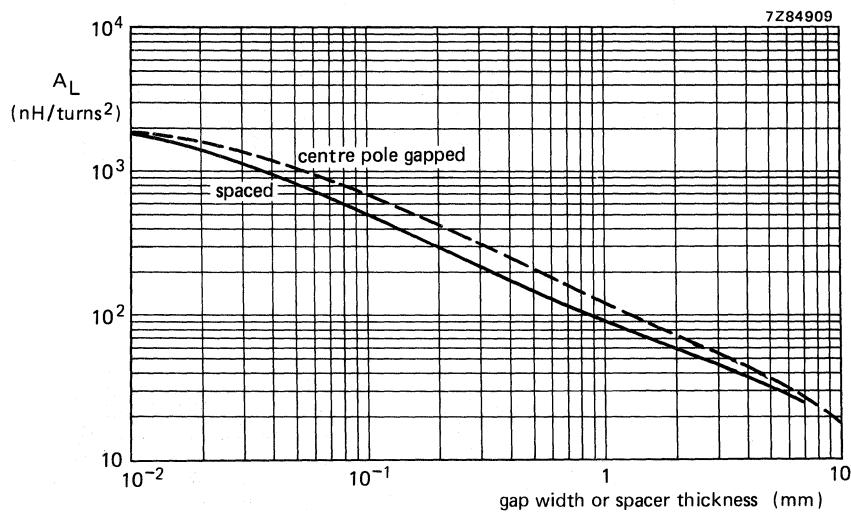


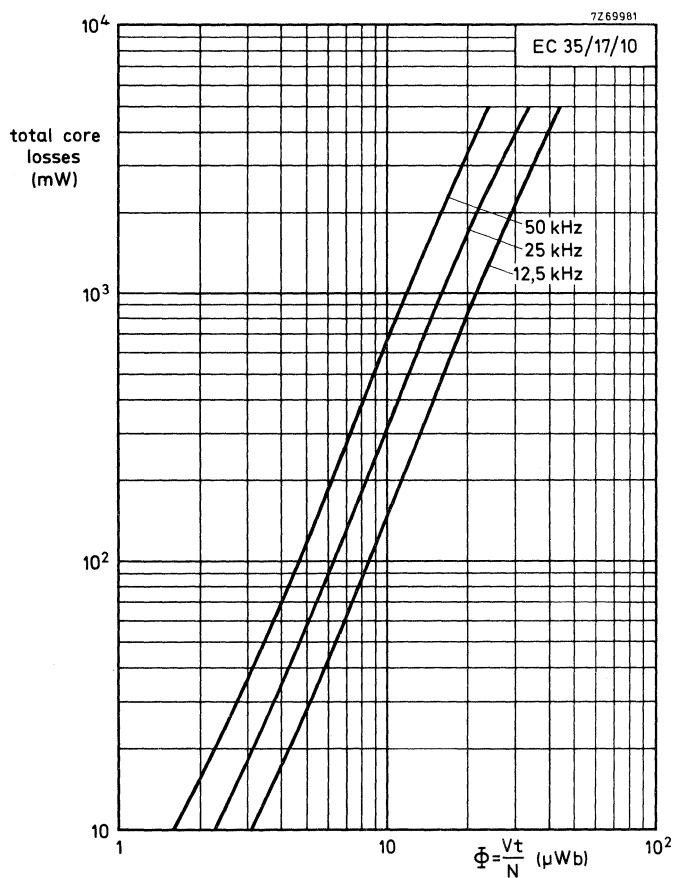

Total core losses as a function of total flux at hot-spot core temperature.

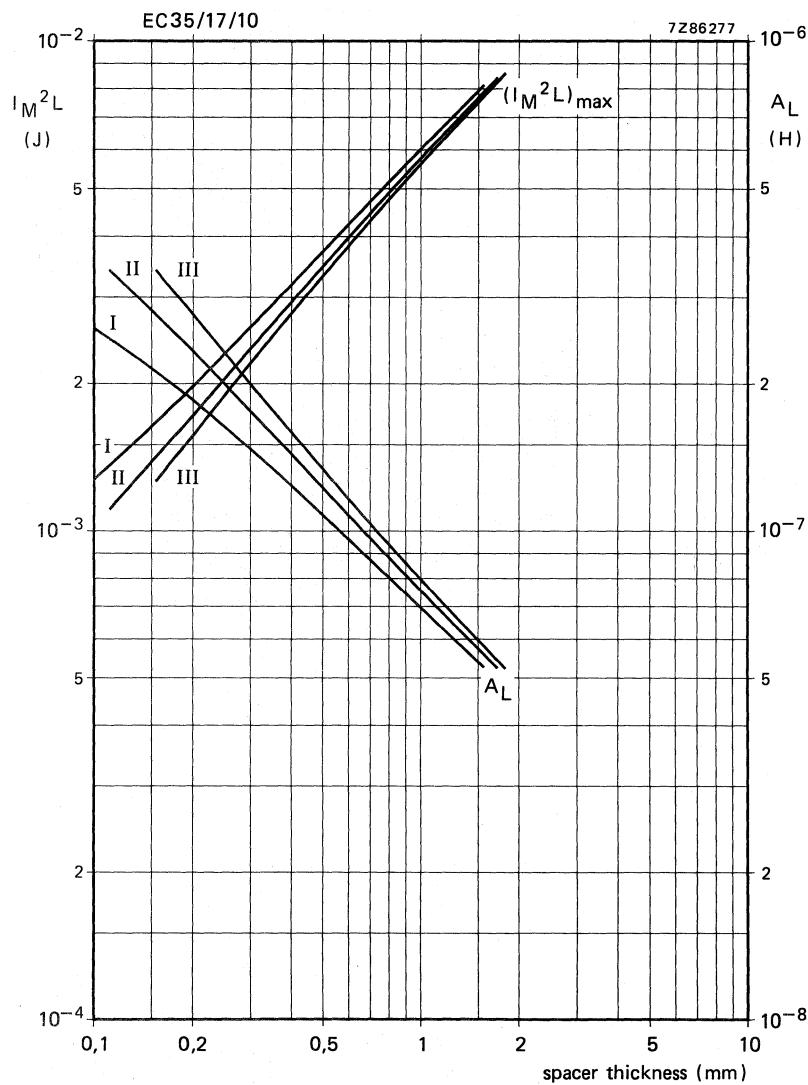


Choke design chart.

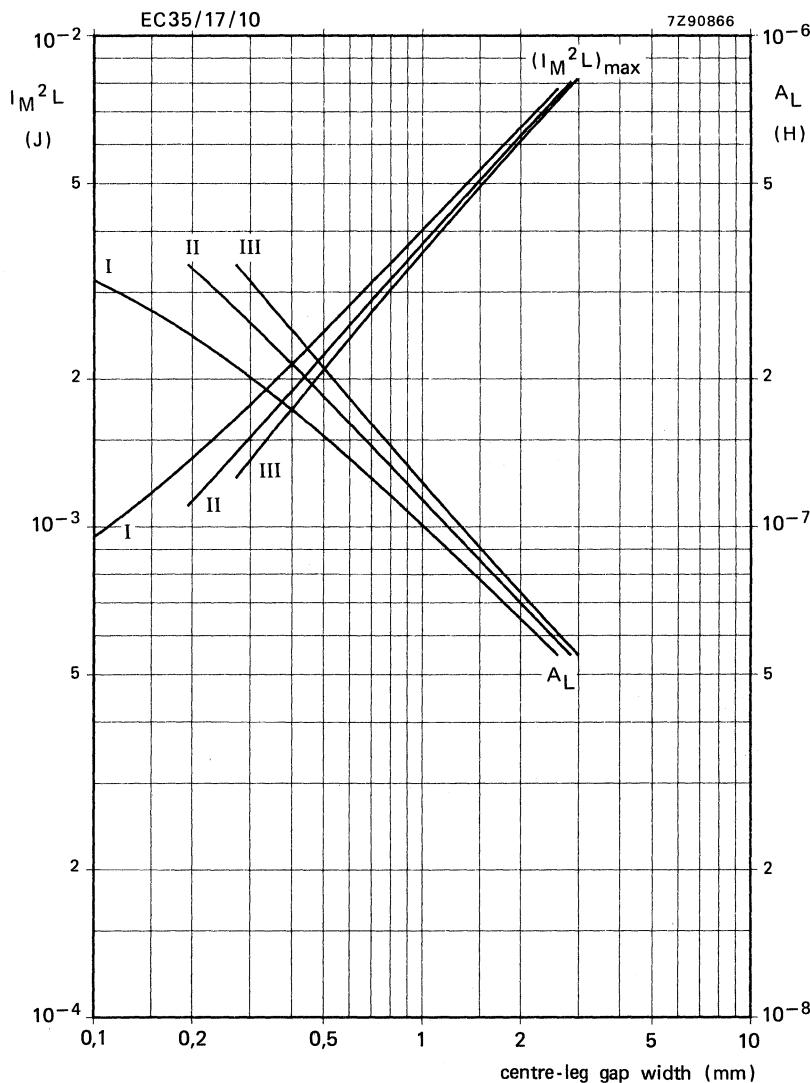

Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.

## EC-CORE

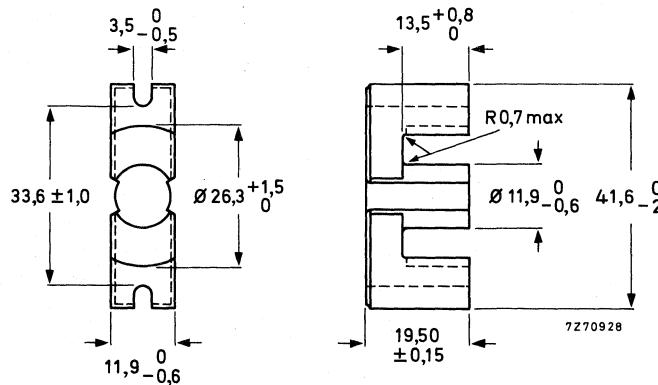

Mass

approx. 26 g

Ferroxcube grade

3C8

Catalogue number of EC-core without air gap\*

● 4322 020 52510

## DIMENSIONAL PARAMETERS FOR A PAIR OF CORES

(Assuming nominal dimensions, unless otherwise stated.)

Core constant \*\*

 $C_1 = 0,735 \text{ mm}^{-1}$ 

Minimum cross-sectional centre pole area

 $A_{CPmin} = 100,3 \text{ mm}^2$ 

Cross-sectional centre pole area

 $A_{min} = 106 \text{ mm}^2$ 

Back and leg cross-sectional area

 $A_b = 130 \text{ mm}^2$ 

Centre pole volume

 $V_{CP} = 2950 \text{ mm}^3$ 

Back and leg volume

 $V_b = 9650 \text{ mm}^3$ 

Total core volume

 $V_f = 12600 \text{ mm}^3$ 

Effective magnetic path length \*\*

 $l_e = 89,3 \text{ mm}$ 

Effective cross-sectional area \*\*

 $A_e = 121 \text{ mm}^2$ 

Effective core volume \*\*

 $V_e = 10800 \text{ mm}^3$ 

\* Cores with air gap are available on request.

\*\* According to IEC 205.



● Preferred type.

**MAGNETIC PROPERTIES FOR A PAIR OF CORES WITHOUT AIR GAP**

Relative amplitude permeability ( $\mu_a$ ) at $\theta = 100^\circ\text{C}$ , $\hat{B} = 320 \text{ mT}$ in $\Delta CP_{\min}$	> 1000
Permissible induction in centre pole ( $\hat{B}$ ) with min. cross-sectional area, at $\theta = 100^\circ\text{C}$	$\leq 320 \text{ mT}$
Resistivity ( $\rho$ ), measured with d.c. current	$\geq 1 \Omega\text{m}$
Curie point	$\geq 200^\circ\text{C}$
Effective total core loss ( $P$ ) referred to $A_e$ at $f = 25 \text{ kHz}$ , $\theta = 100^\circ\text{C}$ , $\hat{B} = 160 \text{ mT}$	$\leq 2,2 \text{ W}$
Inductance factor $A_L$ at $f < 10 \text{ kHz}$ , $\theta = 25^\circ\text{C}$ , $\hat{B} < 0,1 \text{ mT}$	$2700 \pm 25\%$ ←


## COIL FORMERS

Material	glass-fibre-filled polyteraphthalate; solder-plated brass tags
Minimum window area	138 mm <sup>2</sup>
Mean length of turn	62 mm
Mass, 9 tags inserted	10 g
Flammability	according to UL 94 V-0
Mounting	horizontal and vertical
Catalogue number	see next page
Tag arrangement	see next page

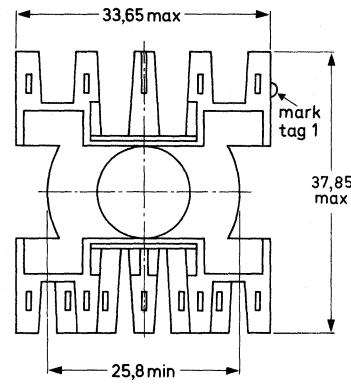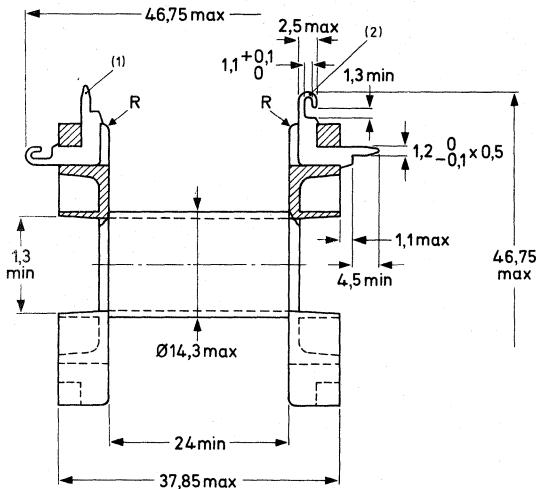


**Tag arrangement****Horizontal mounting**





9 tags inserted

catalogue number  
4322 021 33320

12 tags inserted

catalogue number  
4322 021 33480**Vertical mounting**

9 tags inserted

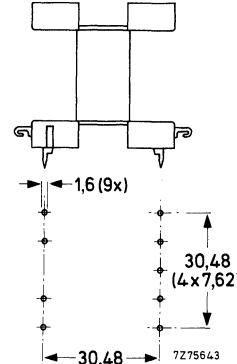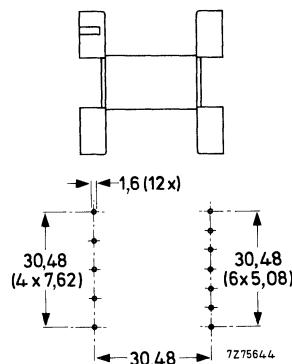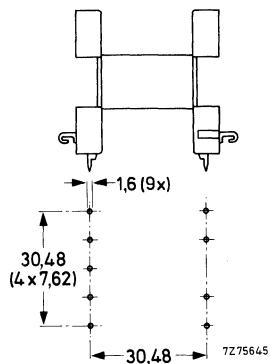
catalogue number  
4322 021 33350

Catalogue number of coil former with 21 tags: 4322 021 33490

Catalogue number of coil former without tags: 4322 021 33010

Catalogue number of tag: 4322 021 33060

## MOUNTING PARTS

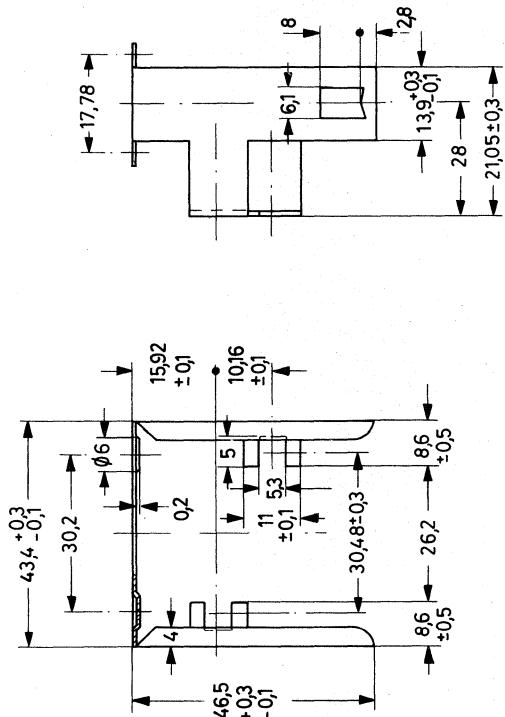

Clasp.

Material: zinc plated steel, bichromated.

Catalogue numbers:



without mounting stud 4312 021 26020

with mounting stud 4312 021 26030.

Spring.


Material: zinc plated steel, bichromated.

Catalogue number: 4312 021 26160.

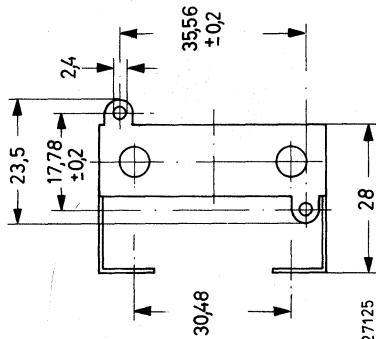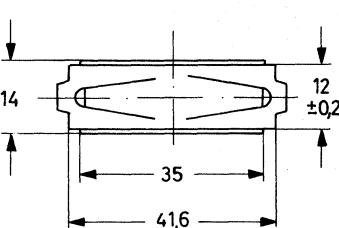


VM 727125


## CHARACTERISTIC CURVES

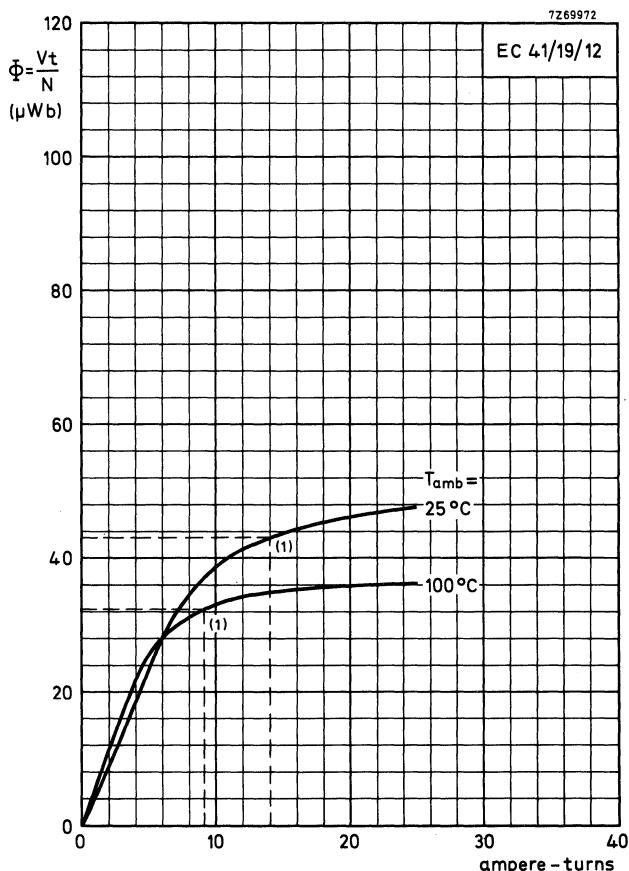


(1) Recommended maximum working flux.  
Total flux as a function of ampere-turns.

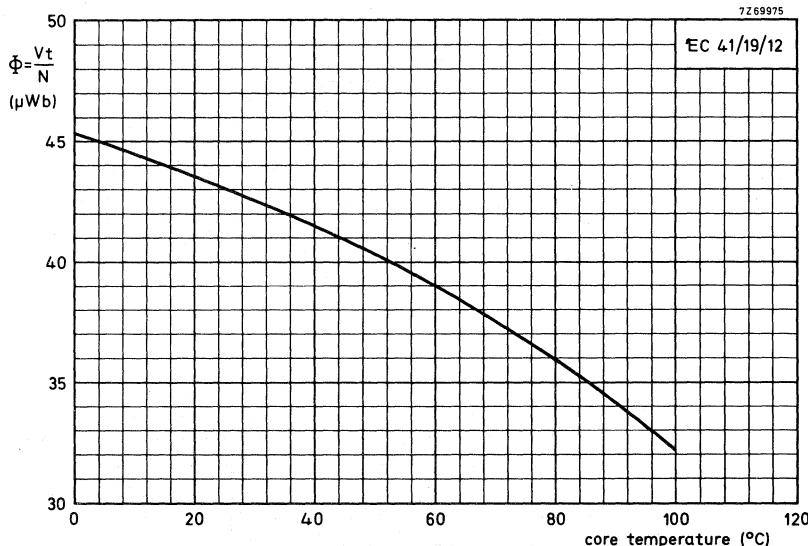


Recommended maximum working flux as a function of core temperature.

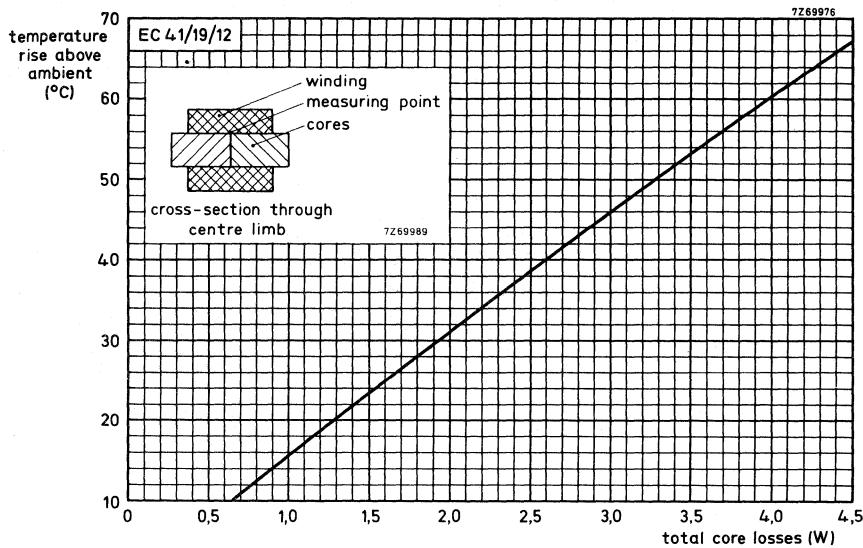


Transformer temperature rise as a function of total core losses, in free air conditions, without heatsink.

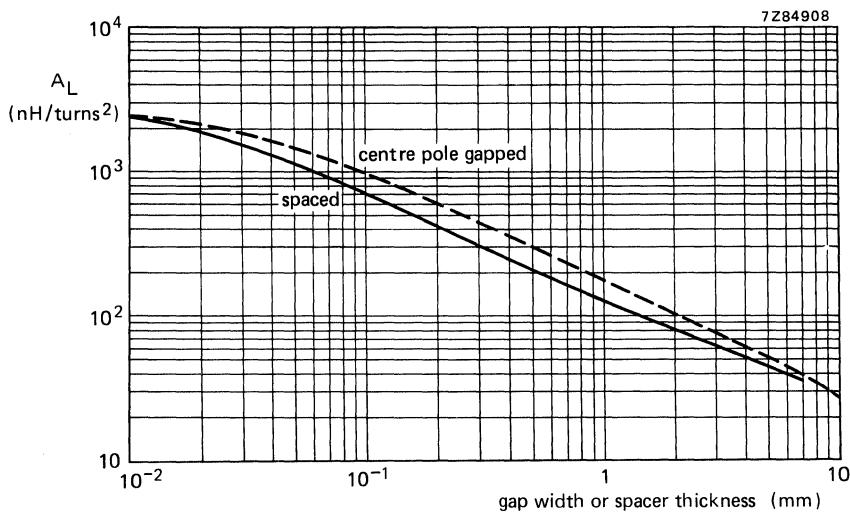

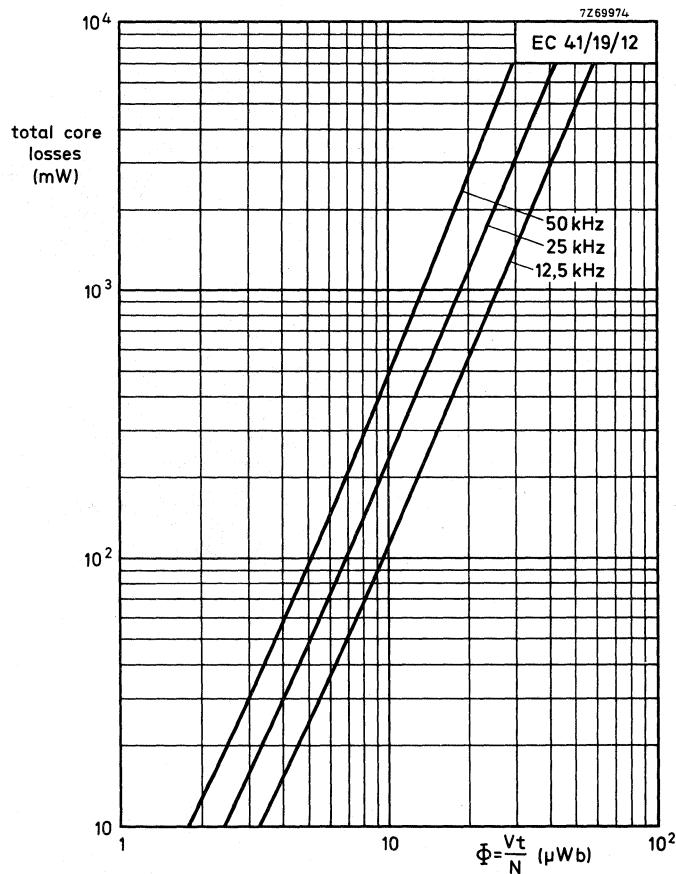


Total core losses as a function of total flux at hot-spot core temperature.

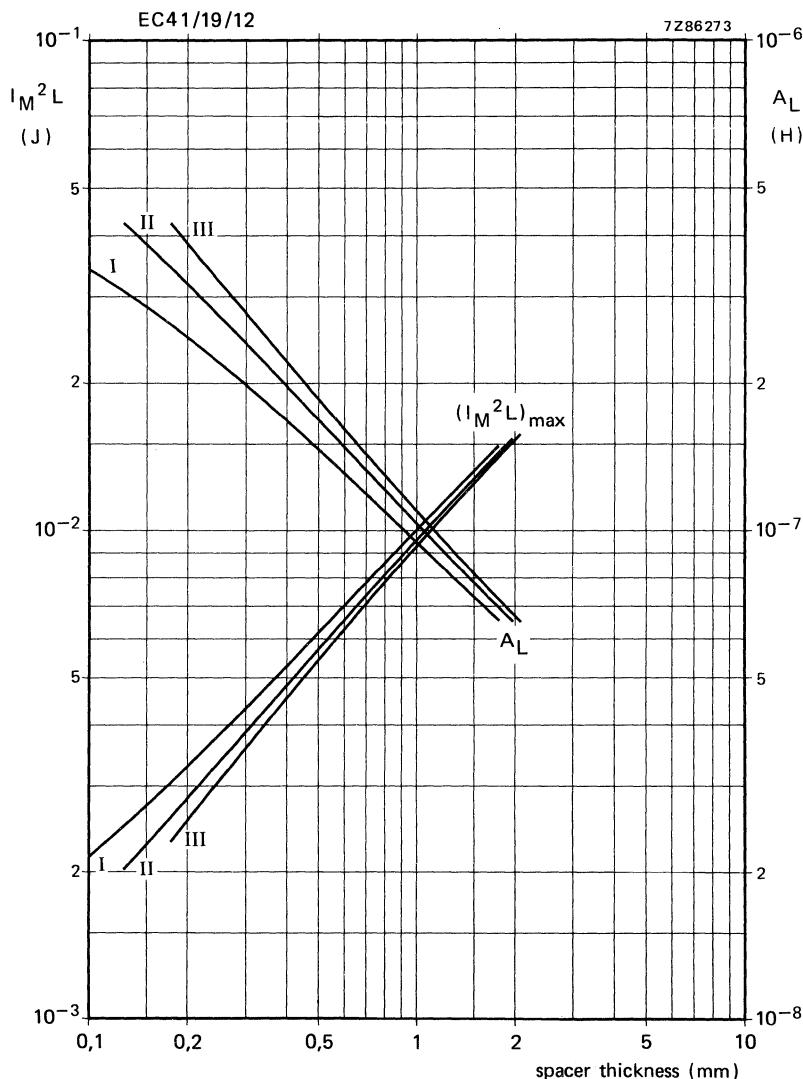

Choke design chart.


For application classes I, II and III see 'Power choke design' in the Introduction.

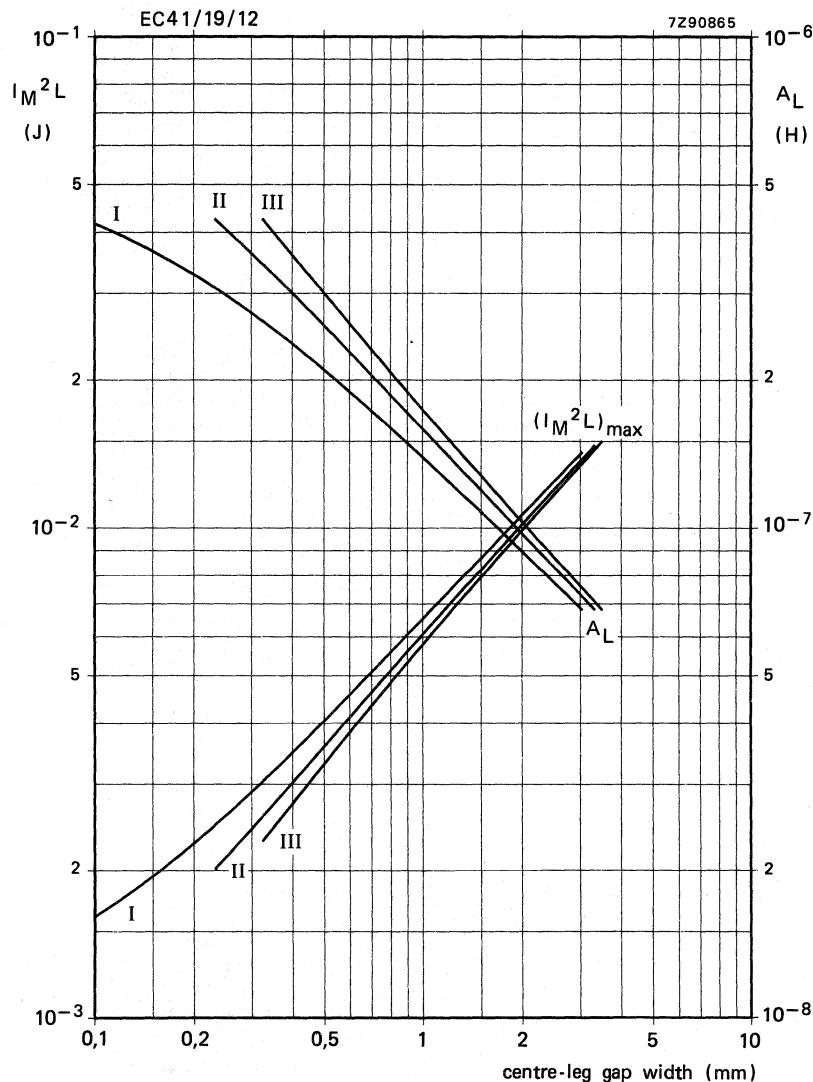

Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.

## EC-CORE

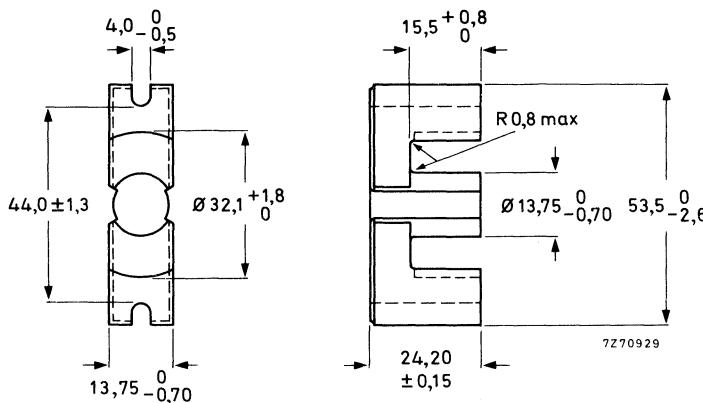

Mass

approx. 55,5 g

Ferroxcube grade

3C8

Catalogue number of EC-core without air gap\*

● 4322 020 52520

## DIMENSIONAL PARAMETERS FOR A PAIR OF CORES

(Assuming nominal dimensions, unless otherwise stated.)

Core constant \*\*

 $C_I = 0,581 \text{ mm}^{-1}$ 

Minimum cross-sectional centre pole area

 $A_{CPmin} = 133,8 \text{ mm}^2$ 

Cross-sectional centre pole area

 $A_{min} = 141,0 \text{ mm}^2$ 

Back and leg cross-sectional area

 $A_b = 222,0 \text{ mm}^2$ 

Centre pole volume

 $V_{CP} = 4480 \text{ mm}^3$ 

Back and leg volume

 $V_b = 19820 \text{ mm}^3$ 

Total core volume

 $V_f = 24300 \text{ mm}^3$ 

Effective magnetic path length \*\*

 $l_e = 105 \text{ mm}$ 

Effective cross-sectional area \*\*

 $A_e = 180 \text{ mm}^2$ 

Effective core volume \*\*

 $V_e = 18800 \text{ mm}^3$ 

\* Cores with air gap are available on request.

\*\* According to IEC 205.

● Preferred type.

**MAGNETIC PROPERTIES FOR A PAIR OF CORES WITHOUT AIR GAP**

Relative amplitude permeability ( $\mu_a$ )	
at $\theta = 100^\circ\text{C}$ , $\hat{B} = 320 \text{ mT}$ in $A_{CP\min}$	$> 1000$
Permissible induction in centre pole ( $\hat{B}$ )	
with min. cross-sectional area, at $\theta = 100^\circ\text{C}$	$\leq 320 \text{ mT}$
Resistivity ( $\rho$ ), measured with d.c. current	$\geq 1 \Omega\text{m}$
Curie point	$\geq 200^\circ\text{C}$
Effective total core loss ( $P$ ) referred to $A_e$	
at $f = 25 \text{ kHz}$ , $\theta = 100^\circ\text{C}$ , $\hat{B} = 160 \text{ mT}$	$\leq 2,7 \text{ W}$
Inductive factor $A_L$	
at $f < 10 \text{ kHz}$ , $\theta = 25^\circ\text{C}$ , $\hat{B} < 0,1 \text{ mT}$	$3600 \pm 25\%$

## COIL FORMER

**Material**

glass-fibre-filled polyteraphthalate;  
solder-plated brass tags

**Minimum window area**

210 mm<sup>2</sup>

**Mean length of turn**

70 mm

**Mass, 11 tags inserted**

18 g

**Flammability**

according to UL 94 V-0

**Mounting**



horizontal and vertical

**Catalogue number**

see next page


**Tag arrangement**

see next page

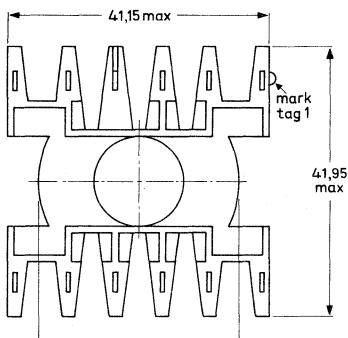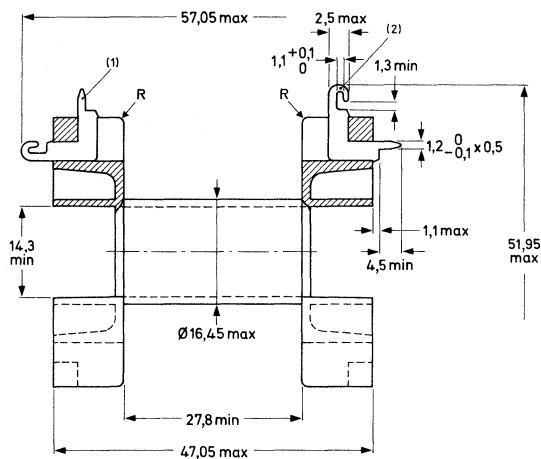


**Tag arrangement****Horizontal mounting**





11 tags inserted

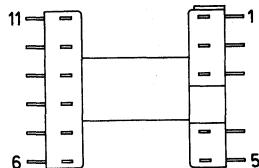catalogue number  
4322 021 33330

14 tags inserted



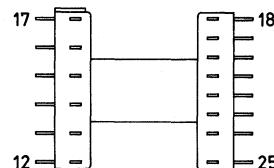
catalogue number  
4322 021 33500**Vertical mounting**

11 tags inserted

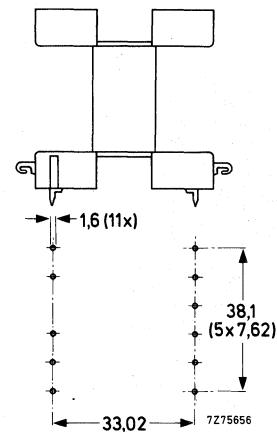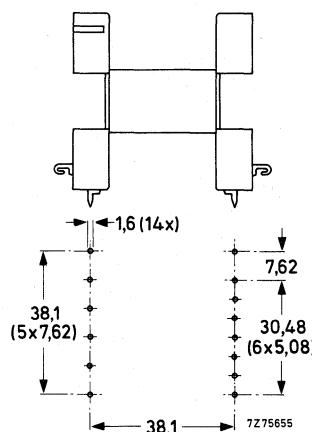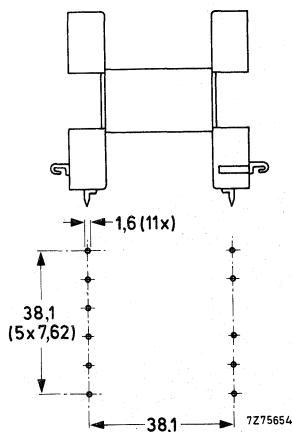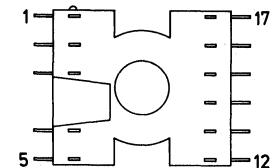catalogue number  
4322 021 33360

→ Catalogue number of coil former without tags: 4322 021 33020  
 Catalogue number of tag: 4322 021 33070

## MOUNTING PARTS

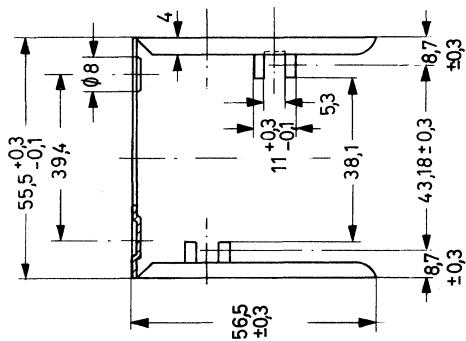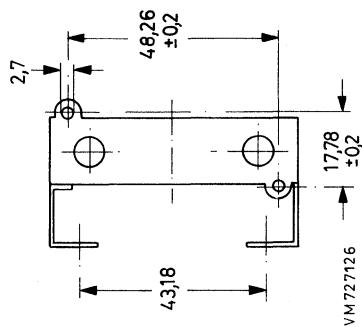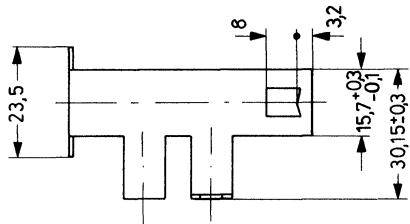


## Clasp.

Material: zinc plated steel, bichromated.

Catalogue number:

without mounting stud 4312 021 26040

with mounting stud 4312 021 26050.

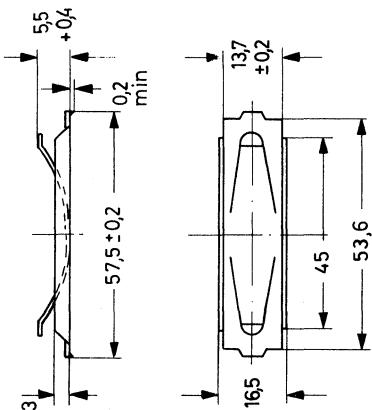


## Spring.

Material: zinc plated steel, bichromated.

Catalogue number: 4312 021 26170.


## CHARACTERISTIC CURVES

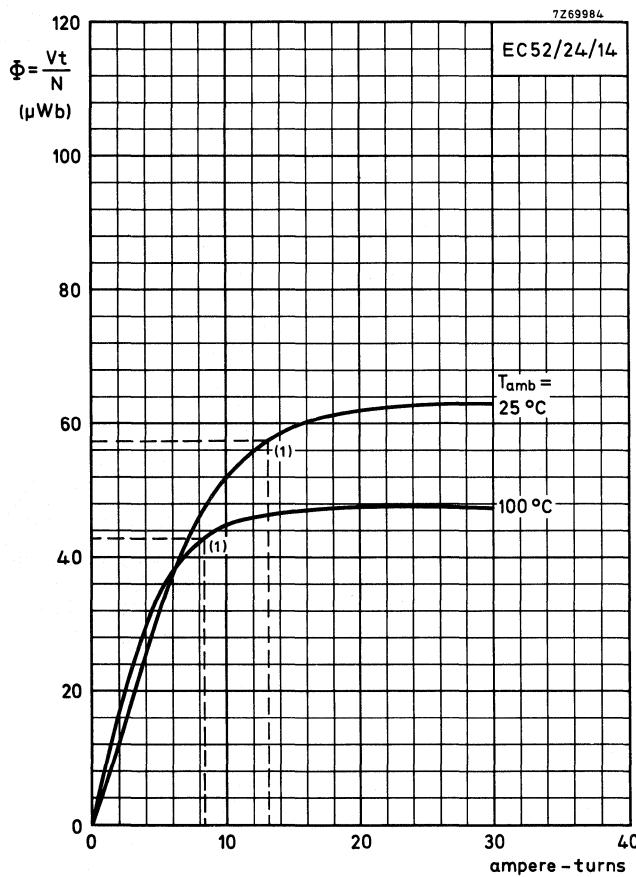


(1) Recommended maximum working flux.  
Total flux as a function of ampere-turns.





Recommended maximum working flux as a function of core temperature.

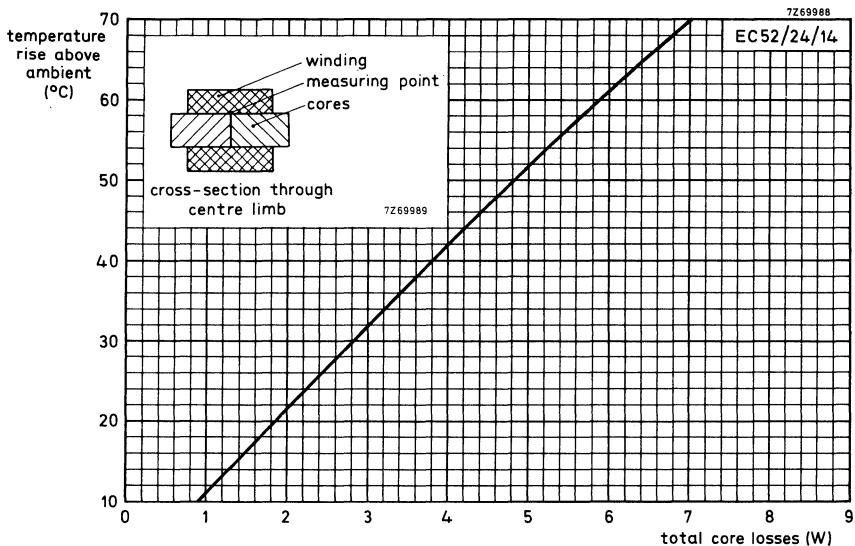

Transformer temperature rise as a function of total core losses, in free air conditions, without heatsink.

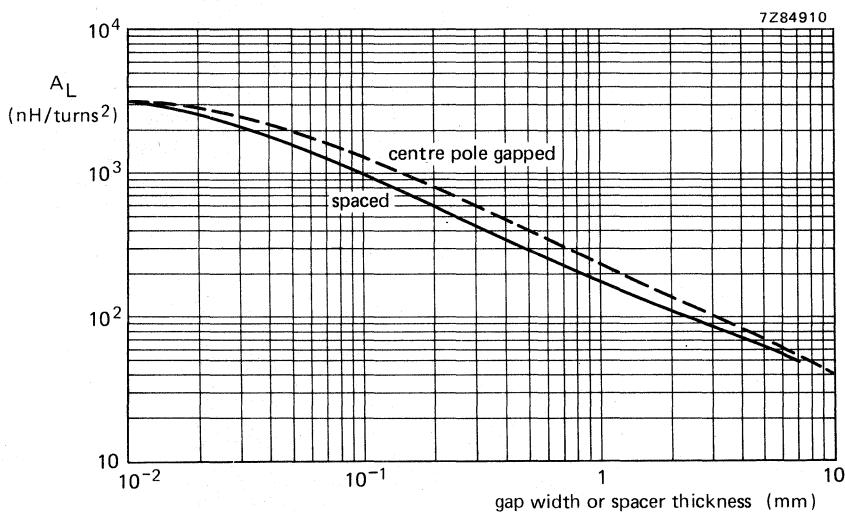


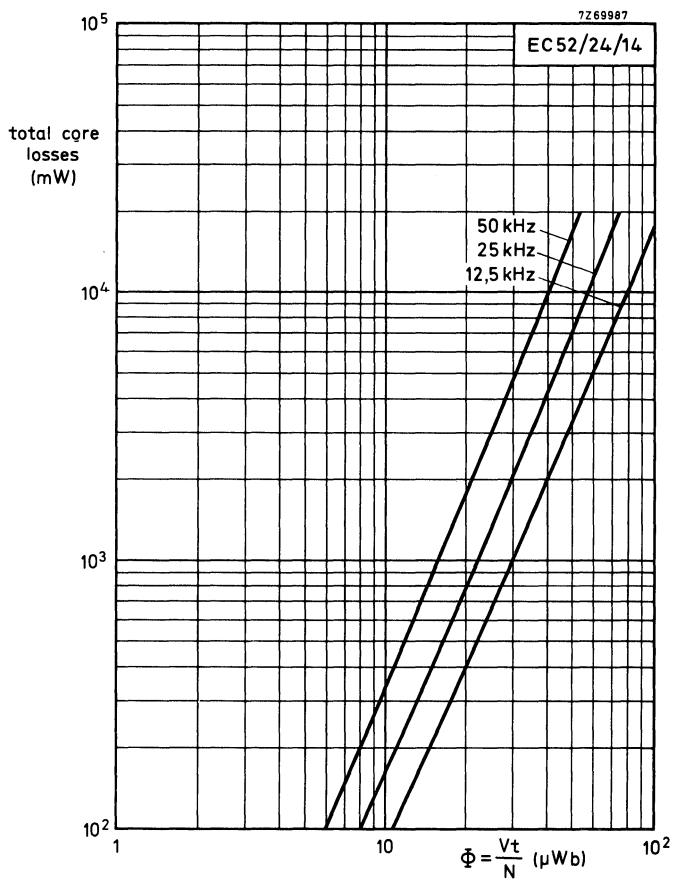

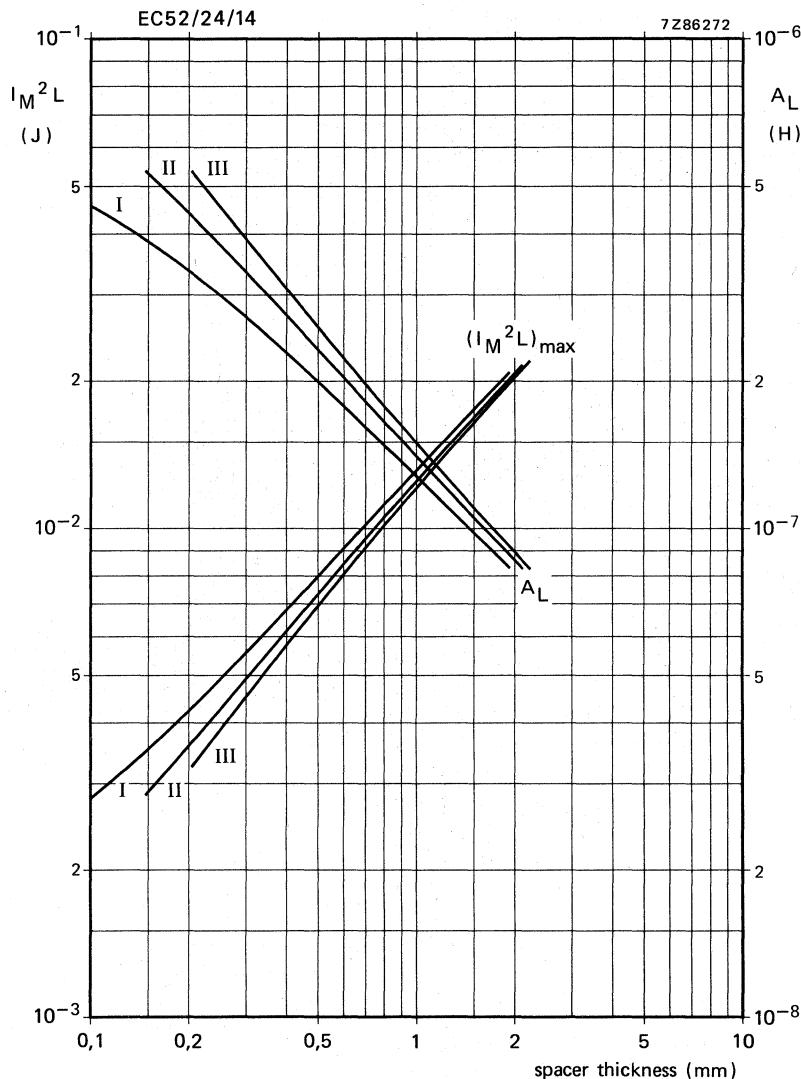

Choke design chart.


For application classes I, II and III see 'Power choke design' in the Introduction.

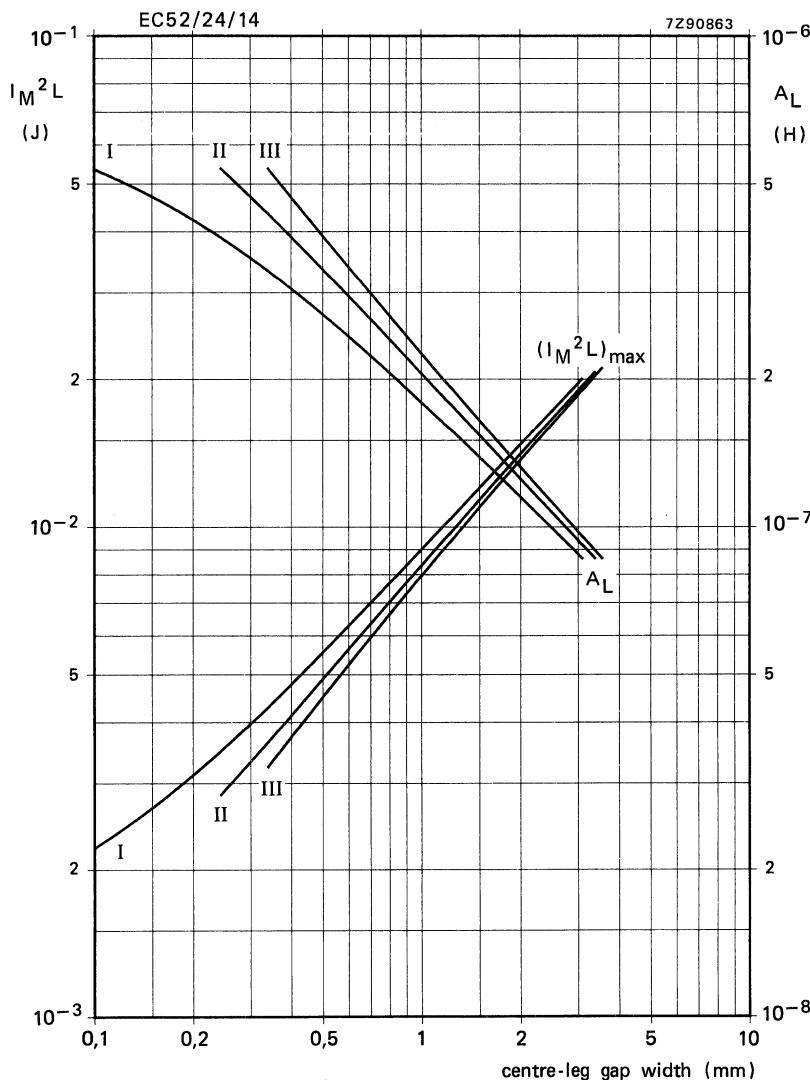

Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.

## EC-CORE

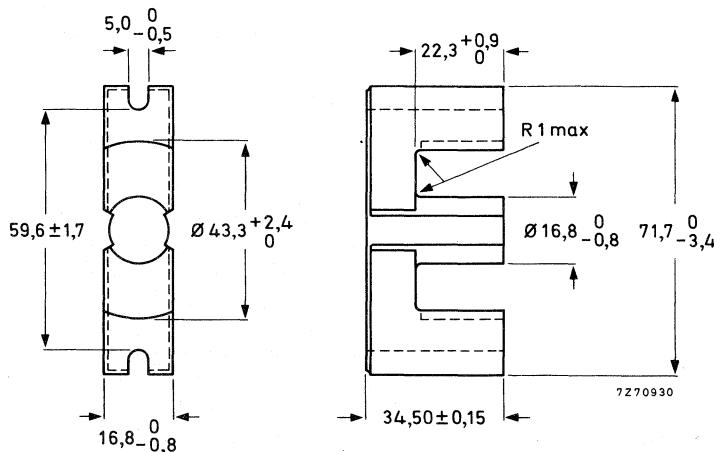

Mass

approx. 126,5 g

Ferroxube grade

3C8

Catalogue number of EC-core without air gap\*

● 4322 020 52530

## DIMENSIONAL PARAMETERS FOR A PAIR OF CORES

(Assuming nominal dimensions, unless otherwise stated.)

Core constant \*\*

$$C_l = 0,514 \text{ mm}^{-1}$$

Minimum cross-sectional centre pole area

$$A_{CPmin} = 201,1 \text{ mm}^2$$

Cross-sectional centre pole area

$$A_{min} = 211,0 \text{ mm}^2$$

Back and leg cross-sectional area

$$A_b = 386,0 \text{ mm}^2$$

Centre pole volume

$$V_{CP} = 9600 \text{ mm}^3$$

Back and leg volume

$$V_b = 46000 \text{ mm}^3$$

Total core volume

$$V_f = 55600 \text{ mm}^3$$

Effective magnetic path length \*\*

$$l_e = 144 \text{ mm}$$

Effective cross-sectional area \*\*

$$A_e = 279 \text{ mm}^2$$

Effective core volume \*\*

$$V_e = 40100 \text{ mm}^3$$

\* Cores with air gap are available on request.

\*\* According to IEC 205.

● Preferred type.


**MAGNETIC PROPERTIES FOR A PAIR OF CORES WITHOUT AIR GAP**

Relative amplitude permeability ( $\mu_a$ ) at $\theta = 100^\circ\text{C}$ , $\hat{B} = 320 \text{ mT}$ in $\text{ACPmin}$	> 1000
Permissible induction in centre pole ( $\hat{B}$ ) with min. cross-sectional area, at $\theta = 100^\circ\text{C}$	$\leq 320 \text{ mT}$
Resistivity ( $\rho$ ), measured with d.c. current	$\geq 1 \Omega\text{m}$
Curie point	$\geq 200^\circ\text{C}$
Effective total core loss ( $P$ ) referred to $A_e$ at $f = 25 \text{ kHz}$ , $\theta = 100^\circ\text{C}$ , $\hat{B} = 160 \text{ mT}$	$\leq 5 \text{ W}$
Inductance factor $A_L$ at $f < 10 \text{ kHz}$ , $\theta = 25^\circ\text{C}$ , $\hat{B} < 0,1 \text{ mT}$	$3900 \pm 25\%$

←


## COIL FORMERS

Material	glass-fibre-filled polyterephthalate; solder-plated brass tags
Minimum window area	464 mm <sup>2</sup>
Mean length of turn	96 mm
Mass, 15 tags inserted	approx. 36 g
Flammability	according to UL 94 V-0
Mounting	horizontal and vertical
Catalogue numbers	see next page
Tag arrangement	see next page

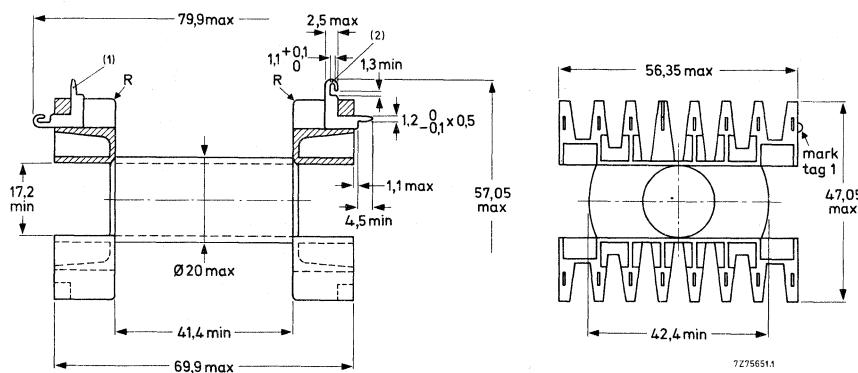


**Tag arrangement****Horizontal mounting**


15 tags inserted

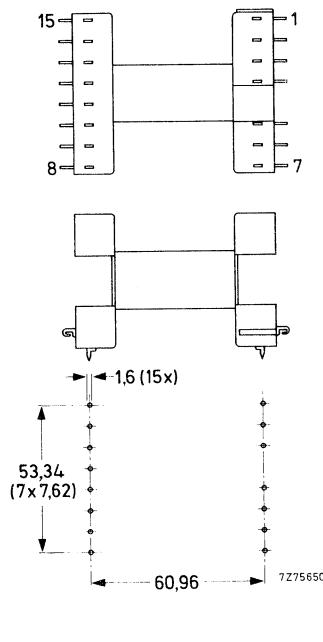catalogue number  
4322 021 33340**Vertical mounting**


15 tags inserted

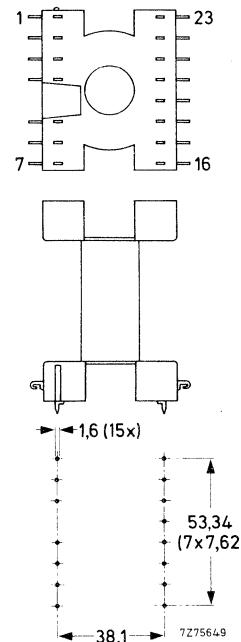catalogue number  
4322 021 33370


## MOUNTING PARTS

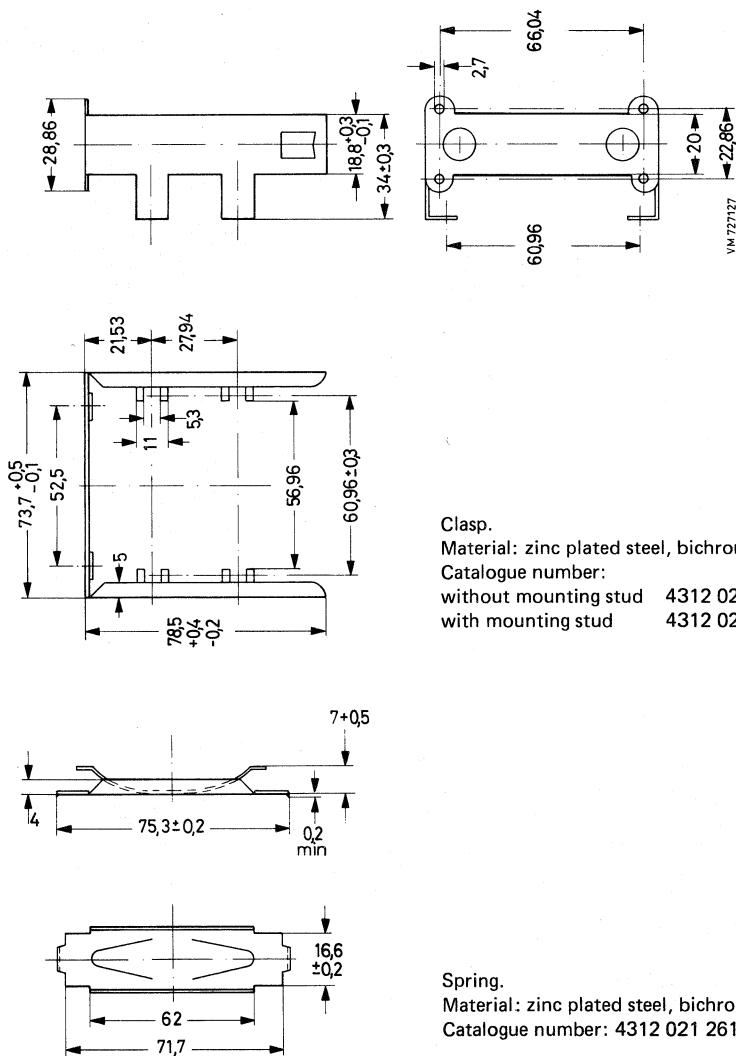


## CHARACTERISTIC CURVES

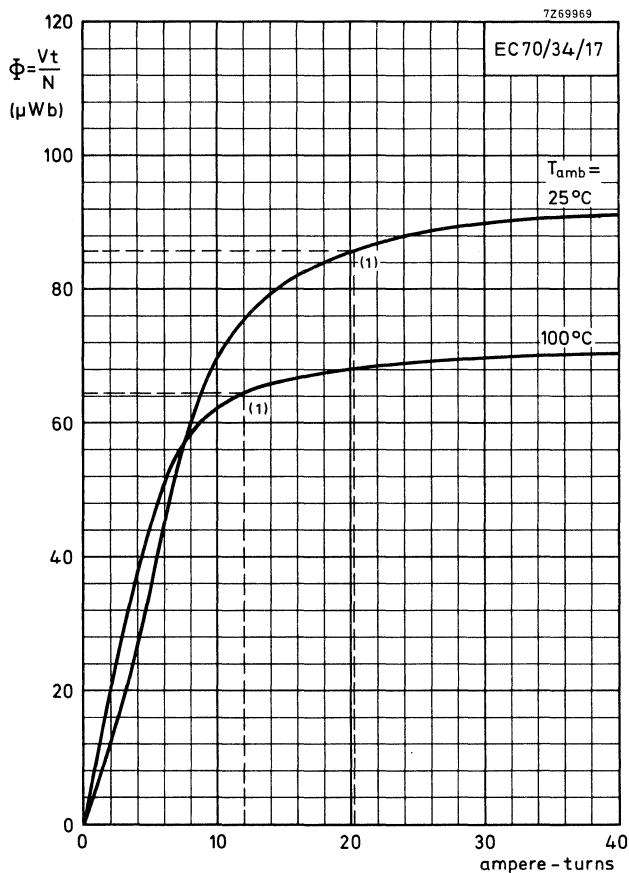


(1) Recommended maximum working flux.  
Total flux as a function of ampere-turns.

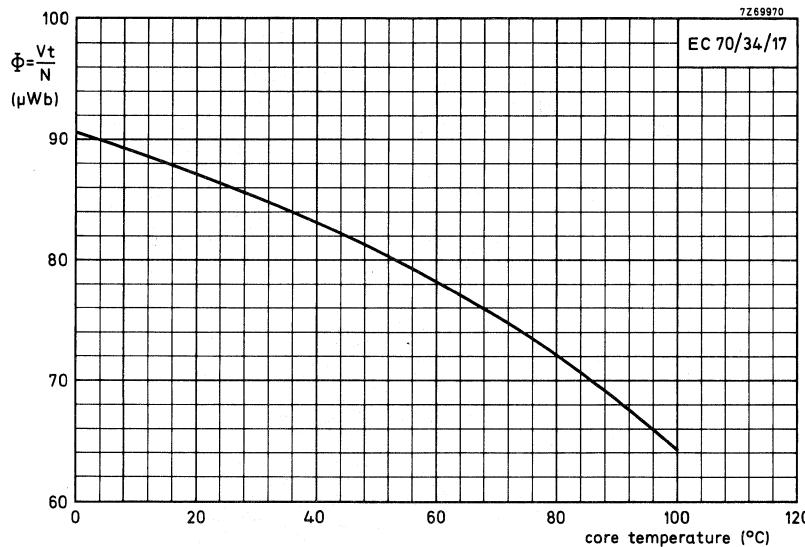


Recommended maximum working flux as a function of core temperature.

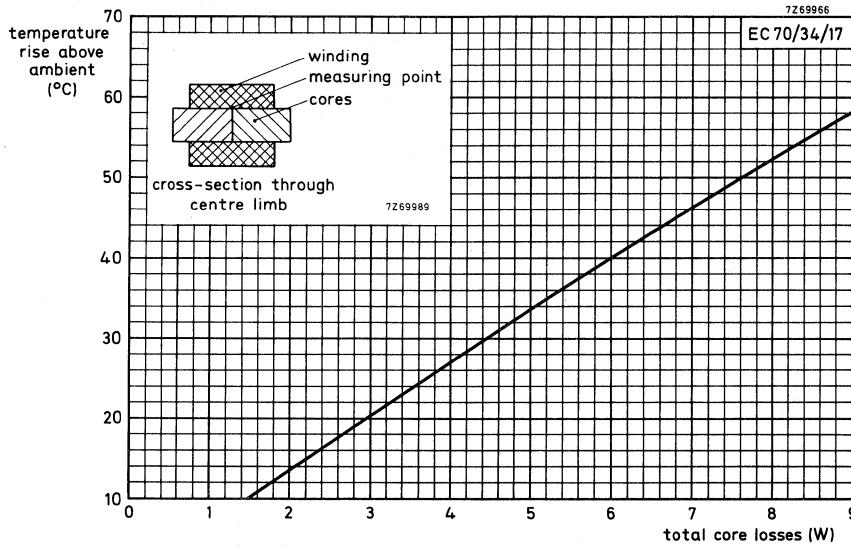


Transformer temperature rise as a function of total core losses, in free air conditions, without heatsink.

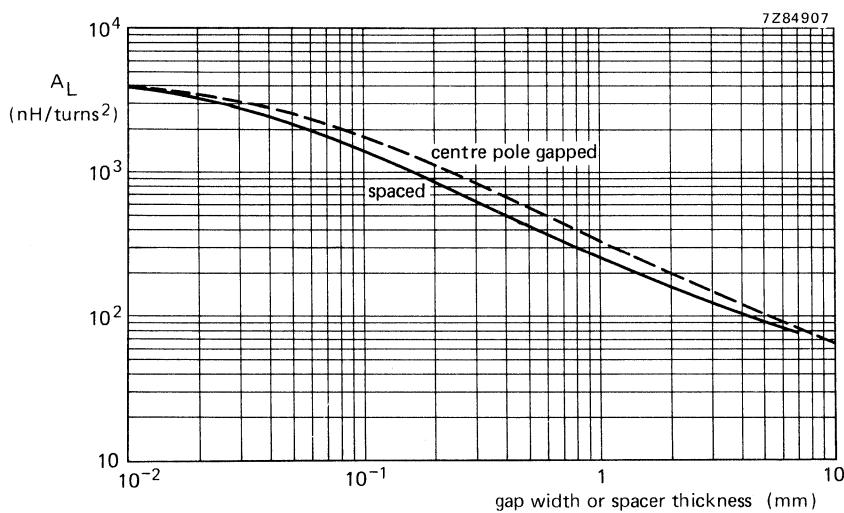

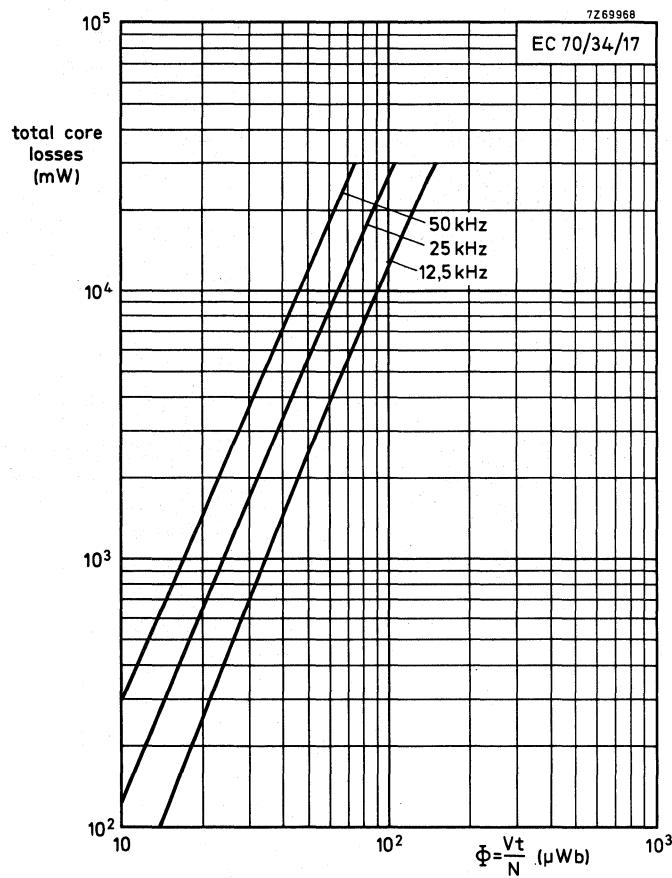


Total core losses as a function of total flux at hot-spot core temperature.

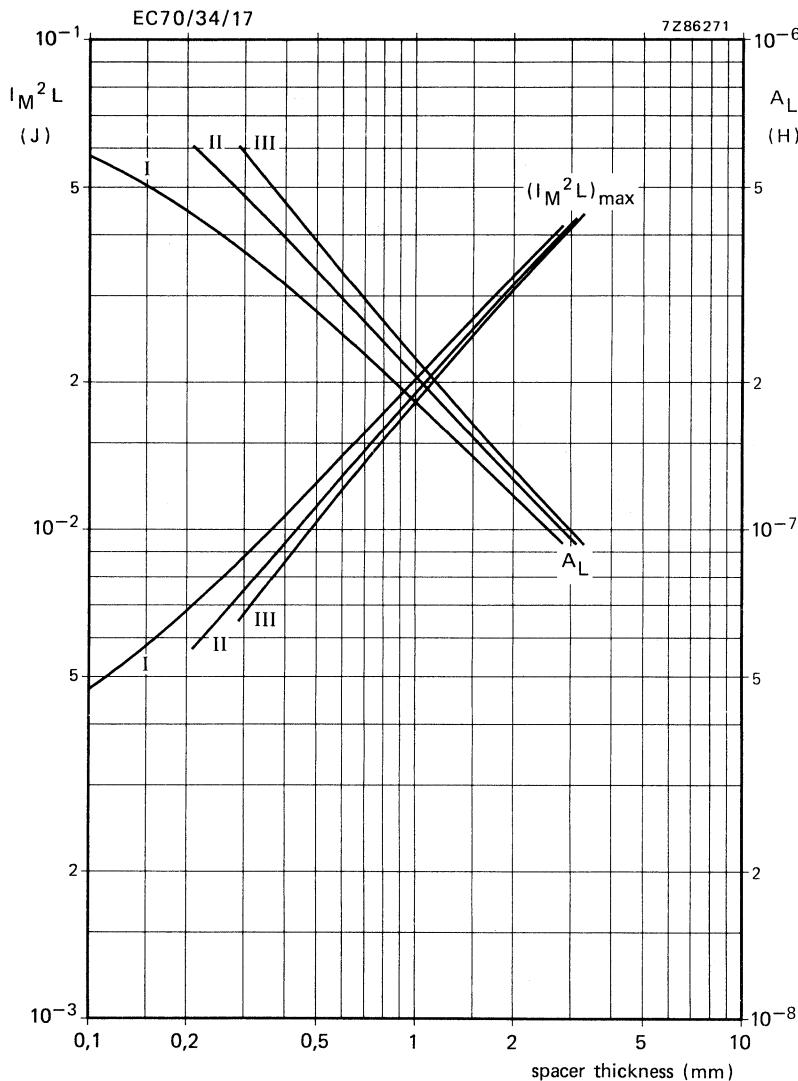

Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.

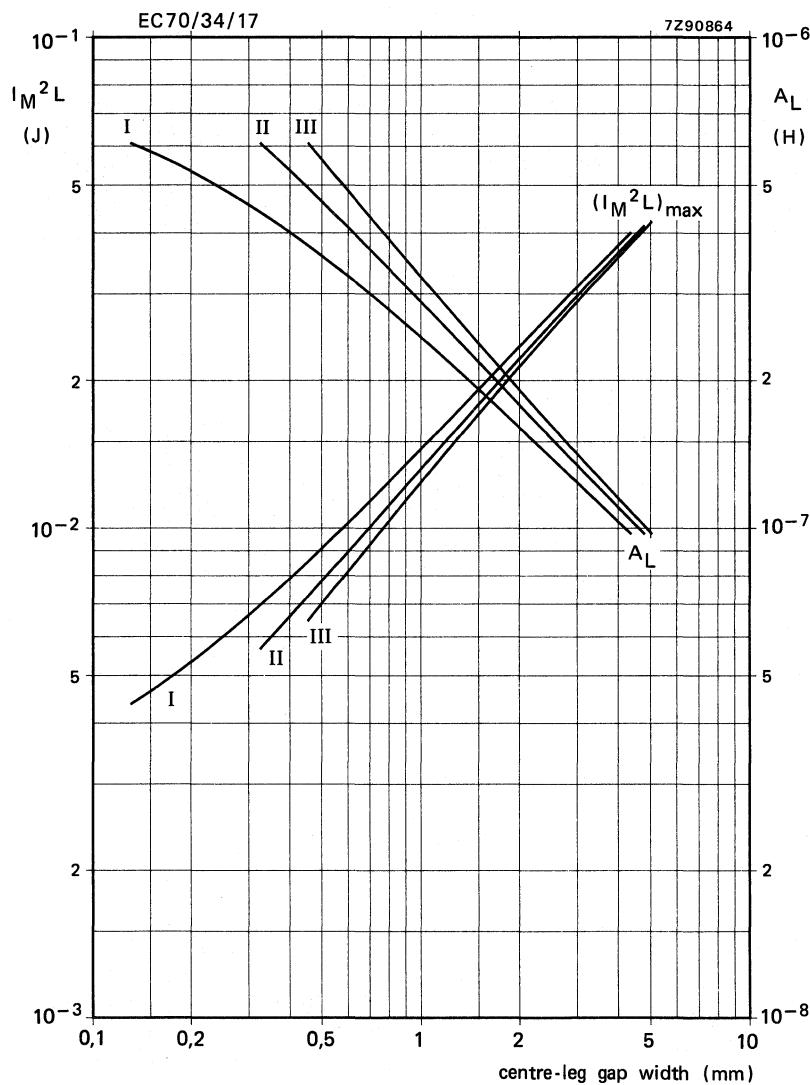

Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.


## INTRODUCTION

The Economic Transformer Design (ETD) series consists of a number of high frequency power cores in Ferroxcube 3C8 and 3C85, which have been optimized to meet the current requirements of switched-mode power supplies. The cores are available for assembly as ungapped or gapped versions, with a range of four nominal  $A_L$  values for the gapped cores.

### Features

- Round centre pole for minimum conductor length.
- Maximum throughput power in the frequency range 20 to 150 kHz.
- Minimum core weight due to constant cross-sectional area and proper choice of transition frequency\*.
- Winding breadth sufficient for full IEC mains isolation in specified configurations.
- Sufficient winding height for minimum loss windings.

### Assembly and mounting

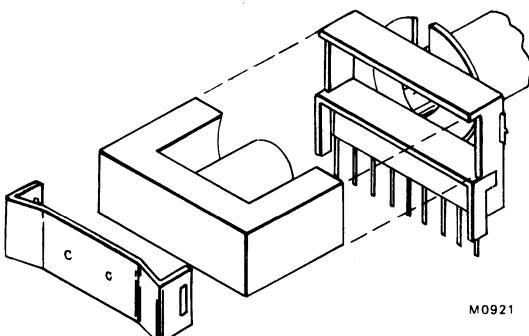

Coil former assembly operation.

The polyterephthalate coil former is suitable for single spindle or automatic machine winding. It is terminated, after winding, to integral pins. The two cores are assembled to the coil former in one operation, as shown in the figure.


Two stainless steel clips retain the cores in the coil former assembly, maintaining adequate pressure at the mating pole faces.

The complete assembly is suitable for mounting on a printed-wiring board.

\* Transition frequency is the frequency, at which the design changes from 'saturation limited' to 'core loss limited'.

## ETD34 SYSTEM

## FERROXCUBE CORE

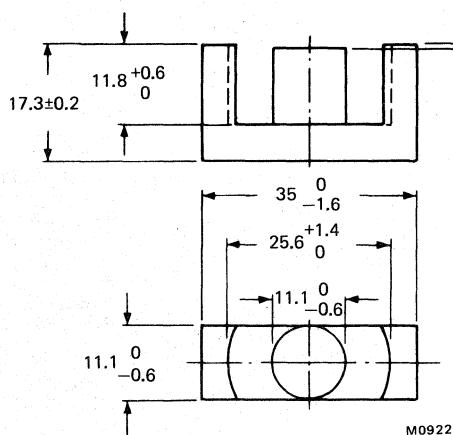

Material: Ferroxcube grade 3C8 and 3C85

Mass per core: 20 g

		catalogue number	
gap width mm	nominal $A_L$ nH	grade 3C8	grade 3C85
$\cong 0$	$2500 \pm 25\%$	• 4312 020 37000	• 4312 020 37200
$0,1 \pm 0,02$	800	4312 020 37010	4312 020 37210
$0,2 \pm 0,03$	480	4312 020 37020	4312 020 37220
$0,5 \pm 0,05$	230	4312 020 37030	4312 020 37230
$1,0 \pm 0,1$	140	4312 020 37040	4312 020 37240

The  $A_L$  values shown above apply to the gapped core indicated, assembled with an ungapped core.

- Preferred type.

**EFFECTIVE PARAMETERS**

For calculating the magnetic properties of a pair of cores, the following parameters should be used.

parameter	symbol	value	unit
effective magnetic path length	$l_e$	78.6	mm
effective area of magnetic path	$A_e$	97.1	mm <sup>2</sup>
effective magnetic volume	$V_e$	7640	mm <sup>3</sup>
core factor $\sum \frac{l}{A}$	$C_1$	0,8096	mm <sup>-1</sup>

**NOMINAL DESIGN DATA FOR A PAIR OF CORES**

parameter	symbol	value	unit
centre pole area	$A_{min}$	91,6	mm <sup>2</sup>
length of the mean turn	$l_w$	60	mm

**ELECTRICAL AND MAGNETIC PROPERTIES OF A PAIR OF CORES IN FXC 3C8**

property	temperature (°C)	frequency (kHz)	parameter	value	unit
total power loss (P)	60–100	25	$\hat{B} = 200 \text{ mT}^*$	<1,6	W
saturation induction ( $\hat{B}_{max}$ )	100	25	H = 250 A/m	≥320	mT

**ELECTRICAL AND MAGNETIC PROPERTIES OF A PAIR OF CORES IN FXC 3C85**

property	temperature (°C)	frequency (kHz)	parameter	value	unit
total power loss (P)	60–100	25	$\hat{B} = 200 \text{ mT}^*$	<1,1	W
		100	$\hat{B} = 100 \text{ mT}^*$	<1,3	W
saturation induction ( $\hat{B}_{max}$ )	100	25	H = 250 A/m	≥320	mT

$$* \hat{B} = \frac{\sqrt{2U}}{\omega A_{min} N}$$

## CHOKE DESIGN CHART

For application classes I, II and III see 'Power choke design' in the Introduction.

class I			class II*			class III**			centre leg gap width mm	core halves ▲ catalogue number 4312 020 followed by
$I_{ML}^2$	$N_{max} \times I_M$	$A_{L2}$	$I_{ML}^2$	$N_{max} \times I_M$	$A_{L2}$	$I_{ML}^2$	$N_{max} \times I_M$	$A_{L2}$		
mJ	A	nH	mJ	A	nH	mJ	A	nH		
1,09	55,6	354	0,71	36,2	541	0,47	24,1	803	0,1	37000 & 37010
1,43	72,8	270	1,04	53,2	368	0,79	41,0	472	0,2	37010 & 37010
1,86	90,9	225	1,46	71,1	289	1,21	58,8	350	0,3	37010 & 37020
2,26	108	194	1,86	88,0	240	1,61	75,7	281	0,4	37020 & 37020
2,85	127	176	2,45	108	212	2,20	95,1	244	0,5	37000 & 37030
3,11	141	157	2,71	121	185	2,46	109	208	0,6	37010 & 37030
3,47	156	143	3,06	136	166	2,81	123	185	0,7	37020 & 37030
4,55	199	115	4,15	179	130	3,90	166	141	1,0	37030 & 37030
4,77	210	108	4,37	190	121	4,11	178	130	1,1	37010 & 37040
5,08	223	102	4,67	203	114	4,42	190	122	1,2	37020 & 37040
6,04	260	89	5,63	240	98	5,38	228	104	1,5	37030 & 37040
7,38	316	74	6,97	296	80	6,72	284	84	2,0	37040 & 37040



Calculate  $N_{min}$  with  $N_{min} = \sqrt{L_{min}/A_{L2} \times 10^{-9}}$

▲ Preferred combinations.



\* For frequencies beyond 40 kHz enter the table at  $f/40 \times I_{ML}^2$  and calculate  $N_{max} = (N_{max} \times I_M)/I_M \times \sqrt{f/40}$  (f in kHz).

\*\* For frequencies beyond 10 kHz enter the table at  $0,1 f \times I_{ML}^2$  and calculate  $N_{max} = (N_{max} \times I_M)/I_M \times \sqrt{0,1 f}$  (f in kHz).

## COIL FORMER

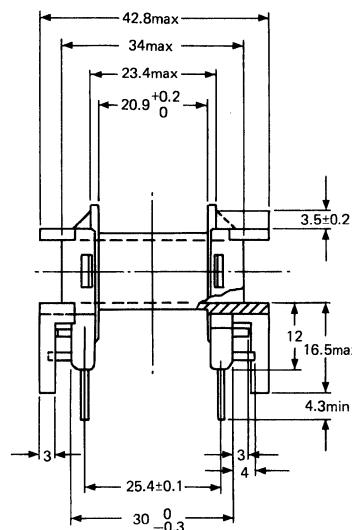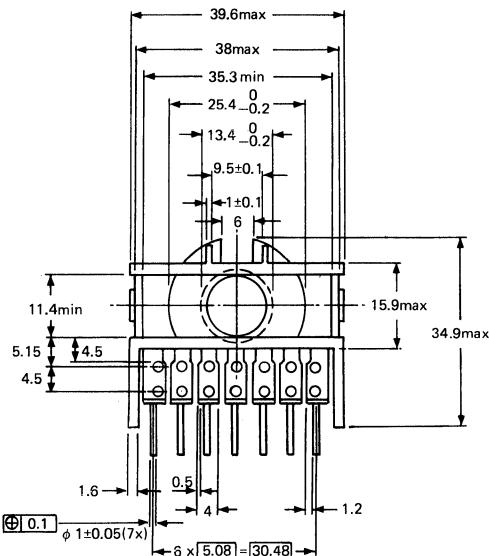

Pin arrangement

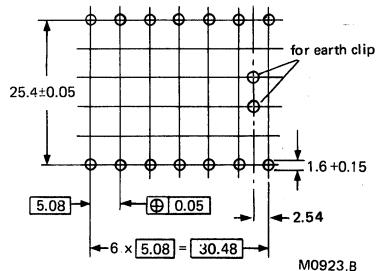

Material

glass-fibre-filled polyteraphthalate;  
14 copper-nickel alloy pins are inserted

Minimum window area

123 mm<sup>2</sup>

Mean length of turn

60 mm

Flammability

according to UL94 V-0



Solderability

400 °C for 4 s

Catalogue number

4322 021 33850

## MOUNTING PARTS

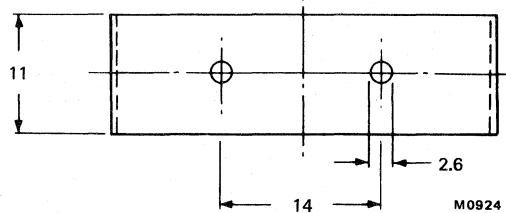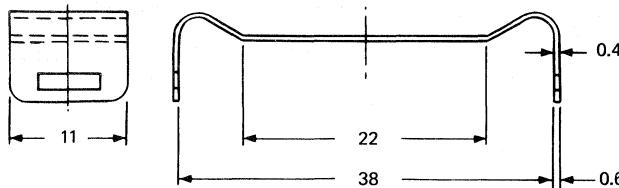


Assembly clip.  
Material  
Catalogue number

stainless steel  
4322 021 33890

Earth clip.  
Material  
Terminations  
Catalogue number


nickel silver  
hot tinned  
4322 021 33940

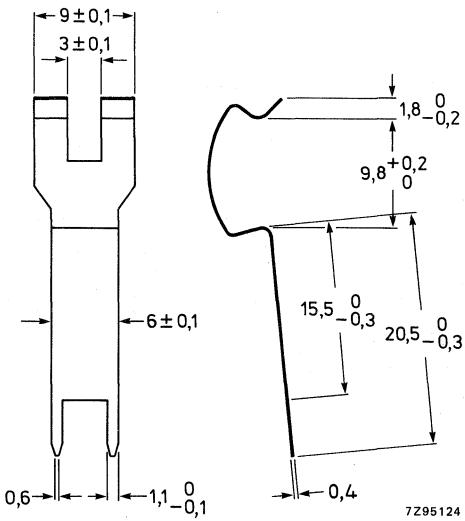

Both core halves can be connected to earth by means of this clip.

## ETD39 SYSTEM

## FERROXCUBE CORE

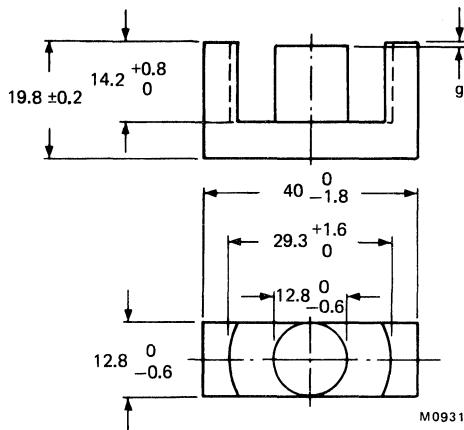

Material: Ferroxcube grade 3C8 and 3C85

Mass per core: 30 g

gap width mm	nominal $A_L$ nH	catalogue number	
		grade 3C8	grade 3C85
≈ 0	2800 ± 25%	● 4312 020 37050	● 4312 020 37250
0,1 ± 0,02	1000	4312 020 37060	4312 020 37260
0,2 ± 0,03	600	4312 020 37070	4312 020 37270
0,5 ± 0,05	295	4312 020 37080	4312 020 37280
1,0 ± 0,1	170	4312 020 37090	4312 020 37290

The  $A_L$  values shown above apply to the gapped core indicated, assembled with an ungapped core.

- Preferred type.

**EFFECTIVE PARAMETERS**

For calculating the magnetic properties of a pair of cores, the following parameters should be used.

parameter	symbol	value	unit
effective magnetic path length	$l_e$	92.2	mm
effective area of magnetic path	$A_e$	125	mm <sup>2</sup>
effective magnetic volume	$V_e$	11 500	mm <sup>3</sup>
core factor $\sum \frac{l}{A}$	$C_1$	0,7373	mm <sup>-1</sup>

**NOMINAL DESIGN DATA FOR A PAIR OF CORES**

parameter	symbol	value	unit
centre pole area	$A_{min}$	123	mm <sup>2</sup>
length of the mean turn	$l_w$	69	mm

**ELECTRICAL AND MAGNETIC PROPERTIES OF A PAIR OF CORES IN FXC 3C8**

property	temperature (°C)	frequency (kHz)	parameter	value	unit
total power loss (P)	60 – 100	25	$\hat{B} = 200 \text{ mT}^*$	< 2,2	W
saturation induction ( $\hat{B}_{max}$ )	100	25	$H = 250 \text{ A/m}$	$\geq 320$	mT

**ELECTRICAL AND MAGNETIC PROPERTIES OF A PAIR OF CORES IN FXC 3C85**

property	temperature (°C)	frequency (kHz)	parameter	value	unit
total power loss (P)	60 – 100	25 100	$\hat{B} = 200 \text{ mT}^*$ $\hat{B} = 100 \text{ mT}^*$	< 1,6 < 1,9	W W
saturation induction ( $\hat{B}_{max}$ )	100	25	$H = 250 \text{ A/m}$	$\geq 320$	mT

$$* \hat{B} = \frac{\sqrt{2} U}{\omega A_{min} N}$$

## CHOKE DESIGN CHART

For application classes I, II and III see 'Power choke design' in the Introduction.

class I			class II*			class III**			centre leg gap width mm	core halves ▲ catalogue number 4312 020 followed by
$I_M^2 L$	$N_{max} \times I_M$	$A_{L2}$	$I_M^2 L$	$N_{max} \times I_M$	$A_{L2}$	$I_M^2 L$	$N_{max} \times I_M$	$A_{L2}$		
mJ	A	nH	mJ	A	nH	mJ	A	nH		
1,70	64,2	413	1,07	40,4	655	0,67	25,6	1022	0,1	37050 & 37060
2,17	81,8	324	1,53	57,8	457	1,12	42,8	610	0,2	37060 & 37060
2,76	100	274	2,11	76,2	363	1,69	61,1	453	0,3	37060 & 37070
3,32	118	239	2,66	93,6	304	2,24	78,5	365	0,4	37070 & 37070
4,15	138	217	3,49	114	270	3,07	98,6	316	0,5	37050 & 37080
4,51	152	195	3,85	128	236	3,43	113	270	0,6	37060 & 37080
5,01	168	178	4,34	143	212	3,92	128	240	0,7	37070 & 37080
6,53	212	145	5,86	188	167	5,44	172	183	1,0	37080 & 37080
6,84	224	136	6,17	200	155	5,75	184	169	1,1	37060 & 37090
7,27	237	129	6,60	213	146	6,18	197	158	1,2	37070 & 37090
8,62	277	113	7,94	252	125	7,53	237	135	1,5	37080 & 37090
10,51	335	94	9,84	310	102	9,42	295	108	2,0	37090 & 37090


Calculate  $N_{min}$  with  $N_{min} = \sqrt{L_{min}/A_{L2} \times 10^{-9}}$

▲ Preferred combinations.



\* For frequencies beyond 40 kHz enter the table at  $f/40 \times I_M^2 L$  and calculate  $N_{max} = (N_{max} \times I_M)/I_M \times \sqrt{f/40}$  (f in kHz).

\*\* For frequencies beyond 10 kHz enter the table at  $0,1 f \times I_M^2 L$  and calculate  $N_{max} = (N_{max} \times I_M)/I_M \times \sqrt{0,1 f}$  (f in kHz).

## COIL FORMER

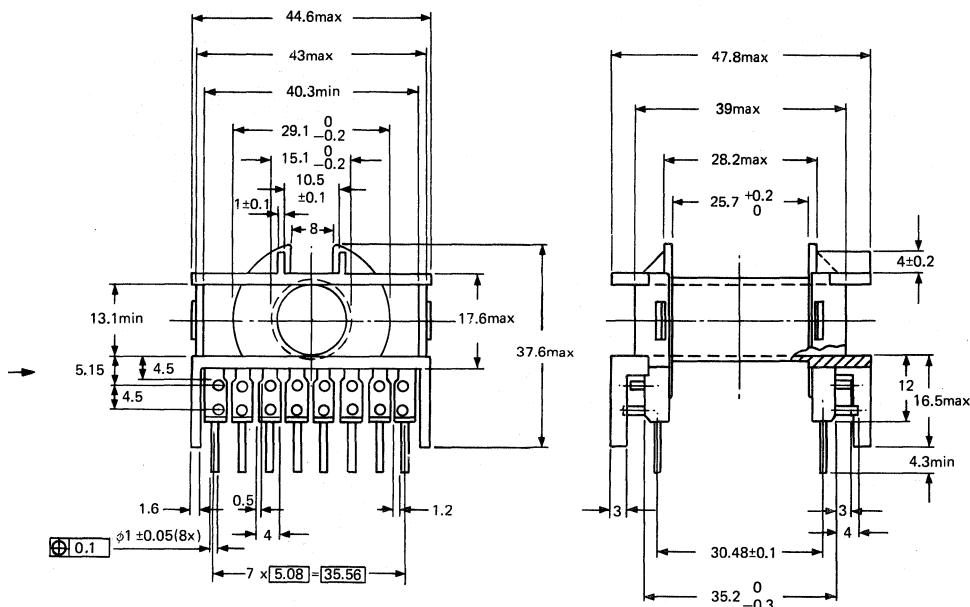

Pin arrangement

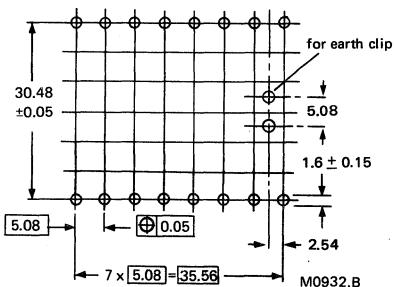

## Material

Minimum window area

Mean length of turn

Flammability

Solderability

Catalogue number

glass-fibre-filled polyterephthalate;  
16 copper-nickel alloy pins are inserted177 mm<sup>2</sup>



69 mm

according to UL94 V-0

400 °C for 4 s


4322 021 33860

## MOUNTING PARTS

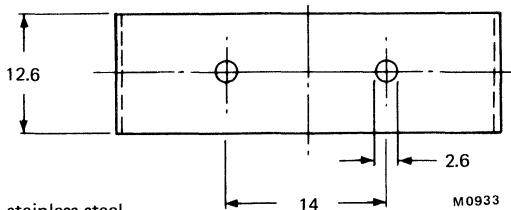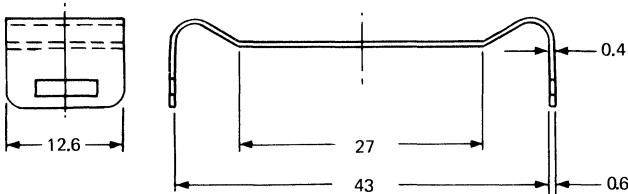

Assembly clip.  
Material  
Catalogue number

stainless steel  
4322 021 33900

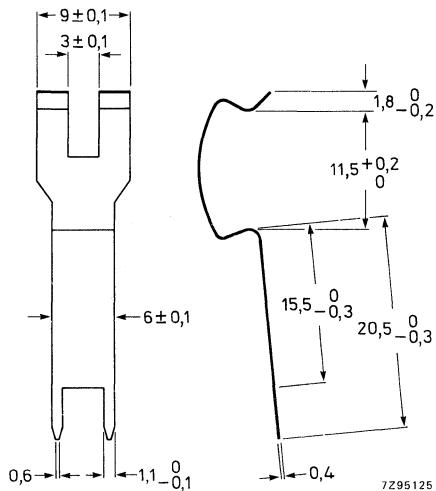


Earth clip.  
Material  
Terminations  
Catalogue number

nickel silver  
hot tinned  
4322 021 33900

Both core halves can be connected to earth by means of this clip.

## ETD44 SYSTEM

## FERROXCUBE CORE

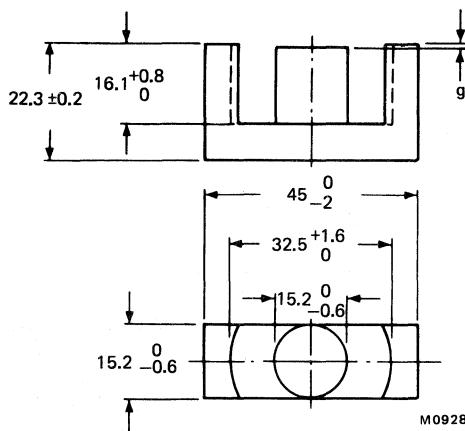

Material: Ferroxcube grade 3C8 and 3C85

Mass per core: 47 g

		catalogue number	
gap width mm	nominal $A_L$ nH	grade 3C8	grade 3C85
$\cong 0$	$3500 \pm 25\%$	● 4312 020 37100	● 4312 020 37300
$0.2 \pm 0.03$	800	4312 020 37110	4312 020 37310
$0.5 \pm 0.05$	400	4312 020 37120	4312 020 37320
$1.0 \pm 0.1$	230	4312 020 37130	4312 020 37330
$1.5 \pm 0.15$	170	4312 020 37140	4312 020 37340

The  $A_L$  values shown above apply to the gapped core indicated, assembled with an ungapped core.

- Preferred type.

**EFFECTIVE PARAMETERS**

For calculating the magnetic properties of a pair of cores, the following parameters should be used.

parameter	symbol	value	unit
effective magnetic path length	$l_e$	103	mm
effective area of magnetic path	$A_e$	173	mm <sup>2</sup>
effective magnetic volume	$V_e$	17 800	mm <sup>3</sup>
core factor $\sum \frac{l}{A}$	$C_1$	0,5886	mm <sup>-1</sup>

**NOMINAL DESIGN DATA FOR A PAIR OF CORES**

parameter	symbol	value	unit
centre pole area	$A_{min}$	174	mm <sup>2</sup>
length of the mean turn	$l_w$	77	mm

**ELECTRICAL AND MAGNETIC PROPERTIES OF A PAIR OF CORES IN FXC 3C8**

property	temperature (°C)	frequency (kHz)	parameter	value	unit
total power loss (P)	60 – 100	25	$\hat{B} = 200 \text{ mT}^*$	< 3,6	W
saturation induction ( $\hat{B}_{max}$ )	100	25	$H = 250 \text{ A/m}$	$\geq 320$	mT

**ELECTRICAL AND MAGNETIC PROPERTIES OF A PAIR OF CORES IN FXC 3C85**

property	temperature (°C)	frequency (kHz)	parameter	value	unit
total power loss (P)	60 – 100	25 100	$\hat{B} = 200 \text{ mT}^*$ $\hat{B} = 100 \text{ mT}^*$	< 2,5 < 3	W
saturation induction ( $\hat{B}_{max}$ )	100	25	$H = 250 \text{ A/m}$	$\geq 320$	mT

$$* \hat{B} = \frac{\sqrt{2} U}{\omega A_{min} N}$$

## CHOKE DESIGN CHART

For application classes I, II and III see 'Power choke design' in the Introduction.

class I			class II*			class III**			centre leg gap width mm	core halves ▲ catalogue number 4312 020 followed by
$I_M^2 L$	$N_{max} \times I_M$	$A_{L2}$	$I_M^2 L$	$N_{max} \times I_M$	$A_{L2}$	$I_M^2 L$	$N_{max} \times I_M$	$A_{L2}$		
mJ	A	nH	mJ	A	nH	mJ	A	nH		
3,63	91,7	431	2,56	63,9	626	1,89	46,7	866	0,2	37100 & 37110
5,10	127	317	4,01	98,8	410	3,32	81,4	501	0,4	37110 & 37110
6,33	148	289	5,24	120	364	4,56	102	435	0,5	37100 & 37120
7,62	179	238	6,52	151	287	5,82	133	329	0,7	37110 & 37120
9,91	226	194	8,81	198	225	8,12	180	250	1,0	37120 & 37120
11,0	253	172	9,93	225	197	9,23	207	216	1,2	37110 & 37130
13,1	295	151	12,0	266	169	11,3	249	183	1,5	37120 & 37130
14,1	319	139	13,0	291	154	12,3	273	165	1,7	37110 & 37140
16,0	357	125	14,9	329	138	14,2	311	147	2,0	37130 & 37130
18,7	416	108	17,6	387	117	16,9	369	124	2,5	37130 & 37140
21,2	470	96	20,1	442	103	19,4	424	108	3,0	37140 & 37140





Calculate  $N_{min}$  with  $N_{min} = \sqrt{L_{min}/A_{L2}} \times 10^6$

▲ Preferred combinations.

\* For frequencies beyond 40 kHz enter the table at  $f/40 \times I_M^2 L$  and calculate  $N_{max} = (N_{max} \times I_M)/I_M \times \sqrt{f/40}$  (f in kHz).

\*\* For frequencies beyond 10 kHz enter the table at  $0,1 f \times I_M^2 L$  and calculate  $N_{max} = (N_{max} \times I_M)/I_M \times \sqrt{0,1 f}$  (f in kHz).

## COIL FORMER

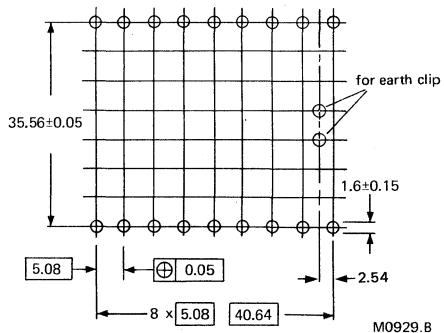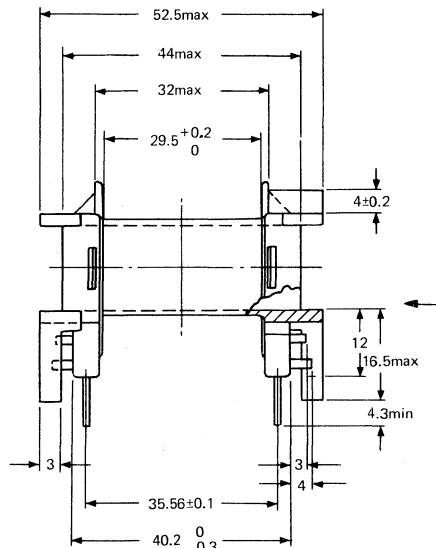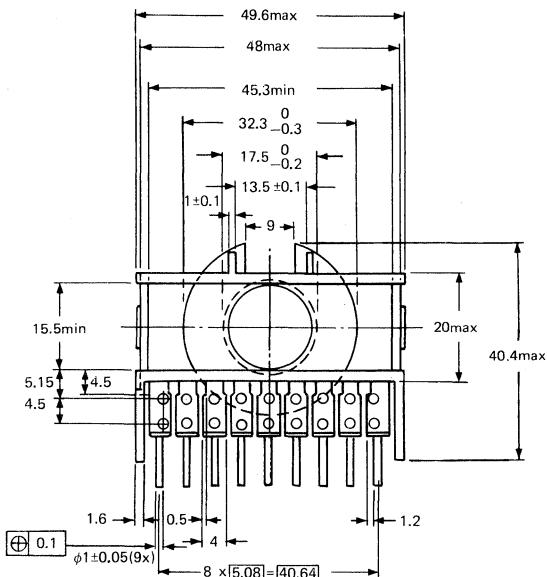

Material

glass-fibre-filled polyteraphthalate;  
18 copper-nickel alloy pins are inserted214 mm<sup>2</sup>

Minimum window area

77 mm

Mean length of turn

according to UL94 V-0

Flammability



400 °C for 4 s

Solderability

Catalogue number

4322 021 33870

## MOUNTING PARTS

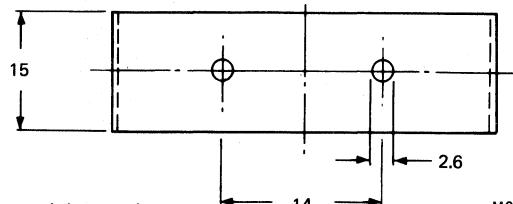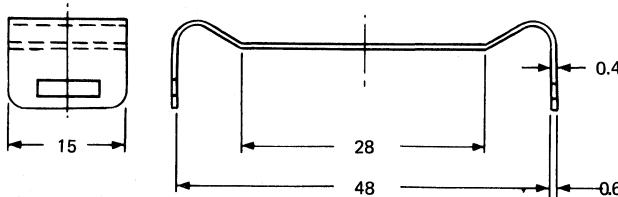


Assembly clip.  
Material  
Catalogue number

stainless steel  
4322 021 33910

M0930

Earth clip.  
Material  
Terminations  
Catalogue number


nickel silver  
hot tinned  
4322 021 33960

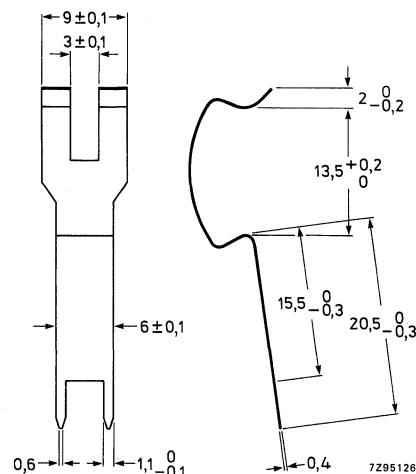

Both core halves can be connected to earth by means of this clip.

## ETD49 SYSTEM

## FERROXCUBE CORE

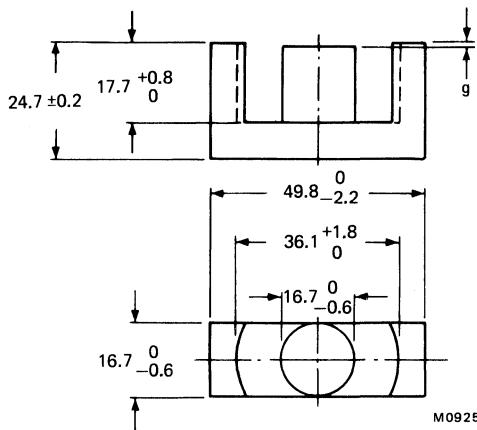

Material: Ferroxcube grade 3C8 and 3C85

Mass per core: 62 g

gap width mm	nominal $A_L$ nH	catalogue number	
		grade 3C8	grade 3C85
≈ 0	$4000 \pm 25\%$	• 4312 020 37150	• 4312 020 37350
$0,2 \pm 0,03$	1000	4312 020 37160	4312 020 37360
$0,5 \pm 0,05$	480	4312 020 37170	4312 020 37370
$1,0 \pm 0,1$	270	4312 020 37180	4312 020 37380
$2,0 \pm 0,2$	150	4312 020 37190	4312 020 37390

The  $A_L$  values shown above apply to the gapped core indicated, assembled with an ungapped core.

- Preferred type.

**EFFECTIVE PARAMETERS**

For calculating the magnetic properties of a pair of cores, the following parameters should be used.

parameter	symbol	value	unit
effective magnetic path length	$l_e$	114	mm
effective area of magnetic path	$A_e$	211	mm <sup>2</sup>
effective magnetic volume	$V_e$	24 000	mm <sup>3</sup>
core factor $\sum \frac{l}{A}$	$C_1$	0,5335	mm <sup>-1</sup>

**NOMINAL DESIGN DATA FOR A PAIR OF CORES**

parameter	symbol	value	unit
centre pole area	$A_{min}$	211	mm <sup>2</sup>
length of mean turn	$l_w$	85	mm

**ELECTRICAL AND MAGNETIC PROPERTIES OF A PAIR OF CORES IN FXC 3C8**

property	temperature (°C)	frequency (kHz)	parameter	value	unit
total power loss (P)	60 – 100	25	$\hat{B} = 200 \text{ mT}^*$	$< 4,6$	W
saturation induction ( $\hat{B}_{max}$ )	100	25	$H = 250 \text{ A/m}$	$\geq 320$	mT

**ELECTRICAL AND MAGNETIC PROPERTIES OF A PAIR OF CORES IN FXC 3C85**

property	temperature (°C)	frequency (kHz)	parameter	value	unit
total power loss (P)	60 – 100	25 100	$\hat{B} = 200 \text{ mT}^*$ $\hat{B} = 100 \text{ mT}^*$	$< 3,4$ $< 4$	W
saturation induction ( $\hat{B}_{max}$ )	100	25	$H = 250 \text{ A/m}$	$\geq 330$	mT

$$* \hat{B} = \frac{\sqrt{2} U}{\omega A_{min} N}$$

## CHOKE DESIGN CHART

For application classes I, II and III see 'Power choke design' in the Introduction.

class I			class II*			class III**			centre leg gap width mm	core halves ▲ catalogue number 4312 020 followed by
$I_M^2 L$	$N_{max} \times I_M$	$A_{L2}$	$I_M^2 L$	$N_{max} \times I_M$	$A_{L2}$	$I_M^2 L$	$N_{max} \times I_M$	$A_{L2}$		
mJ	A	nH	mJ	A	nH	mJ	A	nH		
4,68	97,5	492	3,25	66,9	727	2,35	47,8	1026	0,2	37150 & 37160
6,50	133	366	5,04	102	481	4,12	83,1	596	0,4	37160 & 37160
8,02	155	334	6,57	124	428	5,65	105	516	0,5	37150 & 37170
9,63	187	276	8,15	155	337	7,33	136	390	0,7	37160 & 37170
12,5	235	226	11,0	204	265	10,1	184	297	1,0	37170 & 37170
13,9	263	201	12,4	231	232	11,5	212	256	1,2	37160 & 37180
16,5	306	176	15,0	274	199	14,1	255	216	1,5	37170 & 37180
20,1	370	147	18,6	339	162	17,7	319	173	2,0	37180 & 37180
21,3	394	137	19,8	362	151	18,9	342	161	2,2	37160 & 37190
23,5	430	127	22,0	399	138	21,1	379	146	2,5	37170 & 37190
26,7	487	113	25,2	455	122	24,3	436	128	3,0	37180 & 37190
32,7	593	93	31,2	561	99	30,2	542	103	4,0	37190 & 37190


Calculate  $N_{min}$  with  $N_{min} = \sqrt{L_{min}/A_{L2} \times 10^{-9}}$

▲ Preferred combinations.



\* For frequencies beyond 40 kHz enter the table at  $f/40 \times I_M^2 L$  and calculate  $N_{max} = (N_{max} \times I_M)/I_M \times \sqrt{f/40}$  (f in kHz).

\*\* For frequencies beyond 10 kHz enter the table at  $0,1 f \times I_M^2 L$  and calculate  $N_{max} = (N_{max} \times I_M)/I_M \times \sqrt{0,1 f}$  (f in kHz).

## COIL FORMER

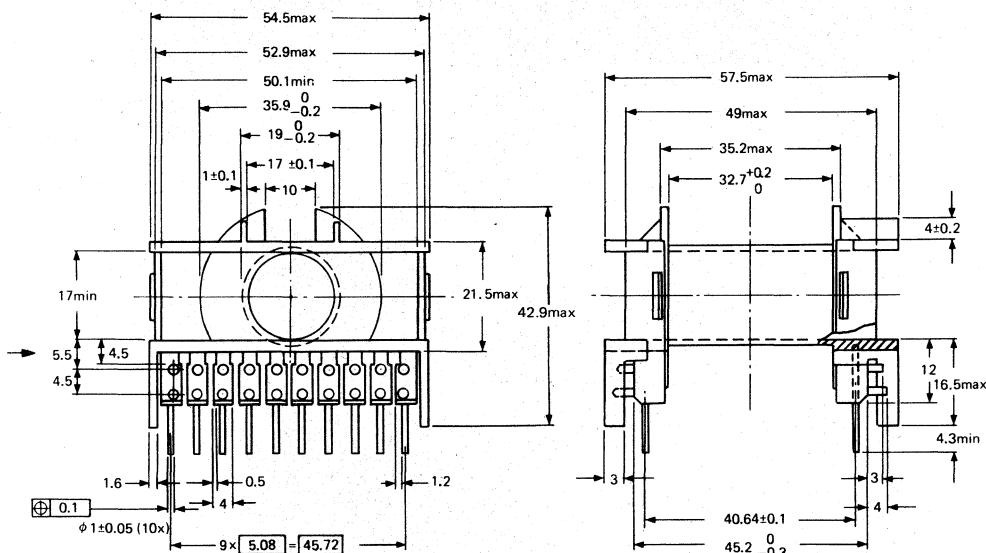

Pin arrangement

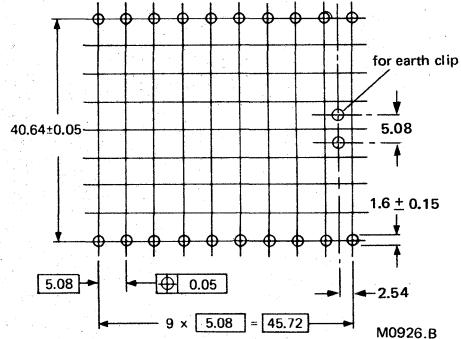

## Material

glass-fibre-filled polyteraphthalate;  
20 copper-nickel alloy pins are inserted

273 mm<sup>2</sup>

85 mm

according to UL94 V-0

400 °C for 4 s

4322 021 33880

## Minimum window area



## Mean length of turn

## Flammability

## Solderability

## Catalogue number

## MOUNTING PARTS

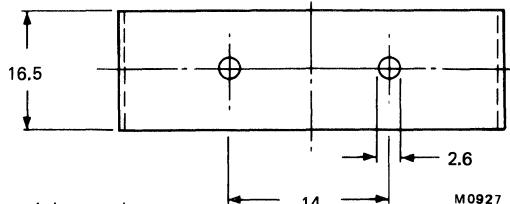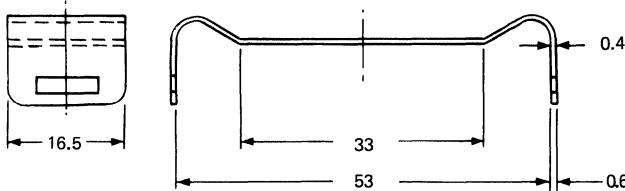


Assembly clip.  
Material  
Catalogue number

stainless steel  
4322 021 33920


Earth clip.  
Material  
Terminations  
Catalogue number

nickel silver  
hot tinned  
4322 021 33970

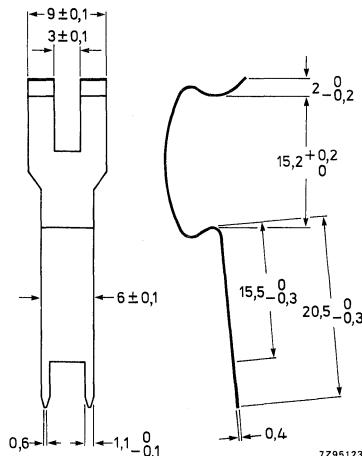

Both core halves can be connected to earth by means of this clip.

## I-CORE

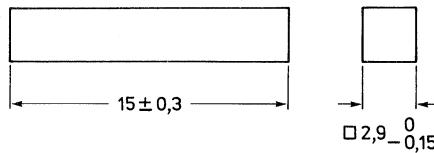


7295133

Ferroxcube grade  
Catalogue number

3C8  
3122 134 90730

## COIL FORMER

suited for one core I-15/3/3

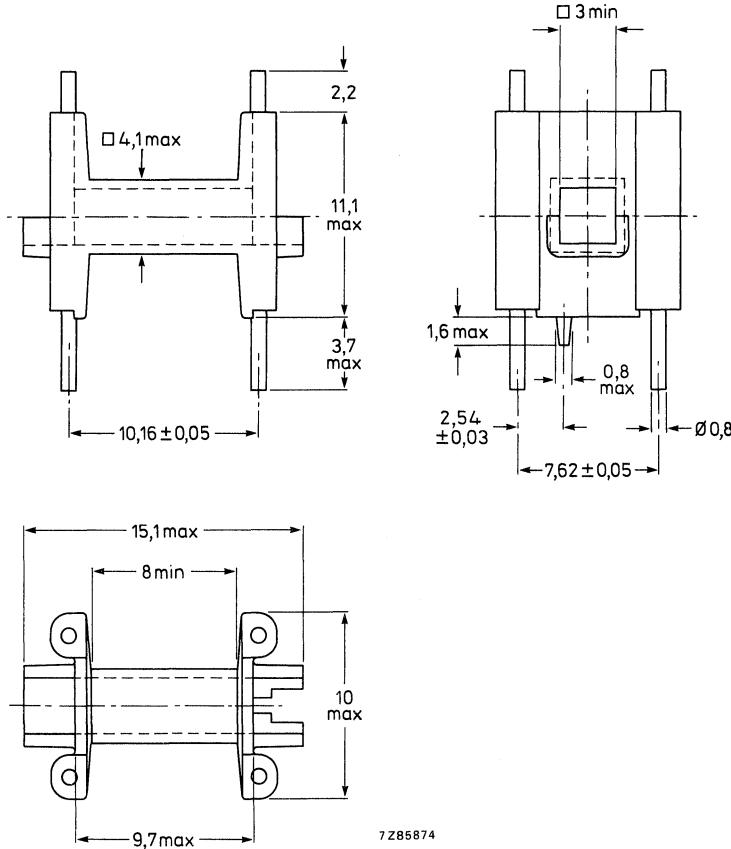


Catalogue number

3122 134 02590

I-20/6/5

I-CORE

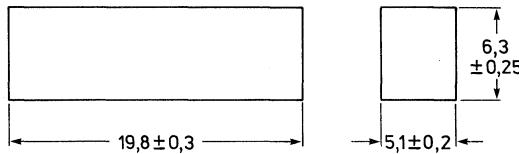


7Z95131

Ferroxcube grade  
Catalogue number

3C8  
3122 134 90720

## COIL FORMER


suited for one core I-20/6/5

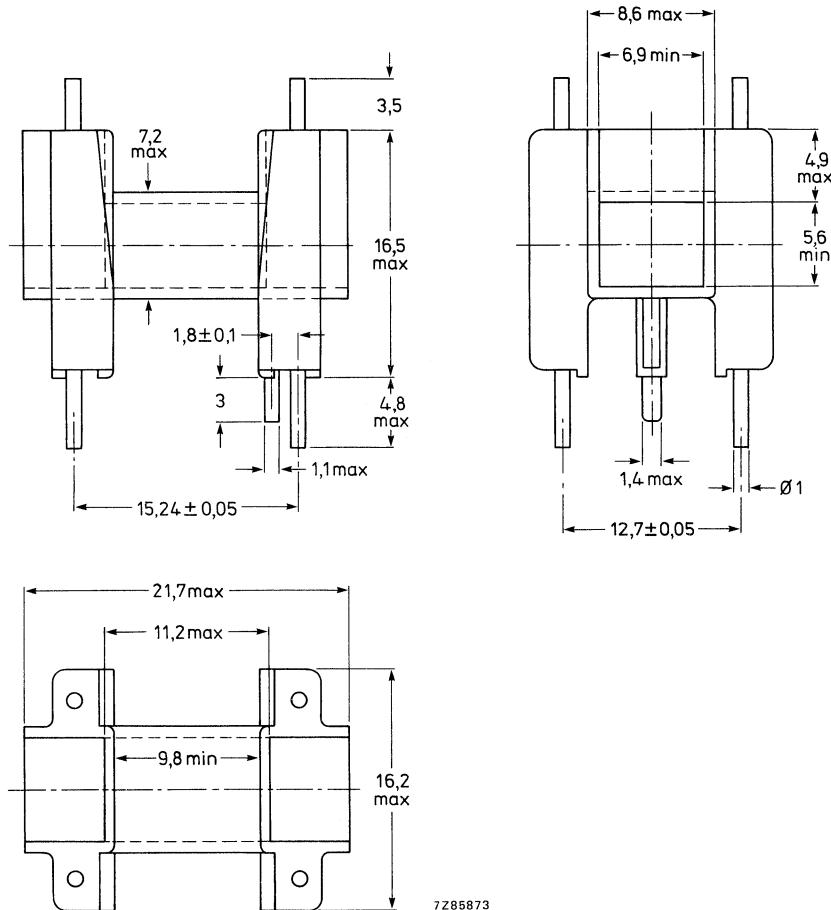

Catalogue number

3122 134 02540

## I-CORE

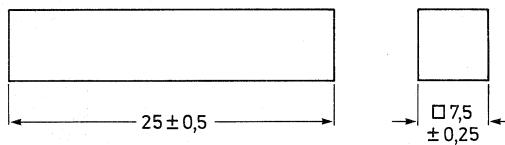


7Z95132

Ferroxcube grade  
Catalogue number

3C8  
3122 134 90620

## COIL FORMER


suites for one core I-25/7/7

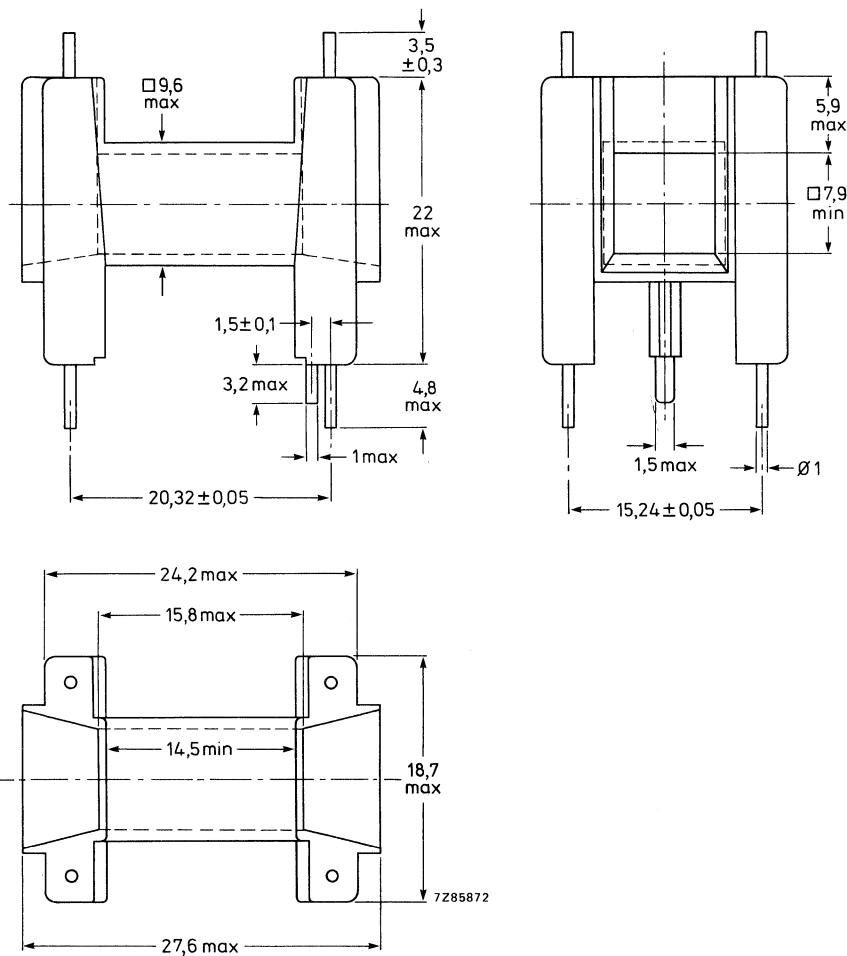

Catalogue number

3122 137 64140

## U-CORE

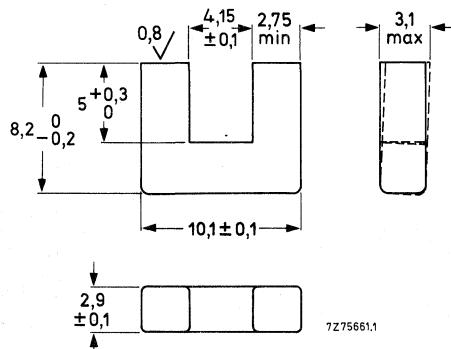

Mass      0,85 g

#### MAGNETIC DATA

Guaranteed values, measured at 16 kHz, for a core-pair UU-10/16/3.

grade	temperature °C ± 5	induction B (mT)	field strength H (A/m)	catalogue number of one U-core
3C8	25 100	≥ 140 ≥ 315	50 250	● 3122 134 91160

#### Magnetic dimensions

$$l_e = 38,4 \text{ mm}$$


$$A_e = 8,6 \text{ mm}^2$$

$$V_e = 330 \text{ mm}^3$$

- Preferred type.

## COIL FORMER


suited for two cores U-10/8/3

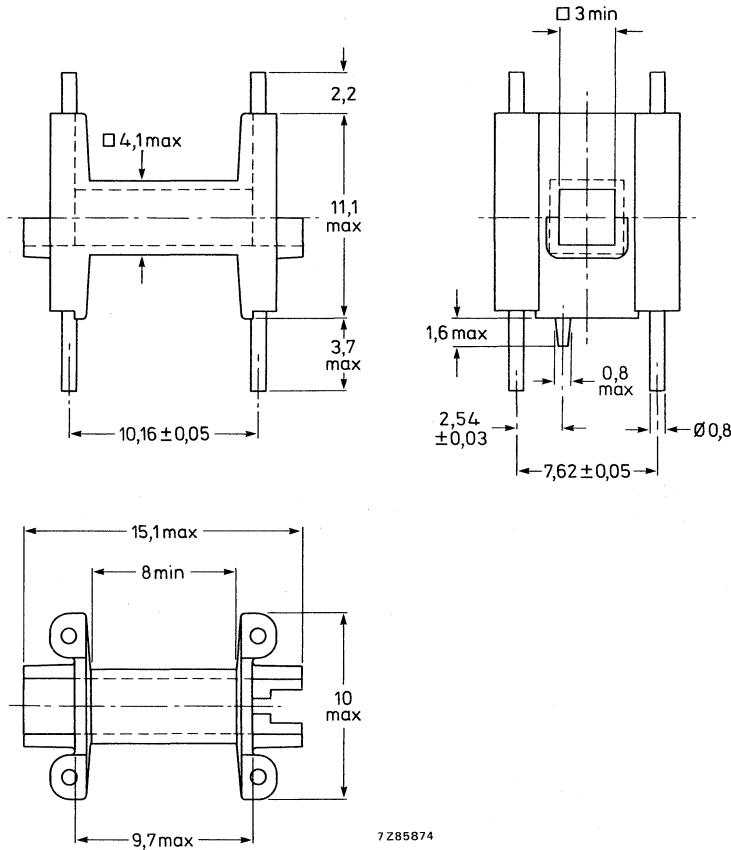

Catalogue number

3122 134 02590

## U-CORE

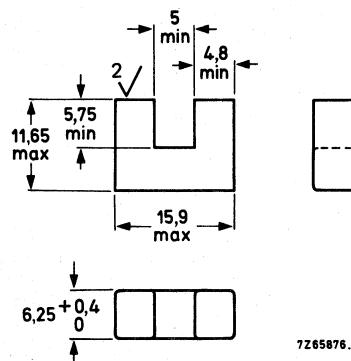

7265876.1

Mass 4,35 g

## MAGNETIC DATA

Guaranteed values, measured at 16 kHz, for a core-pair UU-15/22/6.

grade	temperature °C ± 5	induction B (mT)	field strength H (A/m)	losses W	catalogue number of one U-core
3C8	25	200	—	≤ 0,18	
	100	200	—	≤ 0,16	
	100	≥ 315	250	—	● 3122 134 90690

## Magnetic dimensions

$$l_e = 48 \text{ mm}$$


$$A_e = 30 \text{ mm}^2$$

$$V_e = 1440 \text{ mm}^3$$


- Preferred type.

## COIL FORMER

suited for two cores U-15/11/6

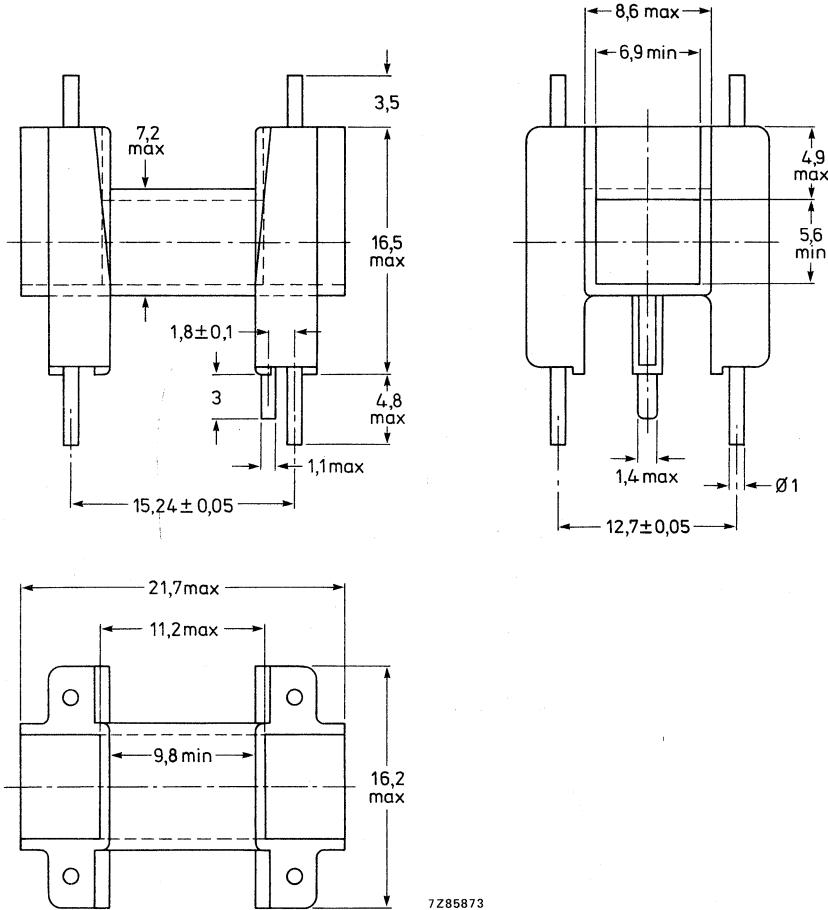


## CHARACTERISTIC CURVES

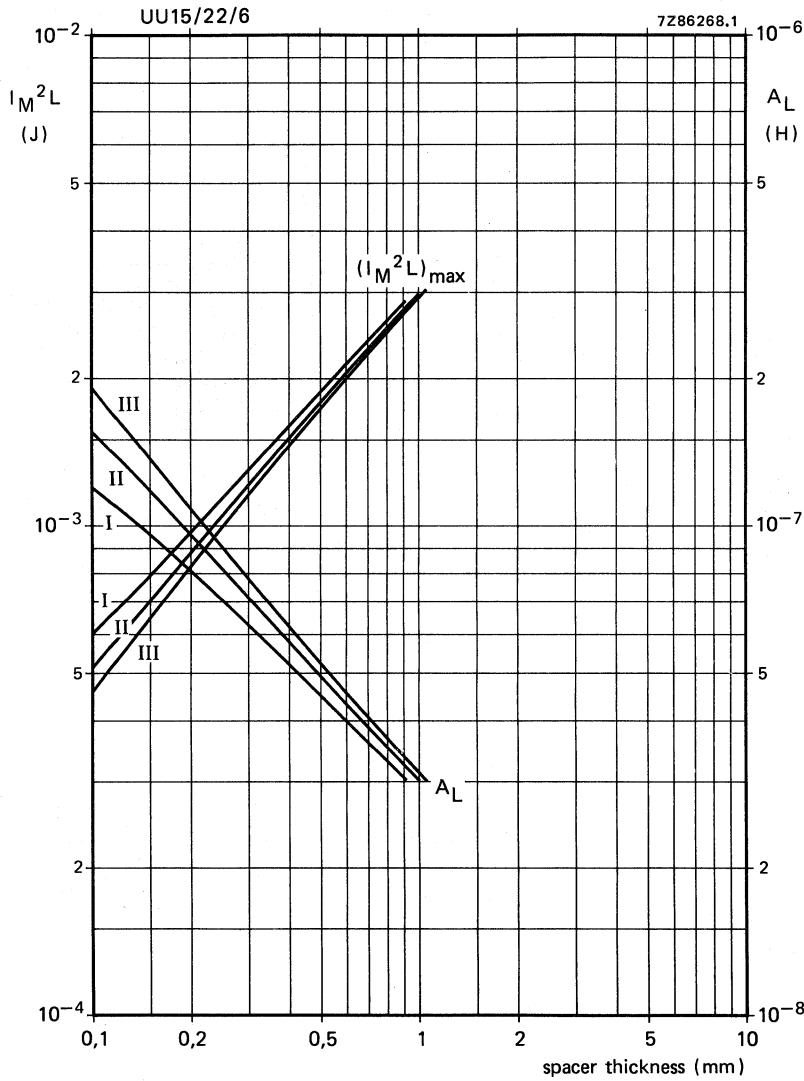

Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.

## U-CORE

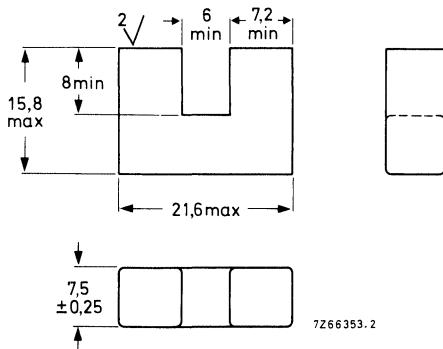

Mass 9 g

#### MAGNETIC DATA

Guaranteed values, measured at 16 kHz, for a core-pair UU-20/32/7.

grade	temperature °C ± 5	induction $\hat{B}$ (mT)	field strength $\hat{H}$ (A/m)	losses W	catalogue number of one U-core
3C8	25	200	—	≤ 0,46	● 3122 134 90200
	100	200	—	≤ 0,42	
	100	≥ 315	250	—	

#### Magnetic dimensions

$$l_e = 68 \text{ mm}$$


$$A_e = 56 \text{ mm}^2$$

$$V_e = 3800 \text{ mm}^3$$

- Preferred type.

## COIL FORMER


suited for two cores U-20/16/7

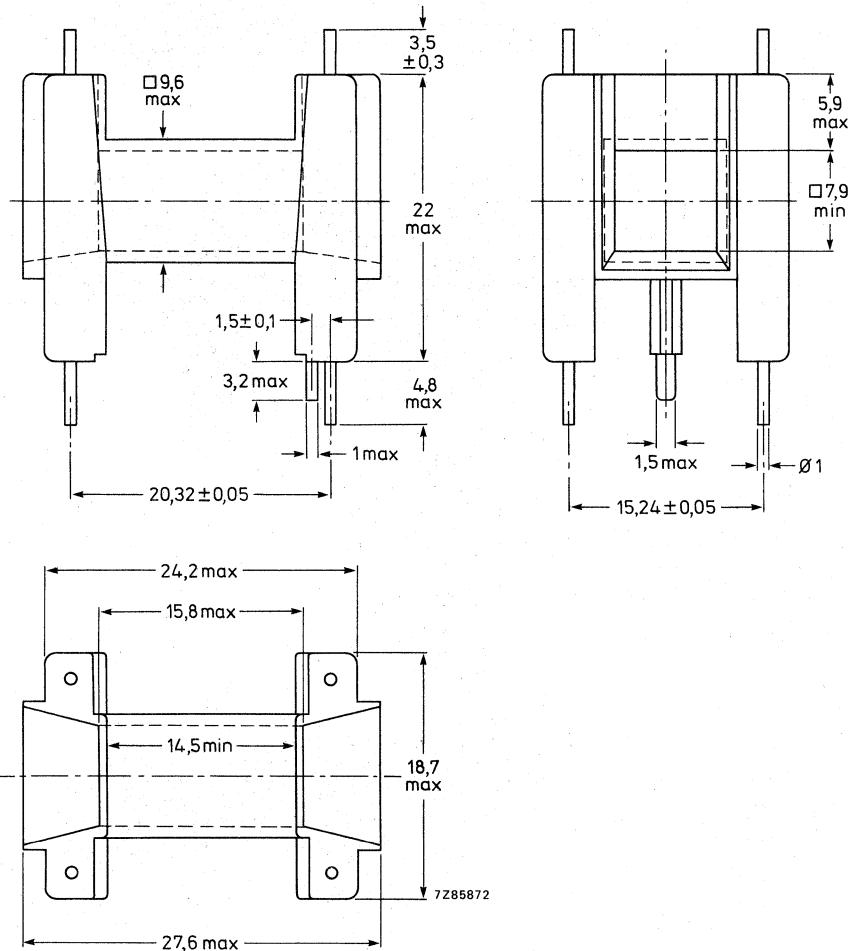

Catalogue number

3122 137 64140


## CHARACTERISTIC CURVES

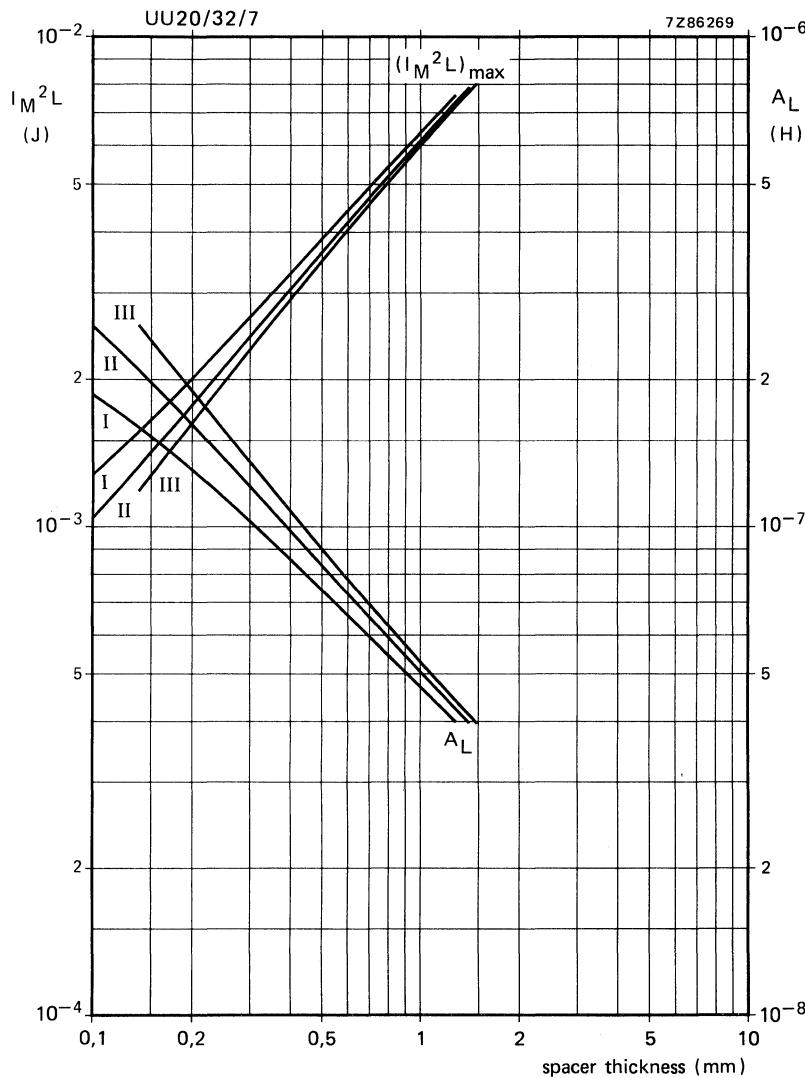

Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.

## U-CORE

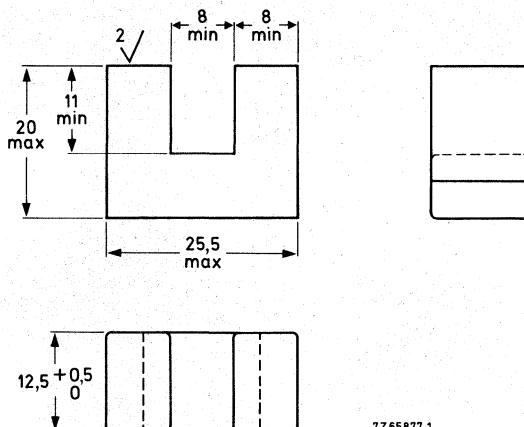

Mass 21 g

## MAGNETIC DATA

Guaranteed values, measured at 16 kHz, for a core-pair UU-25/40/13.

grade	temperature °C ± 5	induction $\hat{B}$ (mT)	field strength $\hat{H}$ (A/m)	losses W	catalogue number of one U-core
3C8	25 100 100	200 200 $\geq 315$	— — 250	$\leq 1,1$ $\leq 1,0$ —	● 3122 134 90460

## Magnetic dimensions

$$l_e = 86 \text{ mm}$$




$$A_e = 100 \text{ mm}^2$$

$$V_e = 8600 \text{ mm}^3$$

- Preferred type.

**COIL FORMER**

suited for two cores U-25/20/13

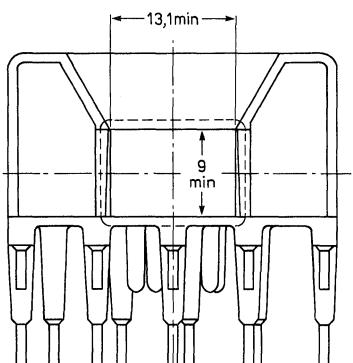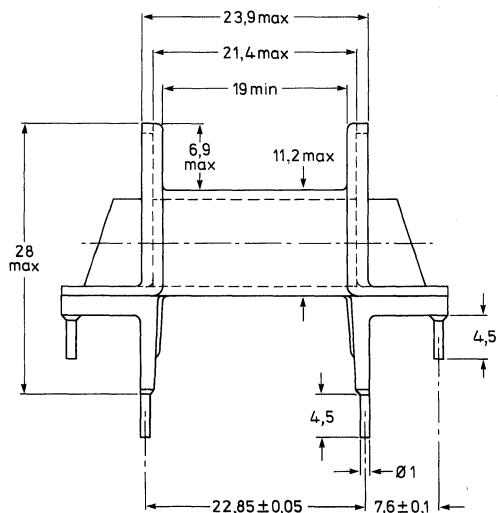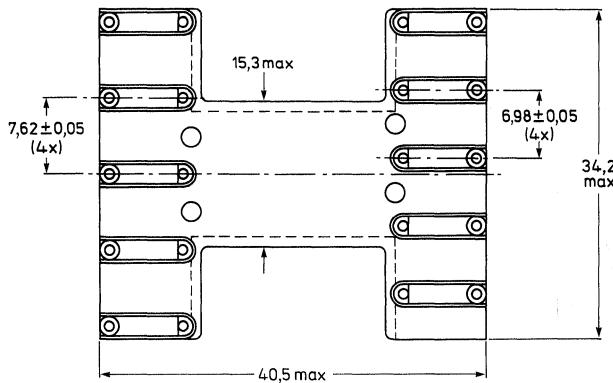


7Z85871

Catalogue number

3122 137 61910


## CHARACTERISTIC CURVES

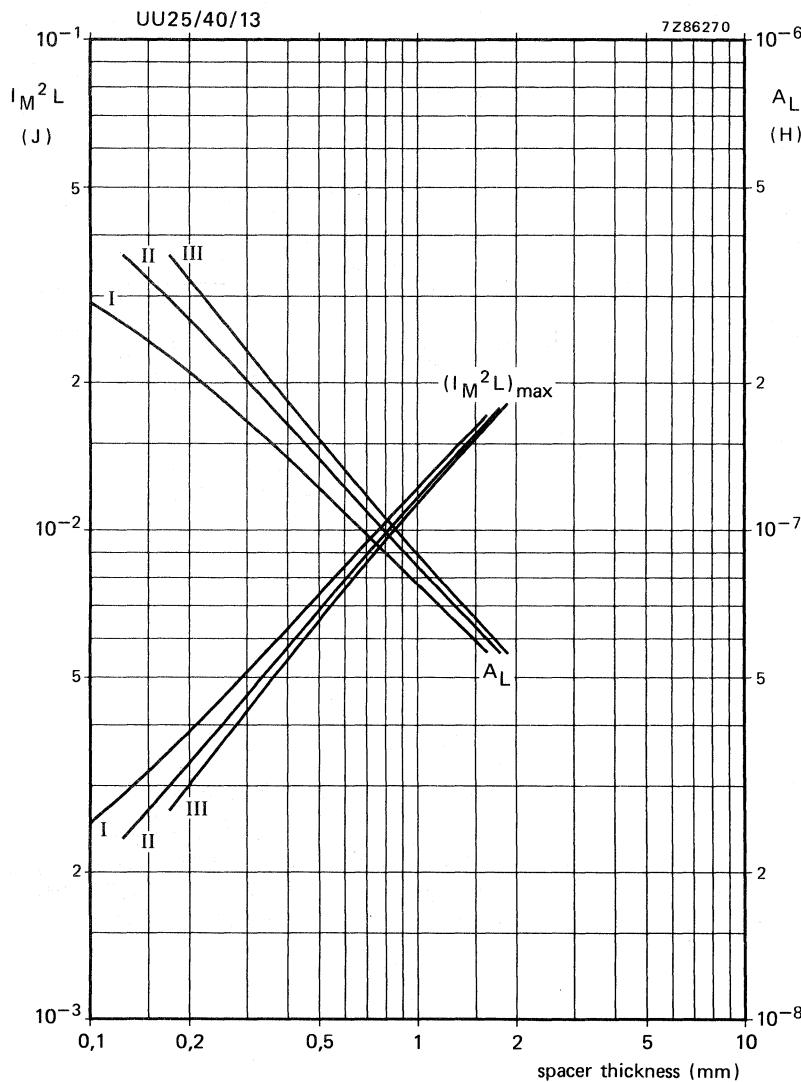

Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.

## U-CORE

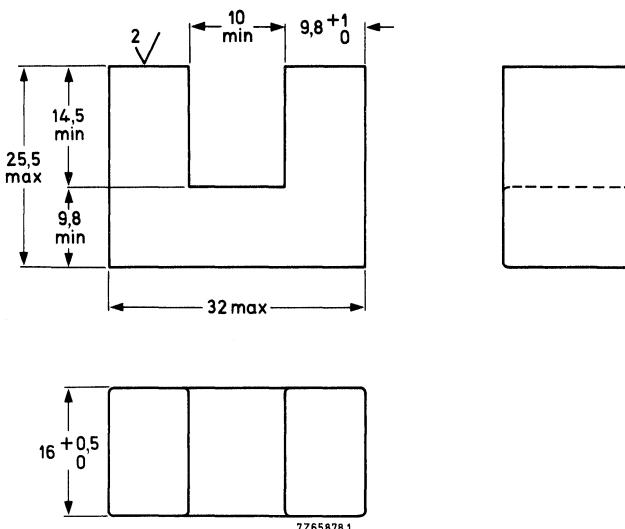

Mass 48 g

#### MAGNETIC DATA

Guaranteed values, measured at 16 kHz, for a core-pair UU-30/50/16.

grade	temperature °C ± 5	induction B (mT)	field strength H (A/m)	losses W	catalogue number of one U-core
3C8	25 100 100	200 200 ≥ 335	— — 400	≤ 2,4 ≤ 2,0 —	• 3122 134 90760

#### Magnetic dimensions

$$l_e = 111 \text{ mm}$$


$$A_e = 157 \text{ mm}^2$$

$$V_e = 17400 \text{ mm}^3$$

- Preferred type.


## COIL FORMER

suited for two cores U-30/25/16

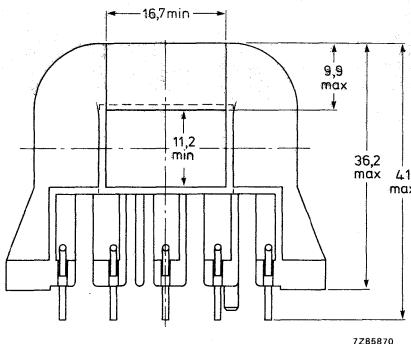


7285870

Catalogue number 3122 137 55360

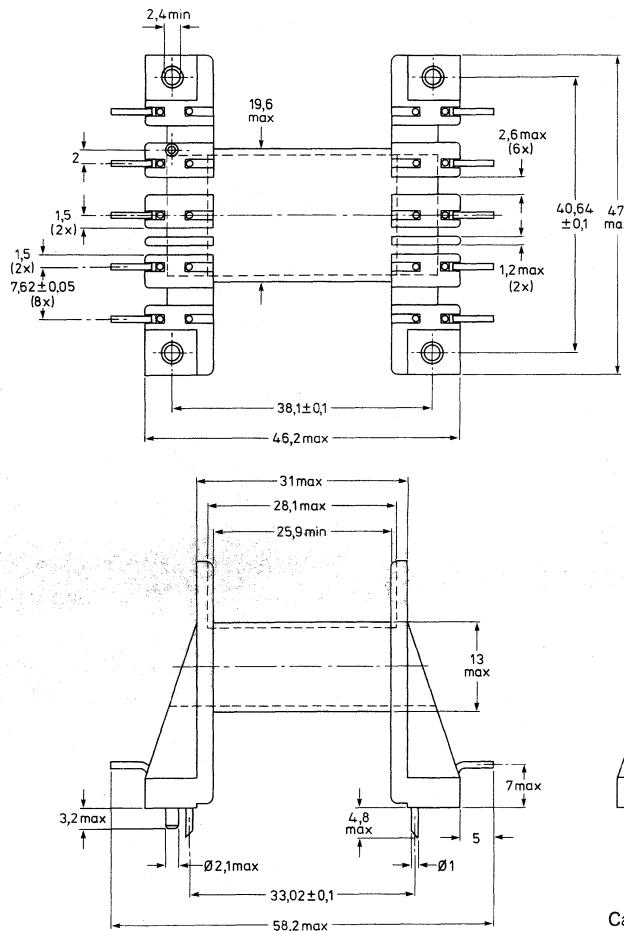


## CHARACTERISTIC CURVES

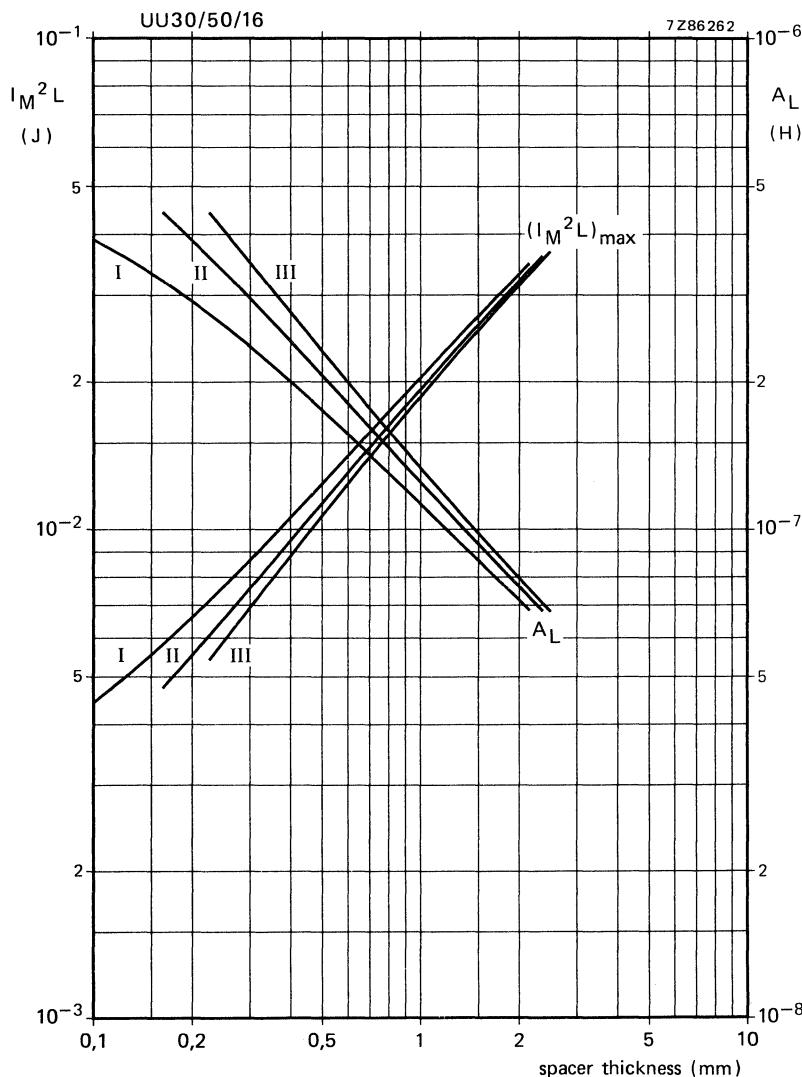

Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.

## U-CORE

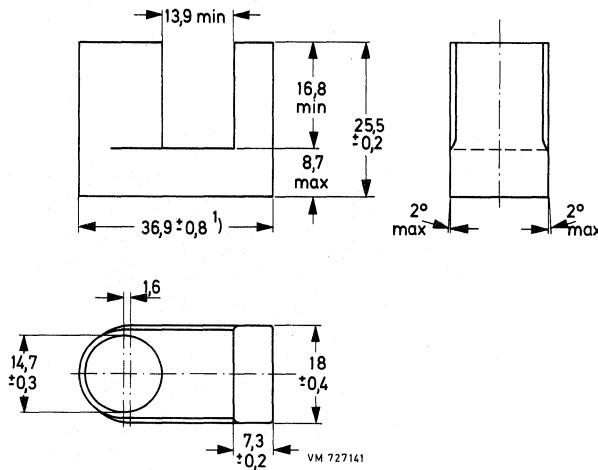

Mass 48 g

## MAGNETIC DATA

Guaranteed values, measured at 16 kHz, for a core pair UU 37/50/18

grade	temperature °C ± 5%	induction B (mT)	field strength H (A/m)	losses W	catalogue number
3C8	25	200	—	≤ 2,3	
	100	200	—	≤ 2,1	
	100	≥ 330	250	—	4312 020 34740


## Magnetic dimensions

$$l_e = 125 \text{ mm}$$

$$A_e = 150 \text{ mm}^2$$

$$V_e = 18800 \text{ mm}^3$$

## U-CORE

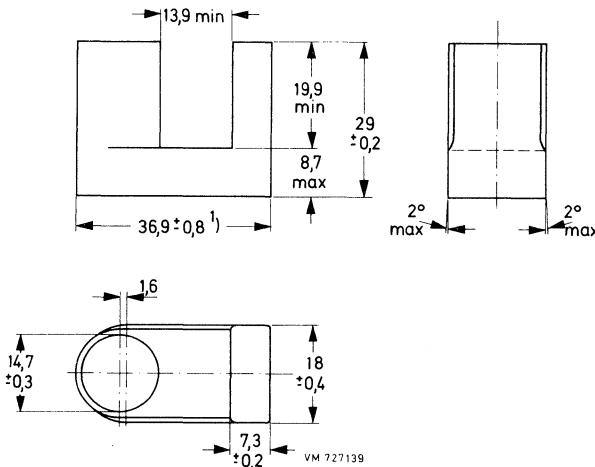

Mass 55 9

## MAGNETIC DATA

Guaranteed values, measured at 16 kHz, for a core pair UU 37/58/18

grade	temperature °C ± 5%	induction B (mT)	field strength H (A/m)	losses W	catalogue number
3C8	25 100 100	200 200 $\geq 330$	— — 250	$\leq 2,6$ $\leq 2,4$ —	• 4312 020 33710

## Magnetic dimensions



$$l_e = 145 \text{ mm}$$

$$A_e = 150 \text{ mm}^2$$

$$V_e = 21500 \text{ mm}^3$$

- Preferred type.

## UI-CORES

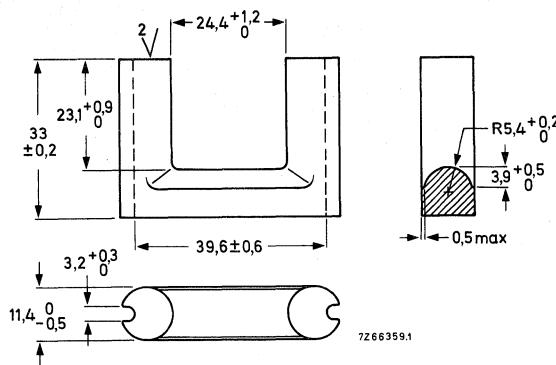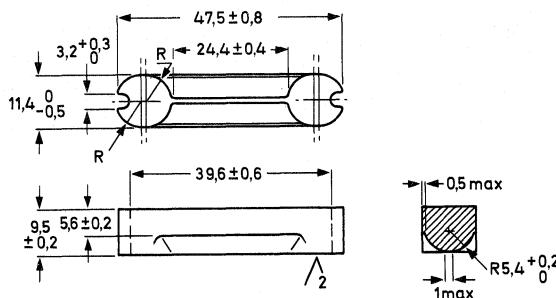

Mass      U-core    38 g  
          I-core    20 g

### MAGNETIC DATA

Guaranteed values, measured at 16 kHz, for a core-pair UI-46/43/11.

grade	temperature $^{\circ}\text{C} \pm 5$	induction $\dot{B}$ (mT)	field strength $H$ (A/m)	losses W	shape	catalogue number of one core
3C8	25	200	—	$\leq 1,97$	U	3122 104 90480
	100	200	—	$\leq 1,62$		3122 104 90470
	100	$\geq 290$	250	—		


### Magnetic dimensions

$$l_e = 129 \text{ mm}$$

$$A_e = 88 \text{ mm}^2$$

$$V_e = 11600 \text{ mm}^3$$

## U-CORE

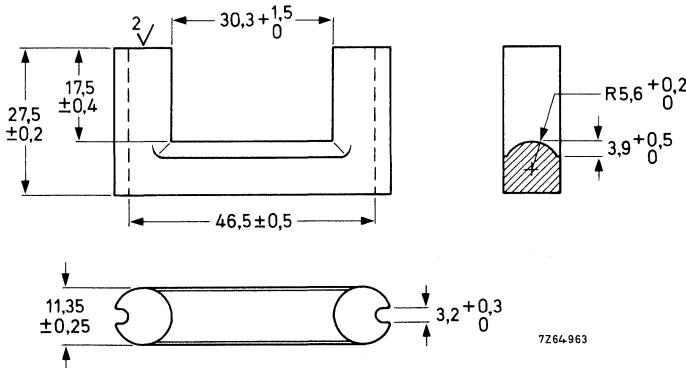

Mass 40 g

## MAGNETIC DATA

Guaranteed values, measured at 16 kHz, for a core-pair UU-52/56/11.

grade	temperature °C ± 5	induction B (mT)	field strength H (A/m)	losses W	catalogue number one U-core
3C8	25	200	—	≤ 1,9	• 3122 134 90480
	100	200	—	≤ 1,75	
	100	≥ 330	250	—	

## Magnetic dimensions


$$l_e = 165 \text{ mm}$$

$$A_e = 95 \text{ mm}^2$$

$$V_e = 15700 \text{ mm}^3$$

- Preferred type.

## U-CORE

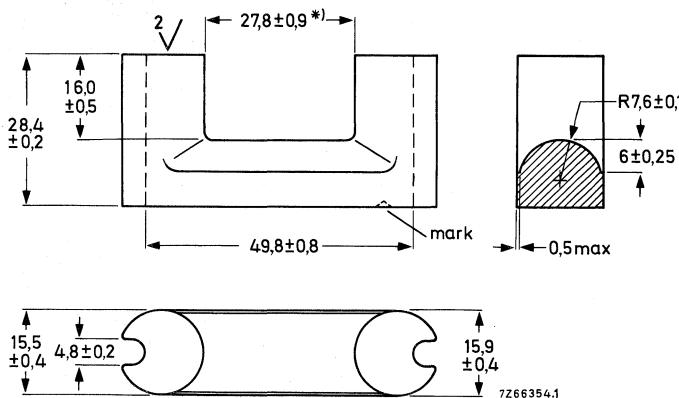

Mass 70 g

## MAGNETIC DATA

Guaranteed values, measured at 16 kHz, for a core-pair UU-57/57/16.

grade	temperature °C ± 5	induction $\hat{B}$ (mT)	field strength $\hat{H}$ (A/m)	losses W	catalogue number of one U-core
3C8	25	200	—	≤ 3,3	4312 020 33190
	100	200	—	≤ 3,05	
	100	≥ 330	250	—	

## Magnetic dimensions


$$l_e = 163 \text{ mm}$$

$$A_e = 171 \text{ mm}^2$$

$$V_e = 27500 \text{ mm}^3$$

\* The difference in splay between two U-cores, taken at random from one packing, will never exceed 0,8 mm.

## UI-CORES

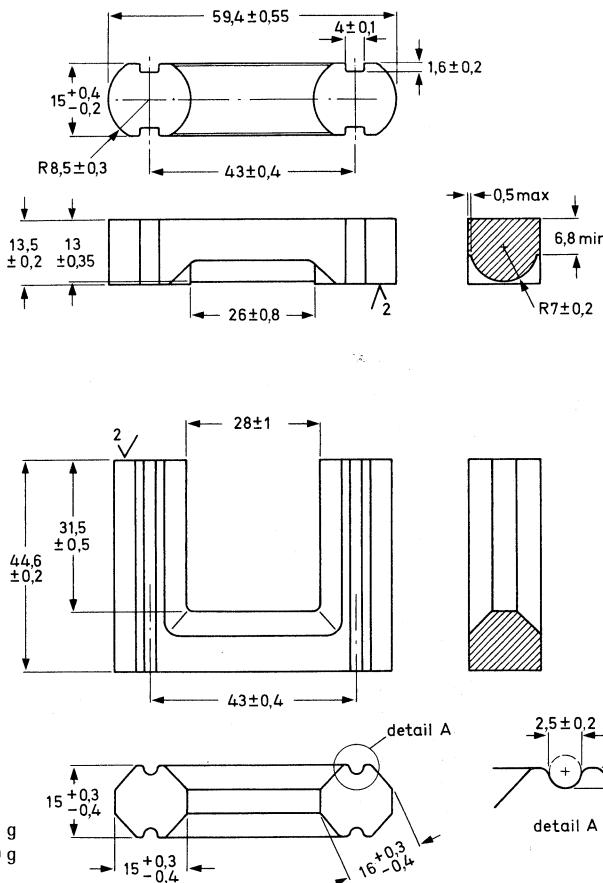

## MAGNETIC DATA


Guaranteed values, measured at 16 kHz, for a core-pair UI-58/58/16.

grade	temperature $^{\circ}\text{C} \pm 5$	induction $\hat{B}$ (mT)	field strength $\hat{H}$ (A/m)	losses W	shape	catalogue number of one core
3C8	25 100 100	200 200 $\geq 330$	— — 250	$\leq 3,5$ $\leq 3,2$ —	U I	3122 104 94760 3122 104 94770

## Magnetic dimensions

$$l_e = 164 \text{ mm}; A_e = 175 \text{ mm}^2; V_e = 28800 \text{ mm}^3.$$

## U-CORE

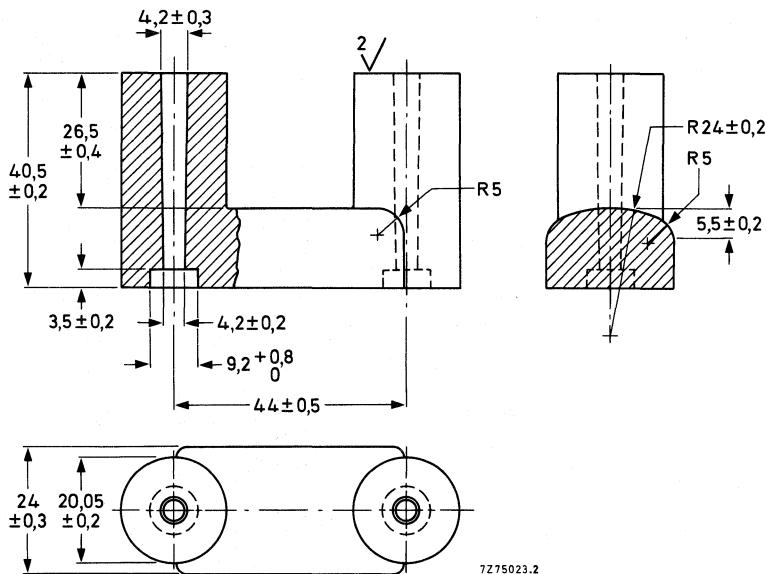

**Mass** 155 g

#### MAGNETIC DATA

Guaranteed values, measured at 16 kHz, for a core-pair UU-64/79/20

grade	temperature $^{\circ}\text{C} \pm 5$	induction $\dot{B}$ (mT)	field strength H (A/m)	losses W	catalogue number of one U-core
3C8	25 100 100	200 200 $\geq 330$	— — 250	$\leq 8,5$ $\leq 7,0$ —	3122 134 91390


#### Magnetic dimensions

$$l_e = 210 \text{ mm}$$

$$A_e = 290 \text{ mm}^2$$

$$V_e = 61000 \text{ mm}^3$$


## CHARACTERISTIC CURVES

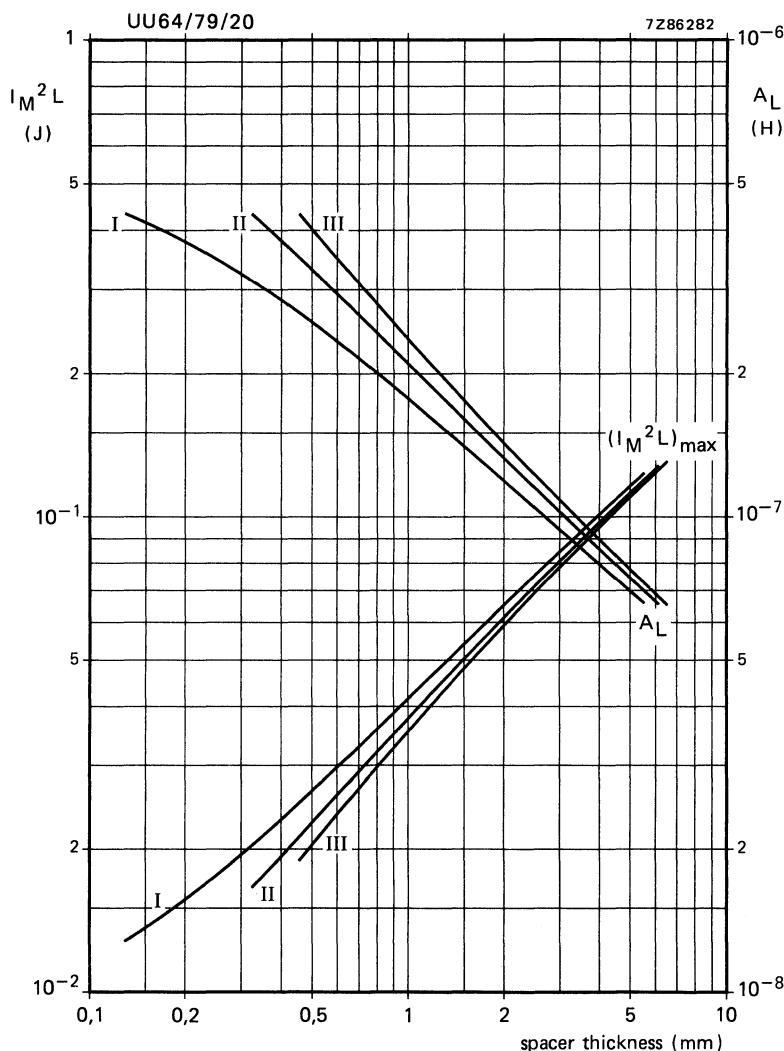

Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.

## U-CORE

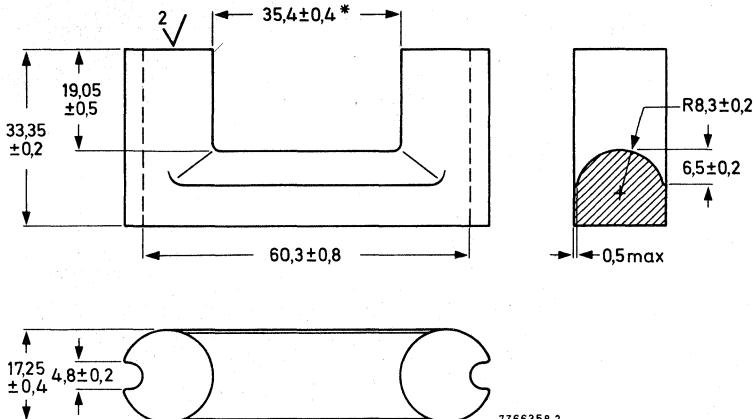

Mass 108 g

## MAGNETIC DATA

Guaranteed values, measured at 16 kHz, for a core-pair UU-70/67/17.

grade	temperature °C ± 5	induction $B$ (mT)	field strength $H$ (A/m)	losses W	catalogue number of one U-core
3C8	25	200	—	≤ 5,3	3122 104 93950
	100	200	—	≤ 5,0	
	100	≥ 330	250	—	

## Magnetic dimensions


$$l_e = 197 \text{ mm}$$

$$A_e = 214 \text{ mm}^2$$

$$V_e = 43800 \text{ mm}^3$$

\* The difference in splay between two U-cores taken at random from one packing will never exceed 1 mm.

### UI-CORES

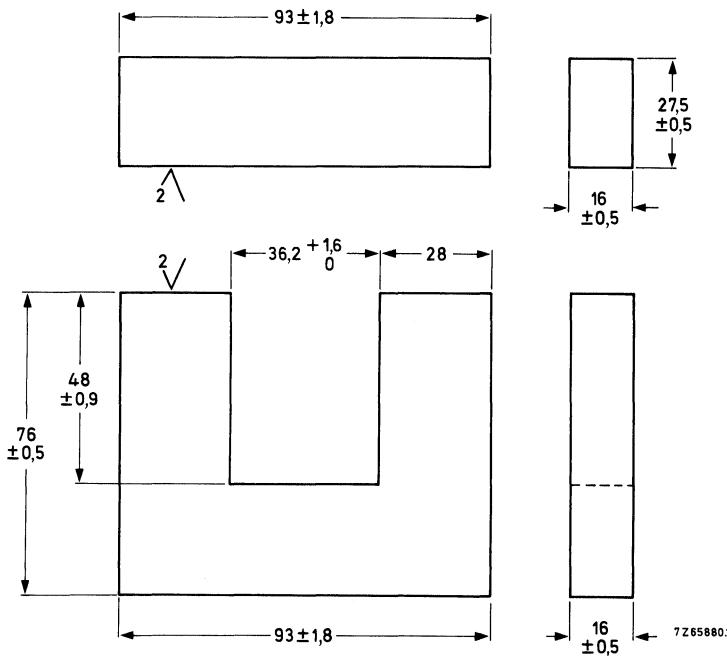

Mass      U-core      403 g  
          I-core      194 g

### MAGNETIC DATA


Guaranteed values, measured at 16 kHz, for core-pairs UI-93/104/16 and UU-93/152/16.

grade	temperature $^{\circ}\text{C} \pm 5$	induction $\hat{B}$ (mT)	field strength $\hat{H}$ (A/m)	losses W	shape	catalogue number of one core
3C8	25	200	—	$\leq 12,8$	UI	4312 020 33550
	100	200	—	$\leq 11,8$		4312 020 33560
	100	$\geq 330$	250	—		
3C8	25	200	—	$\leq 17,6$	UU	4312 020 33550
	100	200	—	$\leq 16,2$		
	100	$\geq 290$	250	—		

### Magnetic dimensions

	UI-93/104/16	UU-93/152/16	
$l_e$	254	350	mm
$A_e$	420	450	$\text{mm}^2$
$V_e$	107 000	147 000	$\text{mm}^3$


## CHARACTERISTIC CURVES

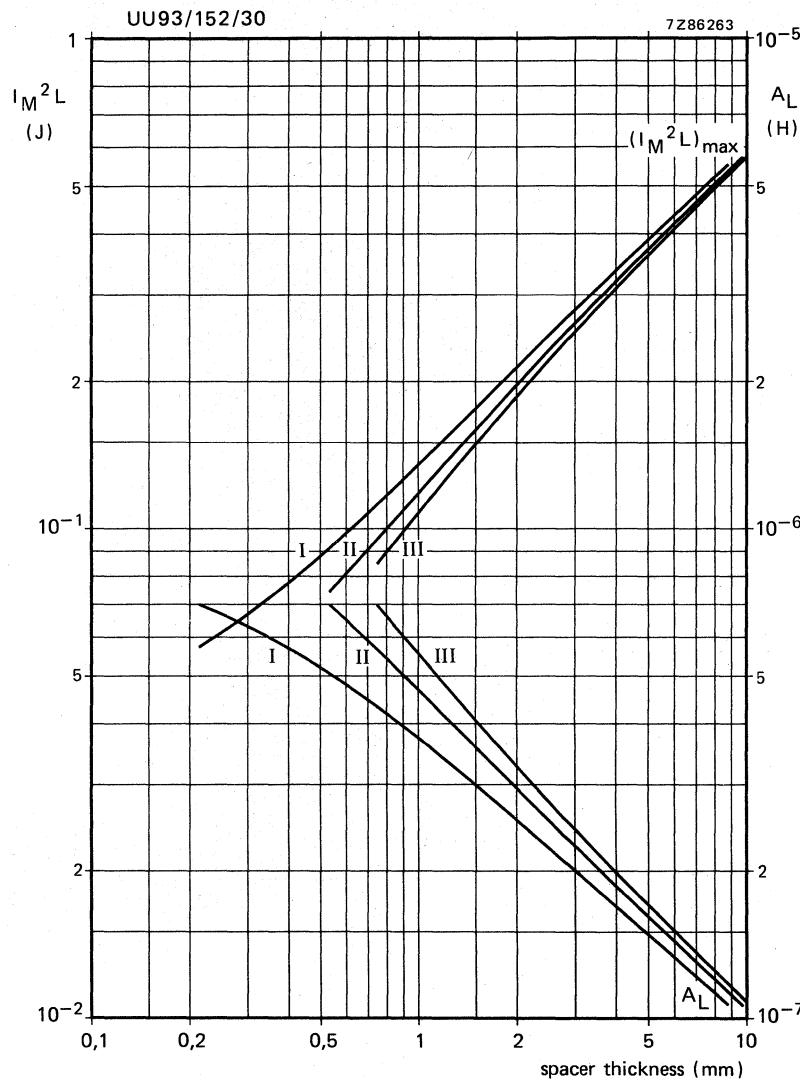

Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.

## UI-CORES

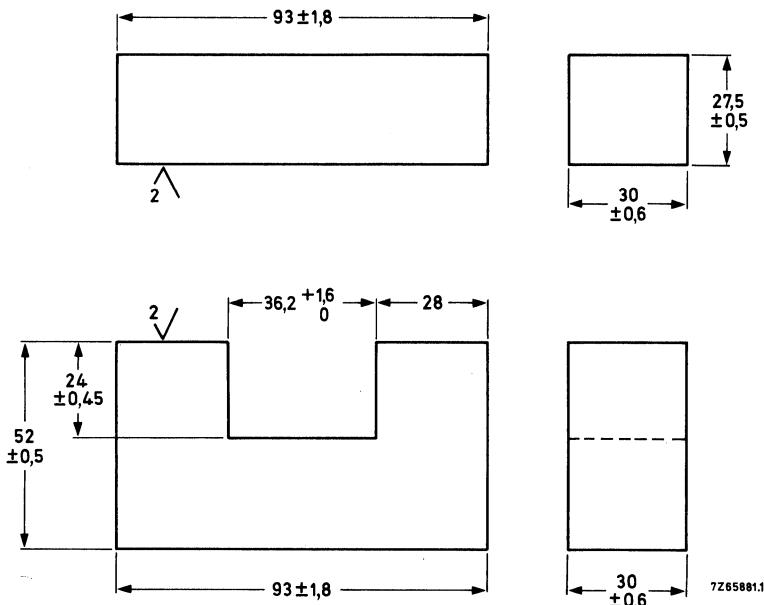

Mass      U-core      562 g  
          I-core      365 g

### MAGNETIC DATA


Guaranteed values, measured at 16 kHz, for core-pairs UI-93/80/30 and UU-93/104/30.

grade	temperature °C ± 5	induction $\hat{B}$ (mT)	field strength $\hat{H}$ (A/m)	losses W	shape	catalogue number of one core
3C8	25	200	—	≤ 19,0	UI	4312 020 33580
	100	200	—	≤ 17,4		4312 020 33590
	100	≥ 330	250	—		
3C8	25	200	—	≤ 24,0	UU	4312 020 33580
	100	200	—	≤ 22,0		
	100	≥ 290	250	—		

### Magnetic dimensions

	UI-93/80/30	UU-93/104/30	
$I_e$	204	254	mm
$A_e$	780	780	mm <sup>2</sup>
$V_e$	158 000	200 000	mm <sup>3</sup>


## CHARACTERISTIC CURVES

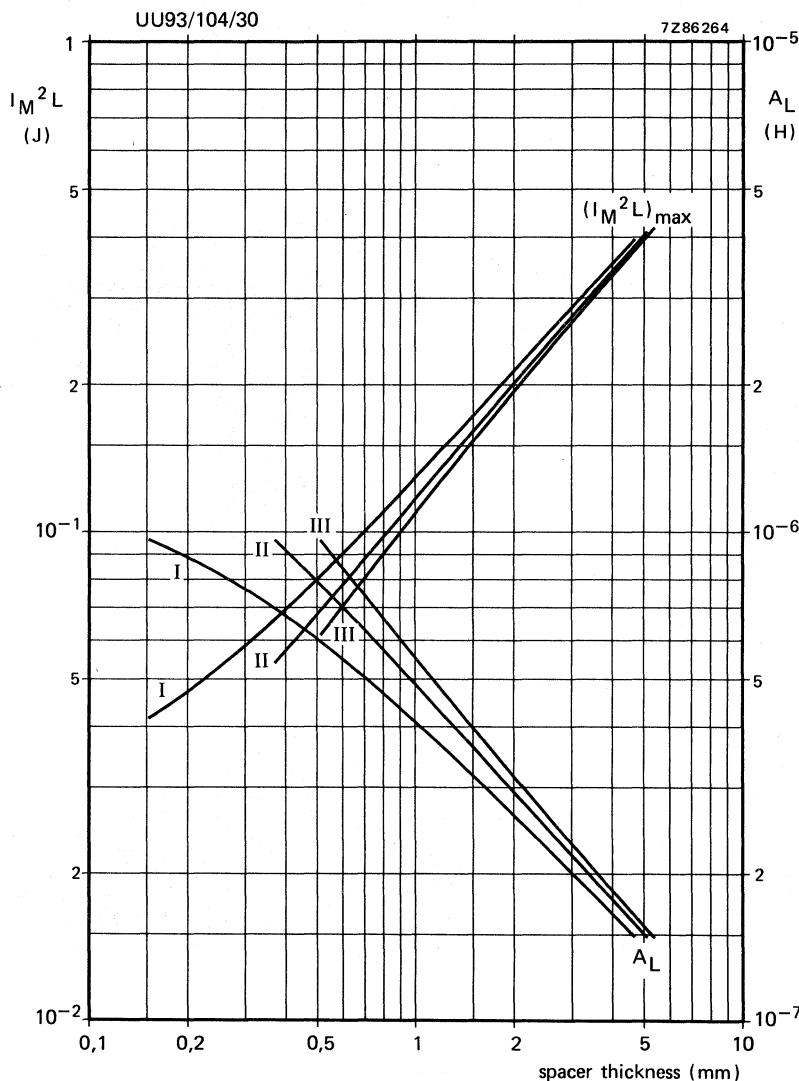

Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.

### UI-CORES

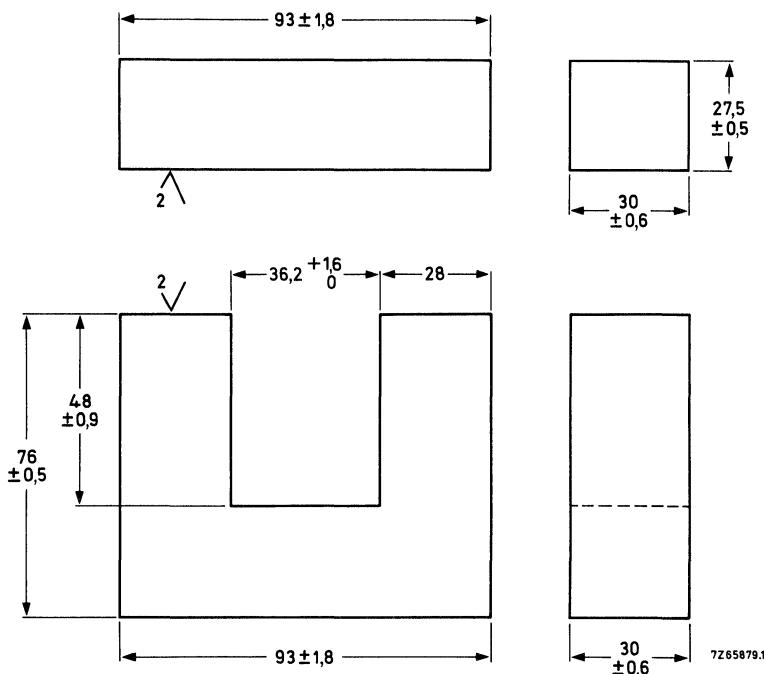

Mass      U-core      756 g  
          I-core      365 g

### MAGNETIC DATA


Guaranteed values, measured at 16 kHz, for core-pairs UI-93/104/30 and UU-93/152/30.

grade	temperature $^{\circ}\text{C} \pm 5$	induction $\hat{B}$ (mT)	field strength $\hat{H}$ (A/m)	losses W	shape	catalogue number of one core
3C8	25	200	—	$\leq 24,0$	UI	4312 020 33570
	100	200	—	$\leq 22,0$		4312 020 33590
	100	$\geq 330$	250	—		
3C8	25	200	—	$\leq 32,8$	UU	4312 020 33570
	100	200	—	$\leq 30,0$		
	100	$\geq 290$	250	—		

### Magnetic dimensions

	UI-93/104/30	UU-93/152/30	
$I_e$	254	350	mm
$A_e$	780	780	$\text{mm}^2$
$V_e$	200 000	273 000	$\text{mm}^3$


## CHARACTERISTIC CURVES

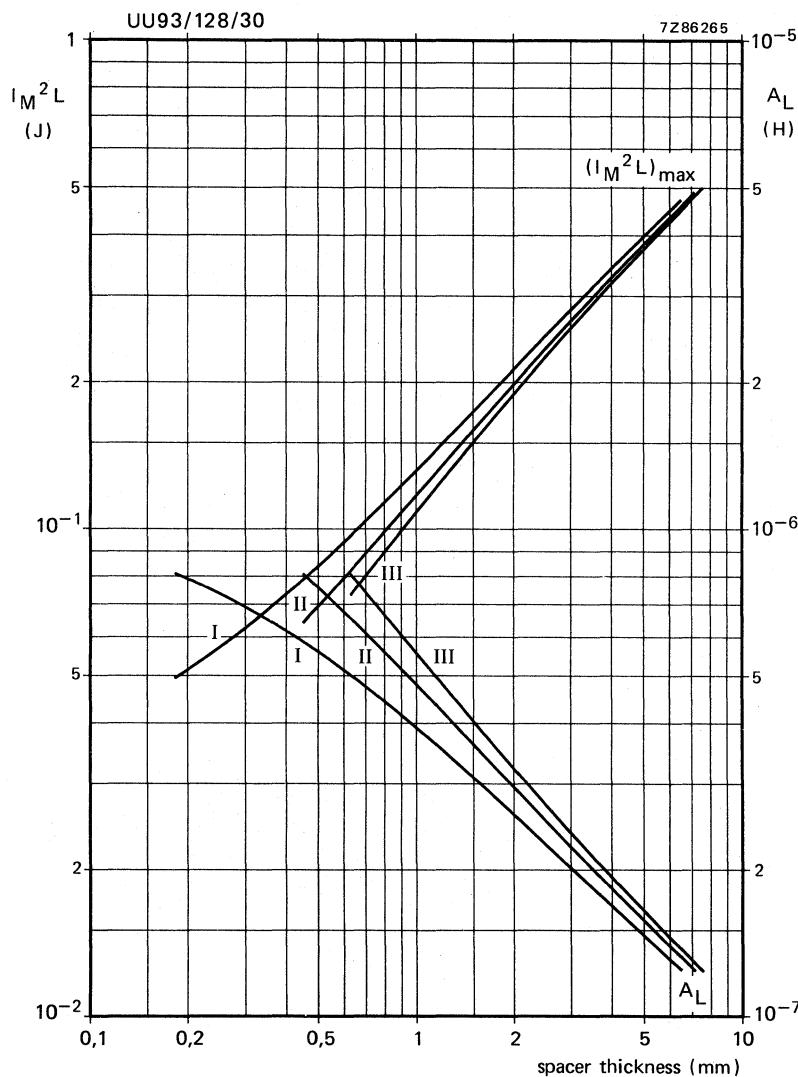

Choke design chart.

For application classes I, II and III see 'Power choke design' in the Introduction.

## UI-CORES

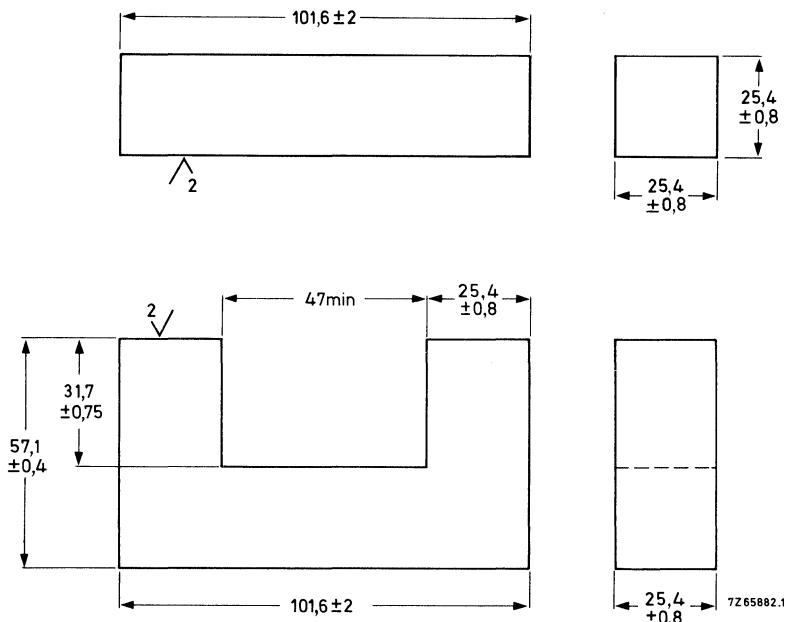

Mass            U-core            506 g  
                I-core            310 g

### MAGNETIC DATA

Guaranteed values, measured at 16 kHz, for core-pairs UI-100/82/25 and UU-100/114/25.

grade	temperature °C ± 5	induction $\hat{B}$ (mT)	field strength $\hat{H}$ (A/m)	losses W	shape	catalogue number of one core
3C8	25	200	—	≤ 17,9	UI	4312 020 33600
	100	200	—	≤ 16,4		4312 020 33610
	100	≥ 330	250	—		
3C8	25	200	—	≤ 24,5	UU	4312 020 33600
	100	200	—	≤ 20,5		
	100	≥ 290	250	—		

### Magnetic dimensions

	UI-100/82/25	UU-100/114/25	
$I_e$	240	300	mm
$A_e$	620	620	mm <sup>2</sup>
$V_e$	149 000	186 000	mm <sup>3</sup>



SECTION D  
MATERIALS AND CORES FOR MAGNETIC RECORDING



## MATERIALS AND CORES FOR MAGNETIC RECORDING

These grades of Ferroxcube were developed primarily for the production of magnetic recording heads in audio, video and industrial and professional applications. Their high density give these materials excellent performance in these applications. The main features are the high resistance to wear and good magnetic performance resulting from the well-controlled micro-structure. This structure enables machining, lapping and high-gloss polishing. Glass or epoxy bonding may be used. The materials are available void-free in the form of bars, tiles, core configurations and cores with glass-bonded gaps. Our experience in the processing and machining of ferrite allows ferrite materials to be ground to virtually any shape with very tight tolerances.

## MATERIAL DATA

## FXC 8C1

This NiZn material is used for the manufacturing of recording heads for industrial and professional applications, including data processing, professional audio recorders and instrumentation recorders.

## Material properties

Unless otherwise stated, all properties of the material have been measured at an atmospheric pressure of 86 to 106 kPa and at a relative humidity of 45 to 75%. Measured on a machined toroid, dimensions approx.  $\phi$  23 x  $\phi$  14 x 6 mm. The coefficient of expansion,  $\alpha_m$ , is measured on a rod of approx. 2 x 2 x 10 mm and determined by :  $\alpha_m = \Delta L/L_{20}$  (T-20).

	freq. kHz	B mT	temp. °C	typical values
initial permeability	4	< 0,1	25 ± 5	1600
Curie point	4	< 0,1		150 °C
resistivity	d.c.		25 ± 5	$1 \times 10^4$ Ωm
density			25 ± 5	5330 kg/m <sup>3</sup>
hardness (Vickers)*			25 ± 5	750 Hv 0,05/30
coefficient of linear expansion, $\alpha_m$				see Fig. 4

FXC 8C1 is available in the form of bars:

140 ± 2 mm x 45 ± 2 mm x 35 + 2 mm, catalogue number 4322 020 43020 or custom-made shapes on request.

\* Measured with 0,05 kg for 30 s.

# MAGNETIC RECORDING

8C1

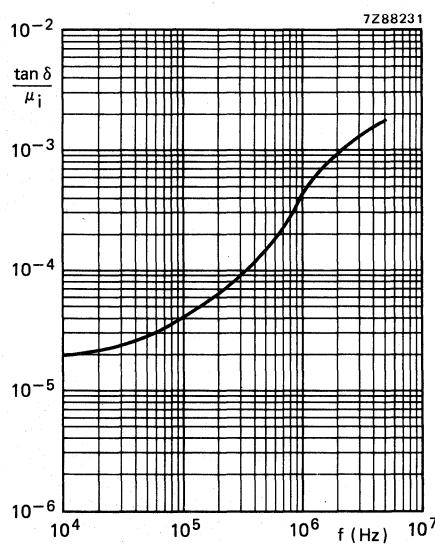


Fig. 1.

8C1

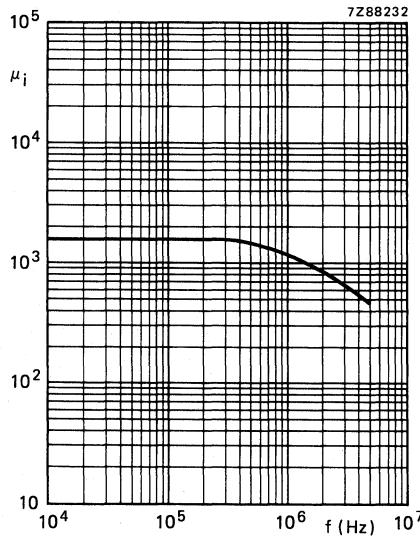


Fig. 2.

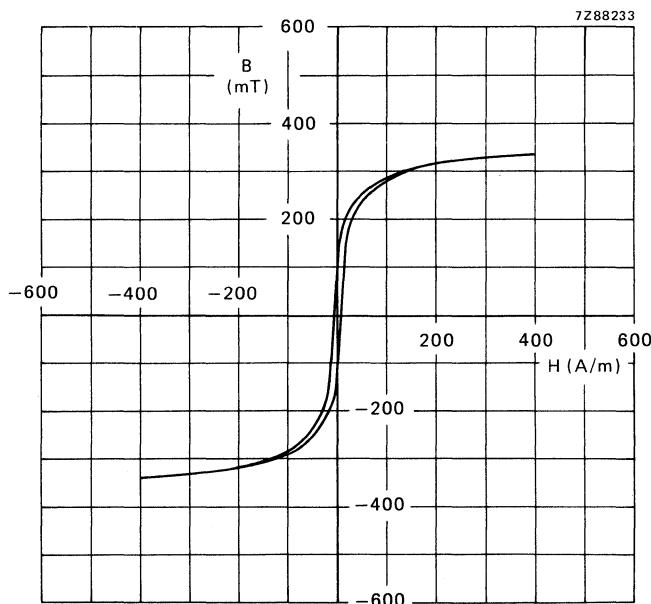


Fig. 3.

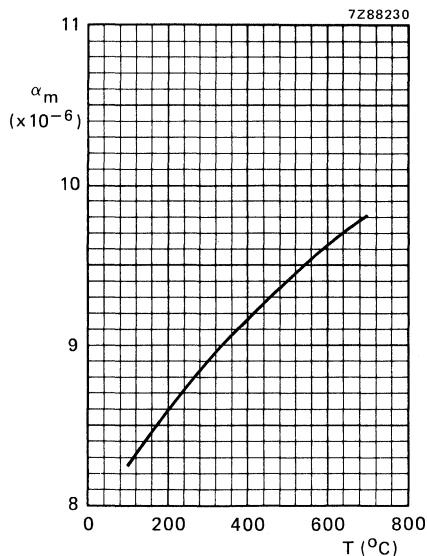


Fig. 4 Coefficient of linear expansion as a function of the temperature.

## NON-MAGNETIC STRUCTURAL MATERIALS

Two grades of non-magnetic structural materials, 8A5 and 8A41 for use in combination with NiZn and MnZn ferrites respectively are available as the non-magnetic component of glass-bonded structures. The matched coefficient of thermal expansion, the absence of pores and the excellent resistance to wear give a stable and tight-toleranced tape contact surface to the recorder head.

### Material properties

The properties of the materials have been measured at an atmospheric pressure of 86 to 106 kPa and at a relative humidity of 45 to 75%. The density has been measured on a plate, dimensions approx. 22 x 35 x 4 mm; the coefficient of expansion on a rod of approx. 2 x 2 x 10 mm. The  $\alpha_m$  value is determined by  $\alpha_m = \Delta L/L_0 (T-20)$ .

material		8A5	8A41
density	typ.	4700	4090 kg/m <sup>3</sup>
coefficient of linear expansion $\alpha_m$	See Fig. 5.	See Fig. 5	
hardness (Vickers), measured with 0,05 kg for 30 s	1300	1100	Hv 0,05/30

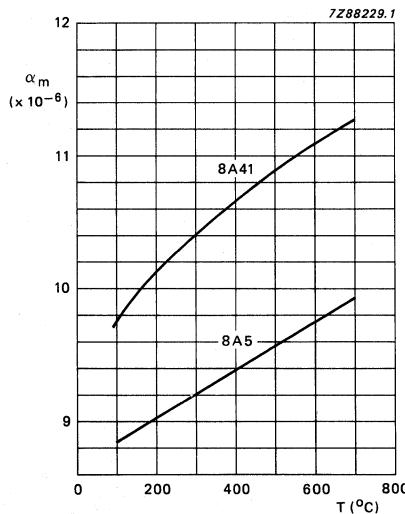


Fig. 5.

### Available shapes

grade	dimensions (mm)	catalogue number
8A5	145 ± 5 x 35 ± 3 x 22 ± 2	4322 020 97630
8A5	210 ± 6 x 37 ± 3 x 34 ± 3	4322 020 97640
8A41	145 ± 5 x 35 ± 3 x 22 ± 2	4322 020 97720

Other shapes on request.

**FXC 8E1, 8E2 and 8E21**

These manganese-zinc materials are intended for the production of erasing heads for audio and video applications. Effective erasing of magnetic tape for a low-noise level requires a high level of induction at a frequency in the range 50 to 100 kHz. Thus, for the use in erasing heads, a low eddy-current-loss core material is recommended. Low eddy current losses imply low heat dissipation and consequently less erasing power. Material FXC 8E1 is intended for erasing heads for iron-oxide or chromium dioxide tapes. Materials FXC 8E2 and 8E21 are for erasing heads for metal tapes.

**Material properties**

Unless otherwise stated, all properties of the material have been measured at an atmospheric pressure of 86 to 106 kPa and at a relative humidity of 45 to 75%. The coefficient of expansion,  $\alpha_m$ , is measured on a rod of approx.  $2 \times 2 \times 10$  mm and determined by :  $\alpha_m = \Delta L/L_{20}$  (T-20).

	freq. kHz	B mT	H A/m	temp. °C	grade 8E1      8E2      8E21 typical values		
					8E1	8E2	8E21
$\mu_i$	4	< 0,1		25 ± 5	3200	2800	3600
$B_s$	ballistic		250	25 ± 5	400	490	490
$\tan \delta$	100	< 0,1		25 ± 5	$3 \cdot 10^{-6}$	$3 \cdot 10^{-6}$	$2,5 \cdot 10^{-6}$
$\frac{\mu_i}{\mu_i}$							
$\eta_B$	100	1,5 to 3		25 ± 5	$0,5 \cdot 10^{-3}$	$0,5 \cdot 10^{-3}$	$0,5 \cdot 10^{-3}$
power losses	45	100	25	25 ± 5	$40 \cdot 10^3$	$40 \cdot 10^3$	$20 \cdot 10^3$
				85 ± 5	$60 \cdot 10^3$	$60 \cdot 10^3$	$50 \cdot 10^3$
Curie temp.	4	< 0,1			180	180	210
resistivity	d.c.			25 ± 5	5*	5*	3*
density				25 ± 5	4700	4700	4750
hardness (Vickers) **					560	730	730
linear expansion coefficient $\alpha_m$					Fig. 9	Fig. 13	Fig. 17

Unless otherwise stated, measured on a machined toroid, dimensions approximately  $\phi 23 \times \phi 14,5 \times 6$  mm.

Note: The properties of the products made from this material are dependent on dimensions and technology of the product. Deviations may occur.

The materials are available in the form of bars:

100 x 35 x 7,8 mm 8E2 catalogue number 4322 020 97500

100 x 28 x 12,5 mm 8E1 catalogue number 4322 020 37400


100 x 35 x 12,5 mm 8E1 catalogue number 4322 020 37480

100 x 35 x 14 mm 8E1 catalogue number 4322 020 37470

100 x 49 x 14 mm 8E1 catalogue number 4322 020 37460

215 x 37 x 26 mm 8E21 catalogue number 4322 020 97680

and in custom made shapes on request, see photograph.

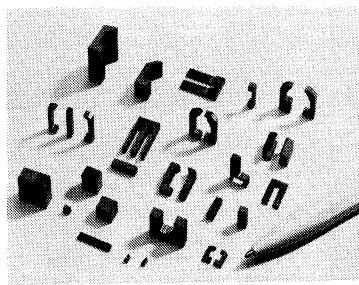

780118-21-02

\* Measured on a machined bar, dimensions approximately 3 x 2 x 15 mm.

\*\* Measured with 0,05 kg for 30 s.

# MAGNETIC RECORDING

8E1

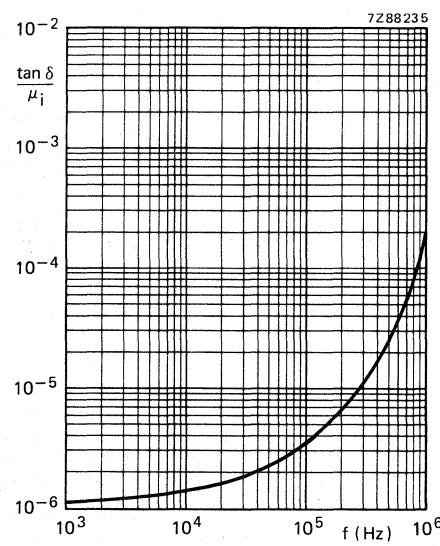


Fig. 6.

8E1

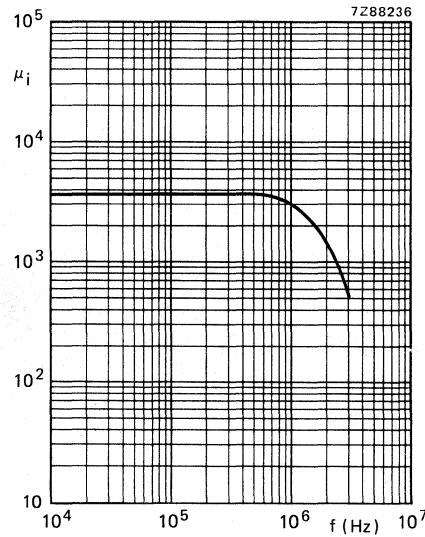


Fig. 7.

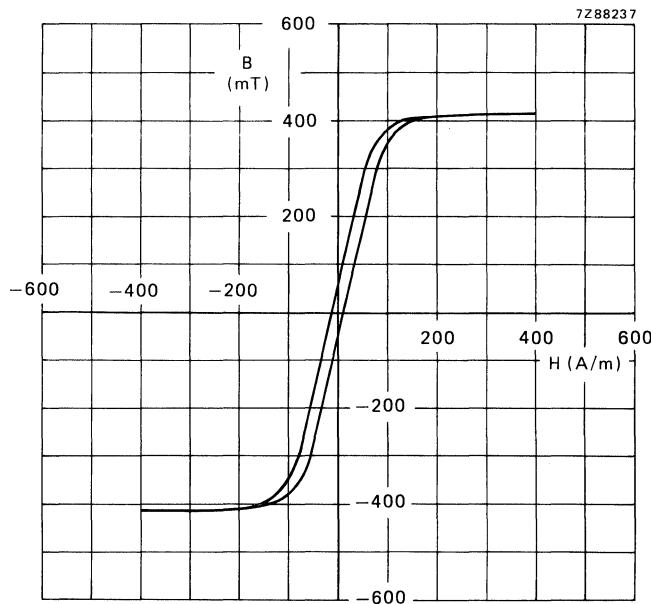


Fig. 8.

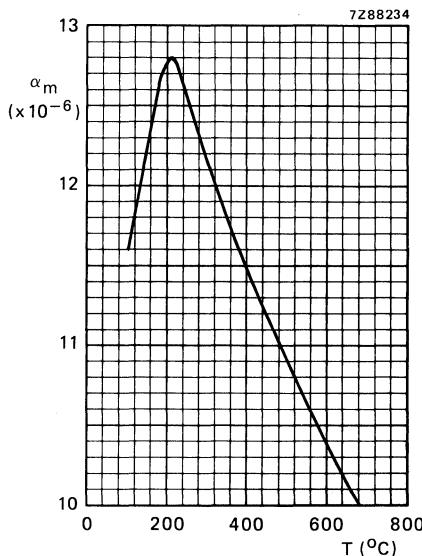


Fig. 9 Coefficient of linear expansion as a function of the temperature.

8E2

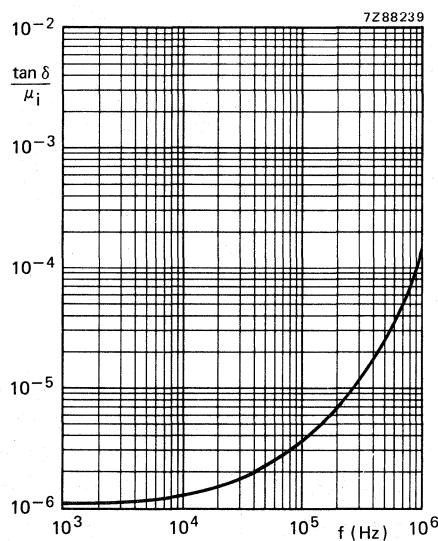


Fig. 10.

8E2

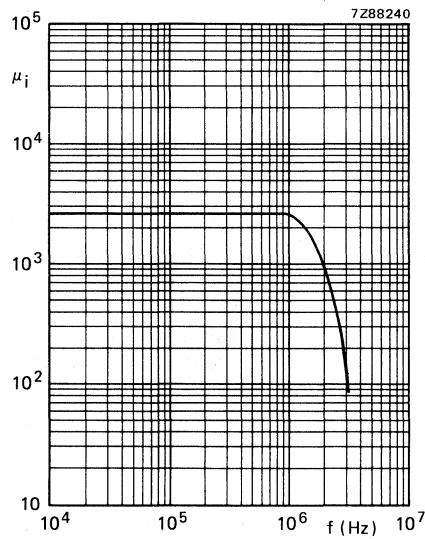


Fig. 11.

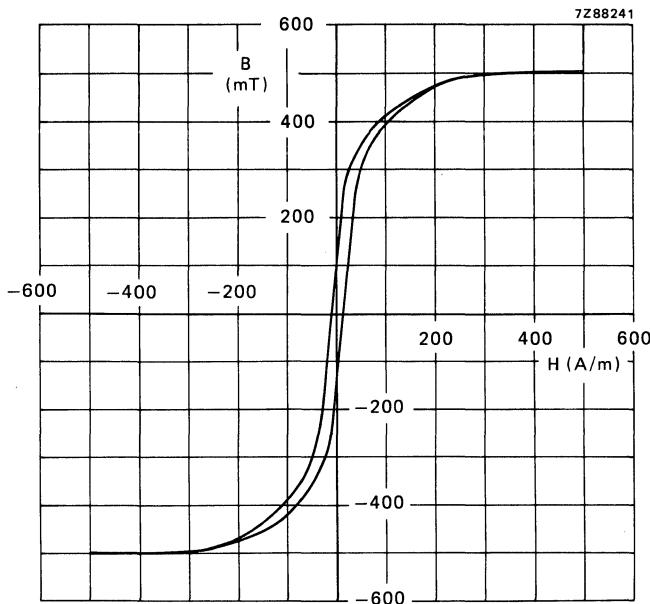


Fig. 12.

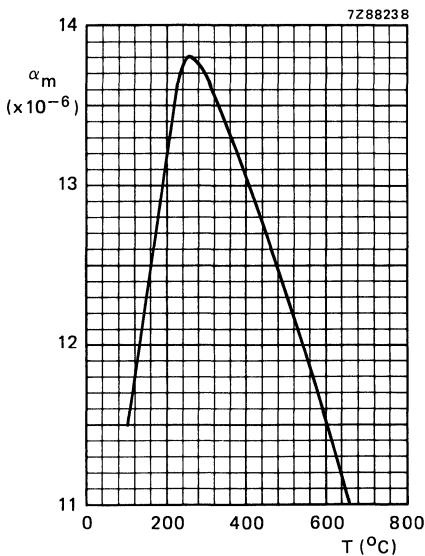


Fig. 13 Coefficient of linear expansion as a function of the temperature.

# MAGNETIC RECORDING

8E21

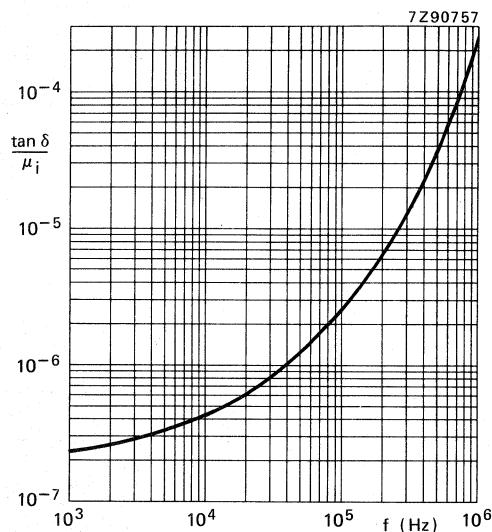


Fig. 14.

8E21

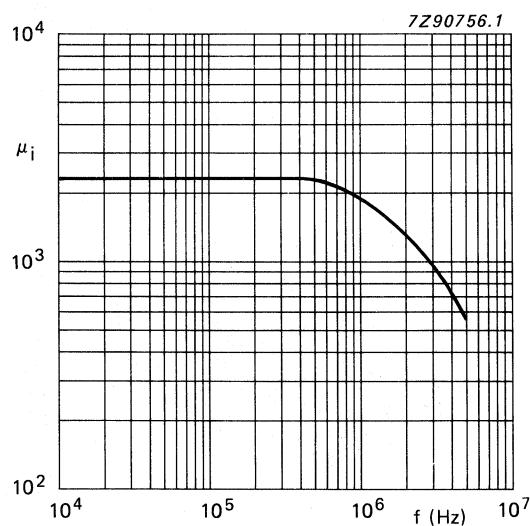


Fig. 15.

Measured on a toroid  $\phi 9 \times \phi 5 \times 0.5$  mm.

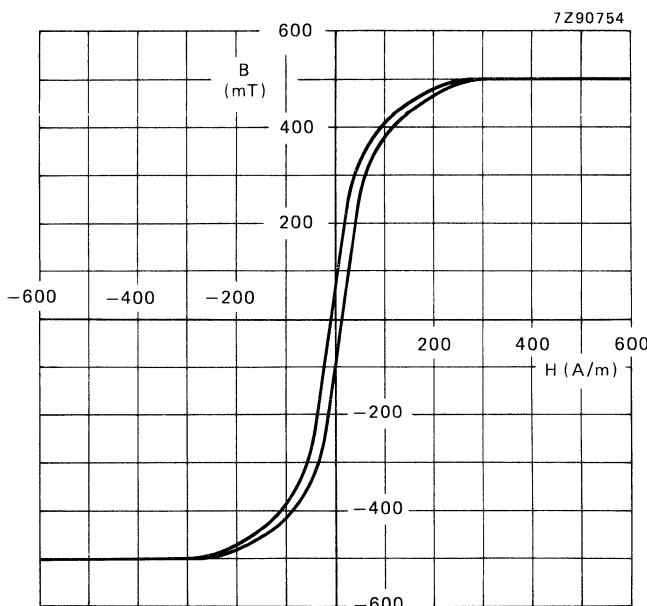


Fig. 16.

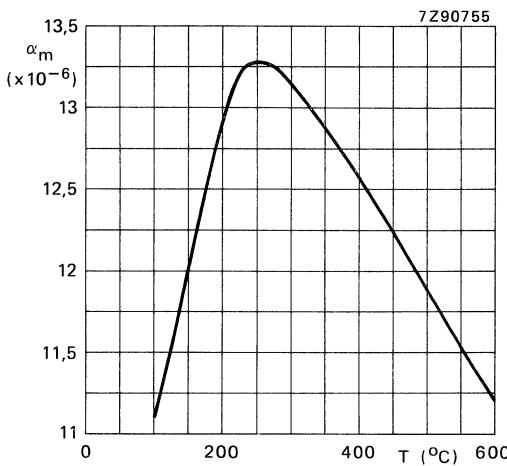


Fig. 17 Coefficient of linear expansion as a function of temperature.

## FXC 8X1

This MnZn single-crystal ferrite is mainly used as the basic material for the manufacture of video cassette recorder heads. The unique magnetic properties, homogeneity, outstanding wear resistance and the ability to machine this material to extremely tight tolerances, makes FXC 8X1 ideal for video use and other applications where a specified signal level with high information density on a very small track width is required.

Magnetic and mechanical characteristics of MnZn single-crystal ferrites depend on the direction of orientation of the crystal.

For details please consult us.

- The coefficient of expansion,  $\alpha_m$ , is measured on a rod of approx.  $2 \times 2 \times 10$  mm and determined by :  $\alpha_m = \Delta L/L_{20}$  (T-20).

### Material properties


	freq. kHz	B mT	H A/m	typical value
$\mu_i$	500	$\leq 1$		1800*
	5000	$\leq 1$		600**
$\frac{\tan \delta}{\mu_i}$	5000	$\leq 1$		$2 \times 10^{-3}^{***}$
$B_{sat}$	ballistic		800	490* mT
$B_r$	ballistic			140* mT
$H_c$	ballistic		800	3* A/m
resistivity	d.c.			$3 \cdot 10^{-3}$ $\Omega \text{m}$
linear expansion coefficient $\alpha_m$				see Fig. 21
Curie point	$< 10$			180 $^{\circ}\text{C}$
hardness (Vickers), measured with 0,05 kg during 30 s				730 Hv 0,05/30

The material is available in oriented tiles; one side polished to a flatness of 0,5  $\mu\text{m}$ :

- 16 x 8 x 1,52 mm, catalogue number 4322 020 97690.

Other dimensions and orientations can be supplied on request.

Diagram showing the orientations of the tile 4322 020 97690.

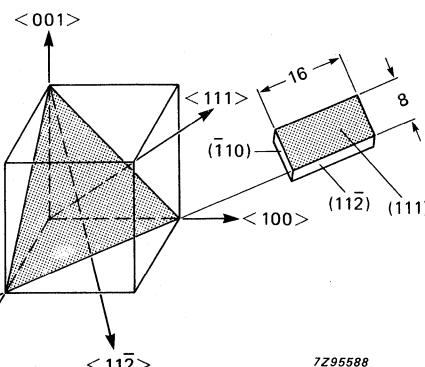

\* Measured on toroid  $\phi 9 \times \phi 5 \times 0,5$  mm.  $<\bar{1}10>$

\*\* Measured on toroid  $\phi 9 \times \phi 5 \times 0,2$  mm.  $<010>$

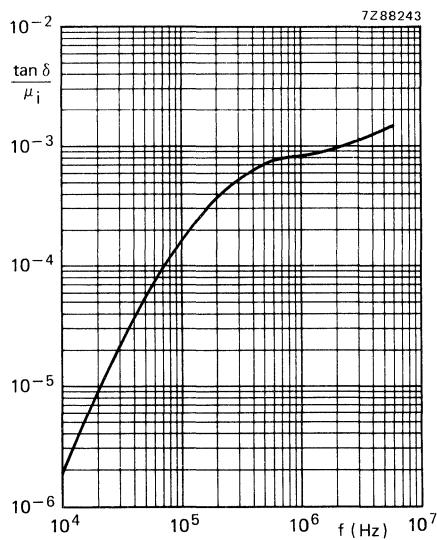


Fig. 18.

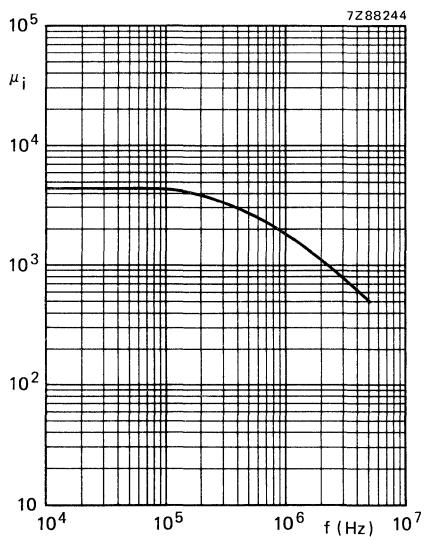


Fig. 19.

# MAGNETIC RECORDING

8X1

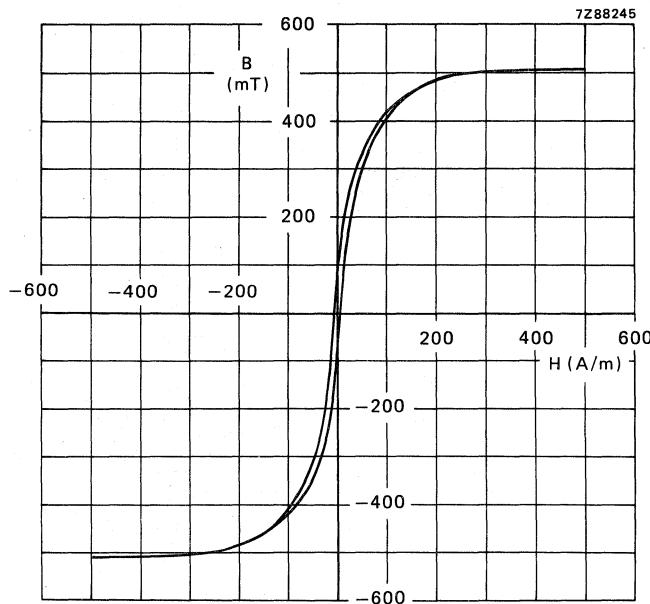


Fig. 20.

8X1

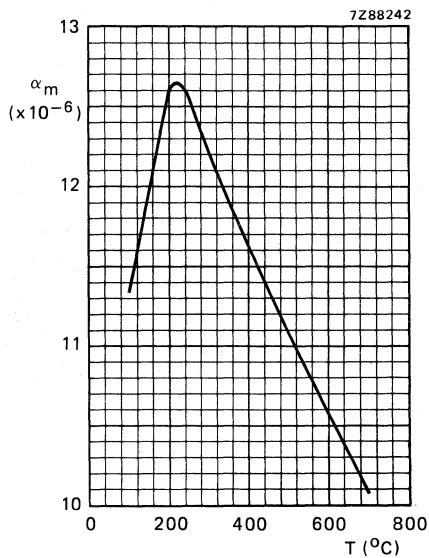


Fig. 21 Coefficient of linear expansion as a function of the temperature.

SECTION E  
SMALL CORES AND CHOKES

## DEVELOPMENT DATA


This data sheet contains advance information and specifications are subject to change without notice.

## IRON POWDER MATERIALS

Small cores, e.g. pins, rods, tubes, toroids and U cores can be supplied in iron powder materials. Six different grades can be made as mentioned below.

Details on dimensions and catalogue numbers on request.

grade	1P04	1P11	1P30	2P45	2P70	2P90	unit
initial permeability	4	11	30	45	70	90	$\pm 10\%$
frequency	3 - 63	1,5 - 45	0,3 - 5	0,01 - 0,1	0,01 - 0,1	0,01 - 0,1	MHz
loss factor	800 - 3000	350 - 2000	300 - 2500	2500	2000	2000	$\times 10^{-6}$
temp. factor	10	15	3	19	12	15	$\times 10^{-6}/K$
max. operating temp.	130	130	140	140	140	140	°C
radial breaking strength	10	37	25	12	19	24	kN/mm <sup>2</sup>

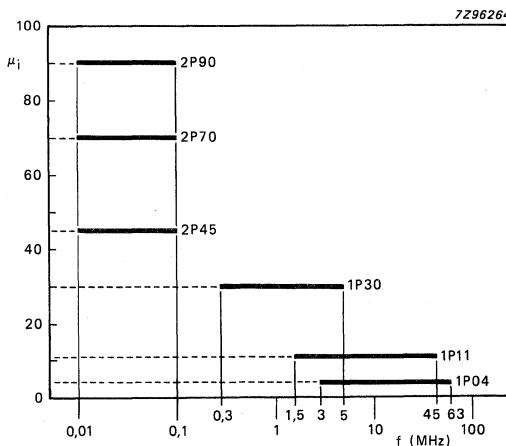

Frequency ranges for the various iron powder materials.

## TOROIDS

Toroids, having no air gap, generate only a small magnetic stray field and thus have a high permeability. In spite of the closed magnetic circuit the losses are low due to the favourable properties of Ferroxcube. They are used in small broadband transformers and pulse transformers. Toroids are also effective for interference suppression filters when they function as differential transformers offering no impedance to symmetrical line-current flow, since no flux change takes place in the core due to these currents. However, unsymmetrical current drawn unequally from either the line or the power supply will cause flux changes and the windings will act as an impedance to this current flow. Toroids are not recommended for tuned circuits.

Toroids are available in various sizes and Ferroxcube grades. They are barrel-finished and can be obtained in nylon insulated or non-coated versions.

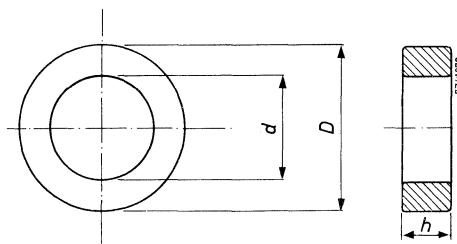


Table 1 Dimensional quantities, tolerances and mass of non-coated toroids.

D mm	d mm	h mm	$l_e$ mm	$\Sigma \frac{I}{A}$ mm <sup>-1</sup>	$V_e$ mm <sup>3</sup>	mass g
4 ± 0,1	2,2 ± 0,1	1,1 ± 0,1	9,46	9,56	9,37	0,045
6 ± 0,15	4 ± 0,15	2 ± 0,1	15,5	7,75	31,0	0,15
9 ± 0,2	6 ± 0,2	3 ± 0,1	23,3	5,17	105	0,50
14 ± 0,3	9 ± 0,25	5 ± 0,15	35,5	2,85	445	2,14
19 ± 0,4	10,6 ± 0,3	15 ± 0,3	44,0	0,718	2690	14
23 ± 0,5	14 ± 0,35	7 ± 0,2	57,0	1,81	1790	8,6
26 ± 0,55	14,5 ± 0,45	10 ± 0,3	60,3	1,08	3360	17
26 ± 0,55	14,5 ± 0,45	20 ± 0,45	60	0,538	6660	35
29 ± 0,5	19 ± 0,4	7,5 ± 0,2	75,0	2,01	2580	13
36 ± 0,7	23 ± 0,5	10 ± 0,2	92,0	1,42	5600	29
36 ± 0,7	23 ± 0,5	15 ± 0,3	92,0	0,942	8500	44

#### Notes

1. All  $\mu$ -values in the following pages are determined with the  $\Sigma \frac{I}{A}$  values of Table 1 at 25 °C.

The relevant  $A_L$  values can be calculated from:  $A_L = \frac{0,4 \pi \mu}{\Sigma \frac{I}{A}}$ . ( $A_L$  in nH,  $\Sigma \frac{I}{A}$  in mm<sup>-1</sup>).

2. L can be calculated from the formula:  $L = A_L \cdot N^2$  (L in nH).

3. The smaller a toroid, the more its properties deviate from the material properties. Therefore a straightforward translation of the material figures is not always possible.

# TOROIDS

Table 2. Dimensions and tolerances of coated toroids

D mm	d mm	h mm	Insulation breakdown kV	Derived from non-coated toroids with dimensions
≤ 4,5	≥ 1,7	≤ 1,6	≥ 1,5	4 x 2,2 x 1,1
≤ 6,55	≥ 3,45	≤ 2,5	≥ 1,5	6 x 4 x 2
≤ 9,7	≥ 5,3	≤ 3,6	≥ 1,5	9 x 6 x 3
≤ 14,9	≥ 8,15	≤ 5,75	≥ 1,5	14 x 9 x 5
≤ 24,3	≥ 12,85	≤ 8,0	≥ 2	23 x 14 x 7
≤ 30,3	≥ 17,7	≤ 8,5	≥ 2	29 x 19 x 7,5
≤ 37,5	≥ 21,7	≤ 11,0	≥ 2	36 x 23 x 10
≤ 37,5	≥ 21,7	≤ 16,0	≥ 2	36 x 23 x 15

Table 3. Grades, sizes and catalogue numbers.


grade	$\mu_i$	colour coating	dimensions * mm	nylon coated	non-coated
				catalogue number 4322 020 .....	
3E1	2700 ± 20% at 25 °C	green	29 x 19 x 7,5 36 x 23 x 10 36 x 23 x 15	97000 97010 97020	31310 31320 31330
3E2	> 5000 at +25 to +70 °C	blue	4 x 2,2 x 1,1 6 x 4 x 2 9 x 6 x 3 14 x 9 x 5 23 x 14 x 7	97030 97040 97050 97060 97070	31420 31430 31440 31450 31460
3E5	10 000 ± 25% at 25 °C	—	14 x 9 x 5 29 x 19 x 7,5 36 x 23 x 10 36 x 23 x 15	— — — —	95190 95160 95520 95180
3H2	2300 to 3100 at +25 °C $D_F \leq 5 \times 10^{-6}$ at $23 \pm 1$ °C	grey	4 x 2,2 x 1,1 6 x 4 x 2 9 x 6 x 3 14 x 9 x 5 23 x 14 x 7	97110 97120 97130 97140 97150	31350 31370 31380 31390 31400
4C6	> 100 at +5 to +55 °C	violet	6 x 4 x 2 9 x 6 x 3 14 x 9 x 5 23 x 14 x 7 36 x 23 x 15	97160 97170 97180 97190 97200	90750 90760 90770 90860 90870
				catalogue number 4312 020 .....	
3C11	4000 ± 25%	white	19 x 10,6 x 15 26 x 14,5 x 10 26 x 14,5 x 20 36 x 23 x 15	— — — —	36300 36280 36250 36310

\* These dimensions refer to non-coated toroids. More exact details are given in Tables 1 and 2.



## RODS AND TUBES

Ferrox cube rods and tubes can be used in r.f. and h.f. coils with an open magnetic circuit such as in i.f. transformers, fixed or adjustable inductances, and filters. Not only tubes, used as beads, are suitable for interference suppression but also small rods (pins) can effectively be used because of their relatively high insensitivity for premagnetization.

The table below lists standard diameters and matching lengths of rods and tubes. On the next page details are given on length tolerances and curvature limits, followed by a type list of currently available types.



7275926



7275927

### RODS

grade	dia. group	length group	dia. tol. group	matching length	
	mm	mm	mm	mm	
3B	1,6	5-30	-0,2	5-30	
			-0,05	5-8	
			-0,03	5-8	
			-0,2	5-30	
			-0,05	5-10	
	2,0		-0,03	5-10	
			-0,25	5-30	
			-0,1	5-20	
			-0,05	5-10	
			-0,25	5-30	
3C6	2,5	5-30	-0,25	5-30	
3C8	3,1	5-30	-0,1	5-20	
3D3			-0,05	5-10	
3E1	3H2	5-30	-0,25	5-30	
3H2			-0,1	5-25	
			-0,05	5-15	
4A4	4,0	8-30	-0,3	8-30	
4B1	4C6	8-30	-0,1	8-30	
4C6			-0,05	8-20	
4D1	5,0	10-50	-0,3	10-50	
4D2	4E1	10-50	-0,1	10-40	
4E1			-0,05	10-30	
			-0,3	10-60	
	6,3	10-60	-0,1	10-45	
	10,0	10,100	-0,5	10-100	
			-0,3	10-100	

### TUBES

outer dia. group mm	inner dia. max. mm	inner dia. tol. mm	length group mm	outer dia. tol. group mm	matching length mm
2,5	1,0	+ 0,15	3-30	-0,3	3-30
3,1	1,5	+ 0,15	3-30	-0,3	3-30
4,0	2,0	+ 0,2	4-40	-0,3	4-40
5,0	3,0	+ 0,2	5-50	-0,3	5-50
6,3	4,0	+ 0,3	10-60	-0,3	10-60
10,0	6,0	+ 0,3	10,60	-0,4	20-60

# CORES FOR SMALL FIXED CHOKES

Tolerances on length (in mm) of standard-size rods and tubes.

length	tolerance class	
	coarse	fine
< 6	0	0
	-0,4	-0,2
6-8	0	0
	-0,5	-0,3
8-10	0	0
	-0,6	-0,6
10-13	0	0
	-0,7	-0,4
13-16	0	0
	-0,8	-0,4
16-20	0	0
	-0,9	-0,4
> 20	0	0
	4%	-0,4


## Curvature

The curvature of rods and tubes is the maximum deviation from the straight line through the end face centres. This curvature may be checked by means of a tubular gauge with dimensions as given below:

$$\text{gauge inner diameter } d = d_1 + \frac{\ell_1}{100}$$

$$\text{gauge length } \ell \geq \ell_1$$

where  $d_1$  = maximum outer dia. of the rod or tube  
 $\ell_1$  = maximum length of the rod or tube

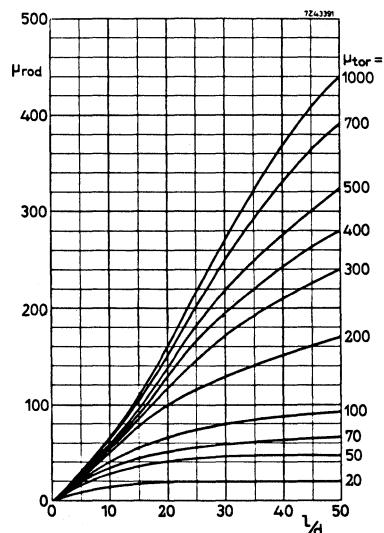

Rod permeability as a function of the ratio  $l/d$  with the relative initial permeability of a toroidal core as parameter.

## Type list of rods

D max.	tol.	L max.	tol.	FXC grade 3	catalogue number
				4	
1,40	-0,02	6,85	- 0,2	4C5	3122 104 92040
1,40	-0,02	6,85	- 0,20	3D3	3122 104 91920
1,60	-0,10	3,95	- 0,20	4D2	3122 134 91190
1,65	-0,05	9,2	- 0,4	3D3	4312 020 30160
1,65	-0,05	9,2	- 0,4	4B1	3122 104 91060
1,65	-0,05	12,2	- 0,4	3B	3122 104 91100
1,65	-0,05	12,2	- 0,4	4B1	3122 104 91110
1,65	-0,05	14	- 0,4	4B1	4330 020 31770
1,65	-0,05	25,2	- 0,4	3B	3122 104 91170
1,65	-0,05	28,2	- 0,4	4B1	4330 020 32090
1,70	-0,15	14,2	- 0,4	4E1	4322 020 32060
1,70	-0,15	17,8	- 1,0	3B	3122 104 92020
1,70	-0,15	18,5	- 1	4B1	3122 104 91150
1,75	-0,2	6,2	- 0,4	3B	4312 020 30020
1,75	-0,2	10,2	- 0,4	3B	3122 104 91130
1,75	-0,20	12,2	- 0,4	4B1	3122 104 92070
1,75	-0,20	14,2	- 0,4	4B1	4312 020 30560
1,75	-0,2	14,2	- 0,4	4A4	8230 302 05540
1,78	-0,03	8,95	- 0,45	3D3	4322 020 39480
2,0	-0,2	12,0	- 0,7	4C6	4330 030 30320
2,0	-0,2	16,5	- 1,0	4B1	4330 030 30360
2,0	-0,05	16,5	- 1	4B1	4330 030 30590
2,0	-0,2	16,5	- 1	4B1	8230 302 05790
2,1	-0,2	12,5	- 1,0	4B1	4330 030 30130
2,2	-0,2	16,5	- 1,0	4B1	4312 020 30460
2,30	-0,05	10,2	- 0,4	3D3	4312 020 30030
2,50	-0,25	16,3	- 0,8	4B1	4330 030 30450
2,50	-0,25	20	- 1	4B1	4312 020 30510
2,5	-0,25	24	- 0,9	4B1	8230 302 03530
3,0	-0,1	14	- 0,5	4B1	4330 030 30060
3,0	-0,1	14	- 0,5	4C6	4330 030 30270
3,0	-0,05	17,3	- 0,6	3B	8230 302 05400
3,0	-0,25	20	- 0,6	4B1	4330 030 30220
3,0	-0,05	22,5	- 1	4B1	4330 030 30490
3,05	-0,1	16,5	- 1	4C6	4330 030 30390
3,15	-0,3	16,5	- 1,0	4C6	4330 030 30070
3,15	-0,3	24,35	- 0,7	4B1	4312 020 30520
3,2	-0,2	11,5	- 1	4B1	4330 020 30560
3,4	-0,2	35	- 1	3C6	4330 030 30370
3,43	-0,50	11,35	- 0,5	3C6	4330 030 30620
3,5	-0,3	17	- 0,5	3B	4330 030 30400
4,0	-0,2	9	- 0,3	3B	8230 302 05750
4,0	-0,05	10	- 0,4	4E1	4330 030 30410
4,0	-0,05	13,3	- 0,8	4B1	4330 030 30210
4,0	-0,3	16	- 0,8	4B1	4330 030 30560
4,0	-0,3	20	- 0,6	3C6	4312 020 30320
4,0	-0,05	21	- 1	4C6	4330 030 30040
4,0	-0,3	25	- 1	4B1	4330 030 30250
4,00	-0,05	25	- 1	3C6	4312 020 30290
4,1	-0,2	21	- 1	4B1	4330 030 30120
4,1	-0,2	25,5	- 1	3B	4330 030 30310

# CORES FOR SMALL FIXED CHOKES

Type list of rods (continued)

D max.	tol.	L max.	tol.	FXC grade		catalogue number
				3	4	
4,1	-0,2	40	- 1	3B		4330 020 30380
4,5	-0,05	15,5	- 0,8		4B1	9230 302 03500
4,75	-0,05	30	- 1,2		4B1	4330 030 30580
4,95	-0,1	36	- 0,5	3C6		3122 104 90490
4,95	-0,1	50	- 0,5	3C6		3122 134 90110
5,0	-0,3	14	- 0,8		4B1	4330 030 30110
5,0	-0,05	18,3	- 0,6		4B1	4330 030 30240
5,0	-0,3	18,3	- 0,6	3D3		4330 030 30530
5,0	-0,3	18,3	- 0,6		4B1	4312 020 30490
5,0	-0,3	20,5	- 1		4B1	4312 020 30570
5,0	-0,05	21	- 1	3C6		4330 030 30280
5,0	-0,3	24,5	- 1	3D3		4312 020 30190
5,0	-0,3	25	- 1		4B1	4330 030 30080
5,0	-0,2	25,5	- 1	3B		4322 020 39450
5,0	-0,1	25,5	- 1	3C6		4330 030 30630
5,0	-0,05	29,8	- 0,4	3C6		4330 030 30600
5,0	-0,3	30	- 1,2		4B1	4330 030 30030
5,0	-0,05	30,2	- 0,4	3C6		3122 134 91120
5,0	-0,2	41	- 2	3B		4322 020 39470
5,3	-0,6	35,6	- 1,2		4B1	4330 030 30470
5,4	-0,05	25,2	- 0,4	3B		3122 104 91050
5,65	-0,05	15	- 0,5	3C6		4330 030 30540
6,55	-0,4	25,5	- 1		4A4	8230 302 05600
6,8	-0,6	25,6	- 1,2		4B1	4330 030 30520
7,5	-0,05	35	- 0,6	3C6		8230 302 05710
7,5	-0,05	50	- 0,6	3C6		8230 302 05720
8,25	-0,5	164	- 8	3B		8230 302 05020
10,0	-0,5	20,5	- 1	3C6		4330 030 30380
10,0	-0,5	30,5	- 1	3C6		4330 030 30510
10,0	-0,5	32,5	- 0,5		4B1	4330 030 30570
10,0	-0,5	50,5	- 1		4B1	4330 030 30350
10,0	-0,5	51	- 2	3C6		4330 030 30010
10,0	-0,5	55	- 1		4E1	8230 302 04850
10,0	-0,6	125	- 10		4B1	4330 020 30030
10,0	-0,5	164	- 8	3B		8230 302 05030
10,0	-0,6	185	- 10		4B1	4330 020 30690
10,0	-0,5	204	- 8		4B1	8230 302 03350
10,1	-0,8	167,3	- 0,6		4B1	4330 020 30580
12	-0,7	164	- 8	3B		8230 302 05040

Rods and tubes

Type list of tubes

D max.	d tol.	L max.	L tol.	FXC grade 3	FXC grade 4	catalogue number
1,6	-0,03	0,7	+0,1	7,55	- 0,3	4A4
1,6	-0,03	0,7	+0,1	7,55	- 0,3	4E1
2,2	-0,4	0,6	+0,2	3,25	- 0,5	4E1
2,5	-0,1	1,0	+0,2	1,2	- 0,4	4B1
2,6	-0,3	1,05	+0,3	1,75	- 0,3	4E1
2,7	-0,4	1,2	+0,2	3,5	- 0,5	4E1
2,75	-0,2	1,85	+0,2	8,15	- 0,3	4A4
2,75	-0,2	1,85	+0,2	8,15	- 0,3	4E1
2,8	-0,05	1,2	+0,2	8,4	- 0,4	3B
3,0	-0,2	0,9	+0,1	6,5	- 0,4	4A4
3,0	-0,05	1,0	+0,15	17,2	- 0,6	3D3
3,10	0,02	1,3	+0,2	18,8	- 0,5	3B
3,2	-0,4	0,8	+0,4	5,2	- 0,4	4E1
3,35	-0,03	0,9	+0,1	7,55	- 0,3	4A4
3,5	-0,1	1,6	+0,2	13,5	- 0,5	3D3
3,5	-0,05	1,7	+0,2	14,2	- 0,4	3B
3,6	-0,3	1,3	+0,2	3,5	- 0,5	3B
3,6	-0,1	1,3	+0,2	4,2	- 0,4	4C6
3,7	-0,4	1,0	+0,4	5,5	- 1,0	4E1
3,7	-0,4	1,0	+0,4	5,5	- 1,0	4D1
3,7	-0,4	1,2	+0,2	3,5	- 0,5	3B
3,7	-0,4	1,2	+0,2	3,5	- 0,5	4A1
3,7	-0,4	1,2	+0,2	3,5	- 0,5	4B1
3,7	-0,4	1,2	+0,3	15,8	- 0,1	4A4
3,7	-0,4	1,3	+0,2	5,5	- 0,5	3B
3,7	-0,4	1,3	+0,2	5,5	- 0,5	4B1
3,7	-0,4	1,3	+0,2	8,0	- 0,5	3B
3,7	-0,4	1,3	+0,2	15,2	- 0,4	3B
3,7	-0,4	1,5	+0,2	3,5	- 0,5	3B
3,7	-0,4	1,5	+0,2	8,0	- 0,5	3B
4,0	-0,2	0,75	+0,1	14,0	- 0,7	4B1
4,05	-0,25	1,35	+0,3	5,7	- 0,4	4B1
4,15	-0,05	2,0	+0,2	7,2	- 0,4	4A1
4,15	-0,05	2,0	+0,2	12,2	- 0,4	4B1
4,15	-0,05	2,0	+0,2	12,2	- 0,4	4C6
4,15	-0,05	2,0	+0,2	12,2	- 0,4	4D1
4,15	-0,05	2,0	+0,2	12,2	- 0,4	4B1
4,15	-0,05	2,0	+0,2	15,2	- 0,4	4A1
4,15	-0,05	2,0	+0,2	21,2	- 0,4	4C6
4,15	-0,3	2,0	+0,2	36,6	- 1,2	3C6
4,2	-0,4	1,8	+0,4	5,5	- 1,0	3B5
4,2	-0,1	2,0	+0,2	7,2	- 0,4	3D3
4,2	-0,1	2,0	+0,2	11,2	- 0,4	3D3
4,2	-0,1	2,0	+0,2	20,2	- 0,4	3B
4,2	-0,1	2,0	+0,2	25,4	- 1,0	3B1
4,3	-0,4	1,8	+0,4	49,3	- 0,6	3B1
4,3	-0,2	2,0	+0,2	3,2	- 0,4	3B1
4,3	-0,2	2,0	+0,2	3,5	- 0,5	3B1
4,3	-0,2	2,0	+0,2	3,5	- 0,5	4A1
4,3	-0,2	2,0	+0,2	4,7	- 0,4	3B1
4,3	-0,2	2,0	+0,2	7,2	- 0,4	3B
4,3	-0,2	2,0	+0,2	7,2	- 0,4	4A1

# CORES FOR SMALL FIXED CHOKES


Type list of tubes (continued)

D max.	d min.	L max.	FXC grade 3	catalogue number		
D tol.	d tol.	L tol.	4			
4,3	-0,2	2,0	+0,2	7,2 - 0,4	4D1	4311 020 50710
4,3	-0,2	2,0	+0,2	7,2 - 0,4	4D1	3122 104 93890
4,3	-0,2	2,0	+0,2	12,8 - 0,6	3B1	4322 020 34490
4,3	-0,2	2,0	+0,2	15,4 - 0,8	3B	4322 020 36750
4,3	-0,2	2,0	+0,2	16,4 - 0,8	3B1	8230 302 02390
4,3	-0,2	2,0	+0,2	18,5 - 0,5	3B1	4322 020 36770
4,3	-0,2	2,0	+0,2	25,5 - 1,0	3B	4322 020 36780
4,3	-0,2	2,0	+0,2	25,5 - 1,0	4B1	3122 104 90810
4,3	-0,2	2,0	+0,2	30,5 - 1,0	4B1	4311 020 54310
4,3	-0,2	2,0	+0,2	35,7 - 1,4	3B1	4311 020 50430
4,4	-0,3	2,0	+0,2	29,8 - 0,8	3B1	4312 020 31080
4,45	-0,3	2,0	+0,3	21,2 - 0,4	4B1	4322 020 34480
4,95	-0,1	1,3	+0,2	15,2 - 0,4	3C6	3122 104 90370
4,95	-0,1	1,3	+0,2	23,2 - 0,4	3C6	3122 104 90380
4,95	-0,1	1,3	+0,2	26,2 - 0,5	3C6	3122 104 94030
4,95	-0,1	1,3	+0,2	40,5 - 1,0	3C6	3122 104 93110
4,95	-0,1	2,9	+0,2	36,0 - 0,5	3C6	3122 104 93760
5,0	-0,3	1,3	+0,2	40,5 - 1,0	3C6	4330 030 32610
5,0	-0,2	1,8	+0,4	6,0 - 0,2	3D3	8230 301 02980
5,0	-0,3	2,5	+0,2	12,0 - 0,5	3C6	8230 302 04630
5,0	-0,3	2,5	+0,2	23,0 - 1,0	3D3	8230 302 04640
5,0	-0,3	2,5	+0,2	29,5 - 1,0	3C6	8230 302 04100
5,1	-0,3	1,5	+0,15	10,3 - 0,6	4D2	4330 030 32900
5,1	-0,4	3,9	+0,3	8,0 - 0,15	4A4	4322 020 36970
5,3	-0,2	3,0	+0,2	22,4 - 0,8	3B	4322 020 36810
5,4	-0,4	3,3	+0,3	21,2 - 0,4	4A1	3104 101 80630
6,0	-0,3	3,0	+0,2	18,0 - 0,9	3C6	4330 030 32940
6,15	-0,3	2,9	+0,2	18,0 - 1,0	3C6	4330 030 32770
6,3	-0,3	3,8	+0,3	10,2 - 0,5	3C6	4330 030 32880
7,0	-0,4	2,6	+0,2	10,4 - 0,7	3D3	4330 030 32890
7,0	-0,3	2,8	+0,2	17,15 - 0,65	3B1	4330 030 32050
8,0	-0,4	3,0	+0,2	8,0 - 0,4	3B1	4330 030 32710
8,0	-0,4	4,2	+0,6	51,4 - 2,8	3B	4322 020 34310
8,0	-0,4	4,2	+0,6	51,4 - 2,8	4B1	4322 020 34320
8,2	-0,4	4,3	+0,4	8,4 - 0,4	4A1	3922 074 01120
8,5	-0,5	3,5	+0,3	15,3 - 0,6	4B1	4312 020 31200
9,5	-0,5	4,5	+0,3	16,0 - 0,8	4B1	4330 030 32020
9,8	-0,6	6,3	+0,4	17,5 - 0,5	3B	4313 020 15180
10,0	-0,5	4,0	+0,3	143,0 - 6,0	4B1	4330 030 32620
10,0	-0,6	4,0	+0,1	183,6 - 7,2	4B1	4330 030 32870
10,15	-0,3	7,8	+0,25	20,2 - 0,5	3B1	4330 030 32820
10,3	-0,6	3,8	+0,4	205,0 - 10,0	3B1	4330 030 32860
10,3	-0,6	4,8	+0,4	155,0 - 10,0	3B1	4330 030 32930
10,8	-0,5	6,7	+0,4	19,5 - 0,4	4A4	3122 134 90780
12,0	-0,8	6,0	+2,0	183,6 - 7,2	4B1	8230 302 00910
12,3	-0,6	4,8	+0,4	124,0 - 8,0	4A4	4330 030 32810
12,4	-0,8	5,8	+0,4	155,0 - 10,0	3B1	4330 030 32920
14,5	-1,0	4,8	+1,0	51,0 - 2,0	3B1	8230 302 02510
14,5	-1,0	7,3	+1,0	28,0 - 6,0	4A1	4311 020 51880
16,0	-1,0	8,0	+3,0	183,6 - 7,2	4B1	8230 302 00900
17,2	-1,2	10,4	+1,2	60,0 - 2,5	3B1	4330 030 32030

FERRITE COIL FORMERS  
for axial coils

These cylindrical ferrites with two axial wires glued into the ferrite are very suitable to be provided with a number of turns to form a required axial coil.

Available types:

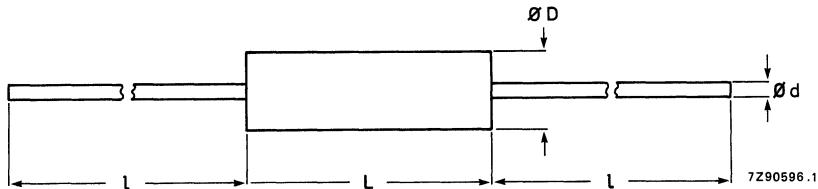

dimensions in mm				FXC grade	catalogue number
D	d	L	l		
2,7	0,7	8	34	4A4	8230 302 02080
4	0,7	14	34	4B1	4330 030 38070
6	0,6	20	28	4A4	8230 302 02170

The coil formers can also be made available with lead diameters from 0,5 mm to 0,7 mm.



## BEADS

### for interference suppression

Three grades of Ferroxcube have been developed primarily for interference suppression in such applications as power supplies, radio and television receivers, and automotive and domestic equipment. These grades are FXC3S1, FXC3S2 and FXC4S3. The table on the next page lists the ferrite beads available in these three material grades, together with their dimensions and guaranteed minimum impedances. Impedances are measured with the beads threaded on a straight copper wire.

#### Choice of material grade

In practice, choosing the correct material grade for a given application is very simple. First, determine the frequency range of the interfering signals that are to be suppressed, then, from the graph of Fig. 1, find the most suitable material grade and, finally, using the table of impedances, determine the bead dimensions for the required attenuation.

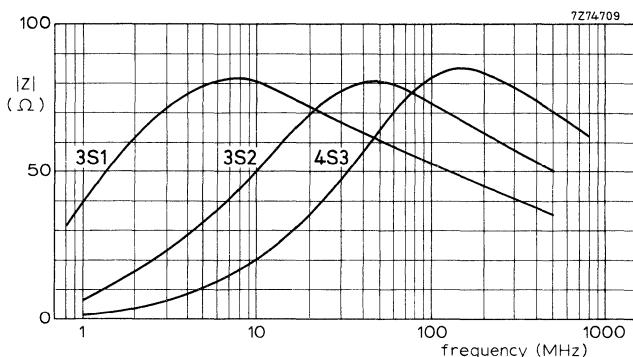


Fig. 1 Impedance of Ferroxcube grades as a function of frequency. The curves are typical for a bead size of 5 x 2 x 10 mm.

The high surface resistivity of FXC4S3 beads makes them suitable for mounting on bare wires. Increasing the surface resistivity of all grades by means of lacquer or any other insulation does not interfere with the magnetic properties of the Ferroxcube material.

The values of initial permeability  $\mu_i$  and saturation flux density  $B_s$  of FXC3S1, FXC3S2 and FXC4S3 have been optimized for the following ranges of application:

- FXC3S1: a very high  $\mu_i$  combined with a high  $B_s$ . Beads of this grade have a high  $|Z_S|$  at frequencies from 1 MHz to 50 MHz\* (maximum  $|Z_S|$  occurs between 6 MHz and 10 MHz), but are easily saturated by d.c. owing to the high  $\mu_i$ .
- FXC3S2: a medium  $\mu_i$  and a high  $B_s$ . At frequencies greater than about 20 MHz, these beads have a higher  $|Z_S|$  than those of grade 3S1. They can be used up to about 200 MHz.\* Maximum  $|Z_S|$  occurs between 40 MHz and 60 MHz.
- FXC4S3: a low  $\mu_i$  and a high  $B_s$ . At frequencies greater than about 80 MHz, these beads have a higher  $|Z_S|$  than those of grade 3S2. They can be used up to about 1 GHz.\* Maximum  $|Z_S|$  occurs between 100 MHz and 200 MHz.

\* See "Notes".

# CORES FOR SMALL FIXED CHOKES

Guaranteed minimum bead  
impedances  $|Z_S|$  ( $\Omega$ ) at  
various frequencies.

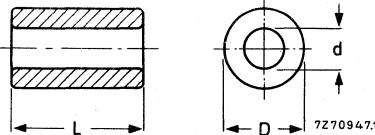


Fig. 2.

	frequency in MHz							catalogue number	dimensions (mm)			
	1	3	10	30	100	300	$ Z_S $ ( $\Omega$ )		D	d	L	$L \cdot I_n$ (D/d)
grade 3S1	10	18	24	20	17	15	4330 030 32180	5	2,0	4	3,7	
	14	29	30	24	20	18	32120	3	1,0	4	4,4	
	10	20	32	26	22	20	32160	5	1,5	4	4,8	
	19	38	39	31	26	23	32100	3	0,7	4	5,8	
	27	52	53	42	36	32	32140	5	0,7	4	7,9	
	29	51	61	49	42	37	32190	5	2,0	10	9,2	
	33	72	73	58	50	44	32130	3	1,0	10	11,0	
	40	72	80	64	55	48	32170	5	1,5	10	12,0	
	58	95	97	77	66	58	32110	3	0,7	10	14,5	
	70	125	128	90	70	50	32150	5	0,7	10	19,7	
grade 3S2 (blue)	2	8	16	20	26	17	4330 030 32280	5	2,0	4	3,7	
	2	8	17	22	28	18	32340	8	3,0	4	3,9	
	3	9	19	25	32	20	32220	3	1,0	4	4,4	
	3	10	21	27	35	22	32260	5	1,5	4	4,8	
	4	11	24	31	33	26	32320	8	2,0	4	5,6	
	2	8	25	32	42	27	32200	3	0,7	4	5,8	
	5	16	34	44	57	37	32240	5	0,7	4	7,9	
	6	19	40	51	66	43	32290	5	2,0	10	9,2	
	6	20	42	55	62	45	32350	8	3,0	10	9,8	
	7	23	48	61	79	51	32230	3	1,0	10	11,0	
	7	25	52	68	87	55	32270	5	1,5	10	12,0	
	9	28	60	77	100	64	32330	8	2,0	10	13,9	
	9	30	63	81	104	67	32210	3	0,7	10	14,5	
grade 4S3 (red)	10	34	72	93	90	77	32310	8	1,5	10	16,7	
	12	40	75	110	142	91	32250	5	0,7	10	19,7	
	1	2	7	17	32	36	4330 030 32440	5	2,0	4	3,7	
	1	3	8	18	34	38	32500	8	3,0	4	3,9	
	1	3	9	20	38	43	32380	3	1,0	4	4,4	
	1	3	9	22	41	47	32420	5	1,5	4	4,8	
	1	3	11	26	49	55	32480	8	2,0	4	5,6	
	1	3	11	27	50	57	32360	3	0,7	4	5,8	
	1	4	13	31	57	65	32460	8	1,5	4	6,7	
	2	5	16	36	68	77	32400	5	0,7	4	9,7	
	2	6	18	42	80	89	32450	5	2,0	10	9,2	
	2	6	19	45	85	95	32510	8	3,0	10	9,8	
	2	8	21	50	95	107	32390	3	1,0	10	11,0	
	2	7	23	55	104	116	32430	5	1,5	10	12,0	
	2	9	27	64	121	134	32490	8	2,0	10	13,9	
	2	9	28	67	126	140	32370	3	0,7	10	14,5	
	3	10	32	77	145	161	32470	8	1,5	10	16,7	
	4	12	38	90	170	190	32410	5	0,7	10	19,7	

In many applications, leads through suppressor beads also carry a d.c. or a 50 Hz a.c. current. In such cases the impedance of grades 3S1 and 3S2 will decrease.

Figure 3 shows the effect of d.c. on the impedance of 3S1 and 3S2 beads. This is caused by partial saturation of the beads, which will, of course, be more pronounced with smaller beads, and those of lower  $B_S$  and higher  $\mu_i$  material. Therefore, the effect of d.c. on grade 4S3 is negligible. Consequently, where high d.c. (or 50 Hz a.c.) currents flow, grades 4S3 or 3S2 should be used.

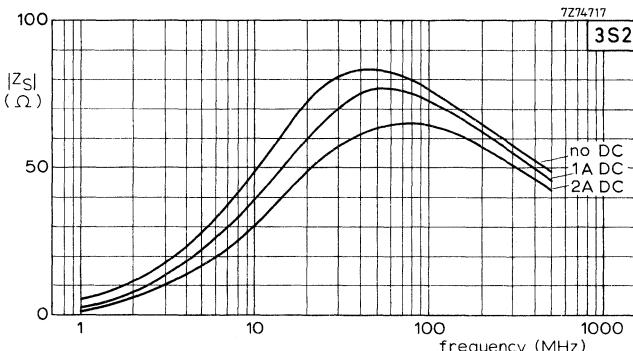


Fig. 3a Impedance  $|Z_S|$  of a  $5 \times 2 \times 10$  mm bead of grade 3S2 as a function of frequency with the premagnetizing current as a parameter.

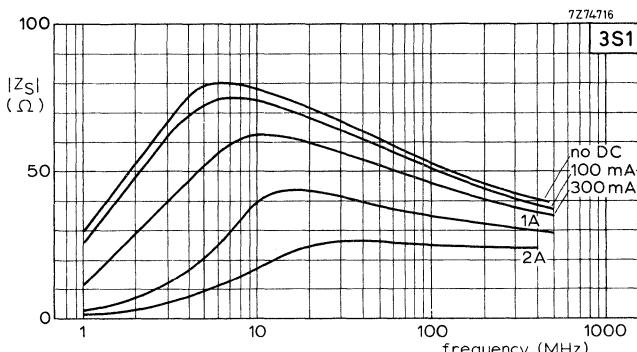


Fig. 3b Impedance  $|Z_S|$  of a  $5 \times 2 \times 10$  mm bead of grade 3S1 as a function of frequency with the premagnetizing current as a parameter.


#### Notes

The attenuation of a given type of bead used beyond the frequency limit for its material grade may vary significantly from batch to batch. Although the attenuation will never be less than that given in the table of guaranteed minimum values, it may be much higher. However, the guaranteed minimum attenuation of a bead of the correct material grade for the frequency will always be higher than that of one beyond its frequency limit.

Beads used beyond the frequency limit for their grade should not be too large. This is because the possible deterioration of attenuation may become excessive for greater  $L_{in} / (D/d)$  values. Rather than increase  $L_{in} / (D/d)$  it is usually better to use several well-separated beads with smaller  $L_{in} / (D/d)$  values.

BEADS ON WIRE  
on tape

A number of beads on wire, for suppression of incoming or outgoing interferences in various applications, can be supplied on tape for automatic processing. The bandolier fits most commonly used automatic mounting machines. See Fig. 1 and Table 1.

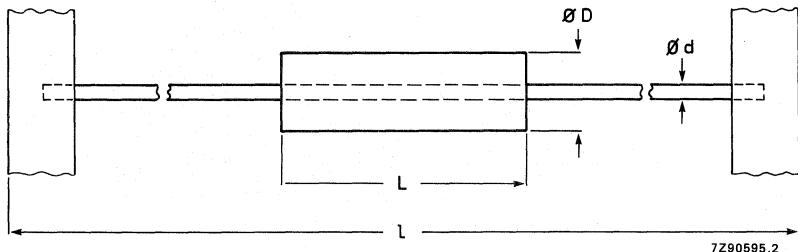

7Z90595.2

Table 1

grade	frequency in MHz						catalogue number	dimensions				tape standard
	1	3	10	30	100	300		D	L	I	d	
3D3	11	36	100	130	80	60	8230 301 04180	4,1	11,0	75,0	0,6	IEC 286 part 1
3S2	5	18	48	70	80	65	8230 301 03330	3,5	6,0	75,0	0,6	IEC 286 part 1
4E1			2	7,5	25		8230 301 04760	2,0	3,0	75,0	0,6	IEC 286 part 1
3S2				34			8230 301 04100	3,5	3,5	64,4	0,64	EIA-RS-296-D
4A1				35			8230 301 04110	3,5	3,5	64,4	0,64	EIA-RS-296-D
4S3					54		8230 301 04120	3,5	3,5	64,4	0,64	EIA-RS-296-D
4S2					46		8230 301 04130	3,5	3,5	64,4	0,64	EIA-RS-296-D
3E2			30				8230 301 04140	3,5	3,5	64,4	0,64	EIA-RS-296-D
4S2				60			8230 301 04050	3,5	4,7	64,4	0,64	EIA-RS-296-D
4S2				80			8230 301 04060	3,5	6,0	64,4	0,64	EIA-RS-296-D
4S2				88			8230 301 04070	3,5	6,7	64,4	0,64	EIA-RS-296-D
4S2				105			8230 301 04080	3,5	7,6	64,4	0,64	EIA-RS-296-D
4S2				117			8230 301 04090	3,5	8,9	64,4	0,64	EIA-RS-296-D

## MULTI-HOLE TUBES

Multi-hole tubes are used for small h.f. transformers for voltage or impedance matching in television, communications, data transmission, instrumentation and similar applications.

### A. With two holes, "twin beads"





Fig. 1.




Fig. 2.

Fig.	D mm	d mm	L mm	H mm	grade	catalogue number
1	5,6 ± 0,25	0,95 + 0,15	4,5 – 0,5	–	4D1	3122 134 90800
	5,6 ± 0,15	1,5 ± 0,15	12 ± 0,2	–	4B1	4330 030 32740
	5,9 – 0,6	0,75 + 0,3	12,4 – 0,8	–	4B1	3122 104 90960
	6,6 – 0,6	1,05 + 0,3	5 ± 0,2	–	4B1	3122 104 94840
2	8,5 – 0,5	3,5 + 0,5	8 ± 0,3	14 + 0,5	4B1	4312 020 31570
	8,5 – 0,5	3,5 + 0,5	14 ± 0,4	14 + 0,5	4B1	4312 020 31520

With twin beads advantages can be taken of mutual inductance to increase inductance L and loss resistance R caused by  $\Delta L$  and  $\Delta R$  respectively. This is shown in Fig. 3 for a twin bead 4312 020 31520 on two straight wires. Grade 4B1 provides ample insulation between bare wires.

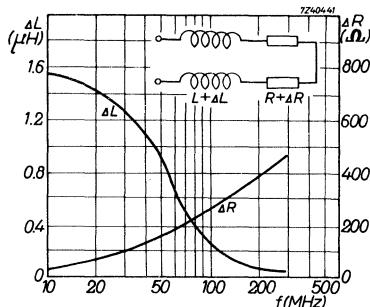


Fig. 3.

## CORES FOR SMALL FIXED CHOKES

### B. With six holes

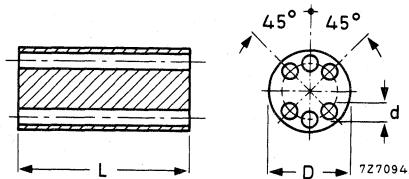



Fig. 4.

D mm	d mm	L mm	grade	catalogue number
$6 \pm 0,3$	$0,7 + 0,2$	$10 \pm 0,5$	3B	4312 020 31500
$6 \pm 0,3$	$0,7 + 0,2$	$10 \pm 0,5$	4B1	4312 020 31550

## SCREW CORES

Ferrocube screw cores are used in adjustable inductances in r.f. and h.f. coils with an open magnetic circuit.

### Stud trimming

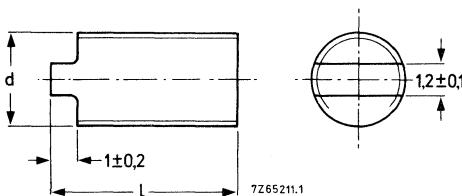

nom. diameter x pitch	$l$ mm	d mm	grade	catalogue number
3,5 x 0,7	$10 \pm 0,2$	$3,5 \pm 0,05$	3B	3122 104 90550

## WOUND SIX-HOLE BEADS

Wide-band h.f. chokes are used for interference suppression, e.g. in electric motors. Double chokes are used for twin leads, in which case the advantage of mutual inductance can be utilized.

The chokes can be supplied with six axial holes through which 1,5, 2,5 or 2 x 1,5 (double chokes) turns of tinned copper wire are threaded.

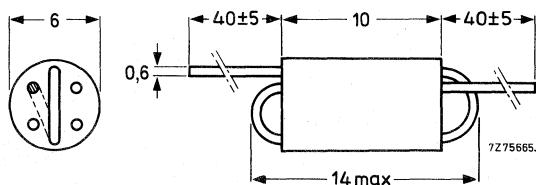


Fig. 1.

number of turns	$Z_{max}$ k $\Omega$	f at $Z_{max}$ MHz	decrease of impedance		grade	catalogue number
			In the freq. range MHz	dB		
1,5	$\geq 0,3$	120	10-300	$\leq 7$	3B	4312 020 36630
1,5	$\geq 0,35$	250	80-300	$\leq 3$	4B1	4312 020 36690
2,5	$\geq 0,6$	50	10-200, 30-100	$\leq 7, \leq 3$	3B	4312 020 36640
2,5	$\geq 0,7$	180	50-300, 80-220	$\leq 6, \leq 3$	4B1	4312 020 36700
2 x 1,5	$\geq 0,7$	50	10-220, 30-100	$\leq 7, \leq 3$	3B	4312 020 36650
2 x 1,5	$\geq 0,8$	110	50-300, 80-220	$\leq 7, \leq 3$	4B1	4312 020 36710

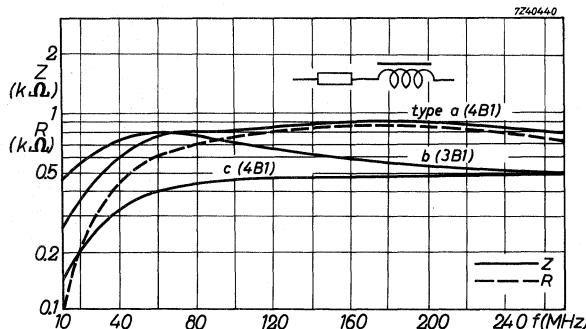


Fig. 2 Performance of three single chokes.

Type a = 4312 020 36700

b = 4312 020 36640

c = 4312 020 36690

Figure 2 shows some performance details of three single chokes. It will be noted that above approx. 80 MHz the impedance is substantially resistive and tends to be constant. Double chokes are used for twin leads, in which case the advantages of mutual inductance can be utilized. Figure 3 compares the typical obtainable performance.

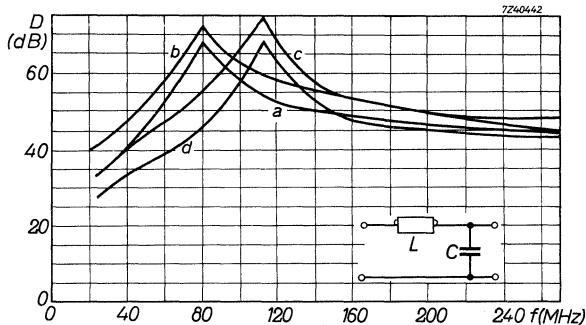


Fig. 3 Damping in an LC circuit consisting of a Ferroxcube choke and a ceramic disc capacitor.

- a.  $L = 4312\ 020\ 36690$ ,  $C = 1500\ pF$   
 b.  $L = 4312\ 020\ 36700$ ,  $C = 1500\ pF$

- c.  $L = 4312\ 020\ 36700$ ,  $C = 550\ pF$   
 d.  $L = 4312\ 020\ 36690$ ,  $C = 550\ pF$ .

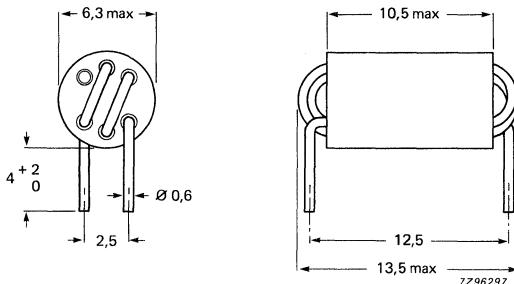


Fig. 4.

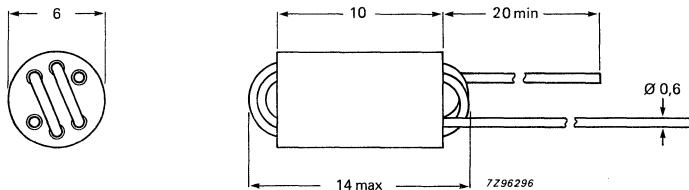


Fig. 5.

number	Fig.	$L$ $\mu H$	grade	catalogue number
2,5	4	$\geq 9$	3B	4330 030 38080
3	5		3B	4312 020 36760



**SECTION F**  
**MATERIALS FOR PARTICLE ACCELERATORS**



## MATERIALS FOR PARTICLE ACCELERATORS

Several grades of Ferroxcube have been developed especially for use in particle accelerators. Applications include kicker magnets for beam extraction, and accelerating stations. For kicker magnets, materials of low coercivity and low degassing rate are required. Materials for accelerating stations must have a high  $\mu Qf$  product at the working flux density. The dynamic behaviour of the materials under pulse conditions is important for both applications.

The data given in the following table allows a preliminary selection of material grade to be made. However, consultation with the manufacturer is always advisable to establish finally the material properties and component geometries for each application.

### NOTE ON DATA

Losses given in terms of  $\mu Q$  factors may be converted into losses in  $\text{kW/m}^3$  ( $\text{mW/cm}^3$ ) using the following expression.

$$\text{Losses in } \text{kW/m}^3 = \frac{2,5 \times f \times B^2}{\mu Q}$$

where  $f$  is in kHz and  $B$  in mT. For example, the losses in FXC 3F1 material at 200 kHz and 10 mT induction are

$$\frac{2,5 \times 200 \times 10^2}{200 \times 10^3} = 0,25 \text{ kW/m}^3.$$

# SELECTION GUIDE

material	3H22	8C11	3F1	8C12	4L2	4M2	4E2
$\mu_i$	$\geq 2500$	$\geq 1000$	$1800 \pm 360$	$900 \pm 150$	$250 \pm 50$	$140 \pm 30$	$25 \pm 5$
$\mu_{rem}$ approx.	2300	850	1500	600	200	130	20
$B_{sat}$ 25° (mT, 800 A/m)	$\geq 400$	$\geq 300$	$\geq 400$	280	240	250	250
$B_{sat}$ 40° (mT, 800 A/m)	$\geq 350$	$\geq 280$	$\geq 350$	250	220	220	220
$H_c$ (A/m, after 800 A/m)	$\leq 15$	$\leq 20$	$\leq 20$	30	90	100	500
$\rho$ d.c. ( $\Omega$ M)	$\geq 1$	$\geq 10^3$	$\geq 10$	$\geq 10^3$	$\geq 10^3$	$\geq 10^3$	$\geq 10^3$
$T_c$ (°C)	$\geq 125$	$\geq 125$	$\geq 200$	$\geq 125$	$\geq 150$	$\geq 150$	$\geq 400$
$\mu_Q$ in remanence							
200 kHz	10 mT			$200.10^3$	$15.10^3$		
	20 mT			$160.10^3$	$9.10^3$		
	50 mT			$75.10^3$	$4.10^3$		
	100 mT			$30.10^3$			
500 kHz	10 mT			$110.10^3$	$10.10^3$		
	20 mT			$90.10^3$	$6.10^3$		
	50 mT			$40.10^3$	$2.5.10^3$		
	100 mT			$20.10^3$			
1 MHz	5 mT			$25.10^3$	$10.10^3$	$35.10^3$	$20.10^3$
	10 mT			$23.10^3$	$7.5.10^3$	$26.10^3$	$20.10^3$
	20 mT			$17.10^3$	$5.10^3$	$13.10^3$	$15.10^3$
	30 mT			$15.10^3$		$7.10^3$	$8.10^3$
	50 mT			$14.10^3$			
2,5 MHz	5 mT					$25.10^3$	$20.10^3$
	10 mT					$20.10^3$	$20.10^3$
	20 mT					$9.10^3$	$15.10^3$
	30 mT					$5.10^3$	$7.10^3$
5 MHz	5 mT					$15.10^3$	$15.10^3$
	10 mT					$11.10^3$	$15.10^3$
	20 mT					$5.10^3$	$10.10^3$
	30 mT					$2.10^3$	$7.10^3$

10 MHz	5 mT 10 mT					12.10 <sup>3</sup> 10.10 <sup>3</sup>	
80 MHz	1 mT						2.5.10 <sup>3</sup>
100 MHz							2.10 <sup>3</sup>
Decrease in $\mu\Omega$ , measured 10 ms after application of d.c. bias in % (approx.)			10	10	30	15	30
$\mu\Delta$ with d.c. bias field (approx.)	0 A/m 250 A/m 500 A/m 1000 A/m 2000 A/m 3000 A/m		1500 270 33 13 6 4	600 120 50 22 8 5,5	200 120 55 25 12 8	130 80 40 22 12 8	
Freq. range (with or without d.c. bias) in MHz			0,1–1	0,5–10	1–5	2–10	20–100
Application area and special features	Kickers	Kickers High resistance	Low freq. For large dimensions, eddy current losses have to be considered	High freq. ratio possible with d.c. bias	Rel. high $\mu\Omega$	Fast recovery after magnetic bias	High freq. material



**SECTION G**  
**FERROXCUBE FOR MICROWAVE APPLICATIONS**



## FERROXCUBE FOR MICROWAVE APPLICATIONS

Ferroxcube 5 is a material grade which is especially suited for microwave applications such as circulators and isolators.

The main application areas for these ferrites are radio, television, microwave communication, radar, security systems and industrial control.

They are available as blocks, bars, discs and substrates with dimensions as requested by the customer.

Substrates for microwave integrated circuit (MIC) technology are manufactured in advanced hot isostatic sintering kilns, so that low porosity and high-quality polished surfaces can be guaranteed.

## SURVEY OF FERROXCUBE 5 MATERIALS


Table

	symbol	conditions			unit
		frequency MHz	field strength A/m	temp. °C	
saturation polarization	$J_s$		$8 \times 10^5$		mT
line width	$\Delta H$	9600			A/m
spin wave line width	$\Delta H_K$	9600			A/m
coercive field strength	$H_c$		800		A/m
dielectric loss factor	$\tan \delta(\epsilon)$	9600			
dielectric constant	$\epsilon'$				
temp. coefficient of $J_s$			$8 \times 10^5$	0 - 25 25 - 60	mT/K
Landé factor	$g$				—
remanence	$B_r$		800		mT
saturation flux density	$B_s$		800		mT
Curie temp.	$T_c$				°C
specificic resistance for d.c.	$\rho$				Ωm
density				25 ± 5	kg/m³

## materials for microwave applications


	5G1	5G3	5G4	5G5	5G6	5G7	5G8	5D3
178 ± 9	55 ± 2,5	125 ± 6	87,5 ± 4,5	52,5 ± 2,5	37,5 ± 2,5	182,5 ± 9	300 ± 15	
2200 ±600	2640 ±400	≤ 6000	6800 ±2000	≤ 6000	5200 ±800	< 800	< 20 000	
> 24	> 80	> 400	> 600		> 560	> 24	> 800	
35						15,9		
< 2 × 10 <sup>-4</sup>	< 3 × 10 <sup>-4</sup>	< 20 × 10 <sup>-4</sup>						
15,5 ± 0,5	14,4 ± 0,25	15,5 ± 0,5	15,25 ± 0,25	14,7 ± 0,5	14,5 ± 0,5	15,3 ± 0,75	13,9 ± 0,5	
-0,36	-0,20		-0,14		-0,11	-0,61	-0,32	
2,00	2,00	2,00	2,02	2,02	2,02	2,00	2,24	
120						102		
145								
240	155	280	280	175	145	230	≥ 500	
> 10 <sup>4</sup>						> 10 <sup>8</sup>	10 <sup>5</sup>	
5140	5000	5500	5360	5240	5100	5210	5300	

## BLOCKS

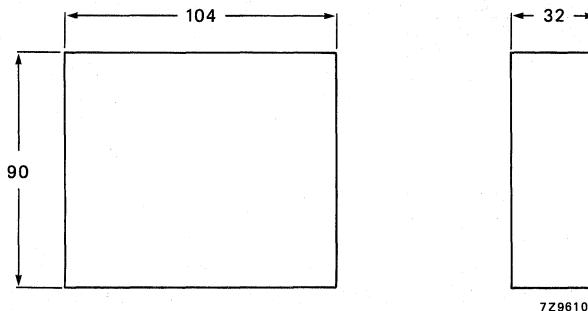


grade	catalogue number
5G1	4322 020 94160
5G4	4322 020 94460
5G5	4322 020 94560
5G6	4322 020 94660
5G7	4322 020 94760

## DISCS



grade	d mm	h mm	catalogue number
5G1	27	1,5	3312 060 74440
	37	1,5	3312 059 01600
	67	2	8222 037 54970
	51	1,5	4322 020 30210
	56	2,9	4322 020 30090
5G8	25	1	3312 060 60430

## SUBSTRATES

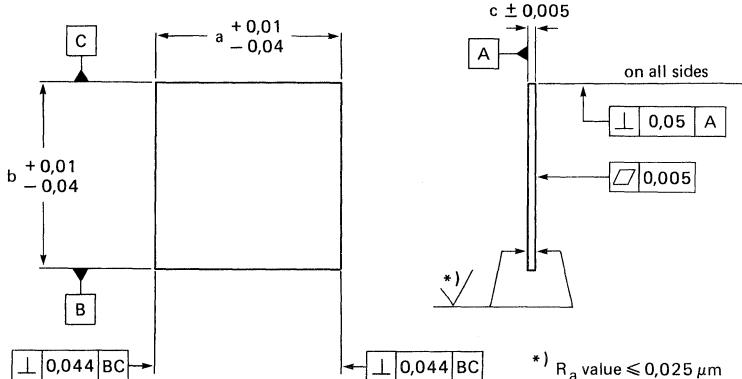

7Z96108

grade	a mm	b mm	c mm	catalogue number
5G1	25,4	25,4	0,51	4322 020 65100
	25,4	38,1	0,51	4322 020 65110
5G4	25,4	25,4	0,51	8222 293 32470
	25,4	25,4	1,02	8222 293 32480
	25,4	38,1	1,02	8222 293 32490
5G5	25,4	38,1	1,02	8222 293 32500
5G6	25,4	25,4	1,02	8222 293 32510
5G7	38,1	38,1	1,02	8222 293 32520 **
				8222 293 32680
5D3	25,4	25,4	0,51	8222 293 32530

\*\* Not polished;  $R_a$  not applicable.



## INDEX OF CATALOGUE NUMBERS

The purpose of this index is to provide identification of the component type when only the catalogue number is known. Details of the particular component are given in the relevant section of this book.  
See also book C4.

catalogue number	page	description	catalogue number	page	description
3104 101 80630	324	Tube core	3122 134 90720	264	I-core
3122 104 90370	324	Tube core	90730	262	I-core
90380	324	Tube core	90750	56	Yoke ring
90470	284	I-core	90760	279	U-core
90480	284	U-core	90770	323	Tube core
90490	322	Rod core	90780	324	Tube core
90550	333	Screw core	90800	331	Multi-hole tube
90810	324	Tube core	90960	138	E-core
90960	331	Multi-hole tube	91120	322	Rod core
91020	321	Rod core	91160	268	U-core
91060	321	Rod core	91390	288	U-core
91100	321	Rod core	91440	57	Yoke ring
91110	321	Rod core	91610	58	Yoke ring
91130	321	Rod core	91680	59	Yoke ring
91150	321	Rod core	91850	60	Yoke ring
91170	321	Rod core	91940	61	Yoke ring
91190	321	Rod core	92030	62	Yoke ring
91690	323	Tube core	92500	63	Yoke ring
91850	322	Rod core	92510	64	Yoke ring
91920	321	Rod core	92590	65	Yoke ring
92040	321	Rod core	92600	66	Yoke ring
92070	321	Rod core	92750	67	Yoke ring
92800	323	Tube core	92780	68	Yoke ring
92900	323	Tube core	93050	69	Yoke ring
93110	324	Tube core	99370	70	Yoke ring
93760	324	Tube core	3122 137 55360	280	Coil former
93840	54	Yoke ring	61910	277	Coil former
93890	324	Tube core	64140	267	Coil former
93950	290	U-core	3922 074 01120	324	Tube core
94030	324	Tube core	4311 020 50430	324	Tube core
94760	287	U-core	50710	324	Tube core
94770	287	I-core	51880	324	Tube core
94840	331	Multi-hole core	53460	323	Tube core
3122 134 02540	265	Coil former	54310	324	Tube core
02590	263	Coil former	4312 020 15460	323	Tube core
90110	322	Rod core	30020	321	Rod core
90200	273	U-core	30030	321	Rod core
90210	179	E-core	30160	321	Rod core
90460	276	U-core	30190	322	Rod core
90480	285	U-core	30290	321	Rod core
90600	55	Yoke ring	30320	321	Rod core
90620	266	I-core	30460	321	Rod core
90690	270	U-core	30490	322	Rod core

# INDEX

catalogue number	page	description	catalogue number	page	description
4312 020 30510	321	Rod core	4312 020 37050	247	ETD core
30520	321	Rod core	37060	247	ETD core
30560	321	Rod core	37070	247	ETD core
30570	322	Rod core	37080	247	ETD core
31030	323	Tube core	37090	247	ETD core
31050	323	Tube core	37100	252	ETD core
31060	323	Tube core	37110	252	ETD core
31080	324	Tube core	37120	252	ETD core
31200	324	Tube core	37130	252	ETD core
31220	323	Tube core	37140	252	ETD core
31250	323	Tube core	37150	257	ETD core
31320	323	Tube core	37160	257	ETD core
31330	323	Tube core	37170	257	ETD core
31450	323	Tube core	37180	257	ETD core
31500	332	Multi-hole tube	37190	257	ETD core
31520	331	Multi-hole tube	37200	242	ETD core
31550	332	Multi-hole tube	37210	242	ETD core
31570	331	Multi-hole tube	37220	242	ETD core
33190	286	U-core	37230	242	ETD core
33550	291	U-core	37240	242	ETD core
33560	291	I-core	37250	247	ETD core
33570	295	U-core	37260	247	ETD core
33580	293	U-core	37270	247	ETD core
33590	293	I-core	37280	247	ETD core
33600	297	U-core	37290	247	ETD core
33610	297	I-core	37300	252	ETD core
33710	285	U-core	37310	252	ETD core
34020	137	E-core	37320	252	ETD core
34070	129	E-core	37330	252	ETD core
34100	169	E-core	37340	252	ETD core
34110	149	E-core	37350	257	ETD core
34120	157	E-core	37360	257	ETD core
34170	157	E-core	37370	257	ETD core
34190	157	E-core	37380	257	ETD core
34380	187	E-core	37390	257	ETD core
34470	128	E-core	4312 021 26010	201	Clasp
34550	142	E-core	26020	212	Clasp
34740	282	U-core	26030	212	Clasp
36250	318	Toroid	26040	223	Clasp
36280	318	Toroid	26050	223	Clasp
36300	318	Toroid	26060	234	Clasp
36310	318	Toroid	26070	234	Clasp
36630	334	Wound bead	26090	178	Clasp
36640	334	Wound bead	26110	196	Clasp
36650	334	Wound bead	26120	141	Clasp
36690	334	Wound bead	26130	178	Spring
36700	334	Wound bead	26140	196	Spring
36710	334	Wound bead	26150	201	Spring
36760	335	Wound bead	26160	212	Spring
37000	242	ETD core	26170	223	Spring
37010	242	ETD core	26180	234	Spring
37020	242	ETD core	26190	141	Spring
37030	242	ETD core	28430	130	Coil former
37040	242	ETD core	28540	139	Coil former

catalogue number	page	description	catalogue number	page	description
4312 021	28550	143	Coil former	4322 020	38450
	28620	151	Coil former		39450
	28710	177	Coil former		39470
	28720	195	Coil former		39480
	28750	140	Coil former		43020
4313 020	15170	323	Tube core		52500
	15180	324	Tube core		52510
	35380	71	Yoke ring		52520
4322 020	31310	318	Toroid		52530
	31320	318	Toroid		90750
	31330	318	Toroid		90760
	31350	318	Toroid		90770
	31370	318	Toroid		90860
	31380	318	Toroid		91870
	31390	318	Toroid		95160
	31400	318	Toroid		95180
	31420	318	Toroid		95190
	31430	318	Toroid		95520
	31440	318	Toroid		97000
	31450	318	Toroid		97010
	31460	318	Toroid		97020
	34310	324	Tube core		97030
	34320	324	Tube core		97040
	34340	323	Tube core		97050
	34380	323	Tube core		97060
	34390	323	Tube core		97070
	34400	323	Tube core		97110
	34410	323	Tube core		97120
	34420	323	Tube core		97130
	34430	323	Tube core		97140
	34440	323	Tube core		97150
	34450	323	Tube core		97160
	34460	323	Tube core		97170
	34470	323	Tube core		97180
	34490	324	Tube core		97190
	34830	129	E-core		97200
	34840	142	E-core		97500
	34850	149	E-core		97630
	34900	169	E-core		97640
	34910	186	E-core		97680
	35070	72	Yoke ring		97690
	36750	324	Tube core	4322 021	20160
	36770	324	Tube core		20170
	36780	324	Tube core		20220
	36810	324	Tube core		20230
	36940	323	Tube core		20240
	36970	324	Tube core		20250
	37320	149	I-core		20290
	37400	305	Bar		31830
	37460	305	Bar		31910
	37470	305	Bar		31920
	37480	305	Bar		33010
	38350	323	Tube core		33020
	38440	323	Tube core		33060
					211
					Clasp
					Spring
					Coil former
					Clasp
					Spring
					Coil former
					Coil former
					Clasp
					Spring
					Coil former
					Coil former
					Tag

# INDEX

catalogue number	page	description	catalogue number	page	description
4322 021 33070	222	Tag	4330 030 30370	321	Rod core
33310	200	Coil former	30380	322	Rod core
33320	211	Coil former	30390	321	Rod core
33330	222	Coil former	30400	321	Rod core
33340	233	Coil former	30410	321	Rod core
33350	211	Coil former	30450	321	Rod core
33360	222	Coil former	30470	322	Rod core
33370	233	Coil former	30490	321	Rod core
33410	199	Coil former	30510	322	Rod core
33480	211	Coil former	30520	322	Rod core
33490	211	Coil former	30530	322	Rod core
33500	222	Coil former	30540	322	Rod core
33850	245	Coil former	30560	321	Rod core
33860	250	Coil former	30570	322	Rod core
33870	255	Coil former	30580	321	Rod core
33880	260	Coil former	30600	322	Rod core
33890	246	Assembly clip	30630	322	Rod core
33900	251	Assembly clip	30530	322	Rod core
33910	256	Assembly clip	32000	323	Tube core
33920	261	Assembly clip	32020	324	Tube core
33940	246	Earth clip	32030	324	Tube core
33950	251	Earth clip	32050	324	Tube core
33960	256	Earth clip	32100	328	Bead
33970	261	Earth clip	32110	328	Bead
4322 090 22730	323	Tube core	32120	328	Bead
22740	323	Tube core	32130	328	Bead
4330 020 30030	322	Rod core	32140	328	Bead
30380	322	Rod core	32150	328	Bead
30560	321	Rod core	32160	328	Bead
30580	322	Rod core	32170	328	Bead
30690	322	Rod core	32180	328	Bead
31770	321	Rod core	32190	328	Bead
32060	321	Rod core	32200	328	Bead
32090	321	Rod core	32210	328	Bead
4330 030 30010	322	Rod core	32220	328	Bead
30030	322	Rod core	32230	328	Bead
30040	321	Rod core	32240	328	Bead
30060	321	Rod core	32250	328	Bead
30070	321	Rod core	32260	328	Bead
30080	322	Rod core	32270	324	Bead
30110	322	Rod core	32280	328	Bead
30120	321	Rod core	32290	328	Bead
30130	321	Rod core	32310	328	Bead
30210	321	Rod core	32320	328	Bead
30220	321	Rod core	32330	328	Bead
30230	323	Tube core	32340	328	Bead
30240	322	Rod core	32350	328	Bead
30250	321	Rod core	32360	328	Bead
30270	321	Rod core	32370	328	Bead
30280	322	Rod core	32380	328	Bead
30310	322	Rod core	32390	328	Bead
30320	321	Rod core	32400	328	Bead
30350	322	Rod core	32410	328	Bead
30360	321	Rod core	32420	328	Bead

catalogue number	page	description	catalogue number	page	description
4330 030	32430	Bead	8230 302	00900	Tube core
	32440	Bead		00910	Tube core
	32450	Bead		01880	Tube core
	32460	Bead		02080	Coil former
	32470	Bead		02170	Coil former
	32480	Bead		02390	Tube core
	32490	Bead		02510	Tube core
	32400	Bead		03350	Rod core
	32410	Bead		03500	Rod core
	32420	Tube core		03530	Rod core
	32610	Tube core		04100	Tube core
	32620	Tube core		04630	Tube core
	32630	Tube core		04640	Tube core
	32640	Tube core		04850	Rod core
	32650	Tube core		05020	Rod core
	32660	Tube core		05030	Rod core
	32670	Tube core		05040	Rod core
	32710	Tube core		05080	Tube core
	32720	Tube core		05400	Rod core
	32750	Tube core		05540	Rod core
	32770	Tube core		05600	Rod core
	32800	Tube core		05710	Rod core
	32810	Tube core		05720	Rod core
	32820	Tube core		05750	321 Rod core
	32830	Tube core		05790	321 Rod core
	32850	Tube core			
	32860	Tube core			
	32870	Tube core			
	32880	Tube core			
	32890	Tube core			
	32900	Tube core			
	32910	Tube core			
	32920	Tube core			
	32930	Tube core			
	32940	Tube core			
	32950	Tube core			
	32740	331 Multi-hole tube			
	37010	Tube core			
	38070	326 Coil former			
	38080	335 Wound bead			
8230 301	02980	324 Tube core			
	03330	330 Bead on wire			
	03710	323 Tube core			
	04100	330 Bead on wire			
	04110	330 Bead on wire			
	04120	330 Bead on wire			
	04130	330 Bead on wire			
	04140	330 Bead on wire			
	04150	330 Bead on wire			
	04160	330 Bead on wire			
	04170	330 Bead on wire			
	04180	330 Bead on wire			
	04190	330 Bead on wire			
	04760	330 Bead on wire			



NOTES

## NOTES

---

---

NOTES

**NOTES**

# Electronic components and materials for professional, industrial and consumer uses from the world-wide Philips Group of Companies

**Argentina:** PHILIPS ARGENTINA S.A., Div. Elcoma, Vedia 3892, 1430 BUENOS AIRES, Tel. 541-7141/7242/7343/7444/7545.

**Australia:** PHILIPS INDUSTRIES HOLDINGS LTD., Elcoma Division, 11 Waltham Street, ARTARMON, N.S.W. 2064, Tel. (02) 439 3322.

**Austria:** ÖSTERREICHISCHE PHILIPS BAUELEMENTE INDUSTRIE G.m.b.H., Triester Str. 64, A-1101 WIEN, Tel. 629111-0.

**Belgium:** N.V. PHILIPS & MBLÉ ASSOCIATED, 9 rue du Pavillon, B-1030 BRUXELLES, Tel. (02) 242 7400.

**Brazil:** IBRAPE, Caixa Postal 7383, Av. Brigadeiro Faria Lima, 1735 SAO PAULO, SP, Tel. (011) 211-2600.

**Canada:** PHILIPS ELECTRONICS LTD., Elcoma Division, 601 Milner Ave., SCARBOROUGH, Ontario, M1B 1M8, Tel. 292-5161.

**Chile:** PHILIPS CHILENA S.A., Av. Santa Maria 0760, SANTIAGO, Tel. 39-4001.

**Colombia:** IND. PHILIPS DE COLOMBIA S.A., c/o IPRELENDO LTD., Cra. 21, No. 56-17, BOGOTA, D.E., Tel. 2497624.

**Denmark:** MINIWATT A/S, Strandlodsvæj 2, P.O. Box 1919, DK 2300 COPENHAGEN S, Tel. (01) 54 1133.

**Finland:** OY PHILIPS AB, Elcoma Division, Kaivokatu 8, SF-00100 HELSINKI 10, Tel. 17271.

**France:** RTC-COMPELEC, 130 Avenue Ledru Rollin, F-75540 PARIS 11, Tel. 43388000.

**Germany (Féd. République):** VALVO, UB Bauelemente der Philips G.m.b.H., Valvo Haus, Burchardstrasse 19, D-2 HAMBURG 1, Tel. (040) 3296-0.

**Greece:** PHILIPS HELLENIQUE S.A., Elcoma Division, 54, Syngro Av., ATHENS 11742, Tel. 9215311/319.

**Hong Kong:** PHILIPS HONG KONG LTD., Elcoma Div., 15/F Philips Ind. Bldg., 24-28 Kung Yip St., KWAI CHUNG, Tel. (0) 245121.

**India:** PEICO ELECTRONICS & ELECTRICALS LTD., Elcoma Dept., Band Box Building,

254-D Dr. Annie Besant Rd., BOMBAY - 400 025, Tel. 4930311/4930590.

**Indonesia:** P.T. PHILIPS-RALIN ELECTRONICS, Elcoma Div., Setiabudi II Building, 6th Fl., Jalan H.R. Rasuna Said (P.O. Box 223/KBY) Kuningan, JAKARTA - Selatan, Tel. 512572.

**Ireland:** PHILIPS ELECTRICAL (IRELAND) LTD., Newstead, Clonskeagh, DUBLIN 14, Tel. 693355.

**Italy:** PHILIPS S.p.A., Sezione Elcoma, Piazza IV Novembre 3, I-20124 MILANO, Tel. 2-6752.1.

**Japan:** NIHON PHILIPS CORP., Shuwa Shinagawa Bldg., 26-33 Takarawa 3-chome, Minato-ku, TOKYO (108), Tel. 448-5611.

(IC Products) SIGNETICS JAPAN LTD., 8-7 Sanbancho Chiyoda-ku, TOKYO 102, Tel. (03) 230-1521.

**Korea (Republic of):** PHILIPS ELECTRONICS (KOREA) LTD., Elcoma Div., Philips House, 200-199 Itaewon-dong, Yongsan-ku, SEOUL, Tel. 794-5011.

**Malaysia:** PHILIPS MALAYSIA SDN. BERHAD, No. 4 Persiaran Barat, Petaling Jaya, P.O.B. 2163, KUALA LUMPUR, Selangor, Tel. 774411.

**Mexico:** ELECTRONICA, S.A de C.V., Carr. México-Toluca km. 62.5, TOLUCA, Ed. de México 50140, Tel. Toluca 91 (721) 613-00.

**Netherlands:** PHILIPS NEDERLAND, Marktgroep Elenco, Postbus 90050, 5600 PB EINDHOVEN, Tel. (040) 793333.

**New Zealand:** PHILIPS NEW ZEALAND LTD., Elcoma Division, 110 Mt. Eden Road, C.P.O. Box 1041, AUCKLAND, Tel. 605-914.

**Norway:** NORSK A/S PHILIPS, Electronica Dept., Sandstuveien 70, OSLO 6, Tel. 68 0200.

**Peru:** CADESA, Av. Alfonso Ugarte 1268, LIMA 5, Tel. 326070.

**Philippines:** PHILIPS INDUSTRIAL DEV. INC., 2246 Pasong Tamo, P.O. Box 911, Makati Comm. Centre, MAKATI-RIZAL 3116, Tel. 86-89-51 to 59.

**Portugal:** PHILIPS PORTUGUESA S.A.R.L., Av. Eng. Duarte Pacheco 6, 1009 LISBOA Codex, Tel. 683121.

**Singapore:** PHILIPS PROJECT DEV. (Singapore) PTE LTD., Elcoma Div., Lorong 1, Toa Payoh, SINGAPORE 1231, Tel. 3502000..

**South Africa:** EDAC (PTY) LTD., 3rd Floor Rainer House, Upper Railway Rd. & Ove St., New Doornfontein, JOHANNESBURG 2001, Tel. 614-2362/9.

**Spain:** MINIWATT S.A., Balmes 22, BARCELONA 7, Tel. 3016312.

**Sweden:** PHILIPS KOMPONENTER A.B., Lidingövägen 50, S-11584 STOCKHOLM 27, Tel. 08/7821000.

**Switzerland:** PHILIPS A.G., Elcoma Dept., Allmendstrasse 140-142, CH-8027 ZÜRICH, Tel. 01-4882211.

**Taiwan:** PHILIPS TAIWAN LTD., 150 Tun Hua North Road, P.O. Box 22978, TAIPEI, Taiwan, Tel. 7120500.

**Thailand:** PHILIPS ELECTRICAL CO. OF THAILAND LTD., 283 Silom Road, P.O. Box 961, BANGKOK, Tel. 233-6330-9.

**Turkey:** TÜRK PHILIPS TİCARET A.S., Elcoma Department, İnnönü Cad. No. 78-80, P.K.504, 80074 İSTANBUL, Tel. 435910.

**United Kingdom:** MULLARD LTD., Mullard House, Torrington Place, LONDON WC1E 7HD, Tel. 01-5806633.

**United States:** (Active Devices & Materials) AMPEREX SALES CORP., Providence Pike, SLATERSVILLE, R.I. 02876, Tel. (401) 762-9000.

(Passive Devices) MEPCO/ELECTRA INC., Columbia Rd., MORRISTOWN, N.J. 07960, Tel. (201) 539-2000.

(Passive Devices & Electromechanical Devices) CENTRALAB INC., 5855 N. Glen Park Rd., MILWAUKEE, WI 53201, Tel. (414) 228-7380.

(IC Products) SIGNETICS CORPORATION, 811 East Argus Avenue, SUNNYVALE, California 94086, Tel. (408) 991-2000.

**Uruguay:** LUZILECTRON S.A., Avda Uruguay 1287, P.O. Box 907, MONTEVIDEO, Tel. 914321.

**Venezuela:** IND. VENEZOLANAS PHILIPS S.A., c/o MAGNETICA S.A., Calle 6, Ed. Las Tres Jotas, App. Post. 78117, CARACAS, Tel. (02) 2393931.

**For all other countries apply to:** Philips Electronic Components and Materials Division, International Business Relations, P.O. Box 218, 5600 MD EINDHOVEN, The Netherlands, Telex 35000 phcnl